

Parametric studies into creep and shrinkage characteristics in railway prestressed concrete sleepers

Li, Dan; Kaewunruen, Sakdirat; Robery, Peter; Remennikov, Alex

DOI:
[10.3389/fbuil.2020.00130](https://doi.org/10.3389/fbuil.2020.00130)

License:
Creative Commons: Attribution (CC BY)

Document Version
Publisher's PDF, also known as Version of record

Citation for published version (Harvard):
Li, D, Kaewunruen, S, Robery, P & Remennikov, A 2020, 'Parametric studies into creep and shrinkage characteristics in railway prestressed concrete sleepers', *Frontiers in Built Environment*, vol. 6, 130.
<https://doi.org/10.3389/fbuil.2020.00130>

[Link to publication on Research at Birmingham portal](#)

General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact UBIRA@lists.bham.ac.uk providing details and we will remove access to the work immediately and investigate.



Parametric Studies Into Creep and Shrinkage Characteristics in Railway Prestressed Concrete Sleepers

Dan Li¹, Sakdirat Kaewunruen^{1,2*}, Peter Robery¹ and Alex M. Remennikov³

¹ Department of Civil Engineering, School of Engineering, University of Birmingham, Birmingham, United Kingdom,

² Birmingham Centre for Railway Research and Education, School of Engineering, University of Birmingham, Birmingham, United Kingdom, ³ School of Civil, Mining and Environmental Engineering, University of Wollongong, North Wollongong, NSW, Australia

OPEN ACCESS

Edited by:

Akira Matsumoto,
Nihon University, Japan

Reviewed by:

Ruilin You,
China Academy of Railway Sciences,
China
Izuru Takewaki,
Kyoto University, Japan

*Correspondence:

Sakdirat Kaewunruen
S.Kaewunruen@bham.ac.uk
sakdirat@gmail.com

Specialty section:

This article was submitted to
Transportation and Transit Systems,
a section of the journal
Frontiers in Built Environment

Received: 30 May 2019

Accepted: 16 July 2020

Published: 14 August 2020

Citation:

Li D, Kaewunruen S, Robery P
and Remennikov AM (2020)
Parametric Studies Into Creep
and Shrinkage Characteristics
in Railway Prestressed Concrete
Sleepers. *Front. Built Environ.* 6:130.
doi: 10.3389/fbuil.2020.00130

It is well known that prestressed concrete is highly suitable for railway sleepers because of its many advantages in performance, maintenance, sustainability, and construction. Prestressed concrete design can improve structural performance since the prestress enables fully compressed cross sections. Higher tensile resistance of prestressed concrete can then take place. However, longer-term performance and durability of concrete sleepers largely depends on creep and shrinkage behaviors. On this ground, the effects of time-dependent phenomena on prestressed concrete sleeper are investigated in this study. In the past decades, a number of material models have been established to estimate creep and shrinkage behavior, but those were mostly based on a generic reinforced concrete design concept. The common uses of prestressed concrete have led to practical concerns by practitioners whether those existing predictive models could be realistically applied to prestressed concrete applications. Due to a relatively higher initial elastic shortening in prestressed concrete, the creep and shrinkage effects should be critically reevaluated among flexural members. This study embarks on comparative studies into the effects of creep and shrinkage on prestressed concrete railway sleepers. A thorough comparison between prediction models underpinned by European Standard Eurocode 2, American Standard ACI, and Australian Standard AS3600-2009 enables new insights into the time-dependent performance of railway concrete sleepers installed in various locations or in different continents. This implies that the durability of railway concrete sleepers can be undermined differently when exposed to different conditions even in the same rail network. The insights stemmed from this study will help track engineers to better design and maintain railway infrastructure, improving asset management efficacy.

Keywords: railway sleepers, creep, shrinkage, prediction model, comparative study

INTRODUCTION

Railway sleepers (or called “railroad ties”), which are generally manufactured using timber, concrete, steel, or other engineered materials, are one of the main safety-critical components of railway track structures (Esveld, 2001). Concrete sleepers have been initially used on rail tracks since 1884 and have recently been used almost everywhere in the world. The major

roles of sleepers are (i) to transfer wheel loads from the superstructure to the substructure and (ii) to secure the gauge between rails for safe passages of trains. In reality, wheel/rail interactions over common defects in either a wheel or a rail can cause severe impact loading conditions (Remennikov and Kaewunruen, 2005; Kaewunruen, 2014; Remennikov and Kaewunruen, 2015; Kaewunruen and Remennikov, 2008a,b,c; Remennikov and Kaewunruen, 2008; Remennikov et al., 2011; Fujino and Siringoringo, 2016; Kaewunruen et al., 2016a; Yahiaoui et al., 2017). The impact loads can significantly undermine structural integrity and durability of railway sleepers over the time. Such actions can exacerbate the structural behaviors of the concrete sleepers affected by extreme or hostile environmental conditions. For example, shrinkage cracks can be further open from the dynamic actions, resulting in water and chloride penetrations, as well as carbonation and corrosion. On this ground, it is vital to understand the time-dependent behaviors of concrete sleepers in order to pre-design and risk-manage the concrete sleepers over their entire service life.

Reinforced concrete was initially used for railway sleepers over a century ago. However, poor structural performance and extensive damage have proved that traditional reinforced concrete design was not an effective solution for railway sleepers. Therefore, a prestressed concrete design concept has been developed and adopted for railway sleepers instead of traditional reinforced concrete structures. The prestressed concrete concept can result in lower maintenance costs and longer life cycles in terms of economic and technical aspects. Nowadays, the most commonly used type of sleepers around the world is the prestressed concrete type, which can provide higher serviceability, stability, and safety, especially in suburban and heavy haul rail networks (Kaewunruen and Remennikov, 2010; Parande, 2013; Taherinezhad et al., 2013; Kaewunruen, 2014; Tang et al., 2015; Padhi and Panda, 2017). Prestressed concrete sleepers must successfully perform to satisfy two key responsibilities: first, transfer the wheel loads from the rails to the ground, and later, restrain the rail gauge to ensure the dynamic and safe travels of trains. However, in some cases, creep, shrinkage, and elastic shortening stemmed from improper, unexpected material responses can foul the rail gauge by excessive time-dependent behaviors (for example, too tight rail gauge, splitting cracks at fasteners, vertical cracks along dowels, holes or web openings). Note that, in reality, concrete sleepers are often modified at construction sites to fit in other systems, such as cables, signaling devices, and drainage pipes. These modifications can further result in structural damages in concrete sleepers when excessive time-dependent behaviors are present.

Creep and shrinkage responses can largely influence the durability and long-term behaviors of prestressed concrete railway sleepers (Wakui and Okuda, 1999; Gustavson, 2002). A number of material models have been developed to predict creep and shrinkage, but those are mostly based on a generic type of concrete and on certain applications of traditional reinforced concrete structures (Wang, 1996; Warner et al., 1998; Bentz, 2000). Worldwide adoptions of prestressed concrete in long-span bridges, stadiums, silos, and confined nuclear power plants have led to various concerns by practitioners

whether those predictive models could be realistically applied to prestressed concrete components (Ercolino et al., 2015; Li et al., 2015). Due to high initial prestress and elastic shortening in prestressed concrete, the creep and shrinkage effects need to be critically reevaluated. This study investigates and compares methods to evaluate creep and shrinkage effects in prestressed concrete railway sleepers. Comparison among design codes of EUROCODE2, ACI, and AS2009-3600 will provide practical insights into the long-term behavior and durability of railway concrete sleepers. The outcome of this study will help track engineers to better design, manufacture, inspect, and maintain railway infrastructures, improving asset management efficacy.

Three approaches have been adopted in order to meet the research aim. Initially, the design codes have been rigorously reviewed in order to understand how these design codes can be used to properly predict creep and shrinkage. In this stage, a calculation sheet for each code has been developed. All calculations have been carried out analytically. The, the analytical data are analyzed. The sensitivity analysis has been carried out to study the effect of creep and shrinkage. The different codes of practice are performed in order to conduct a comparative study. In practice, the concrete sleepers are manufactured within a day by accelerating the concrete strength to meet the transfer requirements. As such, more realistic losses of prestress and the resultant sleeper shortenings can be established.

This research aims at providing a principal understanding of creep and shrinkage effects for railway prestressed concrete sleepers' design and manufacture. After introducing the design codes, the parametric analyses are presented. In this investigation, four key parameters (strength, relative humidity, age at first loading, and curing time) are considered to highlight creep and shrinkage effects. The loss of prestress as a result of deformations due to creep and shrinkage are discussed. This research will also provide a state-of-the-art review of common design criteria of prestressed concrete based on Eurocode 2, the American Concrete Institution code, and Australian Standard 2009-3600. It will then determine creep and shrinkage effects in prestressed concrete railway sleepers (Gjorv, 2013; Kaewunruen and Remennikov, 2013). The creep and shrinkage characteristics in prestressed concrete sleepers have been thoroughly investigated in the past. This study provides new findings to better understand the sensitivity of key vulnerable parameters that can significantly affect railway concrete sleepers exposed to various environmental conditions even in the same railway line in a rail network. In addition, the insights into the application of the design methods will be illustrated in order to provide a new guideline for applying those existing codes of practice.

CREEP

Neville (1995) stated that the strain increases with time even when the concrete is loaded constantly, due to creep effect. Therefore, creep can be defined by the increase of strain in concrete under a sustained stress. With time increments, the

increased strain can be several times larger than initial strain. Generally, creep is a considerable factor in concrete structures. Bhatt (2011) stated that creep can be defined as the increase of strain with time when the stress is held constant. The displacement of concrete can gradually increase with time when the load is left in place. Such displacement can reach a value as large as three to four times of the initial or immediate elastic deformation. The inelastic deformation due to the constant load is known as creep deformation. **Figure 1** shows the behavior of the creep strain over time.

Creep develops in cement paste, which is made of colloidal sheets formed by calcium silicate hydrates and evaporable water. Creep can be influenced by several factors such as concrete mix and environmental and loading conditions. Creep is commonly inversely proportional to concrete strength (e.g., higher strength concrete tends to have lesser creep). In addition, aggregate content and size as well as water/cement ratio can also affect creep strain. Environmental factors like relative humidity, temperature, and exposure conditions also play a significant role on creep. Duration and magnitude of stress and the first loading age are external loading parameters in the creep predictions (Vittorio, 2011). When creep is taken into account, its influences on the design life of concrete sleepers are always evaluated under quasi-permanent combination of actions irrespective of the design situation considered, i.e., persistent, transient, or accidental. Based on such complex situation, various codes of practice simplify each critical parameter to suit its local conditions. On this ground, it is crucial to revisit each code of practice.

Eurocode 2

The total creep strain $\epsilon_{cc}(t, t_0)$ of concrete due to the constant compressive stress of σ_c applied at the concrete age of t_0 is given by

$$\epsilon_{cc}(t, t_0) = \varphi(t, t_0) \times \frac{\sigma_c}{E_c}$$

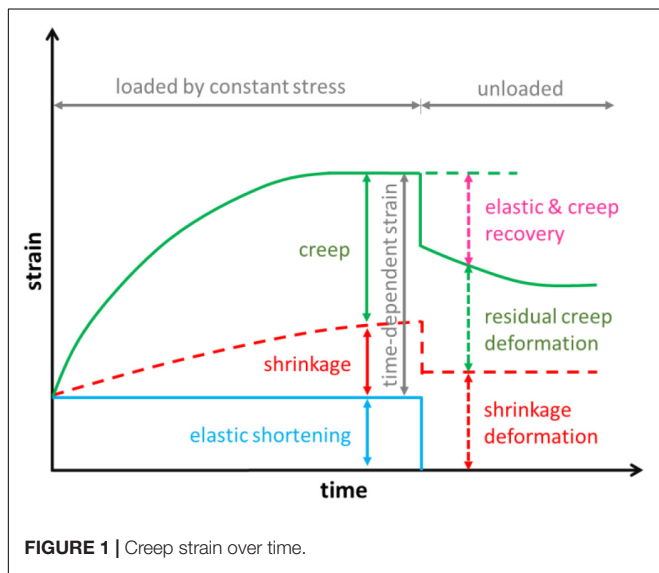


FIGURE 1 | Creep strain over time.

where $\varphi(t, t_0)$ is the final creep coefficient; E_c is the tangent modulus.

$$\varphi(t, t_0) = \varphi_{RH} \times \frac{16.8}{\sqrt{f_{cm}}} \times \frac{1}{(0.1 + t_0^{0.20})}$$

$$\varphi_{RH} = 1 + \frac{1 - 0.01 \times RH}{0.1 + h_0^{0.333}}, f_{cm} \leq 35MPa$$

$$\varphi_{RH} = \left(1 + \frac{1 - 0.01 \times RH}{0.1 + h_0^{0.333}} \alpha_1\right) \alpha_2, f_{cm} > 35MPa$$

$$\alpha_1 = \left(\frac{35}{f_{cm}}\right)^{0.7}, \alpha_2 = \left(\frac{35}{f_{cm}}\right)^{0.2} f_{cm} = f_{ck} + 8 MPa$$

$$t_0 = t_{0,T} \left(\frac{9}{2 + t_{0,T}^{1.2}}\right)^\alpha \geq 0.5, \alpha = \{-1(S), 0(N), 1(R)\}$$

where RH is the relative humidity in percentage; h_0 is the ratio of cross-sectional area and perimeter of the member in contact with the atmosphere, $h_0 = 2A_c/u$; S, R, and N refer to different classes of cement.

ACI Code

According to ACI 209-92, the only predicted parameter is creep coefficient $\varphi(t, t_0)$, and its empirical equation is given by

$$\varphi(t, t_0) = \frac{(t - t_0)^\psi}{d + (t - t_0)^\psi} \varphi_u$$

where $\varphi(t, t_0)$ is the creep coefficient at any time t when a load is applied at age t_0 ; d (in days) and ψ are considered constants for a given member shape and size that define the time-ratio part. ACI-209R-92 recommends an average value of 10 and 0.60 for d and ψ , respectively; φ_u is the ultimate creep coefficient. For the ultimate coefficient φ_u , the average value is suggested using 2.35. However, the creep coefficient still needs to be modified by correction factors:

$$\varphi_u = 2.35\gamma_c$$

$$\gamma_c = \gamma_{c,t0} \gamma_{c,RH} \gamma_{c,vs} \gamma_{c,s} \gamma_{c,\psi} \gamma_{sh,\alpha}$$

where $\gamma_{c,t0}$ is the loading age factor; $\gamma_{c,RH}$ is the ambient relative humidity; $\gamma_{c,vs}$ is the volume-to-surface ratio of the concrete section; $\gamma_{c,s}$ is the slump; $\gamma_{c,\psi}$ is the amount of fine aggregate; $\gamma_{sh,\alpha}$ is the air content.

Australian Standard AS3600-2009

In accordance with AS3600, the creep coefficient at any time φ_{cc} can be determined by

$$\varphi_{cc} = k_2 k_3 k_4 k_5 \varphi_{cc,b}$$

where k_2 is the development of creep with time; k_3 is the factor which depends on the age at first loading τ (in days); k_4 is the factor which accounts for the environment; k_5 is the factor which accounts for the reduced influence of both relative and humidity and specimen size; and φ_{cc} is the basic creep coefficient.

The development of creep with time k_2 can be calculated by

$$k_2 = \frac{\alpha_2(t - \tau)^{0.8}}{(t - \tau)^{0.8} + 0.15t_h}$$

$$\alpha_2 = 1.0 + 1.12e^{-0.008t_h}$$

$$t_h = 2A_g/u_e$$

where t is any time in days; t_h is the hypothetical thickness; A_g is the cross-sectional area of the member; and u_e is the portion of the section perimeter exposed to the atmosphere plus half the total perimeter of any voids contained within the section.

Factor k_3 which depends on the age at first loading τ can be shown as

$$k_3 = \frac{2.7}{1 + \log(\tau)} \text{ (for } \tau > 1 \text{ day)}$$

Factor k_4 accounts for the environment:

$$k_4 = 0.7 \text{ for an arid environment}$$

$$k_4 = 0.65 \text{ for an interior environment}$$

$$k_4 = 0.60 \text{ for a temperate environment}$$

$$k_4 = 0.5 \text{ for a tropical or near-coastal environment}$$

Factor k_5 is given by

$$k_5 = 1.0, f'_c \leq 50 \text{ MPa}$$

$$k_5 = (2.0 - \alpha_3) - 0.02(1.0 - \alpha_3)f'_c, 50 \leq f'_c \leq 100 \text{ MPa}$$

where $\alpha_3 = 0.7/(k_4\alpha_2)$.

The basic creep coefficient φ_{cc} can be determined by interpolation or extrapolation from **Table 1**.

SHRINKAGE

Concrete shrinkage is the time-dependent strain in an unloaded and unrestrained specimen at a constant temperature. Shrinkage is not an entirely reversible process in comparison with creep. Both creep and shrinkage are influenced by similar factors such as relative humidity, concrete strength, and cement. Shrinkage can be divided into plastic shrinkage, chemical shrinkage, thermal shrinkage, and drying shrinkage. The shrinkage strain is usually considered to be categorized into drying shrinkage and endogenous shrinkage. Drying shrinkage is the volumetric reduction due to the loss of water during the drying process. Endogenous shrinkage is sometimes used to refer to the other part of shrinkage of the hardened concrete that is not associated with drying (i.e., this is the sum of autogenous and thermal shrinkage) (Bhatt, 2011; Gilbert et al., 2016).

Eurocode 2

The total shrinkage strain ϵ_{cs} can be given by

$$\epsilon_{cs} = \epsilon_{ds} + \epsilon_{as}$$

where ϵ_{ds} is the drying shrinkage strain; ϵ_{as} is the autogenous shrinkage strain.

The drying shrinkage strain ϵ_{ds} can be estimated by

$$\epsilon_{ds} = \beta_{ds}(t, t_0) \times \epsilon_{cd0} \times k_h$$

$$\epsilon_{cd0} = 0.85 [(220 + 110\alpha_{ds1}) \times \exp(-\alpha_{sd2} \times 0.1f_{cm})] \times 1.55 [1 - (0.01RH)^3] 10^6$$

$$\beta_{ds}(t, t_0) = \frac{(t - t_s)}{(t - t_s) + 0.04\sqrt{h_0^3}}$$

where k_h is a coefficient which depends on the national size h_0 ; RH is the relative humidity in percentage; $h_0 = 2Ac/u$ in mm, Ac is the cross-sectional area, and u is the perimeter of the member in contact with the atmosphere. The values of parameter α_{ds1} and α_{ds2} as a function of the type of cement are shown in **Table 2**.

The autogenous shrinkage strain ϵ_{as} can be calculated from

$$\epsilon_{as} = \beta_{as}(t) \times \epsilon_{ca}(\infty)$$

$$\epsilon_{ca}(\infty) = 2.5 \times (f_{ck} - 10) \times 10^{-6}$$

$$\beta_{as}(t) = 1 - \exp(-0.2t^{0.5})$$

ACI Code

The shrinkage strain $\epsilon_{sh}(t)$ at age of concrete t (days), predicted from the start of drying at t_c , can be calculated by

$$\epsilon_{sh}(t) = \frac{(t - t_c)^\alpha}{f + (t - t_c)^\alpha} \epsilon_{shu}$$

$$\epsilon_{shu} = 780 \times 10^{-6} \text{ mm/mm (in/in)}$$

where f (in days) and α are considered to be constant values for a given member shape and size that define the time-ratio factor, respectively. The average value for f is recommended to be 35 days of moist curing, and α is suggested to use 1.0. ϵ_{shu} is the ultimate shrinkage strain, and $(t - t_c)$ is the time between end of curing and any time after curing.

For the ultimate shrinkage strain ϵ_{shu} , the average value is suggested to be $780 \times 10^{-6} \text{ mm/mm}$. However, the shrinkage strain still needs to be modified by correction factors:

$$\epsilon_{shu} = 780\gamma_{sh} \times 10^{-6} \text{ mm/mm (in/in)}$$

$$\gamma_{sh} = \gamma_{sh,tc} \gamma_{sh,RH} \gamma_{sh,vs} \gamma_{sh,s} \gamma_{sh,\psi} \gamma_{sh,c} \gamma_{sh,\alpha}$$

TABLE 1 | Basic creep coefficient in accordance with AS3600.

f'_c (MPa)	20	25	32	40	50	65	80	100
$\varphi_{cc,b}$	5.2	4.2	3.4	2.8	2.4	2.0	1.7	1.5

TABLE 2 | Cement type and coefficient.

Cement type	α_{ds1}	α_{ds2}
S	3	0.13
N	4	0.12
R	6	0.11

where $\gamma_{sh,tc}$ is the initial moist curing coefficient; $\gamma_{sh,RH}$ is the ambient relative humidity coefficient; $\gamma_{sh,vs}$ is the volume-to-surface ratio of the concrete section coefficient; $\gamma_{sh,s}$ is the slump coefficient; $\gamma_{sh,\psi}$ is the fine aggregate coefficient; and $\gamma_{sh,c}$ is the cement content factor coefficient; $\gamma_{sh,\alpha}$ is the air content coefficient.

Australian Standard AS3600-2009

The total shrinkage strain ϵ_{cs} is shown below:

$$\epsilon_{cs} = \epsilon_{cse} + \epsilon_{csd}$$

where ϵ_{cse} is the autogenous shrinkage strain; ϵ_{csd} is the drying shrinkage.

The autogenous shrinkage can be calculated by

$$\epsilon_{cse} = \epsilon'_{cse} (1.0 - \exp\{-0.1t\})$$

$$\epsilon'_{cse} = (0.6f'_c - 1.0) \times 50 \times 10^{-6} \quad (f'_c \text{ in MPa})$$

$$\epsilon_{csd,b} = (1.0 - 0.008f'_c) \times \epsilon'_{csd,b}$$

where $\epsilon'_{csd,b}$ depends on the quality of the local aggregates and may be taken as 800×10^{-6} for concrete supplied in

Sydney and Brisbane, 900×10^{-6} in Melbourne, and 1000×10^{-6} elsewhere.

The drying shrinkage strain ϵ_{csd} after the beginning of drying ($t - \tau_d$) can be estimated as

$$\epsilon_{csd} = k_1 k_4 \epsilon_{csd,b}$$

where k_1 is the factor, which describes the development of drying shrinkage with time; k_4 is the factor, which accounts for the environment.



The factor k_1 can be given by

$$k_1 = \frac{\alpha_1 (t - \tau_d)^{0.8}}{(t - \tau_d)^{0.8} + 0.15t_h}$$

$$\alpha_1 = 0.8 + 1.2 \exp\{-0.005t_h\}$$

The factor k_4 accounts for the environment:

- $k_4 = 0.7$ for an arid environment
- $k_4 = 0.65$ for an interior environment
- $k_4 = 0.60$ for a temperate environment
- $k_4 = 0.5$ for a tropical or near-coastal environment

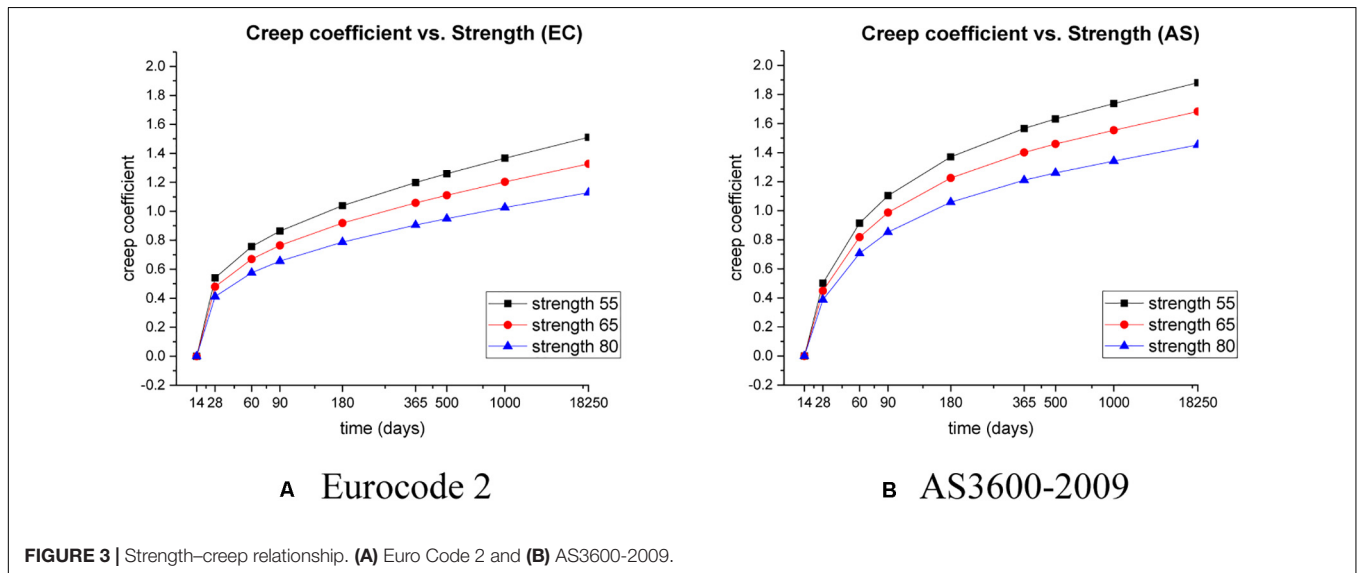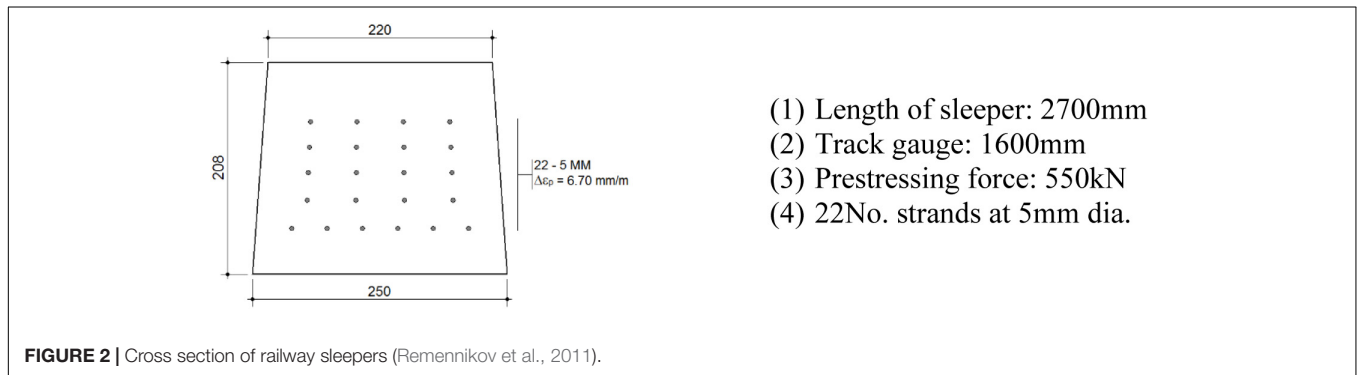


RESULTS AND DISCUSSION



The effects of various key parameters that have significant influences on creep, shrinkage strain, and loss of prestress are evaluated, in order to establish new practical insights for design, manufacture, and maintenance of railway concrete sleepers under uncertain settings (Kaewunruen et al., 2015, 2016b; Setsobhonkul et al., 2017; Li and Kaewunruen, 2019). The fundamental engineering properties of prestressed concrete sleepers used for calculation are based on previous investigations by Remennikov et al. (2011). The parametric results are generated

for comparisons between Eurocode 2 (EC2), the American Concrete Institution’s code (ACI), and Australian Standard AS3600-2009 (AS). **Figure 2** shows the cross section at rail seat of the prestressed concrete sleepers.

Creep Parametric Study Strength of Concrete

Parametric studies into the effect of concrete strength have been conducted using different characteristic strength of concrete (55, 65, and 80 MPa) in order to determine the relationships between the strength of concrete and creep curves, which are

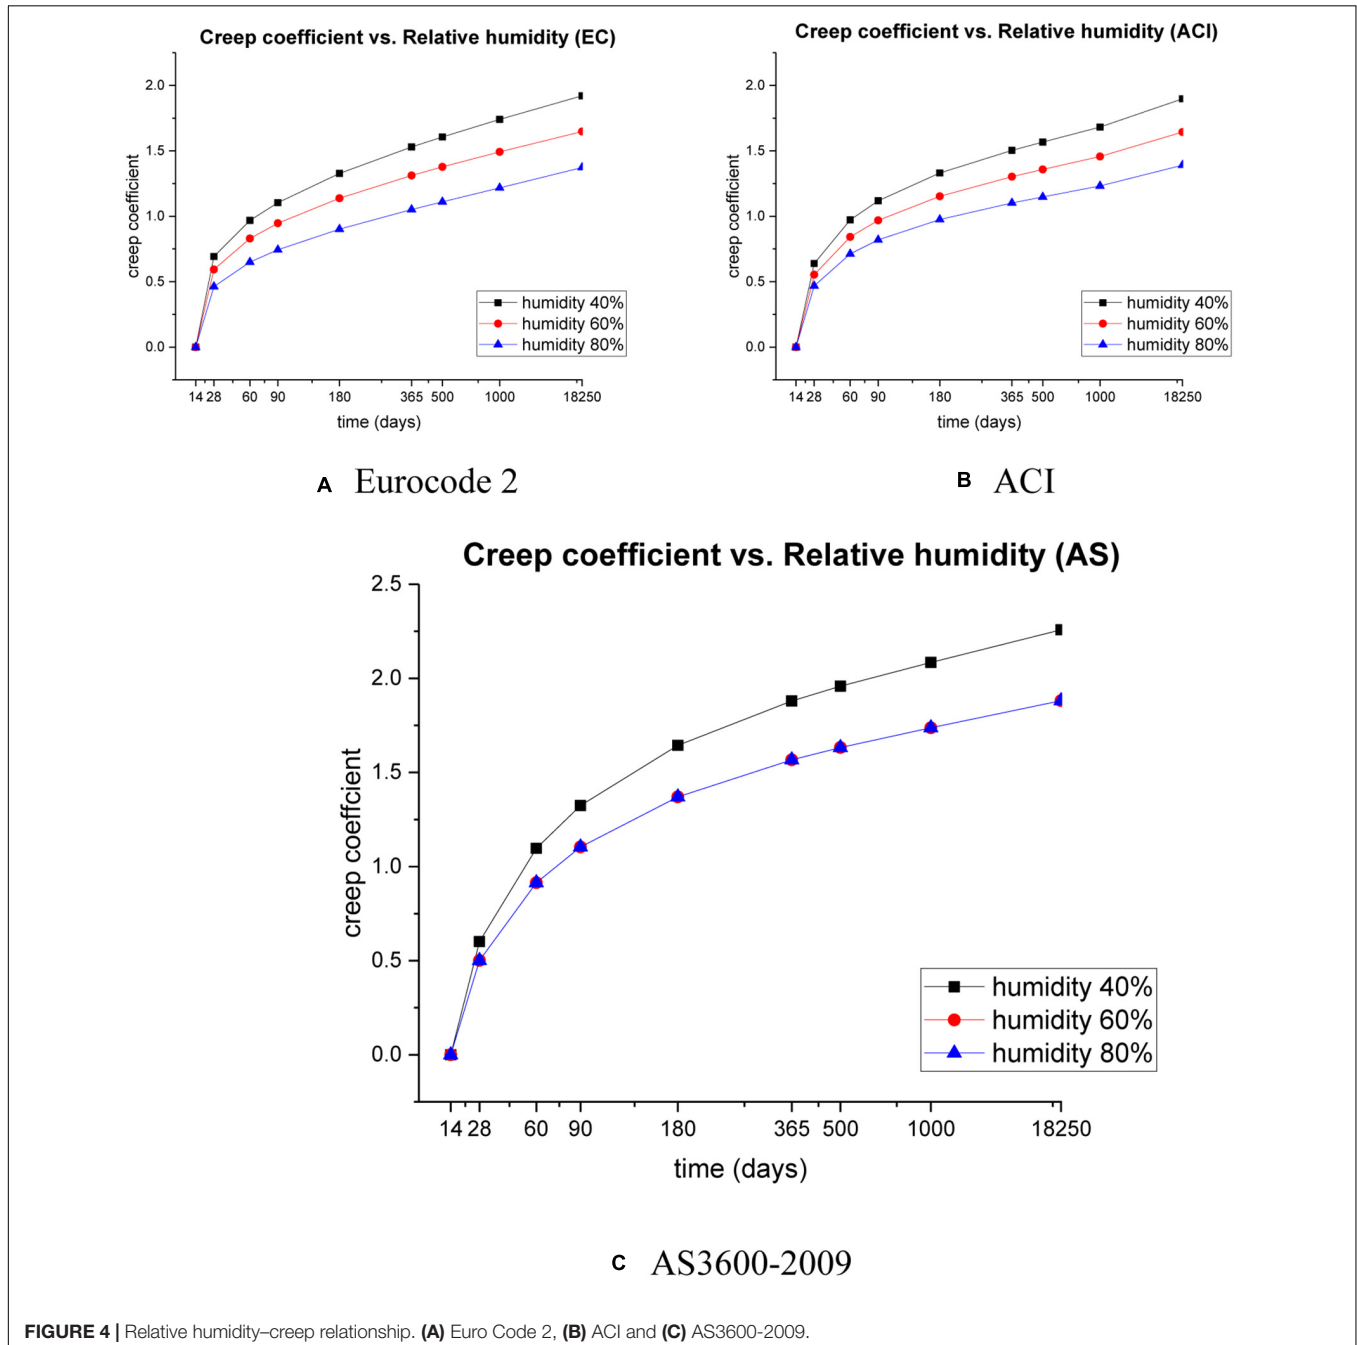

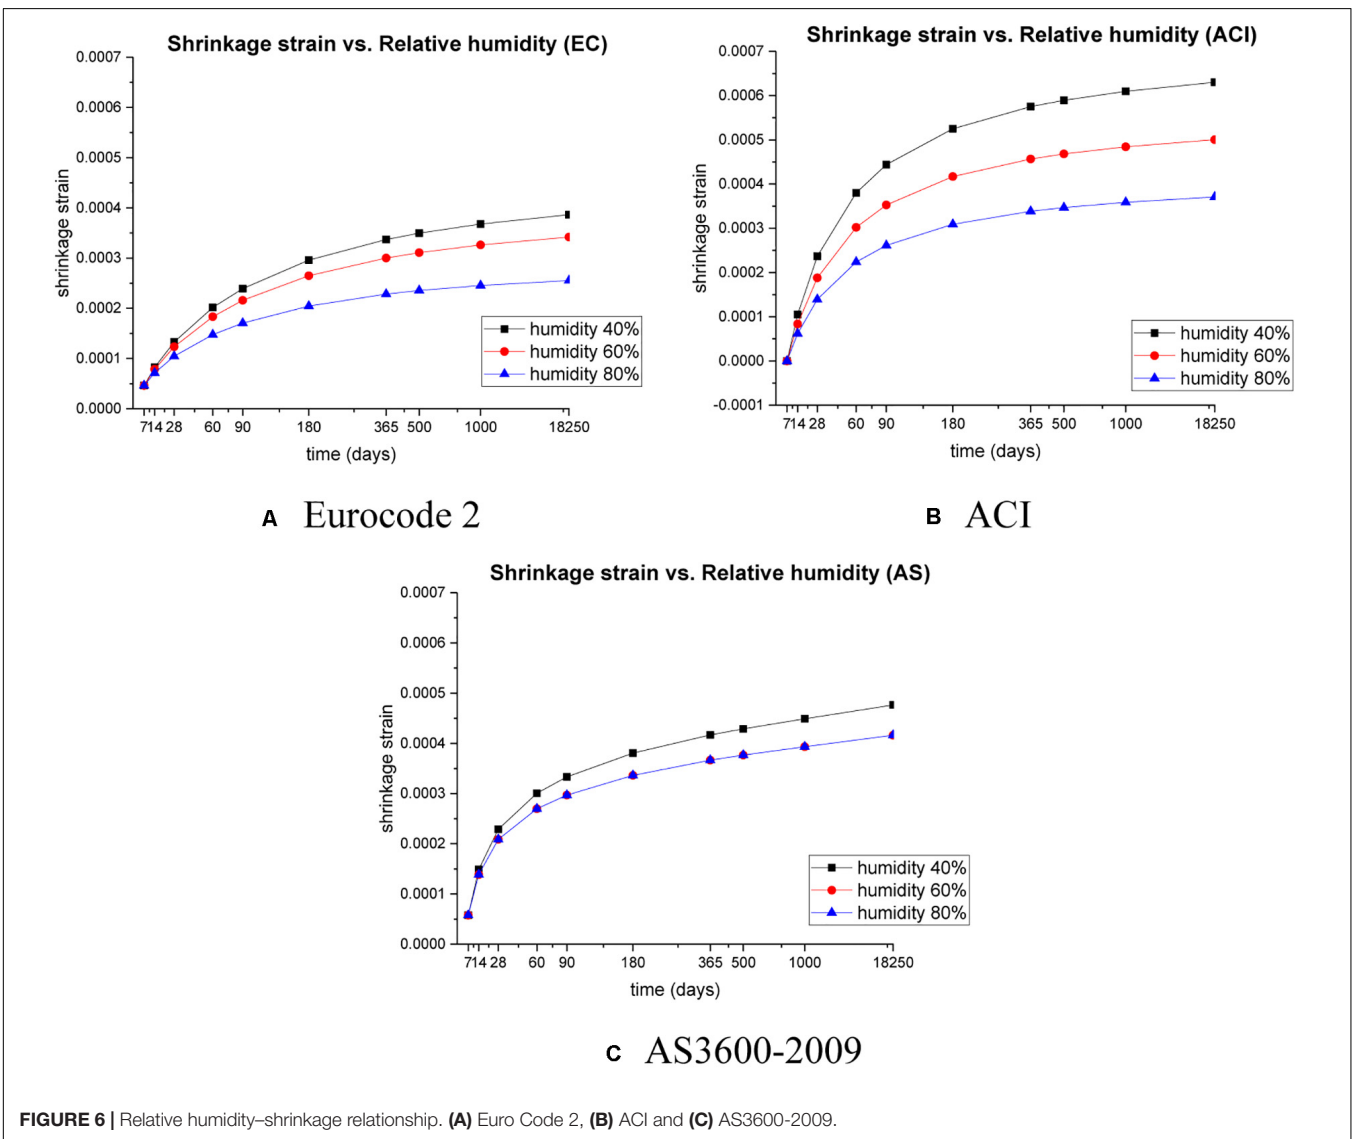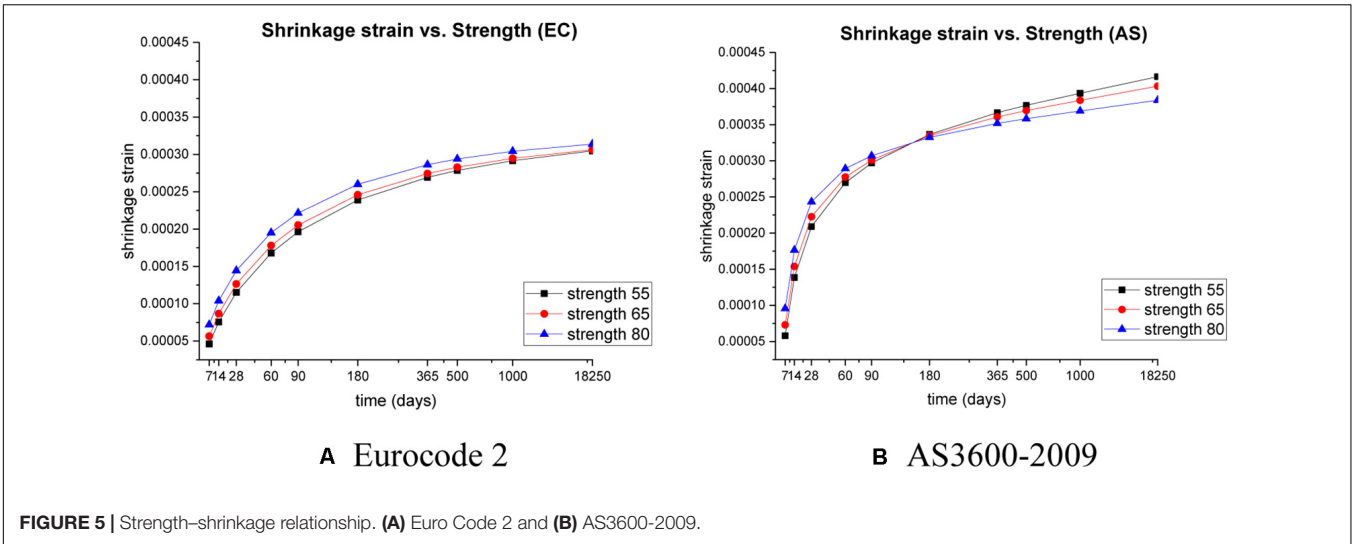

illustrated in **Figure 3**. It is important to note that, according to the empirical formula in ACI209R-92, the creep coefficient calculation is not directly related to concrete strength. As a result, the creep strain and creep coefficient behaviors are determined by only EC2 and AS3600, respectively. All cases are estimated from 14 days up to 18,250 days (50 years, which is a design service life of concrete sleepers) in the same conditions (e.g., uniform dimension of sleepers, 70% relative humidity, and first loading at 14 days).

Relative Humidity

To investigate relationships between the relative humidity and creep, three cases with different relative humidity (40, 60, and 80%) are displayed from the obtained data as shown in **Figure 4**. The creep strain and creep coefficient are determined by using EC2, ACI, and AS3600-2009 codes, respectively. All cases are estimated from 14 days up to 18,250 days (50 years) in the same conditions (uniform dimension of sleepers, 55 MPa strength of concrete).

Shrinkage Parametric Study Strength

Figure 5 demonstrates the influences of different strengths on shrinkage behaviors. Note that according to the formula in ACI209R-92, the shrinkage behavior is also not directly related to concrete strength, analogously to creep. On this ground, this study focuses only on EC2 and AS3600 approaches.

Relative Humidity


Figure 6 highlights the influences of different relative humidity (RH) on the shrinkage characteristics.

Curing Time

Figure 7 shows the shrinkage behaviors affected by different curing times.

Discussion

Based on the sensitivity analyses, the creep and shrinkage behaviors that occurred within prestressed concrete sleepers can

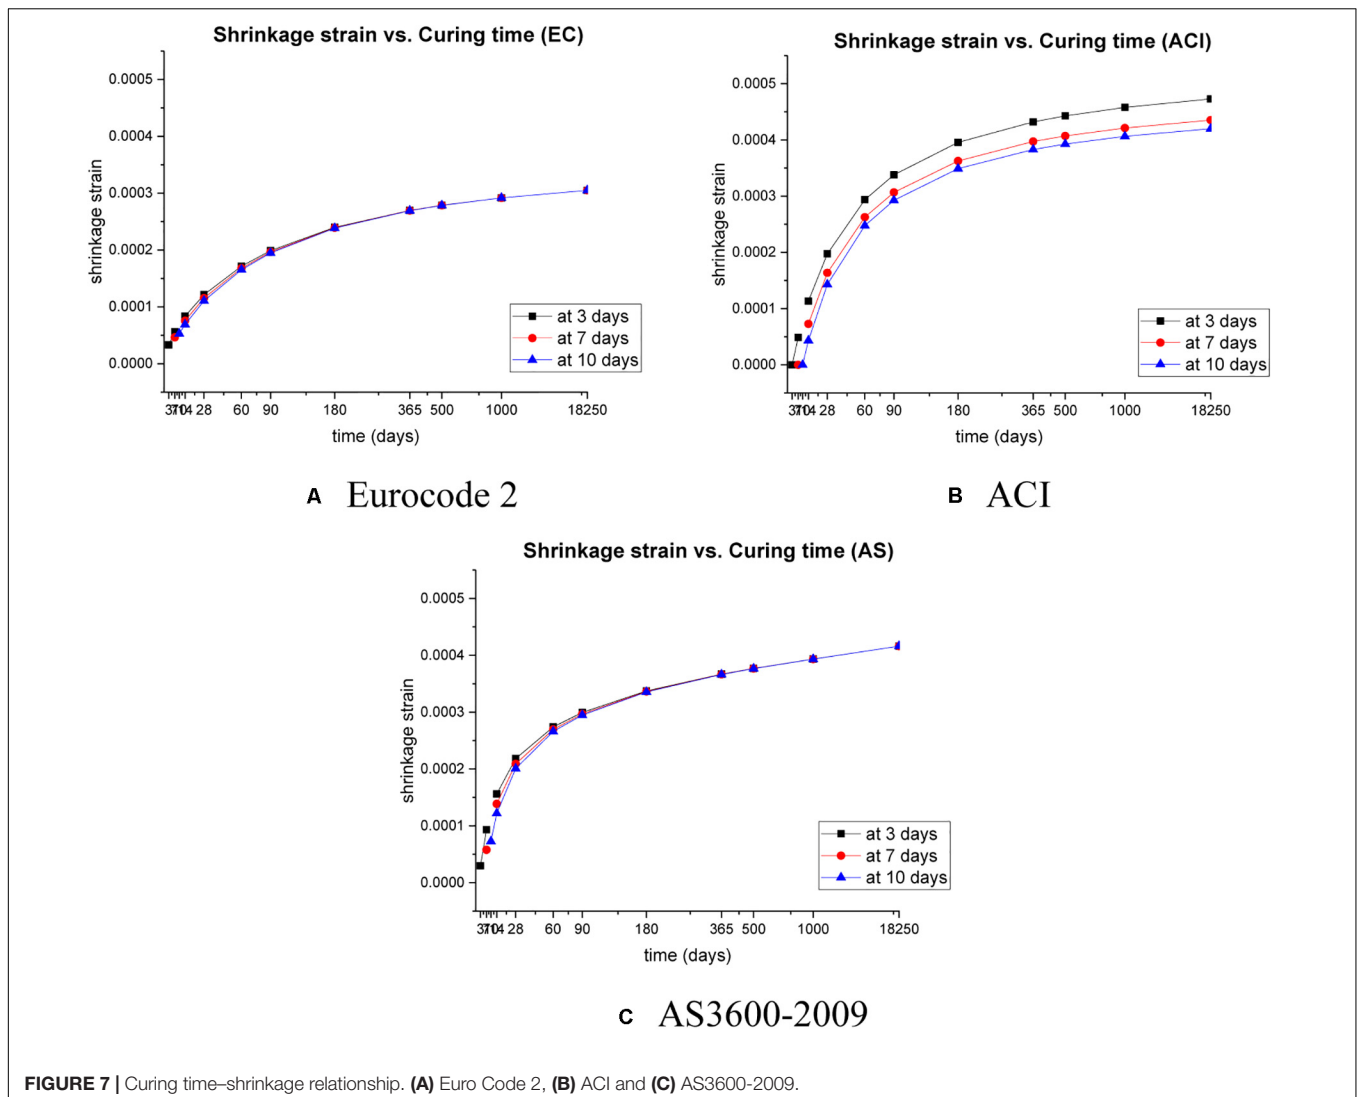

be dependant to a variety of factors. According to the analysis results, the loss of prestress depends largely on axial strain. This implies that a large strain will result in more prestress loss in prestressed concrete sleepers.

Considering a variety of concrete strengths (i.e., 55, 65, and 80 MPa), the parametric characteristics of creep coefficient and shrinkage strain are given in **Figures 3, 5**. It can be observed that a higher strength of concrete exhibits lesser creep. However, the characteristics of shrinkage strain are different from creep. It is apparent that a higher-strength concrete sleeper has higher shrinkage strain at the initial stage. However, over a longer term, the total shrinkage strain of higher strength concrete becomes lesser than that of lower strength concrete. The total shrinkage strain consists of autogenous shrinkage and drying shrinkage, which is an allowance for early thermal shrinkage and is assumed to develop relatively rapidly and to increase with concrete strength.

With respect to the relative humidity, the characteristics of creep coefficient and shrinkage strain are demonstrated in **Figures 4, 6**. It is clear that, with the increase in the relative humidity, both creep and shrinkage in prestressed concrete sleepers decrease.

Our studies illustrate that autogenous shrinkage causes more losses of prestress for higher-strength concrete in comparison with relatively lower-strength concrete at the initial period (Australian Building Codes Board, 1994; Fryba, 1996; Stevens and Dux, 2004). In fact, our prediction results confirm the experimental investigation campaigns done in Australia (Remennikov and Kaewunruen, 2014, 2015).

By comparisons among EC2, ACI, and Australian Standard, it can be observed that the prediction results obtained from each method are not similar even exactly under the same conditions. The main reason leading to different results can be attributed to the fact that different design codes concentrate on different parameters and have been established differently. For example, the predicted strain values are largely dependent on the relative humidity and concrete strength. Higher relative humidity causes lesser creep and shrinkage, which induce lower losses of prestress. Note that the environmental factors according to Australian geographic climate are utilized in Australian Standard instead of the relative humidity. In the ACI code, the concrete strength is not directly used for time-dependent behavior predictions, but the main parameters, which are related to the concrete strength such as cement content, air content, and fine aggregate content, are heavily used in the predictions.

CONCLUSION

The service life of railway prestressed concrete sleepers depends largely on a variety of factors such as concrete and material characteristics, environmental conditions, dynamic loading amplitude, and external abrasions. However, time-dependent behaviors of the concrete sleepers can also influence their durability and long-term performance in the field. In real life, creep and shrinkage strains can potentially have more significant influence on the deformation of track components. In harsh

environments, the railway infrastructure generally experiences highly aggressive loading conditions from increased traffics and load demands. At certain scenarios, a train derailment could happen because of track gauge change (i.e., tight gauge at such critical locations as crossing, slips, etc.). The track gauge change can be stemmed from the shortening and inelastic deflections incurred by creep and shrinkage in prestressed concrete sleepers. There are a number of existing codes of practice, enabling the predictions of creep and shrinkage. Three main design codes are examined critically in this paper. Key parameters that influence creep and shrinkage from a theoretical viewpoint for prestressed concrete sleepers are emphasized. A state-of-the-art review of research on time-dependent creep and shrinkage has been carried out in order to establish comprehensive methods for comparative analyses. This research embarks on the comparative parametric investigations into a variety of methods to determine creep and shrinkage effects in prestressed concrete railway sleepers. Comparisons among the design codes, including European Standard EUROCODE2, the American Concrete Institute ACI Code, and Australian Standard AS3600-2009, provide new practical insights into the time-dependent performance of concrete sleepers. The parametric effects of creep and shrinkage strains have been determined. Limitations of existing codes have been identified together with the recommendations and guidelines for code applications. The outcome of this study will help track engineers to better design, manufacture, inspect, and maintain railway infrastructures in order to enhance asset management efficacy and effectiveness.

DATA AVAILABILITY STATEMENT

All datasets generated for this study are included in the article/supplementary material.

AUTHOR CONTRIBUTIONS

DL analyzed the data. SK contributed the materials and analysis tools. PR and AR provided technical review and advice. All authors wrote the manuscript.

FUNDING

This work has been further developed from an initial work published in Li et al. (2018). The authors are sincerely grateful to European Commission for the financial sponsorship of the H2020-RISE Project No. 691135 “RISEN: Rail Infrastructure Systems Engineering Network,” which enables a global research network that tackles the grand challenge in railway infrastructure resilience and advanced sensing in extreme environments (www.risen2rail.eu). In addition, this project is partially supported by European Commission’s Shift2Rail, H2020-S2R Project No. 730849 “S-Code: Switch and Crossing Optimal Design and Evaluation.” The APC is sponsored by the University of Birmingham Library’s Open Access Fund.

REFERENCES

- Australian Building Codes Board (1994). *Building Code of Australia*, CSIRO Division of Building, Construction and Engineering Sydney, NSW: Australian Building Codes Board.
- Bentz, E. C. (2000). *Reinforced Concrete Sectional Analysis Using the Modified Compression Theory*. Ph. D. thesis, University of Toronto, Canada.
- Bhatt, P. (2011). *Prestressed Concrete Design to Eurocodes*, 1st Edn. Abington: Spon Press.
- Ercolino, M., Farhidzadeh, A., Salamone, S., and Magliulo, G. (2015). Detection of onset of failure in prestressed strands by cluster analysis of acoustic emissions. *Struct. Monitor. Maint.* 2, 339–355. doi: 10.12989/smm.2015.2.4.339
- Esveld, C. (2001). *Modern Railway Track*, 2nd Edn. Netherland: The Netherlands MRT Press.
- Fryba, L. (1996). *Dynamics of Railway Bridges*. London: Thomas Telford House.
- Fujino, Y., and Siringoringo, D. M. (2016). Japan's experience on long-span bridges monitoring. *Struct. Monitor. Maint.* 3, 233–257.
- Gilbert, R. I., Mickleborough, N. C., and Ranzi, G. (2016). *Design of Prestressed Concrete to AS3600-2009*, 2nd Edn. Boca Raton, FL: CRC Press.
- Gjorv, O. E. (2013). Durability design and quality assurance of major concrete infrastructure. *Adv. Concrete Constr.* 1, 45–63. doi: 10.12989/acc.2013.1.1.045
- Gustavson, R. (2002). *Structural Behaviour of Concrete Railway Sleepers*. Ph.D. thesis, Chalmers University of Technology, Sweden.
- Kaewunruen, S. (2014). Monitoring structural deterioration of railway turnout systems via dynamic wheel/rail interaction. *Case Stud. Nondestr. Test. Eval.* 19–24. doi: 10.1016/j.csdnt.2014.03.004
- Kaewunruen, S., Ishida, T., and Remennikov, A. M. (2016a). Impact analyses for negative flexural responses (hogging) in railway prestressed concrete sleepers. *J. Phys.* 744:012101. doi: 10.1088/1742-6596/744/1/012101
- Kaewunruen, S., Sussman, J. M., and Matsumoto, A. (2016b). Grand challenges in transportation and transit systems. *Front. Built. Environ.* 2:4. doi: 10.3389/fbuil.2016.00004
- Kaewunruen, S., and Remennikov, A. M. (2008a). An alternative rail pad tester for measuring dynamic properties of rail pads under large preloads. *Exp. Mech.* 48, 55–64. doi: 10.1007/s11340-007-9059-3
- Kaewunruen, S., and Remennikov, A. M. (2008b). Effect of a large asymmetrical wheel burden on flexural response and failure of railway concrete sleepers in track systems. *Eng. Fail. Anal.* 15, 1065–1075. doi: 10.1016/j.engfailanal.2007.11.013
- Kaewunruen, S., and Remennikov, A. M. (2008c). Experimental simulation of the railway ballast by resilient materials and its verification by modal testing. *Exp. Tech.* 32, 29–35. doi: 10.1111/j.1747-1567.2007.00298.x
- Kaewunruen, S., and Remennikov, A. M. (2010). Dynamic properties of railway track and its components: recent findings and future research direction. *Insight Nondestr. Test. Cond. Monitor.* 52, 20–22. doi: 10.1784/insi.2010.52.1.20
- Kaewunruen, S., and Remennikov, A. M. (2013). On the residual energy toughness of prestressed concrete sleepers in railway track structures subjected to repeated impact loads. *Electronic J. Struct. Eng.* 13, 41–61.
- Kaewunruen, S., Sussman, J. M., and Einstein, H. H. (2015). Strategic framework to achieve carbon-efficient construction and maintenance of railway infrastructure systems. *Front. Environ. Sci.* 3:6. doi: 10.3389/fenvs.2015.00006
- Li, D., and Kaewunruen, S. (2019). Effect of extreme climate on topology of railway prestressed concrete sleepers. *Climate* 7:17. doi: 10.3390/cli7010017
- Li, D., Kaewunruen, S., Robery, P., and Remennikov, A. M. (2018). “Creep and shrinkage effects on railway prestressed concrete sleepers,” in *ICRT 2017: Railway Development, Operations, and Maintenance*, eds W. Zhai and K. C. P. Wang (Reston, VA: American Society of Civil Engineers), 394–405.
- Li, Z., Li, S., Lv, J., and Li, H. (2015). Condition assessment for high-speed railway bridges based on train-induced strain response. *Struct. Eng. Mech.* 52, 199–219. doi: 10.12989/sem.2015.54.2.199
- Neville, A. M. (1995). *Properties of Concrete*, 4th edn. Longman: Longman House.
- Padhi, S., and Panda, K. C. (2017). Fresh and hardened properties of rubberized concrete using fine rubber and silpozz. *Adv. Concrete Constr.* 4, 49–69. doi: 10.12989/acc.2016.4.1.049
- Parande, A. K. (2013). Role of ingredients for high strength and high performance concrete – a review. *Adv. Concrete Constr.* 1, 151–162. doi: 10.12989/acc.2013.01.2.151
- Remennikov, A. M., and Kaewunruen, S. (2008). A review of loading conditions for railway track structures due to train and track vertical interaction. *Struct. Control Health Monitor.* 15, 207–234. doi: 10.1002/stc.227
- Remennikov, A. M., and Kaewunruen, S. (2005). Determination of dynamic properties of rail pads using instrumented hammer impact technique. *Acoust. Aust.* 33, 63–67.
- Remennikov, A. M., and Kaewunruen, S. (2014). Experimental load rating of aged railway concrete sleepers. *Eng. Struct.* 76, 147–162. doi: 10.1016/j.engstruct.2014.06.032
- Remennikov, A. M., and Kaewunruen, S. (2015). Determination of prestressing force in railway concrete sleepers using dynamic relaxation technique. *J. Perform. Constr. Facil.* 29:04014134. doi: 10.1061/(asce)cf.1943-5509.0000634
- Remennikov, A. M., Murray, M. H., and Kaewunruen, S. (2011). Reliability-based conversion of a structural design code for railway prestressed concrete sleepers. *Proc. Inst. Mech. Eng. Part F J. Rail Rapid Transit.* 226, 155–173. doi: 10.1177/0954409711418754
- Setsohnonkul, S., Kaewunruen, S., and Sussman, J. M. (2017). Lifecycle assessments of railway bridge transitions exposed to extreme climate events. *Front. Built Environ.* 3:35. doi: 10.3389/fbuil.2017.00035
- Stevens, N. J., and Dux, P. F. (2004). *A method of Designing A Concrete Railway Sleeper*. International Patent No WO 2004/019772 A1, Geneva: International Bureau.
- Taherinezhad, J., Sofi, M., Mendis, P. A., and Ngo, T. (2013). A review of behaviour of prestressed concrete sleepers. *Electronic J. Struct. Eng.* 13, 1–16.
- Tang, K., Millard, S., and Brattie, G. (2015). Technical and economical feasibility of using GGBS in long-span concrete structures. *Adv. Concrete Constr.* 3, 1–14. doi: 10.12989/acc.2015.3.1.001
- Vittorio, S. (2011). *Time-Dependent Behaviour of Reinforced Concrete Slabs*. Advanced Design of Structures, Thesis, University of Bologna, Bologna.
- Wakui, H., and Okuda, H. (1999). A study on limit-state design for prestressed concrete sleepers. *Concrete Lib. JSCE* 33, 1–25.
- Wang, N. (1996). *Resistance of Concrete Railroad Ties to Impact Loading*. Ph.D. Thesis, University of British Columbia, Canada.
- Warner, R. F., Rangan, B. V., Hall, A. S., and Faulkes, K. A. (1998). *Concrete Structures*, Addison Wesley. Melbourne, Australia: Longman.
- Yahiaoui, W., Kenai, S., Menadi, B., and Kadri, E. H. (2017). Durability of self-compacted concrete containing slag in hot climate. *Adv. Concrete Constr.* 5, 271–288.

Conflict of Interest: The authors declare that the research was conducted in the absence of any commercial or financial relationships that could be construed as a potential conflict of interest.

Copyright © 2020 Li, Kaewunruen, Robery and Remennikov. This is an open-access article distributed under the terms of the Creative Commons Attribution License (CC BY). The use, distribution or reproduction in other forums is permitted, provided the original author(s) and the copyright owner(s) are credited and that the original publication in this journal is cited, in accordance with accepted academic practice. No use, distribution or reproduction is permitted which does not comply with these terms.