

Mid-infrared-perturbed molecular vibrational signatures in plasmonic nanocavities

Chikkaraddy, Rohit; Xomalis, Angelos; Jakob, Lukas A.; Baumberg, Jeremy J.

DOI:

[10.1038/s41377-022-00709-8](https://doi.org/10.1038/s41377-022-00709-8)

License:

Creative Commons: Attribution (CC BY)

Document Version

Publisher's PDF, also known as Version of record

Citation for published version (Harvard):

Chikkaraddy, R, Xomalis, A, Jakob, LA & Baumberg, JJ 2022, 'Mid-infrared-perturbed molecular vibrational signatures in plasmonic nanocavities', *Light: Science and Applications*, vol. 11, no. 1, 19.
<https://doi.org/10.1038/s41377-022-00709-8>

[Link to publication on Research at Birmingham portal](#)

General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact UBIRA@lists.bham.ac.uk providing details and we will remove access to the work immediately and investigate.

ARTICLE

Open Access

Mid-infrared-perturbed molecular vibrational signatures in plasmonic nanocavities

Rohit Chikkaraddy¹✉, Angelos Xomalis^{1,2}, Lukas A. Jakob¹ and Jeremy J. Baumberg¹✉

Abstract

Recent developments in surface-enhanced Raman scattering (SERS) enable observation of single-bond vibrations in real time at room temperature. By contrast, mid-infrared (MIR) vibrational spectroscopy is limited to inefficient slow detection. Here we develop a new method for MIR sensing using SERS. This method utilizes nanoparticle-on-foil (NPOF) nanocavities supporting both visible and MIR plasmonic hotspots in the same nanogap formed by a monolayer of molecules. Molecular SERS signals from individual NPOF nanocavities are modulated in the presence of MIR photons. The strength of this modulation depends on the MIR wavelength, and is maximized at the 6–12 μm absorption bands of SiO_2 or polystyrene placed under the foil. Using a single-photon lock-in detection scheme we time-resolve the rise and decay of the signal in a few 100 ns. Our observations reveal that the phonon resonances of SiO_2 can trap intense MIR surface plasmons within the Reststrahlen band, tuning the visible-wavelength localized plasmons by reversibly perturbing the localized few-nm-thick water shell trapped in the nanostructure crevices. This suggests new ways to couple nanoscale bond vibrations for optomechanics, with potential to push detection limits down to single-photon and single-molecule regimes.

Introduction

Optical detection methods in the mid-infrared regime (MIR, 3–15 μm) with single-photon sensitivity have wide implications in astrophysics and molecular nanoscience. Molecules and polar dielectric systems have characteristic bond vibrations and phonon modes across MIR wavelengths^{1–6}. For ultrasmall sample volumes, optical detection (or pumping) of these modes gives low signals and is challenging due to the weak far-field coupling of these vibrations and low quantum efficiencies of MIR detectors^{7,8}. Fourier transform infrared spectroscopy methods with photoconductive detectors (MCT) remain the workhorse for MIR detection, but they are slow, often require cryogenic cooling, and cannot approach the quantum limit. Upconverting low-energy MIR photons to

high-energy visible photons would significantly benefit from single-photon-sensitive semiconductor (CCD, CMOS) technologies^{9–14}. However, the poor conversion efficiencies and small spatial overlap of MIR and visible photons pose significant challenges¹⁵.

Recent developments have circumvented the limitations associated with optical diffraction at long wavelengths by using near-field tip scanning (s-SNOM), photothermal infrared (PTIR)^{16,17} and far-field mid-infrared photothermal microscopy (MIP)¹⁸. s-SNOM still relies on MCT-based detection schemes but can overcome diffraction limits from near-field scanning tips. Near-field (PTIR) and far-field (MIP) photothermal methods instead utilize efficient detection in the visible. The modulated MIR laser beam changes the reflection/transmission of a visible beam due to thermal expansion, pressure waves, refractive index changes or Grüneisen changes in the medium, which are efficiently detected through lock-in methods¹⁸. Even though the visible detectors used are fast and efficient, the signals obtained in PTIR and MIP are limited by thermal diffusivities on millisecond timescales.


Correspondence: Rohit Chikkaraddy (rc621@cam.ac.uk) or Jeremy J. Baumberg (jjb12@cam.ac.uk)

¹NanoPhotonics Centre, Cavendish Laboratory, Department of Physics, JJ Thompson Avenue, University of Cambridge, Cambridge CB3 0HE, UK. ²Present address: Empa, Swiss Federal Laboratories for Materials Science and Technology, Laboratory for Mechanics of Materials and Nanostructures, Thun, Switzerland

© The Author(s) 2022, corrected publication 2022



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

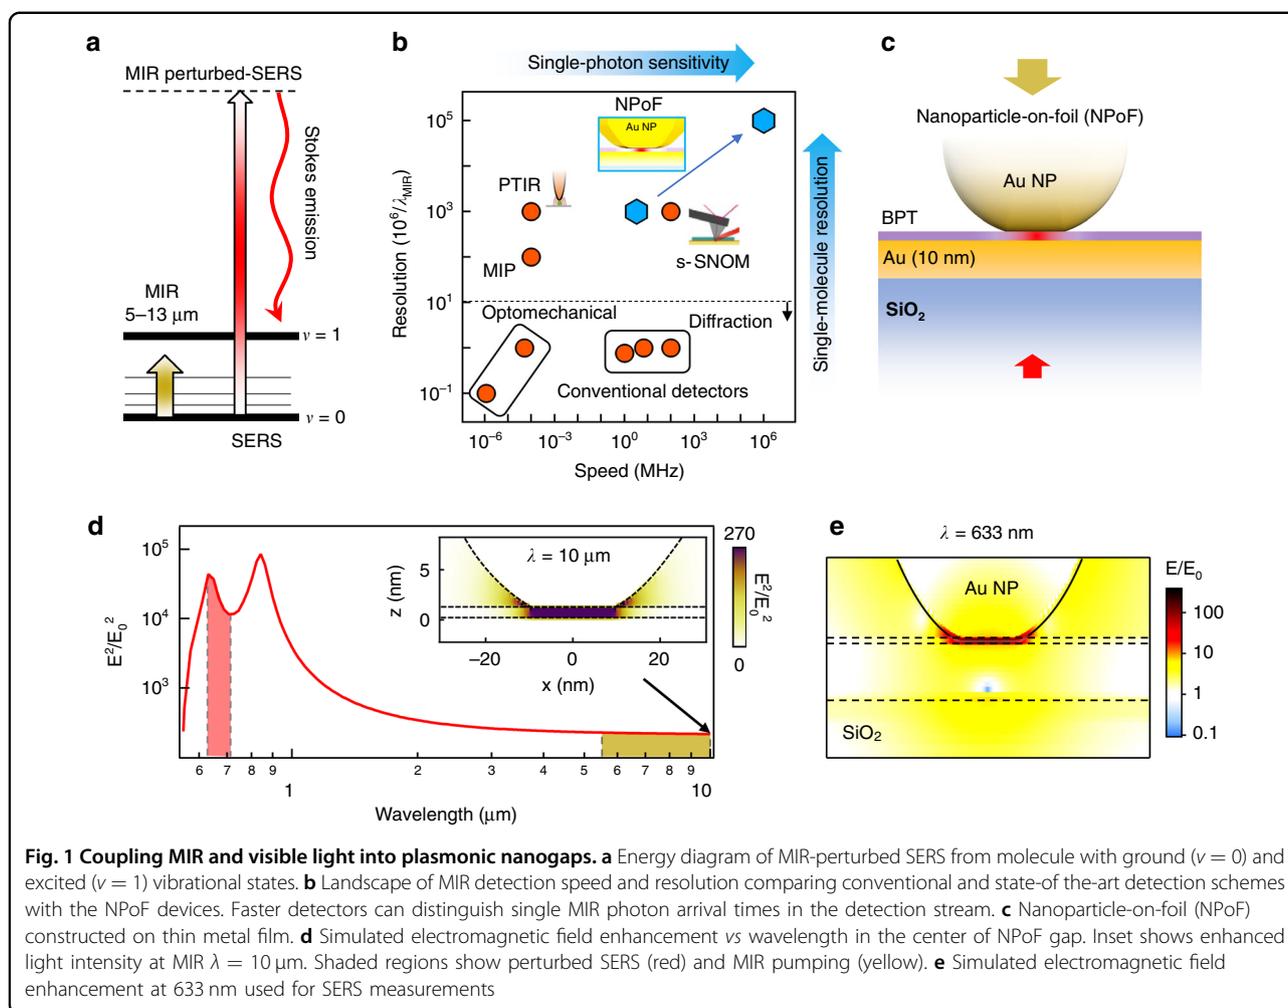

These challenges can be addressed by upconversion which utilizes cavity optomechanical approaches for efficient MIR detection. When MIR light impinges on an optical resonator it can excite mechanical resonances which are read out optically, allowing measurement at room temperature with low noise^{19–22}. Here the detection limits are set by optomechanical coupling strengths (g), proportional to the quality factor of the mechanical mode. However, the diffraction-limited size of such cavities limits g to less than 1 MHz and thus functions worse than conventional MCT-based detectors. Intriguingly, the mechanical motion can now be replaced by vibrating bonds in molecules (Fig. 1a), opening clear avenues for molecular optomechanics and photochemistry^{23,24}. This landscape of detection speed and resolution towards single-photon and single-molecule sensitivity shows how these diverse detection methods compare (Fig. 1b).

Here we develop a MIR-perturbed surface-enhanced Raman scattering (SERS) method which uses single-molecule-sensitive metal nanocavities. The system is constructed using gold nanoparticles (AuNP) on a thin

foil of planar Au with vibrating molecules assembled in the gap formed between them (Fig. 1c). The strong visible-light confinement in the nanogap provides enhanced ($>10^9$) Raman scattering from the molecules in the gap, acting as a near-field probe. In this detection scheme, MIR light is absorbed in molecular bonds on the foil significantly altering the Stokes and anti-Stokes Raman signals at visible wavelengths, which can easily be detected (Fig. 1a). The interaction of light and matter in these sub-nm mode volumes allows extreme sensitivity to (in principle) single MIR photon with resolution down to a single molecule (Fig. 1b).

Results


Coherent electron oscillations coupled with light (plasmon polaritons) trap electromagnetic (EM) fields around metal nanostructures giving a resonant optical response in the visible and broad weaker optical response spanning from visible to MIR wavelengths^{25–30}. While single metal nanoparticles do not provide sufficient field enhancement needed for robust single-molecule SERS,


nanogap confinement improves this greatly. Here we exploit a multilayer nanoparticle-on-foil (NPOF) cavity that resonantly enhances the near-field at visible wavelengths in addition to giving a broad MIR optical response from lighting rod effects^{31,32}. This structure consists of a faceted gold nanoparticle placed ~ 1.3 nm above a thin Au film (10 nm) deposited on a SiO₂ substrate (Fig. 1c). The gap distance between the AuNP and Au film is set by the monolayer height of biphenyl-4-thiol (BPT) molecules preassembled from solution onto the film before AuNP deposition. The resulting NPOF structure supports plasmonic (lm) = (10) and (20) cavity resonances at 850 nm and 650 nm with $E/E_0 > 100$ (Fig. 1e)^{33–35}. This gives strong SERS and a broad uniform near-field enhancement across the MIR absorption wavelengths of 5–15 μ m (Fig. 1d). The NPOF is designed for optimal spatial overlap of visible and MIR light which is vital for MIR-perturbed SERS.

To study the MIR-perturbed SERS from these cavities, we direct a tunable MIR pump beam (500 μ W average

power) and 633 nm SERS probe (150 μ W average power) onto individual NPOF cavities (Fig. 2a). The 633 nm laser is focused through the SiO₂ substrate while the MIR pump is focused via a Cassegrain objective from the air-side, with estimated spot diameters on the sample of 1 μ m for 633 nm and 20 μ m for the MIR beam at $\lambda = 10$ μ m (Supporting Information, Fig. S1). Both beams are co-aligned onto the sample and the back-scattered SERS from BPT molecules is collected through the SiO₂ substrate and routed to the spectrometer. The NPOF supports a unique dual configuration with metal-insulator-metal (MIM) gap mode at the AuNP-foil junction coupling to the insulator-metal-insulator (IMI) mode at the air-foil-glass interface, resulting in tightly confined MIMI modes which radiate SERS light predominately into the glass medium³⁶.

The NPOF cavities provide stable SERS signals upon laser illumination at 633 nm, with characteristic BPT vibrational lines at 1080 cm^{-1} and 1585 cm^{-1} (Fig. 2b).³⁷ The spectral intensity variation obtained from time-series

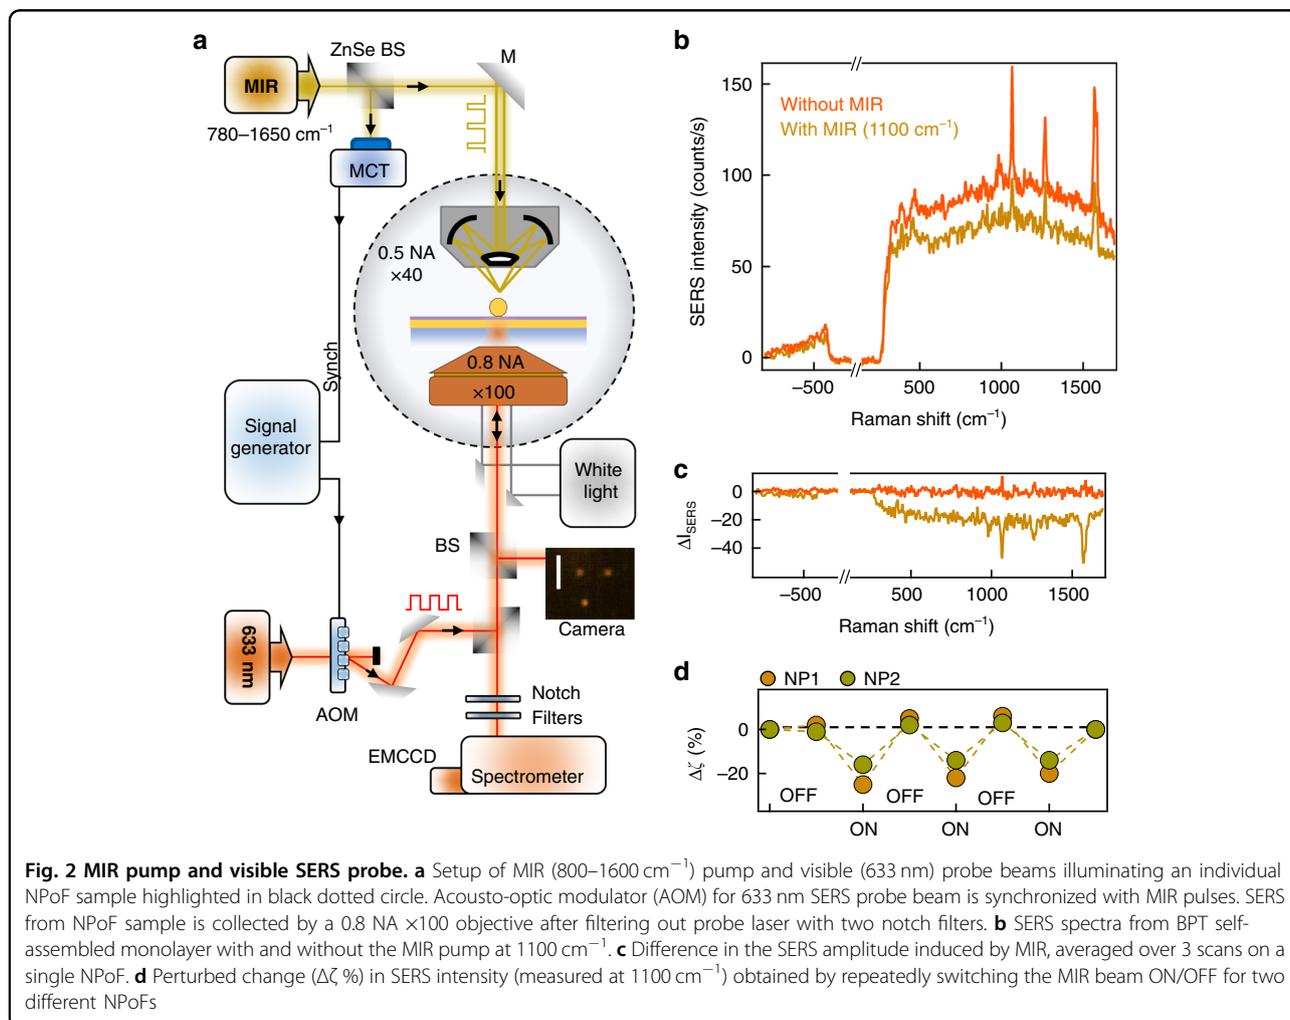

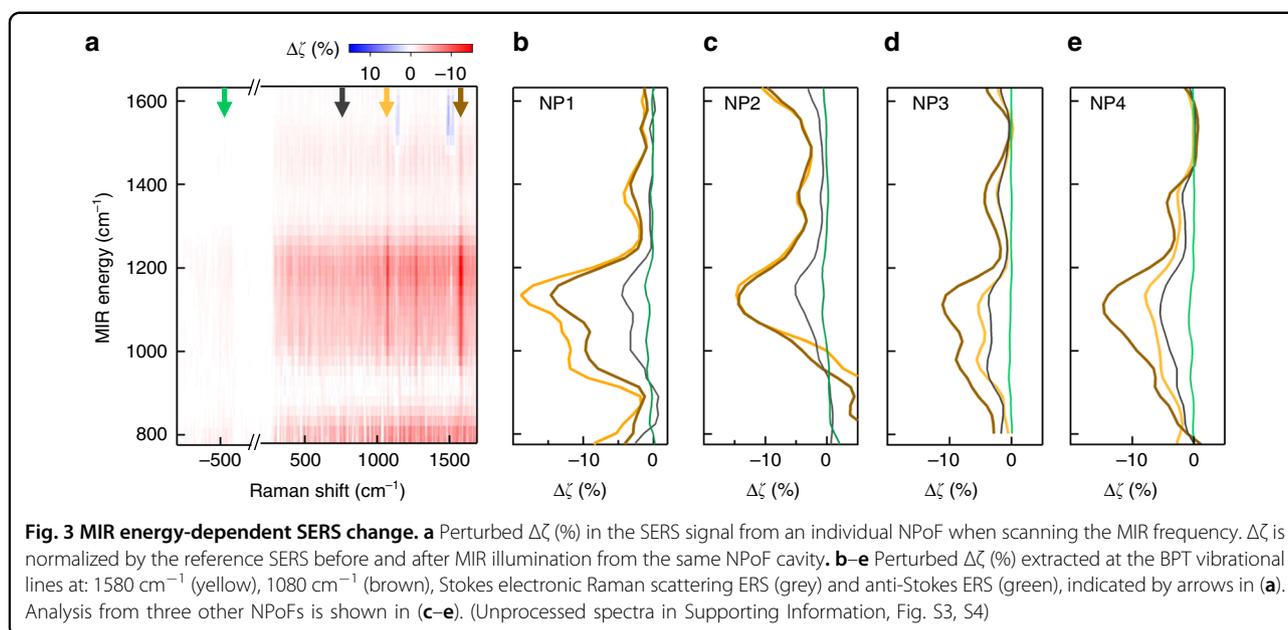

spectra over a period of 30 s from an individual NPoF cavity is $<1\%$ (Supporting Information Fig. S2). Upon irradiating with MIR light at 1100 cm^{-1} , the SERS intensity is found to decrease by $\Delta\zeta > 20\%$ (Fig. 2b). This strong decrease in SERS signal is observed across all the vibrational lines of BPT as well as the Stokes background from the electronic Raman scattering (Fig. 2c). The observed intensity change immediately recovers once the MIR light is turned off (Fig. 2d).


To understand the MIR energy dependence we collect SERS spectra while tuning the MIR energy between 800 and 1600 cm^{-1} (in steps of 20 cm^{-1}). SERS spectra are also collected both before and after the sample is illuminated with MIR light for reference. Scans with large variations ($> 30\%$) in the SERS spectra before and after MIR illumination either due to the alignment drift or diffusion of Au-adatoms in NPoF gaps are not considered^{38–40}. Perturbed changes $\Delta\zeta$ in SERS Stokes and anti-Stokes signals upon tuning the MIR illumination energy (Fig. 3a) show a broadband response. Line profiles extracted from BPT at two different vibrational lines (1080 cm^{-1} and 1585 cm^{-1} , Fig. 3b–e) show the maximum decrease occurs when the MIR is tuned around 1100 cm^{-1} . Electronic Raman signals extracted from the Stokes background exhibit similar line profiles, with a lower magnitude (grey). This characteristic MIR-perturbed peak at 1100 cm^{-1} corresponds to the SiO_2 phonon absorption (see below).

It is important to note that we never observe an increase in SERS, even when using AuNPs with different lower facet size which tunes their plasmon resonances with respect to the 633 nm probe wavelength (Supporting Information, Fig. S10). The measured scattering

resonances match our simulations for AuNPs with average facet sizes of 20 nm, which is consistent with scanning electron microscope images (Supporting Information, Fig. S9). In addition, experiments performed on the foil away from the AuNP do not show any signature of MIR-perturbed SERS, which confirms that the perturbed SERS signals are observed only from the nanogap, and not from the foil on its own.

To confirm the origin of MIR-perturbed signals from the influence of vibrations of the support material underneath the foil, we constructed NPoF systems with polystyrene replacing SiO_2 under the foil (Fig. 4a). The MIR energy dependence on polystyrene-NPoFs show a different spectral dependence and weaker signal intensity compared to SiO_2 samples. Here a smaller MIR frequency range is scanned with a finer resolution of 5 cm^{-1} . The MIR-perturbed SERS spectrum displays sharp peaks matching the vibrational absorption lines of bulk polystyrene, clearly indicating that the signal must originate from interactions with the material underneath the foil. The perturbed SERS signal varies across different NPoF structures which is a characteristic signature of nanoscale inhomogeneities, depending on the exact molecular geometry of polymer underneath the NPoF.

To characterize the dynamics of the MIR-perturbed SERS signal originating from the phonons underneath the foil, we develop a time-correlated single-photon lock-in method to time-resolve the signal. The Stokes part of the SERS signal is routed to a single-photon avalanche diode (SPAD) detector (Fig. 5a). The arrival of each SERS photon is time-correlated to the MIR trigger signal from the quantum cascade laser (QCL). This allows us to resolve the MIR-perturbed signal with a time resolution of

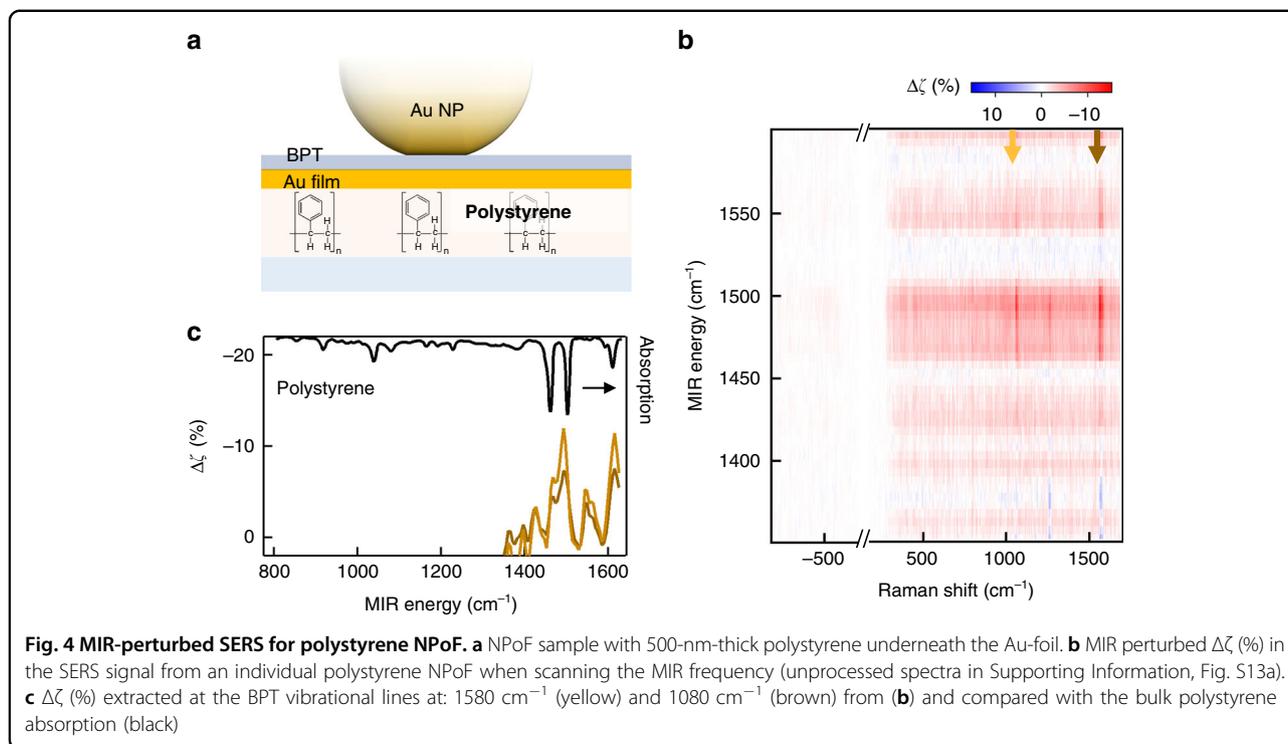

100 ps⁴¹. The QCL is triggered at 0.32 MHz with MIR pulses of width 100 ns. The MIR-perturbed SERS rapidly decreases immediately after the MIR pulse (Fig. 5b), with a timescale of ~ 300 ns consistently obtained across multiple NPoF cavities (not limited by the MIR pulsewidth of 100 ns). Subsequently, the SERS signal recovers with a longer decay time of >500 ns. This temporal response is fit with the single exponential rise and decay times using experiments on >25 NPoF cavities. The rise time is narrowly distributed around 290 ± 50 ns whereas the decay time is more variable spanning 700 ± 250 ns (Fig. 5c). We find a positive correlation between the rise and decay times ($\tau_{\text{decay}} \sim 3.9\tau_{\text{rise}}$), suggesting they are intrinsically linked to the origin of the MIR-perturbed SERS signature.


Discussion

The maximum decrease in SERS signal observed at MIR energies $\sim 1100 \text{ cm}^{-1}$ is consistent across different NPoFs; however, the magnitude of signal varies between $\Delta\zeta = 10\text{--}25\%$. The spectral response of the perturbed SERS does not match with Raman or IR vibrational lines of BPT. This indicates that MIR absorption in BPT is not the dominant contribution to the observed signal. Instead, this characteristic peak at 1100 cm^{-1} corresponds to the SiO_2 phonon absorption. This is also evidenced in the reflection dip that exhibits a typical Reststrahlen band^{42,43} and confirmed by simulations of the MIR absorption at the Au– SiO_2 interface (Fig. 6a, b). Within a band between 900 and 1150 cm^{-1} , the real part of the SiO_2 dielectric

function is negative ($\text{Re}(\epsilon) < 0$). The reduced SERS signal must therefore arise from a decrease in near-field intensity of the 633 nm probe, somehow caused by MIR excitation of this confined mode at the Au– SiO_2 interface. This results in a linear response with MIR power (Fig. 6c).


Direct heating of the Au interface from the 2 mW average power MIR pump contributes only a minimal change of $<1^\circ \text{C}$ in temperature (Fig. 6d, e), which is fully consistent with the unchanged anti-Stokes background of SERS signals observed. The change in refractive index of SiO_2 needed to account for a 20% decrease in SERS is rather high ($\Delta n > 0.2$) for the pump powers used here (Supporting Information, Fig. S5), corresponding to temperatures $>1000^\circ \text{C}$. As a result, simple thermal effects are not sufficient to account for these observations. Further, conventional photothermal signals possess slow timescales (ms)^{44,45} as the induced deflection of visible light requires strong deformations of the substrate underneath. Thermal expansion of Au or SiO_2 for a 10 K increase in local temperature is far too small to modulate the visible probe as required (Supporting Information, Table. S1). Similarly, reversible reconstruction of grain boundaries or polycrystallinity in the Au-foil on SiO_2 seems also unlikely to explain this MIR-perturbed SERS.

The decrease in the SERS signal is thus attributed to a shift in the plasmon resonance wavelength perturbed by the modulation of refractive index directly around the AuNP (Supporting Information, Fig. S6). Exciting the SiO_2 Reststrahlen band shifts the (10) NPoF plasmon by

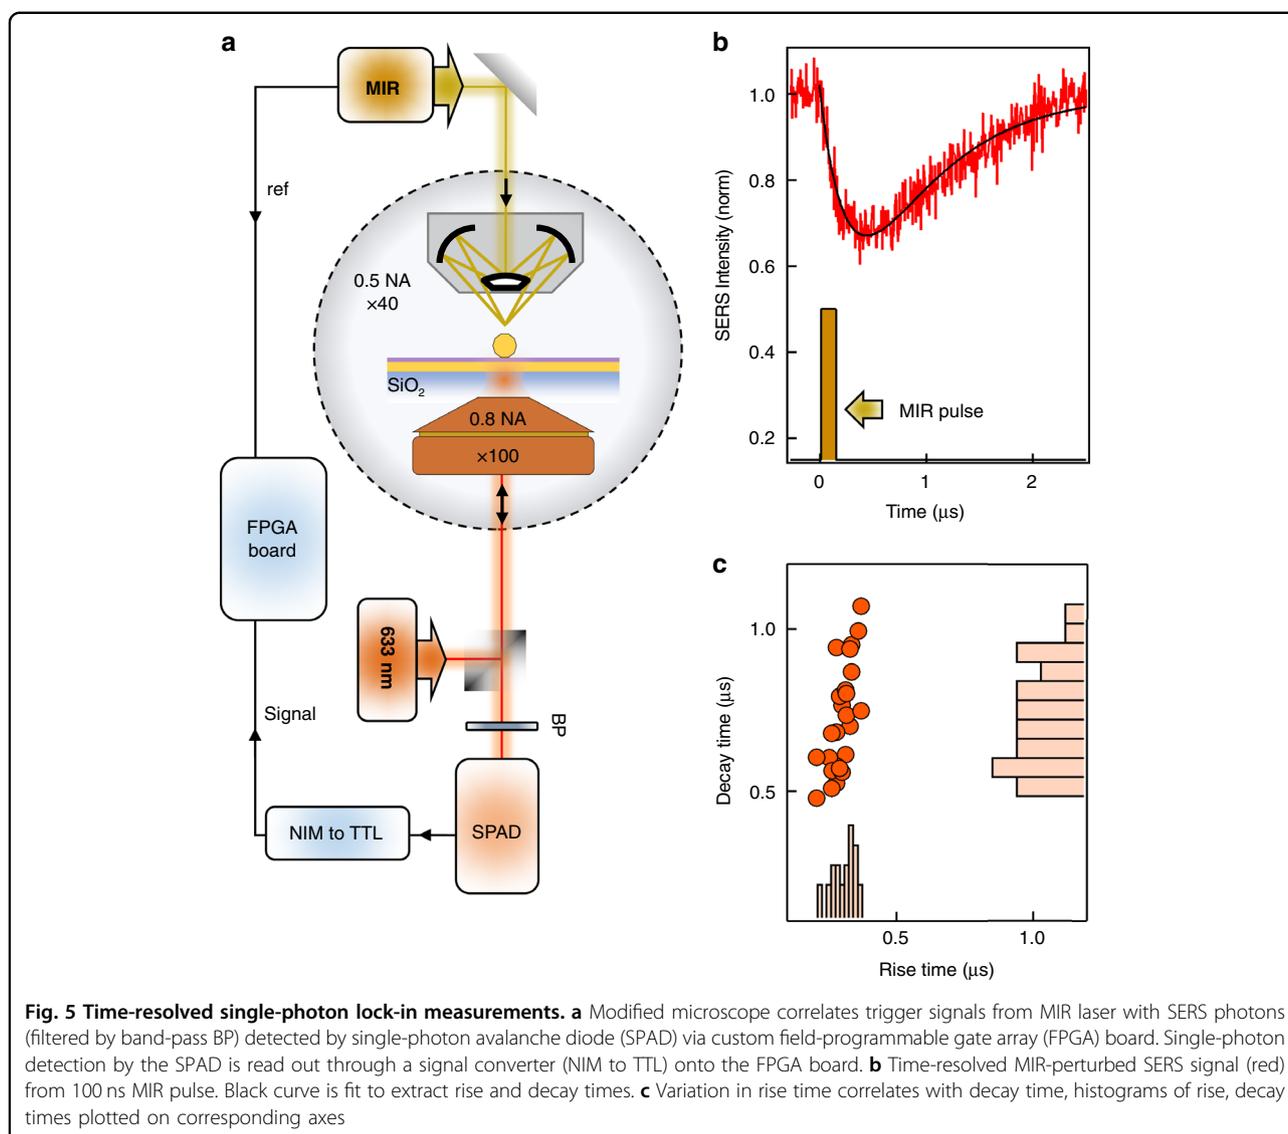

~ 1 nm and reduces the plasmon enhancement of SERS at $\lambda = 633$ nm. We can identify very few possible routes for this modulation, but possibilities can be either from nm-scale deformations in the NP surface or from the effects of a nanoscale shell of water in the crevices under the AuNP. This shell of water is always present for such nano-assemblies in ambient conditions, and extremely hard to remove due to the highly acute crevice angle. The experiments performed here are in ambient dry conditions. However, in such nanogap confined environments, trapped water rearranges into various phases and can never be driven off completely⁴⁶. We perform additional experiments with NPoF samples immersed in water and ethanol where evaporation is absent, and this indeed gives undetectable perturbation of the SERS signal in the presence of MIR light (Supporting Information, Fig. S8). Modelling shows that changing the crevice water shell

width by < 5 nm is sufficient to induce a 20% decrease in the SERS signal (Fig. 6f, g). While the weak direct absorption of MIR light is insufficient to induce this, the situation is very different in the spectral band where SiO_2 acts as a metal⁴⁷ ($\text{Re}(\epsilon) < 0$ from 900 to 1200 cm^{-1}) which allows it to support surface-plasmon-polaritons (SPPs) that amplify the optical field near Au by > 50 . These MIR SPPs are excited only by scattering at the NP, leading to even higher fields directly in the crevices and thus heating trapped water in real time. Indeed, replacing the SiO_2 with Si_3N_4 (which has $\text{Re}(\epsilon) > 0$ throughout our spectral range) eliminates this effect, demonstrating the key role of resonant MIR SPPs²². The total absorbed energy from each MIR pulse is a hundred-fold larger than required to evaporate a 5 nm shell of water. This mechanism is also consistent with the sub- μs rise and decay times, which correspond to thermal diffusion times from the heated nanoparticle (Fig. 6f).

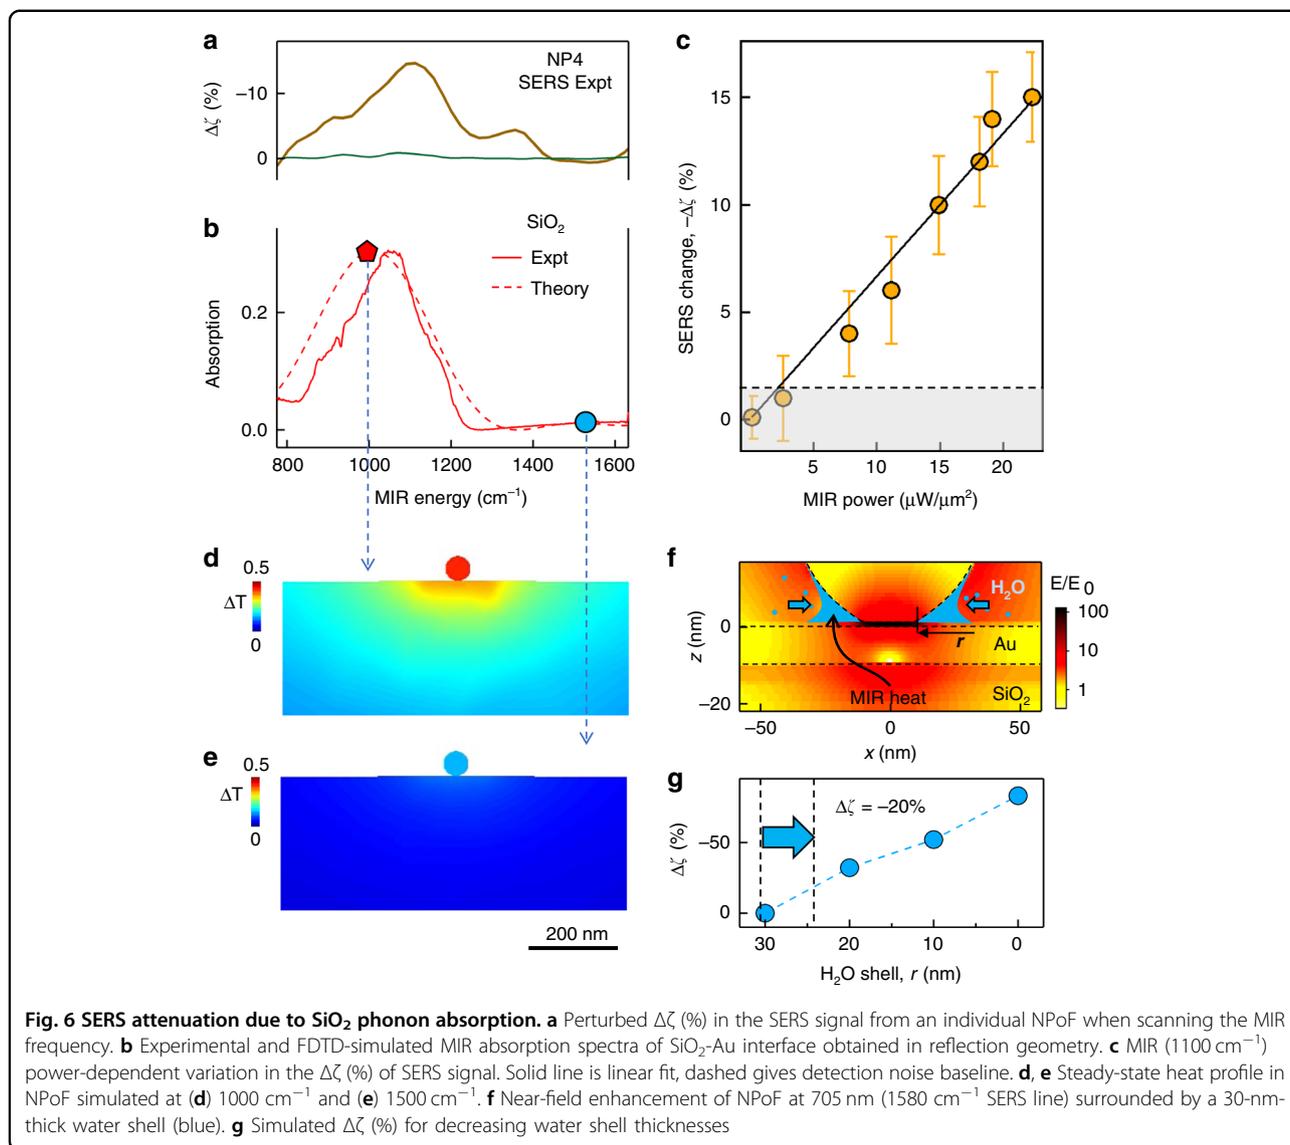

Most dielectrics support vibrational mid-infrared-active phonon modes which interact with light and plasmons in the same fashion as described above^{48,49}. These polariton modes are distributed across the MIR-visible regions and constrain the nanoscale geometries for producing upconverted SERS signals. Since MIR SPP excitation improves the MIR coupling into the gap, there is a trade-off between enhanced SERS upconversion and enhanced thermally perturbed retuning of the plasmon resonances. Our work suggests that avoiding the substrate Reststrahlen band will be needed for observing SERS upconversion from molecules²².

The efficiencies of MIR detection in this NPoF system are compared with state-of-the-art low-dimensional semiconductor heterostructures or graphene that have been implemented for THz detection in recent detection

schemes^{50–53}. From an application perspective, the relevant figure of merit is the noise equivalent power (NEP), which corresponds to the lowest detectable power in 0.5 s integration time. This is measured here as the MIR power-dependent perturbation to the SERS signal (Fig. 6c); however, most of the incident MIR is reflected by the Au-foil and remains undetected instead of being absorbed in the substrate. Given the 100 nm² cross-section of NPoFs at MIR frequencies, the NEP is estimated to be 0.1 nW Hz^{-0.5}, which is close to state-of-the-art detectors. Carefully designed variants of the NPoF geometry with MIR antenna resonances supporting unity absorption of MIR light would greatly boost the NEP. Theoretically the noise level is limited by photon shot noise in the visible laser, although in current experiments the noise is limited by the stability of the SERS signal. Light-

driven diffusion of adatoms^{38,54} and fluctuations³⁹ of defects in the metal nanoparticle contribute to significant variation in SERS intensities. There exists an opportunity to significantly improve the noise reduction by developing more robust nanocavity systems. Further, we suggest additional improvements in MIR detection by deterministically creating adatom picocavities with light^{40,55}.

In summary, we show how molecular SERS signals are modified by irradiating with MIR light across a wide spectral bandwidth from 5.8 to 12 μm (24–51 THz, 800–1700 cm^{-1}). Our observations reveal that phonon resonances of the SiO_2 substrate trap intense MIR SPPs in the Reststrahlen band, which can temporarily retune the localized plasmons by perturbing the outer 5-nm-thick shells of water in the nanostructure crevices. This results in strong reductions in SERS intensity, but could also be used in other ways, for instance for tuning plasmons in real time, as well as for exciting the NPoM in the MIR through SPP waveguides or antenna coupling. This suggests new ways to access nanoscale chemical imaging³, MIR photothermal bolometers⁵⁶, photoacoustic microscopy⁵⁷ and optomechanics⁵⁸.

Materials and methods

Sample preparation

To prepare the thin mirror, we deposit 10 nm of Au on a clean SiO_2 cover slip (150 μm thick) with a deposition rate of 0.5 \AA s^{-1} (Moorfield nanoPVD-T15A thermal evaporator). The Au-coated SiO_2 substrates are dipped into a 1 mM solution of biphenyl-4-thiol (BPT, Sigma Aldrich, 97%) in anhydrous ethanol (Sigma Aldrich, <0.003% H₂O) for 12 h resulting in self-assembled molecular monolayers (SAMs). For NPoF optical cavities, 80 nm faceted NPs (BBI Solutions) are deposited directly onto the BPT-assembled Au-coated SiO_2 substrates. The deposition time is kept below 30 s, resulting in well-dispersed NPs. Lastly, the samples are rinsed thoroughly with double distilled water to remove the excess AuNPs.

Experimental setup

All SERS and MIR spectroscopy measurements are performed in a custom-built dual-channel microscope. For SERS, a spectrally filtered 633 nm diode laser (Matchbox, Integrated Optics) with 150 $\mu\text{W}\mu\text{m}^{-2}$ power on the sample is used as a probe and is filtered with two notch filters before routing it to a Shamrock i303 spectrograph and a Newton EMCCD. The 633 nm light is focused onto the sample with the aid of a $\times 100$ 0.8 NA long working distance microscope objective. For imaging, the reflected light collected through the same objective lens is directed to a camera (Lumenera Infinity3–1). For the MIR light source, a quantum cascade laser (QCL) from LaserTune IR source (Block) with wavelength range of 5.4–13 μm is used (1635–780 cm^{-1})

and maximum average output of 500 μW ($\sim 2 \times 4$ mm collimated) with 5% duty cycle. The pump (MIR light) is coaligned with the probe (visible light) using a 0.4 NA Cassegrain objective lens. For MIR detection, an external mercury-cadmium-telluride (MCT) IR detector is used along with a ZnSe beam-splitter and is synced with the AOM to modulate the 633 nm diode laser. This improves the pump and probe pulse temporal overlap by matching the repetition rate and pulse widths. The sample is placed on a fully automated motorized stage (Prior Scientific H101) which is controlled with code written in Python.

For single-photon time-correlated measurements, arrival times of all photons at the detector (Micro Photon Devices PDM \$PD-100-CTD) and reference signals (MIR laser trigger) are continuously recorded by a time-to-digital converter on a field-programmable gate array (FPGA) board. Comparing the photon timestamps with the reference signal allows recreating the periodic perturbation of the SERS signal by the MIR laser in time, integrated over millions of modulation cycles. This single-photon lock-in detection scheme is described in more detail elsewhere⁴¹.

Acknowledgements

The authors acknowledge support from European Research Council (ERC) under Horizon 2020 research and innovation programme PICOFORCE (Grant Agreement No. 861950), THOR (Grant Agreement No. 829067) and POSEIDON (Grant Agreement No. 861950). We acknowledge funding from the EPSRC (Cambridge NanoDTC EP/L015978/1, EP/L027151/1, EP/S022953/1, EP/P029426/1, and EP/R020965/1). R.C. acknowledges support from Trinity College, University of Cambridge.

Author contributions

R.C. and J.J.B. conceived and designed the experiments. R.C. performed the experiments with input from A.X. and L.A.J. R.C. carried out the simulation and the analytical modelling with input from A.X. R.C., A.X. and J.J.B. analysed the data. R.C. and J.J.B. wrote the manuscript with input from all authors.

Data availability

Source data can be found at <https://doi.org/10.17863/CAM.79290>.

Conflict of interest

The authors declare no competing interests.

Supplementary information The online version contains supplementary material available at <https://doi.org/10.1038/s41377-022-00709-8>.

Received: 12 July 2021 Revised: 15 November 2021 Accepted: 5 January 2022

Published online: 19 January 2022

References

1. Cheng, J. X. & Xie, X. S. Vibrational spectroscopic imaging of living systems: an emerging platform for biology and medicine. *Science* **350**, 6264 (2015).
2. Huth, F. et al. Infrared-spectroscopic nanoimaging with a thermal source. *Nat. Mater.* **10**, 352–356 (2011).
3. O’Callahan, B. T. et al. Photoinduced tip-sample forces for chemical nanoimaging and spectroscopy. *Nano Lett.* **18**, 5499–5505 (2018).
4. Low, T. et al. Polaritons in layered two-dimensional materials. *Nat. Mater.* **16**, 182–194 (2017).

5. Song, B. et al. Enhancement of near-field radiative heat transfer using polar dielectric thin films. *Nat. Nanotechnol.* **10**, 253–258 (2015).
6. Basov, D. N., Fogler, M. M. & de Abajo, J. F. G. Polaritons in van der Waals materials. *Science* **354**, aag1992 (2016).
7. Dorling, K. M. & Baker, M. J. Rapid FTIR chemical imaging: highlighting FPA detectors. *Trends Biotechnol.* **31**, 437–438 (2013).
8. Baker, M. J. et al. Using Fourier transform IR spectroscopy to analyze biological materials. *Nat. Protoc.* **9**, 1771–1791 (2014).
9. Dam, J. S., Tidemand-Lichtenberg, P. & Pedersen, C. Room-temperature mid-infrared single-photon spectral imaging. *Nat. Photonics* **6**, 788–793 (2012).
10. Kviatkovsky, I. et al. Microscopy with undetected photons in the mid-infrared. *Sci. Adv.* **6**, eabd0264 (2010).
11. Junaid, S. et al. Video-rate, mid-infrared hyperspectral upconversion imaging. *Optica* **6**, 702–708 (2019).
12. Knez, D. et al. Infrared chemical imaging through non-degenerate two-photon absorption in silicon-based cameras. *Light: Sci. Appl.* **9**, 125 (2020).
13. Kutas, M. et al. Quantum-inspired terahertz spectroscopy with visible photons. *Optica* **8**, 438–441 (2021).
14. Lindner, C. et al. Nonlinear interferometer for Fourier-transform mid-infrared gas spectroscopy using near-infrared detection. *Opt. Express* **29**, 4035–4047 (2021).
15. Tidemand-Lichtenberg, P. et al. Mid-infrared upconversion spectroscopy. *J. Opt. Soc. Am. B* **33**, D28–D35 (2016).
16. Wang, L. et al. Nanoscale simultaneous chemical and mechanical imaging via peak force infrared microscopy. *Sci. Adv.* **3**, e1700255 (2017).
17. Anderson, M. S. Infrared spectroscopy with an atomic force microscope. *Appl. Spectrosc.* **54**, 349–352 (2000).
18. Bai, Y. R., Yin, J. Z. & Cheng, J. X. Bond-selective imaging by optically sensing the mid-infrared photothermal effect. *Sci. Adv.* **7**, eabg1559 (2021).
19. Bagci, T. et al. Optical detection of radio waves through a nanomechanical transducer. *Nature* **507**, 81–85 (2014).
20. Belacel, C. et al. Optomechanical terahertz detection with single meta-atom resonator. *Nat. Commun.* **8**, 1578 (2017).
21. Roelli, P. et al. Molecular platform for frequency upconversion at the single-photon level. *Phys. Rev. X* **10**, 031057 (2020).
22. Xomalis, A. et al. Detecting mid-infrared light by molecular frequency upconversion with dual-wavelength hybrid nanoantennas. *Science* **374**, 1268 (2021).
23. Zhang, Y., Aizpurua, J. & Esteban, R. Optomechanical collective effects in surface-enhanced Raman scattering from many molecules. *ACS Photonics* **7**, 1676–1688 (2020).
24. Neuman, T. et al. Quantum description of surface-enhanced resonant Raman scattering within a hybrid-optomechanical model. *Phys. Rev. A* **100**, 043422 (2019).
25. Rodrigo, D. et al. Self-similar multiresonant nanoantenna arrays for sensing from near- to mid-infrared. *ACS Photonics* **5**, 4903–4911 (2018).
26. Le, F. et al. Metallic nanoparticle arrays: a common substrate for both surface-enhanced Raman scattering and surface-enhanced infrared absorption. *ACS Nano* **2**, 707–718 (2008).
27. Neubrech, F. et al. Surface-enhanced infrared spectroscopy using resonant nanoantennas. *Chem. Rev.* **117**, 5110–5145 (2017).
28. Huh, J. H., Lee, J. & Lee, S. Soft plasmonic assemblies exhibiting unnaturally high refractive index. *Nano Lett.* **20**, 4768–4774 (2020).
29. Schuller, J. A. et al. Plasmonics for extreme light concentration and manipulation. *Nat. Mater.* **9**, 193–204 (2010).
30. Xu, Y. et al. Light–matter interaction within extreme dimensions: from nanomanufacturing to applications. *Adv. Opt. Mater.* **6**, 1800444 (2018).
31. Gramotnev, D. K. & Bozhevolnyi, S. I. Nanofocusing of electromagnetic radiation. *Nat. Photonics* **8**, 13–22 (2014).
32. Urbieto, M. et al. Atomic-scale lightning rod effect in plasmonic picocavities: a classical view to a quantum effect. *ACS Nano* **12**, 585–595 (2018).
33. Chikkaraddy, R. et al. How ultranarrow gap symmetries control plasmonic nanocavity modes: from cubes to spheres in the nanoparticle-on-mirror. *ACS Photonics* **4**, 469–475 (2017).
34. Baumberg, J. J. et al. Extreme nanophotonics from ultrathin metallic gaps. *Nat. Mater.* **18**, 668–678 (2019).
35. Kongsuwan, N. et al. Plasmonic nanocavity modes: from near-field to far-field radiation. *ACS Photonics* **7**, 463–471 (2020).
36. Chikkaraddy, R. & Baumberg, J. J. Accessing plasmonic hotspots using nanoparticle-on-foil constructs. *ACS Photonics* **8**, 2811–2817 (2021).
37. Benz, F. et al. SERS of individual nanoparticles on a mirror: size does matter, but so does shape. *J. Phys. Chem. Lett.* **7**, 2264–2269 (2016).
38. Xomalis, A. et al. Controlling optically driven atomic migration using crystal-facet control in plasmonic nanocavities. *ACS Nano* **14**, 10562–10568 (2020).
39. Carnegie, C. et al. Flickering nanometre-scale disorder in a crystal lattice tracked by plasmonic flare light emission. *Nat. Commun.* **11**, 682 (2020).
40. Carnegie, C. et al. Room-temperature optical picocavities below 1 nm³ accessing single-atom geometries. *J. Phys. Chem. Lett.* **9**, 7146–7151 (2018).
41. Jakob, L. A. et al. Single-photon multicolor lock-in detection by picosecond time stamping. *Optica* **8**, 1646 (2021).
42. Amarie, S. & Keilmann, F. Broadband-infrared assessment of phonon resonance in scattering-type near-field microscopy. *Phys. Rev. B* **83**, 045404 (2011).
43. Li, P. N. et al. Reversible optical switching of highly confined phonon–polaritons with an ultrathin phase-change material. *Nat. Mater.* **15**, 870–875 (2016).
44. Baffou, G. et al. Simple experimental procedures to distinguish photothermal from hot-carrier processes in plasmonics. *Light: Sci. Appl.* **9**, 108 (2020).
45. Aleshire, K. et al. Far-field midinfrared superresolution imaging and spectroscopy of single high aspect ratio gold nanowires. *Proc. Natl Acad. Sci. USA* **117**, 2288–2293 (2020).
46. Asay, D. B. & Kim, S. H. Effects of adsorbed water layer structure on adhesion force of silicon oxide nanoasperity contact in humid ambient. *J. Chem. Phys.* **124**, 174712 (2006).
47. Turner, A. F., Chang, L. & Martin, T. P. Enhanced reflectance of reststrahlen reflection filters. *Appl. Opt.* **4**, 927–933 (1965).
48. Freitag, M. et al. Substrate-sensitive mid-infrared photoresponse in graphene. *ACS Nano* **8**, 8350–8356 (2014).
49. Autore, M. et al. Substrate matters: surface-polariton enhanced infrared nanospectroscopy of molecular vibrations. *Nano Lett.* **19**, 8066–8073 (2019).
50. Alves, F. et al. Microelectromechanical systems bimaterial terahertz sensor with integrated metamaterial absorber. *Opt. Lett.* **37**, 1886–1888 (2012).
51. Todorov, Y. et al. Ultrastrong light-matter coupling regime with polariton dots. *Phys. Rev. Lett.* **105**, 196402 (2010).
52. Vicarelli, L. et al. Graphene field-effect transistors as room-temperature terahertz detectors. *Nat. Mater.* **11**, 865–871 (2012).
53. Scalari, G. et al. Ultrastrong coupling of the cyclotron transition of a 2D electron gas to a THz metamaterial. *Science* **335**, 1323–1326 (2012).
54. Chikkaraddy, R. et al. Dynamics of deterministically positioned single-bond surface-enhanced Raman scattering from DNA origami assembled in plasmonic nanogaps. *J. Raman Spectrosc.* **52**, 348–354 (2021).
55. Benz, F. et al. Single-molecule optomechanics in “picocavities”. *Science* **354**, 726–729 (2016).
56. Efetov, D. K. et al. Fast thermal relaxation in cavity-coupled graphene bolometers with a Johnson noise read-out. *Nat. Nanotechnol.* **13**, 797–801 (2018).
57. Shi, J. H. et al. High-resolution, high-contrast mid-infrared imaging of fresh biological samples with ultraviolet-localized photoacoustic microscopy. *Nat. Photonics* **13**, 609–615 (2019).
58. Shishkov, V. Y. et al. Enhancement of the Raman effect by infrared pumping. *Phys. Rev. Lett.* **122**, 153905 (2019).