

Bioactive dental materials Developing, promising, confusing

Ferracane, Jack L.; Sidhu, Sharanbir K.; Melo, Mary Anne S.; Yeo, In-Sung Luke; Diogenes, Anibal; Darvell, Brian W.

DOI:

[10.1016/j.jfscie.2023.100022](https://doi.org/10.1016/j.jfscie.2023.100022)

License:

Creative Commons: Attribution-NonCommercial-NoDerivs (CC BY-NC-ND)

Document Version

Publisher's PDF, also known as Version of record

Citation for published version (Harvard):

Ferracane, JL, Sidhu, SK, Melo, MAS, Yeo, I-SL, Diogenes, A & Darvell, BW 2023, 'Bioactive dental materials Developing, promising, confusing', *JADA Foundational Science*, vol. 2, 100022. <https://doi.org/10.1016/j.jfscie.2023.100022>

[Link to publication on Research at Birmingham portal](#)

General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact UBIRA@lists.bham.ac.uk providing details and we will remove access to the work immediately and investigate.

EMERGING SCIENCE


Bioactive dental materials

Developing, promising, confusing



Jack L. Ferracane, PhD^a; Sharanbir K. Sidhu, BDS, MSc, PhD^b;
Mary Anne S. Melo, DDS, MSc, PhD, FADM^c; In-Sung Luke Yeo, DDS, MSD, PhD^d;
Anibal Diogenes, DDS, MS, PhD^e; Brian W. Darvell, DSc^f

^aDepartment of Restorative Dentistry, Oregon Health & Science University, Portland, OR; ^bCentre for Oral Bioengineering, Institute of Dentistry, Queen Mary University of London, London, United Kingdom; ^cDepartment of General Dentistry, School of Dentistry, University of Maryland, Baltimore, MD; ^dDepartment of Prosthodontics, School of Dentistry and Dental Research Institute, Seoul National University, Seoul, South Korea; ^eDepartment of Endodontics, The University of Texas Health Science Center at San Antonio, San Antonio, TX; ^fDental Materials Science, University of Birmingham, Birmingham, United Kingdom.

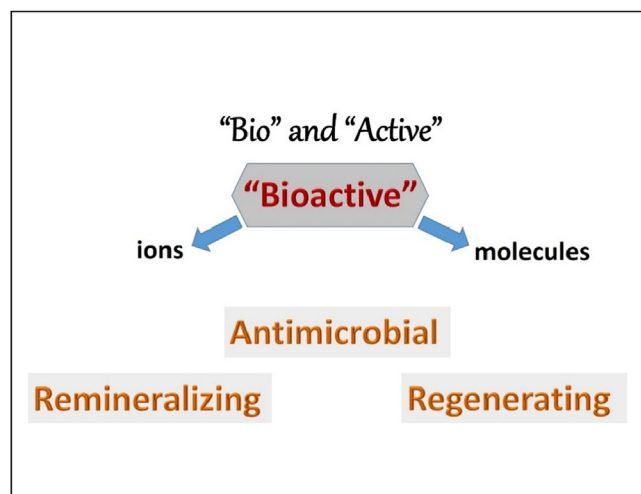

Why Is This Important?

There are often different interpretations by clinicians, manufacturers, and researchers regarding what defines a bioactive material. This has led to confusion amidst varying claims by individual stakeholders. Unlike the more traditional passive materials, bioactive materials are designed to elicit a desired therapeutic or beneficial response. Such materials have been described as releasing ions or molecules to produce an antimicrobial, remineralizing, or regenerating effect within a living organism. Given the complexities of various chemistries, products, and effects, it is virtually impossible to easily identify the essential qualities that qualify a material as bioactive, and clinicians, in particular, often find it challenging to determine whether a product claiming bioactivity is clinically superior and should be used. It is difficult for clinicians to make informed decisions without clarity.

© 2023 THE AUTHOR(S). Published by Elsevier Inc. on behalf of the American Dental Association. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).
<https://doi.org/10.1016/j.jfscie.2023.100022>

Key Words. Bioactive materials; pulp regeneration; implants; restorative materials; antimicrobial.

Introduction

The term bioactivity is used frequently in the oral health field but with great latitude regarding what constitutes the specific activity. Bioactive is defined as having a biological effect or effect on a living organism, tissue, or cell. The bioactivity of certain endogenous molecules may be obvious when promoting specific cellular or tissue responses under appropriate conditions. However, is eliciting a biological

response necessary to be considered bioactive? Indeed, how do we define biological response?

The biochemical term bioactive was applied to the material Bioglass by Hench,¹ the inventor and author of an excellent review of its development. Early emphasis was on materials that formed an apatitelike mineral in appropriate environments, such as simulated body fluid.² Throughout the literature are descriptions of bioactive materials involved in various contexts, including promoting

mineralization of bone or teeth, inducing the recruitment or differentiation of cells to perform specific functions, or exerting an antimicrobial, antifouling, pH buffering, or biofilm modulating effect. However, are all these effects true evidence of bioactivity or perhaps simple chemistry or toxicity?

The rapidly emerging research into bioactive materials holds great promise for improving oral health care but also creates much confusion and potential for misinformation. These issues were the basis of presentations delivered at the 2022 International Association for Dental Research meeting in a symposium titled “Bioactive Dental Materials—Developing, Promising, Confusing.”³

In this speaker-generated symposium summary, we aim to clarify the concept of bioactivity related to restorative and implant dentistry and dental tissue engineering and regeneration. Considering the material presented in the symposium and the previous literature, a definition closer to the reality of bioactivity is proposed.

What Does Bioactivity Imply With Dental Restorative Materials?

Bioactivity is a relatively new term for direct restorative materials, interpreted in many ways by dentists and researchers. As the first-choice material for direct restorations, resin composites have experienced relatively high failure rates because of secondary caries and interfacial bond degradation, requiring frequent replacements. Based on this deficiency, the desire for materials that provide additional benefits to maintain oral health has led to intensive research

into what has been called bioactive resin-based restorative materials.⁴

The use of the term bioactive in clinical dentistry is much broader than is implied by the medical-based description of materials that have a biological effect or are biologically active and form a bond between material and tissue.⁵

From the biomaterials' perspective, the ability to form a surface apatite-containing material, including hydroxyapatite, in a simulated body fluid is defined as bioactivity. From a dental restorative perspective, bioactivity describes a dynamic, positive interaction between the restorative materials and the tooth, promoting health. For example, a bioactive restorative material could modulate the cariogenic biofilm growth over its surface and prevent massive bacterial acid production that could result in the degradation of the tooth-adhesive interface. With this in mind, a bioactive restorative material would need to retain satisfactory mechanical performance to rebuild the tooth form, provide proper shade and translucency to reestablish an esthetic appearance, and provide bioactivity by releasing specific components that modulate cariogenic species and biofilm formation, stimulate specific interactions to control or restore mineral loss, or both (Figure 1).⁶

Do Surface Treatments Make Dental Implants Bioactive?

Bioactive has been defined by 1 source as “having an effect upon a living organism, tissue, or cell.”⁷ In dental implantology, is it possible to have an implant surface that is really

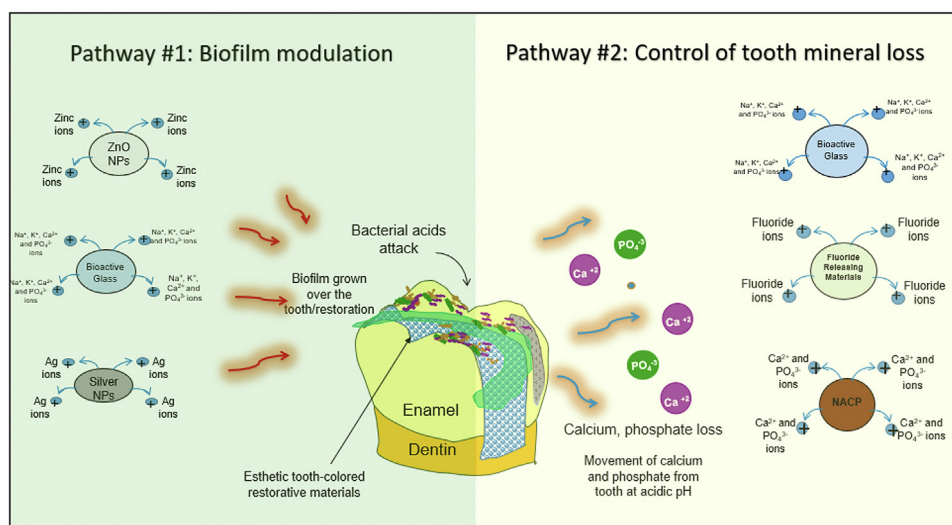


Figure 1 Illustration of the restorative concept of bioactivity toward caries prevention by dental restorative materials. Pathway no. 1: the release of relevant ions, such as calcium ions, to assist in the chemical equilibrium of the mineral net into the hard dental tissues, such as enamel and dentin. Pathway no. 2: the release or contact with bioactive agents that can modulate or suppress bacterial metabolism, consequentially reducing biofilm growth, such as metallic ions provided by nanoparticles. Ag, Silver. Ca²⁺, Calcium ion. K⁺, Potassium ion. Na⁺, Sodium ion. NACP, Nanoparticles of amorphous calcium phosphate. NPs, Nanoparticles. PO₄³⁻, Phosphate ion. ZnO, Zinc oxide.

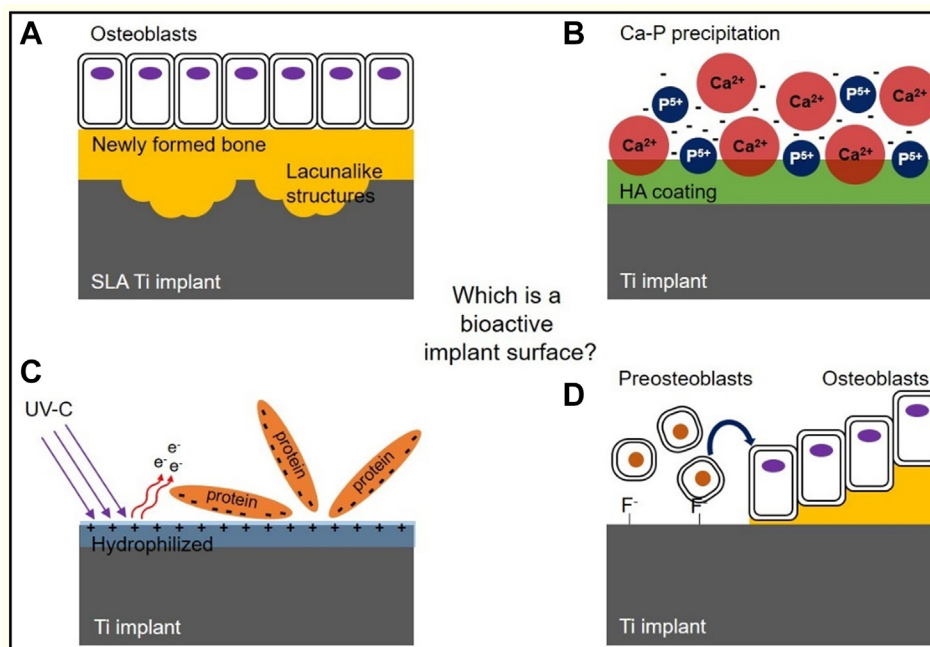


Figure 2 The osteoblast response to the sandblasted large-grit acid-etched (SLA) implant surface, interpreted as the response to structures morphologically similar to Howship lacunae (A). Accelerated mineralization on the hydroxyapatite (HA)-coated surface (B) and improved protein adsorption to the ultraviolet (UV-C) treated surface (C) are chemical reactions, not cellular biological responses. The fluoride-treated surface (D) is bioactive to modulate cellular behavior, stimulating osteoblast differentiation. Ca²⁺, Calcium ion. Ca-P, Calcium-phosphate. e⁻, Electron. F⁻, Fluoride ion. P⁵⁺, Phosphate ion. Ti, Titanium.

bioactive? Topographic, physical or chemical modifications of grade 4 commercially pure titanium implant surfaces appear to modulate cell behavior and tissue response, leading to osseointegration, though exactly how this happens remains undetermined.⁸

Pure titanium is an inert material. However, microtopographic modification of the surface, for example, a sandblasted large-grit acid-etched surface, mimics Howship lacunae formed by osteoclasts, thus resulting in contact osteogenesis that allows de novo bone formation on the surface.⁹ However, this phenomenon is difficult to describe as evidence of bioactivity because this topographical feature does not modulate normal osteogenic cell behavior. Similarly, a hydroxyapatite-coated implant surface contributes to calcium phosphate precipitation and bone mineralization,¹⁰ and ultraviolet irradiation of the implant surface increases surface hydrophilicity and surface attraction to plasma proteins (Figure 2).⁹ However, these effects are chemical and do not modulate cellular behavior. Therefore, carefully interpreting the data showing improved osseointegration to a modified implant surface is important in evaluating an actual bioactive effect. In this light, applying fluoride to an implant surface to stimulate osteoblast differentiation or attaching core peptides derived from endogenous cytokines probably make the inert implant surface bioactive because these molecules modulate osteogenic cell responses.⁸ However, every surface modification of dental implants used in the clinic is unlikely to render them bioactive.

Does Successful Engineering and Regeneration of the Pulp-Dentin Complex Rely on Bioactivity?

Regenerative endodontics focuses on replacing damaged cells and tissue in part or the entirety of the pulp-dentin complex through vital (pulp capping, pulpotomies) or nonvital procedures (revitalization, stem cell transplant). It has been shown that growth factors are fossilized or trapped in the dentin matrix during tooth development, and these non-collagenous proteins can be released on dentin demineralization caused by caries or certain materials used in vital pulp therapies (Figure 3).¹¹ Once released, dentin-derived growth factors are sufficient to drive the recruitment and differentiation of mesenchymal stem cells into an odontoblastlike phenotype and increase their mineralization potential.¹¹ Their reparative potential, in this case, may be attributed to the indirect effect of material placement on dentin.

Regenerative endodontic therapies aim to resolve apical periodontitis and reestablish root development, pulp immune, and sensory functions. Despite high success rates (>85%) of apical periodontitis healing, continued root development and responses to pulp sensitivity (vitality) testing are less predictable,¹² and histologic studies show that the tissue formed does not resemble native dental pulp.¹³

Clinical trials with transplantation of autogenous and allogenic mesenchymal stem cells, such as that by Xuan et al¹⁴ using autogenous transplantation of cells into disinfected root

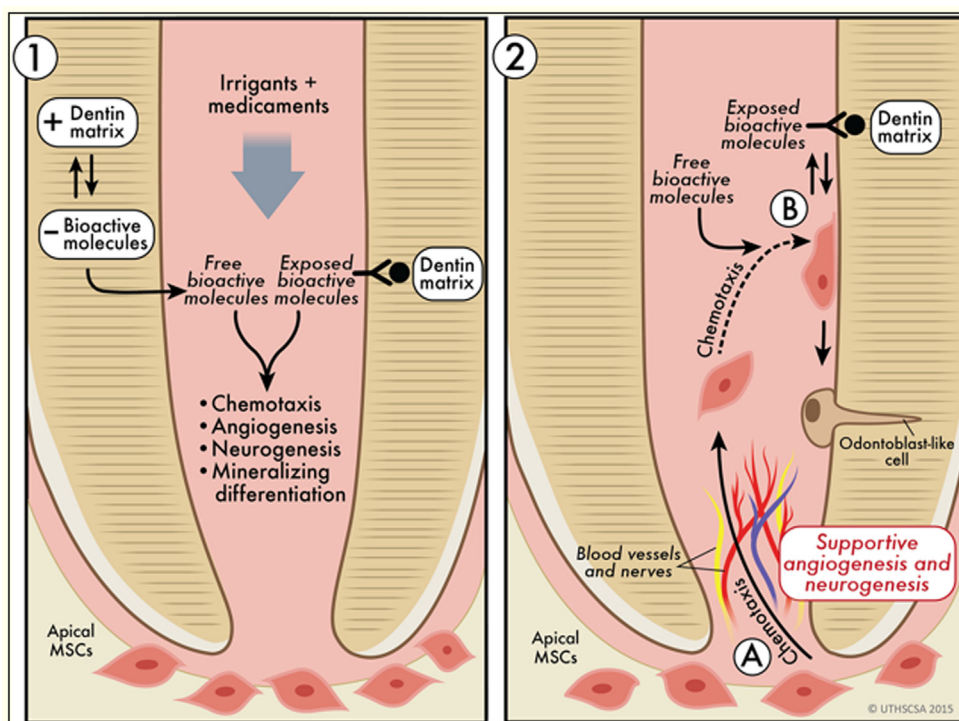


Figure 3 Schematic illustrating the potential actions of irrigants and medicaments in the release or exposure of bioactive molecules sequestered in dentin and their influences on regenerative events, including chemotaxis, odontoblastlike cell differentiation, mineralization, angiogenesis, and neurogenesis. Adapted with permission of the publisher from Smith et al.¹¹ MSCs, mesenchymal stem cells.

canal systems, have shown results with histology assessment showing remarkable organization of the tissue with a circumferential cell layer resembling odontoblasts. The bioactivity observed in this trial can only be attributed to dentin-derived growth factors, an autogenous scaffold (blood clot), and factors released by the transplanted cells, and not to a single bioactive material. Therefore, the bioactivity observed in pulp tissue engineering is primarily mediated indirectly by the release of growth factors and the exposure of the dentin matrix favoring cellular attachment, signaling and differentiation.

Bioactivity: an Overview of the Current Situation

The symposium had nicely illustrated the nature of the problem: the term bioactivity has been devalued almost to the point of uselessness by being applied indiscriminately to include all simple chemistry arising in even vaguely biological contexts as inappropriately to all biological defensive responses to insults and challenges.^{15,16} Many definitions suffer from lack of precision, a narrow focus on forming a bond between the material and tissue, merely dissolution to release supposedly useful ions or even the appearance of hydroxyapatite, whether in vivo or in vitro.¹⁰ Including microbial control, nutrients and pharmaceuticals is questionable and perhaps unhelpful,¹⁶ as is the prejudicial use of the term remineralization when there can be no

tissuelike structure in the calcium phosphates precipitated¹⁵; similarly, the application to any reparative process occasioned by toxicity is injudicious. Moreover, cellular responses to topography were shown to be overstated.

The only clear demonstration of true bioactivity presented was that of sequestered substances released by damage to or destruction of dentin, but properly it applies to those substances themselves, not the agent that did the damage, as was pointed out in the “Does Successful Engineering and Regeneration of the Pulp-Dentin Complex Rely on Bioactivity?” section. Nevertheless, an indirect effect may still be valuable, using such substances in a nondestructive material to induce beneficial biological processes.

The 1 suggestion of true bioactivity using nonbiological means was that of the implant surface doped with fluoride. If verified, this would indeed count and indicates another avenue for investigation.

The definition of bioactive material as one that intentionally modulates a specific, targeted biological process for beneficial effect may be used to establish the veracity of a claim of bioactivity. The 2 examples cited above would pass this test.

It may be too late to rescue the term bioactivity in general use. However, for students, researchers, and clinicians, a clear understanding of what is happening is essential for meaningful study, properly directed research, and realistic treatment design. Truly bioactive materials would indeed make a difference.

Email ferracan@ohsu.edu. Address correspondence to Dr Ferracane.

Disclaimer. Dr Ferracane serves as Editor in Chief for JADA-FS. He was not involved in decisions about the article he wrote, and peer review was handled independently.

Disclosure. None of the authors reported any disclosures.

Part of the material in this article was presented virtually at the 2022 IADR/APR General Session on June 24, 2022.

J.L.F. and S.K.S. wrote the “Introduction” section, M.A.S.M. wrote the “What Does Bioactivity Imply With Dental Restorative Materials?” section, I.-S.L.Y. wrote the “Do Surface Treatments Make Dental Implants Bioactive?” section, A.D. wrote the “Does Successful Engineering and Regeneration of the Pulp-Dentin Complex Rely on Bioactivity?” section, and B.W.D. wrote the “Bioactivity: an Overview of the Current Situation” section.

ORCID Numbers. Jack L. Ferracane: <https://orcid.org/0000-0002-6511-5488>; Sharanbir K. Sidhu: <https://orcid.org/0000-0001-8362-385X>. For information regarding ORCID numbers, go to <http://orcid.org>.

References

- Hench LL. The story of Bioglass®. *J Mater Sci Mater Med*. 2006;17(11):967-978. <https://doi.org/10.1007/s10856-006-0432-z>
- Kokubo T, Ito S, Huang ZT, et al. Ca,P-rich layer formed on high-strength bioactive glass-ceramic A-W. *J Biomed Mater Res*. 1990;24(3):331-343. <https://doi.org/10.1002/jbm.820240306>
- Bioactive Dental Materials—Developing, Promising, Confusing. Paper presented at: 100th General Session & Exhibition of the International Association for Dental Research. June 24, 2022. <https://www.pathlms.com/iadr/courses/46167>
- Ibrahim MS, Balhaddad AA, Garcia IM, et al. pH-responsive calcium and phosphate-ion releasing antibacterial sealants on carious enamel lesions in vitro. *J Dent*. 2020;97:103323. <https://doi.org/10.1016/j.jdent.2020.103323>
- Ibrahim MS, Garcia IM, Kensara A, et al. How we are assessing the developing antibacterial resin-based dental materials? A scoping review. *J Dent*. 2020;99:103369. <https://doi.org/10.1016/j.jdent.2020.103369>
- Montoya C, Jain A, Londoño JJ, et al. Multifunctional dental composite with piezoelectric nanofillers for combined antibacterial and mineralization effects. *ACS Appl Mater Interfaces*. 2021;13(37):43868-43879. <https://doi.org/10.1021/acsami.1c06331>
- Medical definition of bioactive. MedicineNet. Accessed March 28, 2023. <https://www.medicinenet.com/bioactive/definition.htm>
- Yeo IL. Modifications of dental implant surfaces at the micro- and nano-level for enhanced osseointegration. *Materials (Basel)*. 2019; 13(1):89. <https://doi.org/10.3390/ma13010089>
- Hefli T, Frischherz M, Spencer ND, Hall H, Schlottig F. A comparison of osteoclast resorption pits on bone with titanium and zirconia surfaces. *Biomaterials*. 2010;31(28):7321-7331. <https://doi.org/10.1016/j.biomaterials.2010.06.009>
- Pan H, Zhao X, Darvell BW, Lu WW. Apatite-formation ability: predictor of “bioactivity.” *Acta Biomater*. 2010;6(11):4181-4188. <https://doi.org/10.1016/j.actbio.2010.05.013>
- Smith AJ, Duncan HF, Diogenes A, Simon S, Cooper PR. Exploiting the bioactive properties of the dentin-pulp complex in regenerative endodontics. *J Endod*. 2016;42(1):47-56. <https://doi.org/10.1016/j.joen.2015.10.019>
- Chrepa V, Joon R, Austah O, et al. Clinical outcomes of immature teeth treated with regenerative endodontic procedures: a San Antonio study. *J Endod*. 2020;46(8):1074-1084. <https://doi.org/10.1016/j.joen.2020.04.008>
- Martin G, Ricucci D, Gibbs JL, Lin LM. Histological findings of revascularized/revitalized immature permanent molar with apical periodontitis using platelet-rich plasma. *J Endod*. 2013;39(1):138-144. <https://doi.org/10.1016/j.joen.2012.09.015>
- Xuan K, Li B, Guo H, et al. Deciduous autologous tooth stem cells regenerate dental pulp after implantation into injured teeth. *Sci Transl Med*. 2018;10(455):eaaf3227. <https://doi.org/10.1126/scitranslmed.aaf3227>
- Darvell BW. Bioactivity: symphony or cacophony? A personal view of a tangled field. *Prosthesis*. 2021;3(1):75-84. <https://doi.org/10.3390/prosthesis3010008>
- Darvell BW, Smith AJ. Inert to Bioactive: a multidimensional spectrum. *Dent Mater*. 2022;38(1):2-6. <https://doi.org/10.1016/j.dental.2021.11.002>