

Degradation of a model epoxy resin by solvolysis routes

Oliveux, Géraldine; Dandy, Luke O.; Leeke, Gary A.

DOI:

[10.1016/j.polymdegradstab.2015.04.016](https://doi.org/10.1016/j.polymdegradstab.2015.04.016)

License:

Creative Commons: Attribution (CC BY)

Document Version

Publisher's PDF, also known as Version of record

Citation for published version (Harvard):

Oliveux, G, Dandy, LO & Leeke, GA 2015, 'Degradation of a model epoxy resin by solvolysis routes', *Polymer Degradation and Stability*, vol. 118, pp. 96-103. <https://doi.org/10.1016/j.polymdegradstab.2015.04.016>

[Link to publication on Research at Birmingham portal](#)

Publisher Rights Statement:

Published under a Creative Commons Attribution license: <http://creativecommons.org/licenses/by/4.0/>.

Eligibility for repository checked May 2015

General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.


Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact UBIRA@lists.bham.ac.uk providing details and we will remove access to the work immediately and investigate.



Degradation of a model epoxy resin by solvolysis routes



Géraldine Oliveux^{*}, Luke O. Dandy, Gary A. Leeke

School of Chemical Engineering, University of Birmingham, Edgbaston, Birmingham, B15 2TT, UK

ARTICLE INFO

Article history:

Received 11 February 2015

Received in revised form

25 March 2015

Accepted 20 April 2015

Available online 29 April 2015

Keywords:

Recycling

Composites

Epoxy

Solvolysis

ABSTRACT

Different technologies based on hydrolysis were applied to degrade an epoxy resin model: CO₂-expanded water and generally recognised as safe solvents used neat or in mixture with water. The results showed that the degradation reaction can be enhanced thanks to the injection of CO₂ or the addition of a solvent generally recognised as safe, enabling supercritical fluids or enhanced fluidity liquids (resembling supercritical fluids) at lower temperature and pressure than for supercritical water.

© 2015 The Authors. Published by Elsevier Ltd. This is an open access article under the CC BY license (<http://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Fibre reinforced thermoset composites are reported to be non-recyclable as they are infusible once they are polymerised. Currently, these materials are mainly landfilled, however this solution will become more expensive and is exacerbated by their environmental impact as these materials are not biodegradable. Raw materials to produce the resins and the fibres derive from fossil-derived resources. The production of these raw materials is also energy intensive as shown in Table 1. The recovery of valuable products from composite materials (fibres and organic compounds), for re-use in new materials, is therefore essential to improve resource efficiency, decrease the cost of composite re-manufacture and reduce the environmental impact. In light of this, thermochemical methods have been considered to separate the fibres from the resin, which have largely focussed on pyrolysis [2–9] and solvolysis [9–44]. In pyrolysis, composite materials are heated up to 450–600 °C (depending on the nature of the resin) in absence or in presence of oxygen. The resin degradation produces oil, gases and chars that can lead to contamination of the remaining solid fractions (fibres and fillers if they are initially present in the material). The oil and gas products are mainly considered for energy recovery, the lowest level of the recycling hierarchy. The oil fraction contains valuable products with a composition that is too

complex to cost-effectively separate them. The priority therefore in this method is to recover the fibres. In light of this, pyrolysis has been more applied to carbon fibre reinforced composites to reclaim carbon fibres that could compete with virgin fibres at a significantly lower price. The price of virgin carbon fibre is between 33 and 66 \$/kg, whereas for pyrolytically recycled carbon fibre it is between 13 and 19 \$/kg [45]. In the solvolysis method, a solvent medium is used to break the resin into low molecular weight products, and ideally into the monomers initially used to manufacture the resin [13–15,27,30,32,33,39,41,44]. According to the operating conditions (e.g. solvent selection, catalysts, temperature and pressure), it is possible to adjust the physicochemical properties of the medium and therefore to manage the involved chemistry to some extent. The system is heated to accelerate the reaction with the temperature reaching up to 450 °C depending on the resin to recycle, inducing a pressure of up to 250 bar. These conditions were achieved with water and alcohols to bring them in their supercritical state to enhance the diffusion and mass transfer [13–15,18,23,24,28,29,33,34,36]. However the reactors able to withstand such high conditions become very expensive due to the use of specialist steel alloy. The energy consumption at such high temperatures is high. Nevertheless, using solvolysis, it is potentially possible to decrease the treatment temperature in comparison to pyrolysis, and as a consequence the energy consumption. A classical way to reduce the reaction temperature is through the use of catalysts. Sodium or potassium hydroxide and hydrogen peroxide have been the most used catalysts to degrade more easily strong resins, such as epoxides [11,15,23,33,36,40]. An even more resistant resin, poly(etheretherketone) (PEEK), requires very harsh conditions

^{*} Corresponding author. Tel.: +44 121 414 5081.

E-mail addresses: g.oliveux@bham.ac.uk (G. Oliveux), LXD139@student.bham.ac.uk (L.O. Dandy), g.a.leeke@bham.ac.uk (G.A. Leeke).

Table 1
Energy intensity for the production of fibres and resins [1].

Material		Energy intensity for production (MJ/kg)
Resins	Polyester	63–78
	Epoxy	76–80
	PP	72–112
Fibres	GF	13–32
	CF	183–286
	Flax fibre	6.5
Metals	Aluminium	196–257
	Stainless steel	110–210
	Steel	30–60

typically using supercritical water (with temperature higher than 400 °C) [15], otherwise strongly acidic or alkaline conditions are necessary. On the other hand, polyester resins for example can be treated at less severe conditions [10,17,21,22,25,27,32,41] but the economic balance for the recycling of composites made with this type of resin is not satisfactory, as these materials are generally reinforced with glass fibres. Glass fibres recovered by these recycling routes are currently more expensive than virgin glass fibres [46]. On the other hand, virgin carbon fibres are valuable and therefore justify the application of solvolysis methods to recover them. The cost of their recovery can become very competitive to that achieved by pyrolysis, as it is largely dependent on the energy consumption, and as a consequence on the process temperature [47].

In light of this, the objective of the work in this article is to propose new approaches based on solvolysis technologies to recycle thermoset composite materials with improved environmental and economic impact. Chemical reagents generally recognised as safe (GRAS) have been selected to deconstruct different resins. The results obtained for mixtures of solvents and gas-expanded liquids (GXLs) are presented and compared to the reference solvolysis process based on water. In order to separate the problems and to ease the understanding of the involved chemistry, a model epoxy resin was studied as the formulation of commercially available resins is not readily disclosed, and without reinforcement (no fibre effect).

2. Materials and methods

2.1. Materials

The epoxy resin used was based on the diglycidyl ether of bisphenol A (DGEBA) prepolymer, Dow D.E.R. 332 from Sigma Aldrich (Fig. 1), cured with diamine 4,4'-diaminodiphenyl sulfone (DDS – Fig. 2) also from Sigma Aldrich, in stoichiometric conditions. D.E.R 332 epoxy prepolymer has a high purity with an epoxy equivalent weight (EEW) of 171–175 g/eq. These products were chosen to manufacture samples due to their common use in composite materials and the relative simplicity of the resulting bond network. The mixture was first heated up to 120 °C and stirred until




Fig. 2. DDS.

a clear solution was obtained. It was poured into an aluminium container, which was coated beforehand with release agent (PVA Mould Release Agent from Easy Composites). The system was cured over 5 h at 250 °C with a heating ramp of 1 °C/min. The plates were left in the oven until the temperature reached about 25 °C. The resulting glass transition temperature measured by differential scanning calorimetry (DSC) was between 170 and 210 °C, which is comparable to commercial epoxy resins cross-linked with polyamines. This also indicates a degree of crosslinking above 0.8 [48]. Fig. 3 shows the molecular structure of the obtained resin after curing.

A composite was manufactured with seven plies of carbon fibre fabrics made of Grafil Inc. Pyrofil™ TR30S 3K and EL2 epoxy resin cured with AT30 hardener from Easy Composites. The resin is a mixture of bisphenol-A and bisphenol-F. The hardener is based on diamines and bisphenol-A.

Acetone (analytical grade), ethanol (HPLC grade) and 2-propanol (specified laboratory reagent, extra pure) were purchased from Sigma Aldrich. Distilled water was produced in our laboratory. Carbon dioxide (CO₂) was purchased from BOC Industrial Gases (purity 99.9% v/v). Phenol (crystalline solid, Reagent-Plus®, purity ≥ 99%) was purchased from Sigma Aldrich.

2.2. Reactor and experimental methodology

The experiments were realised in a 316 SS Parr Instrument batch reactor of about 115 mL. A resin sample was placed in the vessel with the appropriate solvent system at an initial loading rate (volume of solvent/reactor volume) of 0.5. The system was then heated to the desired temperature, which required between 24 min to reach 250 °C and about 53 min to reach 350 °C. After a desired time, the system was cooled down to ambient temperature by

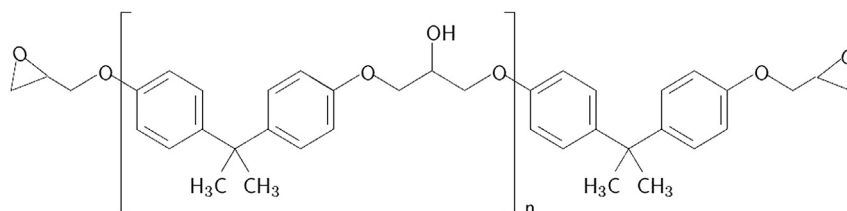


Fig. 1. D.E.R 332 DGEBA, $n = 0.056$.

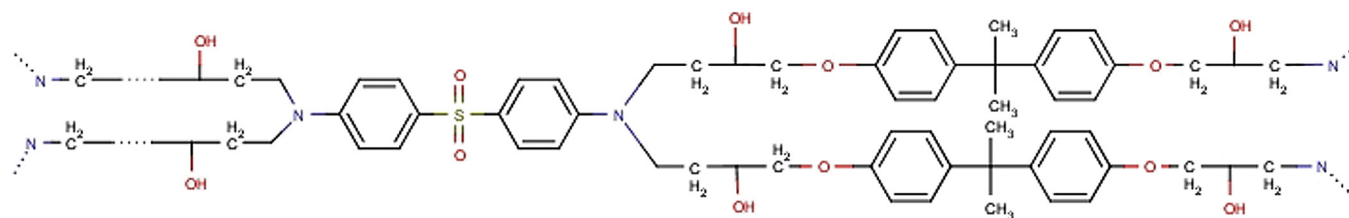


Fig. 3. Structure of the resin after polymerisation.

forced air convection and then by a water bath when the temperature was below 100 °C. The cooling phase required up to 80 min from 350 °C. Depending on the operating conditions, a residual pressure could be observed, indicating the production of gases during the solvolysis treatment. The liquid fractions were then recovered in glass bottles tightly closed and kept at 4 °C before being analysed. Acetone was used to flush the reactor and recover non-soluble products at ambient temperature. A phase separation in the liquid fractions was also observed after rest (from few minutes to several hours) and resulted in a deposit at the bottom of the bottles. The deposit could be dissolved only by acetone and were also subject to analysis.

For the experiments realised with CO₂, the reactor was first pressurised with CO₂ to the desired initial pressure before heating. A blank test was first undertaken to measure the amount of gas injected.

2.3. Analysis

The liquid fractions recovered after solvolysis were analysed by a Waters Corporation gas chromatography coupled with time-of-flight mass spectrometry (GC-TOF MS, model Waters Micromass GCT Premier) with either an HP-5MS or a ZB-WAX column in order to identify the products of the degradation reactions using the library software *NIST MS Search 2.0*. Deposition of the non-soluble reaction products at room temperature or those that exceeded their solubility limit were dissolved in acetone before being subjected to the same analysis.

$$\text{mean } R\% = \frac{R\% \left(10 \frac{\text{mg}}{\text{mL}}, 0 \text{ min} \right) + R\% \left(30 \frac{\text{mg}}{\text{mL}}, 30 \text{ min} \right) + R\% \left(50 \frac{\text{mg}}{\text{mL}}, 60 \text{ min} \right)}{3} \quad (2)$$

2.4. Solvolysis operating conditions

Three different solvolysis methods were used to degrade the epoxy resins: either pure solvent, two-solvent mixtures or CO₂-expanded solvent using the conditions shown in Table 2. The reference solvent was water, of which the efficiency was compared to the other systems. A first series of experiments was performed in water, using a L₉(3³) orthogonal array, at the conditions shown in Table 3 (experiments # 1–9). A few additional experiments were realised according to the conditions given in Table 3. A second

Table 2
Conditions of solvolysis.

	Pure water	Mixtures water + GRAS solvent	CO ₂ expanded liquids
Temperature (°C)	250, 300, 350	250, 300, 350	200, 250, 300
Time (min)	0, 30, 60	30	30
Resin concentration (mg/mL)	10, 30, 50	30	30
Mixture proportions	0	0.2, 0.5, 0.8, 1	0
Initial pressure	0	0	35 or 50 bar

series of experiments, using a L₉(3³) orthogonal array, was then realised with mixtures of water and a GRAS solvent, such as acetone, ethanol and 2-propanol; the mixture proportions and the solvolysis conditions are given in Table 4 (experiments # 31–39). Water and mixtures of water and acetone at 80 vol.% expanded by CO₂ were also considered.

A total of 52 experiments were realised. For each experiment, the degradation rate *R*% was determined using Equation (1). Only those presenting significant results are given in Tables 3 and 4.

$$R\% = \frac{\text{initial mass} - \text{remaining mass}}{\text{initial mass}} \times 100 \quad (1)$$

3. Results and discussion

3.1. Water experiments: effect of the temperature, time and resin concentration

The effects of temperature, time and resin concentration were determined in water alone. For this purpose, the results of the first series of experiments (experiments # 1 to 9 in Table 3) were treated with the statistical analysis software *Minitab 16.2.2* to evaluate the influence of the parameters on the response “mean degradation rate”. The mean degradation rate *R*% is calculated at each parameter level with the other parameters varying as illustrated by the Equation (2) for the temperature at a level of 250 °C.

The results are shown in Fig. 4. They indicate that the degradation rate increased for both increasing temperature and time and decreased with increasing resin concentration. This might be due to a saturation of the solvent medium with degradation products. The maximum resin concentration of 30 mg/mL was therefore considered for all the other experiments.

In water alone, the model epoxy resin is almost completely degraded after 1 h at 350 °C for a resin concentration of 10 mg/mL, whereas at 300 °C the solvolysis rate reached only 23% after 1 h for a resin concentration of 30 mg/mL (experiments # 5 and 7 in

Table 3


Conditions and results of hydrolysis experiments.

Exp. #	Gas and additives	Measured P ₀ (bar)	Measured T (°C)	Measured P (bar)	t (min)	[Resin] (mg/mL)	R% (±1%)
1	No	0	250	35	0	10	0
2					30	30	1
3					60	50	1
4		300	300	80	30	10	23
5					60	30	23
6					0	50	0
7		350	350	155	60	10	84
8					0	30	34
9					30	50	53
10		325	325	114	120	50	43 (stirring)
11					120	50	52 (no stirring)
12					30	30	Model resin: 39 Composite: 65
13	CO ₂	35	300	82	30	30	20
14		50			30	14	
15		35			60	41	
16		35	300	81	60	60	27
17					35	120	51
18					0	30	14
19	CO ₂	35	82	82	30	30	11
20	Phenol 1 g/L	0	81	81	30	30	11
21	CO ₂	35	83	83	30	30	18
	Phenol 10 g/L						

Table 4

Conditions and results for experiments realised with GRAS solvent mixtures, time = 30 min and resin concentration = 30 mg/mL.

Exp. #	Solvent	Proportion (vol.%)	Measured T (°C)	Measured P (bar)	R% (±1%)
31	Acetone	0.5	250	114	-6
32		0.8	300	145	-6
33		0.2	350	156	52
34	Ethanol	0.8	250	82	-5
35		0.2	300	90	6
36		0.5	350	81	73
37	2-propanol	0.5	250	82	-1
38		0.8	300	81	3
39		0.2	350	83	72
40	Acetone	0.8	350	235	93

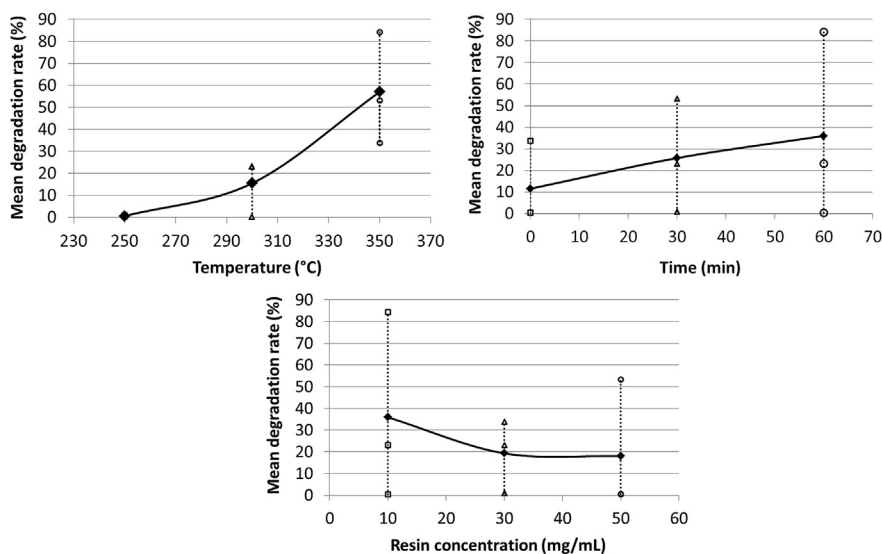**Fig. 4.** Effects of temperature, time and resin concentration on the degradation rate.

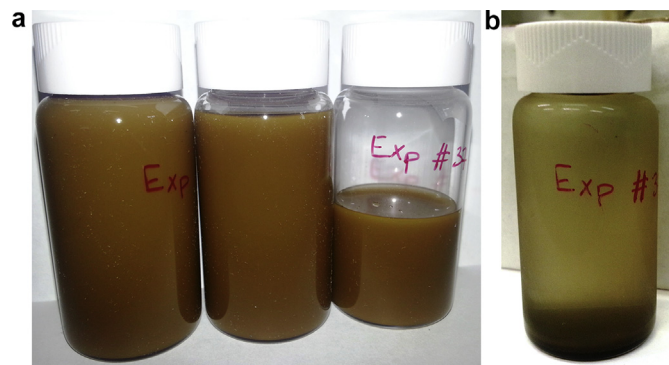


Fig. 5. Liquid fractions recovered after the experiment # 7 (conditions given in Table 3): a) right after the experiment; b) 20 days after the experiment.

Table 3). Furthermore, the solvolysis rate reached about 53% at 350 °C after 30 min with a resin concentration of 50 mg/mL (experiment # 9 in Table 3). A good compromise between time and temperature in water is apparent therefore in the range of 350 °C and 1–2 h with a resin concentration of 30 mg/mL. When the system is cooled after reaction, the solubility of some reaction products in water decreases, resulting in a dark sticky substance that would coat the fibres if an actual composite sample was used. A post-treatment step would be necessary to wash and recover the fibres.

The effect of the stirring was measured at 325 °C (experiments # 10 and 11 in Table 3) and showed that the stirring of the medium is detrimental to the resin degradation. The small molecules produced by bond breaking in the resin structure transfer towards the medium. When the medium is not stirred the local concentration of these molecules (around and into the sample) is high and creates a potential gradient, which tends to establish a constant out-of-equilibrium state at the solid/liquid interface. This gradient is the driving force of the mass transfer. When the medium is stirred, the concentration of the molecules transferred into the medium is uniformed and becomes constant at every points of the medium but evolves according to time. Therefore no gradient is observed at the solid/liquid interface and the mass transfer is not enhanced.

Table 5

Products identified by GC-TOF MS in the organic fractions recovered by hydrolysis at 350 °C, 156 bar during 60 min (experiment# 7 in Table 3 and Fig. 6) and by hydrolysis in the presence of CO₂ at 300 °C, 82 bar during 30 min (experiment # 13 in Table 3 and Fig. 7).

Peak #	Product name
1	Aniline
2	Quinoline
3	Phenol
4	Phenol, 4-(1-methylethyl)-
5	Phenol, 4-ethyl
6	Phenol, 3-(1-methylethyl)-
7	2H-1-benzopyran-3-ol, 3,4-dihydro-
8, 15	Amine derivatives
9	1,2-propanediol, 3-phenoxy
10	p-hydroxybiphenyl
11	Phenyl amine derivative
12	Phenol derivative
13	2-propanol, 1-phenoxy-3-(phenylamino)-
14	1H-indole, 2,5-dimethyl

At the end of the hydrolysis experiment, a residual pressure could be observed depending on the reaction conditions. The smell of the released gas was characteristic of hydrogen sulphide, indicating that the SO₂ bonds in the resin were hydrolysed (Fig. 3). The recovered liquid fraction had a yellow-orange colour and was more or less opaque depending on the reaction conditions (Fig. 5a). After some rest days, a deposit was observed at the bottom of the bottles (Fig. 5b), which is thought to be due to a combination of the insolubility of some reaction products at room temperature and to saturation of water with soluble products. The analysis of the chemical composition of both fractions (liquid and deposit) identified, apart from hydrogen sulphide, mainly two families of products: phenolic compounds, produced by the degradation of the epoxy pre-polymer, and amine compounds, produced by the degradation of the curing agent (Fig. 6 and Table 5). Bisphenol-A (BPA) can be recovered at lower temperature (250 and 300 °C) but it was completely degraded after 60 min at 350 °C. BPA is toxic and eco-toxic however, and might not be a desirable reaction product as it would be hard to reuse directly in new resin.

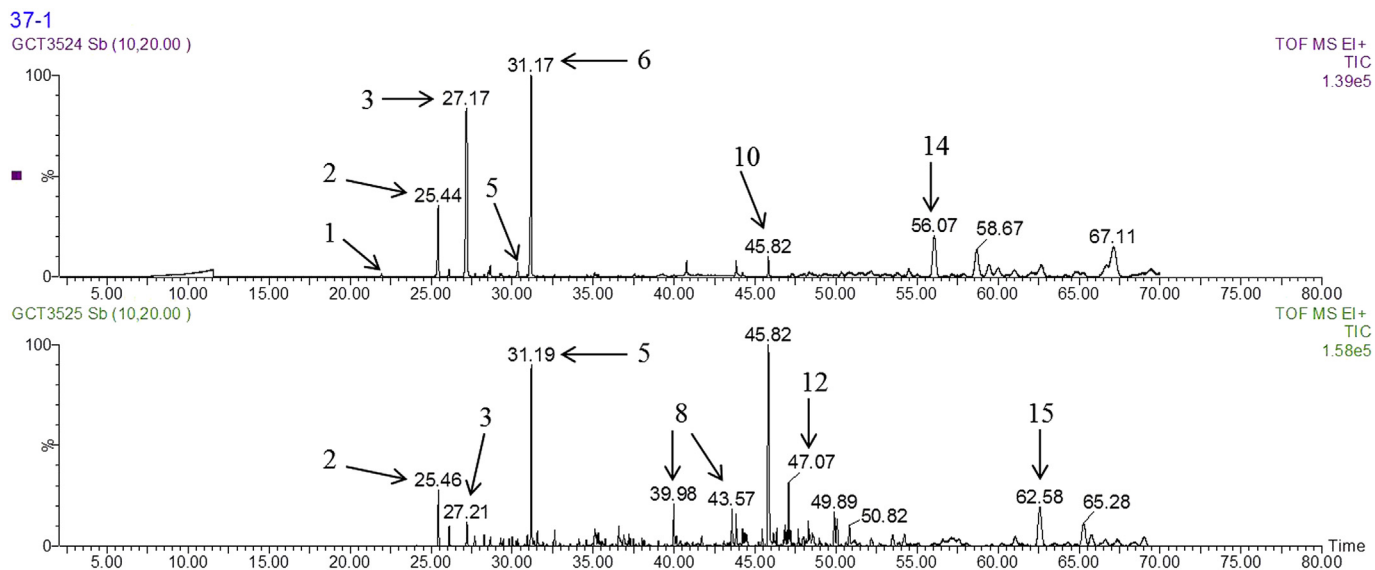


Fig. 6. Chromatograms of the liquid (top image) and deposit (bottom image) fractions recovered from experiment # 7 (conditions shown in Table 3). The relating product names are given in Table 5.

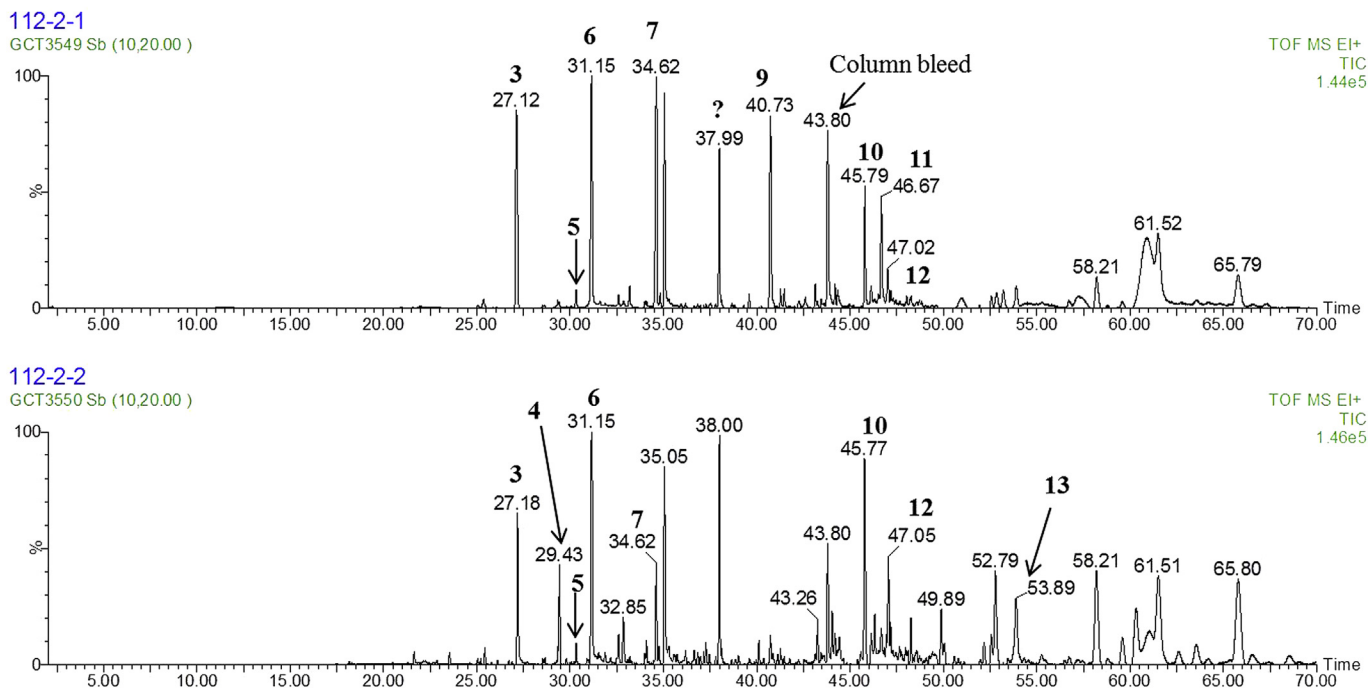


Fig. 7. Chromatograms of the liquid (top image) and deposit (bottom image) fractions recovered from experiment # 13 (conditions shown in Table 3). The relating product names are given in Table 5.

3.2. Efficiency of CO₂-expanded water

The water-CO₂ system is considered as an enhanced fluidity liquid rather than a gas-expanded liquid due to the high temperature and pressure used in the present work [49]. It resembles a supercritical fluid and therefore shows similar properties (low viscosity, high diffusion and mass transfer). This solvent system was chosen because it could create supercritical-like water at significantly lower temperatures and pressures thanks to the low critical point of CO₂ (31 °C, 74 bar and 467.6 kg/m³). The results show that the injection of CO₂ enhanced the resin degradation compared to neat water solvolysis at the same temperature (experiments # 5 and 15 in Table 3). On the other hand, it seems that increasing the amount of CO₂ decreases the degradation rate (experiments # 13 and 14 in Table 3). The chromatograms of the liquid fraction and of the deposit dissolved in acetone indicate that the composition is similar to that obtained for the fractions recovered after neat hydrolysis, although more complex (Figs. 6 and 7).

Following an experiment realised on the model epoxy resin and the composite made with the commercial epoxy resin EL2-AT30 and Pyrofil™ TR30S carbon fibres together (experiment # 12 in Table 3, the overall resin concentration kept at 30 mg/mL), a higher degradation rate of the model epoxy resin was observed compared to the model resin alone. A higher phenol production was also obtained possibly caused by a combined catalytic effect with phenol. This was evaluated by measuring the effect of CO₂ and phenol separately and combined (experiments # 13, 14, 18, 19, 20 and 21 in Table 3). The degradation rates indicate that a combined effect exists between CO₂ and phenol as shown by Fig. 8. The resin degradation was almost doubled when the phenol concentration was increased from 1 to 10 g/L in the presence of CO₂. As phenol is produced during the reaction, the liquid fraction recovered after experiment # 15 was reused to solvolyse a new resin sample under the same experimental conditions (experiment # 16). The results in Table 3 indicate that the resin degradation was significantly lowered despite the presence of phenol in the reused liquid fraction.

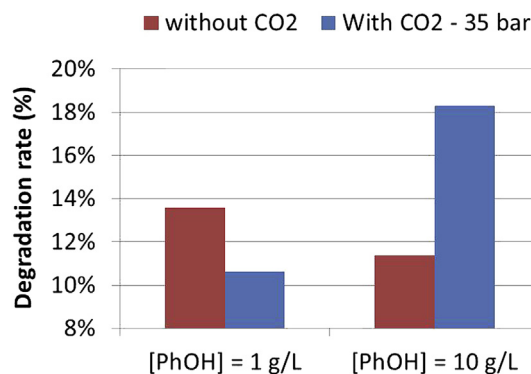


Fig. 8. Interaction effect between CO₂ and phenol during hydrolysis at 300 °C for 30 min with a resin concentration of 30 mg/mL (experiments # 18 to 21 in Table 3).

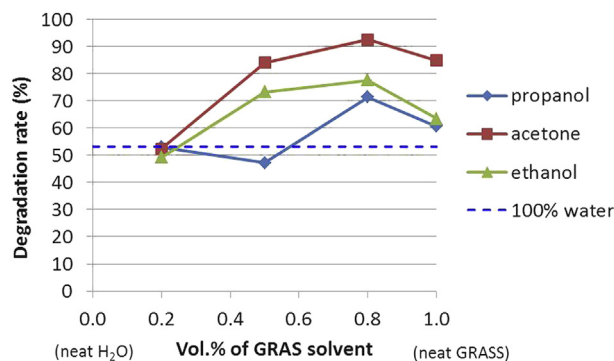


Fig. 9. Effect of the mixture proportion on the degradation rate at 350 °C.

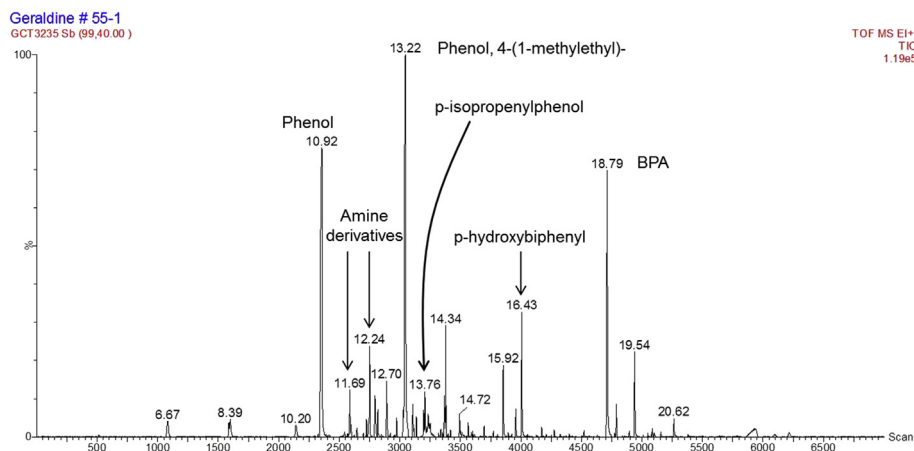


Fig. 10. Chromatogram of the liquid fractions recovered from experiment # 40.

This might be due to its saturation with the various reaction products. Furthermore the liquid fraction recovered after experiment # 15 still contained some dissolved CO_2 and was then enriched by more CO_2 to realise experiment # 16. This may also explain the negative effect on the degradation rate, considering the results obtained for experiments # 13 and 14 in Table 3.

Instead of adding phenol to the solvent system, it might be of interest to solvolyse phenolic and epoxy resins together in order to benefit from the combined effect between injected CO_2 and phenol produced by the degradation of the phenolic resin.

The CO_2 -expanded water system seems therefore to be a promising technology to recycle composite materials more efficiently than with neat water at low CO_2 initial pressure.

3.3. Solvent mixture experiments

A comparison of the results obtained for pure hydrolysis and for solvolysis in mixtures of H_2O -GRAS solvents (Tables 3 and 4) shows that the addition of a GRAS solvent led to a higher solvolysis rate at 350 °C, when the added solvent was ethanol or 2-propanol. This was further investigated by undertaking a series of experiments in different solvent mixtures over a range of solvent volume proportion at 350 °C. The results shown in Fig. 9 indicate that the best mixture is water and acetone at 80 vol.%, leading to a degradation rate of 93% after 30 min at 350 °C. This means that the treatment time can be halved in comparison to neat water. A second advantage is that the reaction products are completely soluble in the mixture, even at room temperature, due to the presence of acetone.

The addition of a GRAS solvent did not seem to accelerate the reaction, however it helps to lower the critical point of the solvent system compared to pure water. Values found in the literature [50] indicate that all the mixtures were supercritical at 350 °C and that all the mixtures at 80 vol.% were supercritical at 300 °C. The increased resin degradation of these systems compared to pure water is assumed to come from the enhanced diffusion and mass transfer from the supercritical state of the fluids. However, it can be observed that, when pure GRAS solvents were used, the degradation rate decreased compared to the mixtures at 80 vol.%. This would infer that the preferred reaction pathway is hydrolysis. Molecules of water and its ions are smaller than that of the GRAS solvents used and would therefore diffuse more easily in the resin.

Negative degradation rate were observed after a treatment at 250 and 300 °C, the samples were therefore heavier after solvolysis. As the final mass of the samples were measured after drying at 70 °C until no mass change was observed, this mass uptake can be

explained by solvent molecules chemically bonded to the resin chemical structure.

The GRAS solvents used are assumed to be co-reactants as the resin degradation occurs in pure GRAS solvent as well. Further investigations are needed to understand the chemistry involved in presence of these GRAS solvents, and acetone in particular.

The liquid fraction recovered from experiment # 30 with 80 vol.% of acetone, at 350 °C, 30 min and a resin concentration of 30 mg/mL (Table 4) was analysed by GC-TOF MS and gave the chromatogram shown in Fig. 10. Similar products were recovered as with neat water, except that BPA can be recovered at 350 °C when acetone is added. Secondary reactions degrading BPA into other phenolic compounds seem therefore to be limited due to the presence of acetone. Similar observations were obtained with the two other GRAS solvents (ethanol and 2-propanol).

4. Conclusion

Different solvolysis technologies were applied to degrade a model epoxy resin. The results from the different GRAS solvents and their mixtures were compared to those solely obtained by reference neat water solvolysis. They indicated that CO_2 -expanded water and a mixture of 80 vol.% acetone and water, in particular, were promising solutions to enhance resin degradation. The addition of either CO_2 or GRAS solvent to water produces either an enhanced fluidity liquid (similar to supercritical fluids) or a supercritical fluid by lowering the critical point of the solvent medium respectively, therefore improving diffusion and mass transfer compared to subcritical water. Furthermore, it seems that CO_2 acts as a catalyst in combination with the phenol produced by the resin degradation. On the other hand, GRAS solvents seem to act more as co-reactants and improve the solubilisation of the reaction products. Recovered fibres would therefore be less contaminated by resin residue. The analysis of the composition of the liquid fractions indicated that valuable products, such as phenol, can be recovered. Hydrolysis appeared to be the more obvious reaction pathway. Further investigations are in progress to understand better the chemistry involved in the degradation of epoxy resins, as well as experiments on real composite materials to assess the fibre integrity.

Acknowledgements

The funding from EPSRC for the EXHUME project (EP/K026348/1) is gratefully acknowledged.

References

- [1] Song YS, Youn JR, Gutowski TG. Life cycle energy analysis of fiber-reinforced composites. *Compos Part A* 2009;40:1257–65.
- [2] Markovic V, Marinkovic S. A study of pyrolysis of phenolic resin reinforced with carbon fibres and oxidized PAN fibres. *Carbon* 1980;18:329–35.
- [3] Pickering SJ, Kelly RM, Kennerley JR, Rudd CD, Fenwick NJ. A fluidised-bed process for the recovery of glass fibres from scrap thermoset composites. *Compos Sci Technol* 2000;60:509–23.
- [4] Meyer LO, Schulte K. Cfrp-recycling following a pyrolysis route: process optimization and potentials. *J Compos Mater* 2009;43:1121–32.
- [5] Gosau JM, Tyler FW, Allred RE. Carbon fiber reclamation from state-of-art 2nd generation aircraft composites. In: Proc. International SAMPE symposium and exhibition (ISSE 2009); may 18–21 2009. Baltimore, MD, USA.
- [6] Lester E, Kingman S, Wong KH, Rudd C, Pickering S, Hilal N. Microwave heating as a means for carbon fibre recovery from polymer composites: a technical feasibility study. *Mater Res Bull* 2004;39:1549–56.
- [7] Åkesson D, Poltynowicz Z, Christ  en J, Skrifvars M. Microwave pyrolysis as a method of recycling glass fibre from used blades of wind turbines. *J Reinf Plastics Compos* 2012;31:1136–42.
- [8] Nahil MA, Williams PT. Recycling of carbon fibre reinforced polymeric waste for the production of activated carbon fibres. *J Anal Appl Pyrolysis* 2011;91:67–75.
- [9] Pimenta S, Pinho ST. Recycling carbon fibre reinforced polymers for structural applications: technology review and market outlook. *Waste Manag* 2011;31:378–92.
- [10] Yoon KH, DiBenedetto AT, Huang SJ. Recycling of unsaturated polyester resin using propylene glycol. *Polymer* 1997;38:2281–5.
- [11] Pooawad P. Degradation of poly(methyl methacrylate) and poly(butylene succinate) under sub- and supercritical water [MSc thesis report]. Thailand: Kasetsart University; 2007.
- [12] Ramakrishna S, Tan WK, Teoh SH, Lai MO. Recycling of carbon fiber/peek composites. *Key Eng Mater* 1998;137:1–8.
- [13] Fromonteil C, Bardelle Ph, Cansell F. Hydrolysis and oxidation of an epoxy resin in sub- and supercritical water. *Indus Eng Chem Res* 2000;39:922–5.
- [14] Okajima I, Yamada K, Sugeta T, Sako T. Decomposition of epoxy resin and recycling of CFRP with sub- and supercritical water. *Kagaku Kogaku Ronbunshu* 2002;28:553–8.
- [15] Tagaya H, Shibasaki Y, Kato C, Kadokawa J, Hatano B. Decomposition reactions of epoxy resin and polyetheretherketone resin in sub- and supercritical water. *J Material Cycles Waste Manag* 2004;6:1–5.
- [16] Dang W, Kubouchi M, Sembokuya H, Tsuda K. Chemical recycling of glass fiber reinforced epoxy resin cured with amine using nitric acid. *Polymer* 2005;46:1905–12.
- [17] Suyama K, Kubota M, Shirai M, Yoshida H. Effects of alcohols on the degradation of crosslinked unsaturated polyester in sub-critical water. *Polym Degrad Stab* 2006;91:983–6.
- [18] Hyde JR, Lester E, Kingman S, Pickering S, Wong KH. Supercritical propanol, a possible route to composite carbon fibre recovery: a viability study. *Compos Part A* 2006;37:2171–5.
- [19] Gersifi KE, Durand G, Tersac G. Solvolysis of bisphenol A diglycidyl ether/anhydride model networks. *Polym Degrad Stab* 2006;91:690–702.
- [20] Gosau JM, Wesley TF, Allred RE. Integrated composite recycling process. In: Proc. 38th SAMPE technical conference; Nov. 7–9 2006. Dallas, Texas, USA.
- [21] Suyama K, Kubota M, Shirai M, Yoshida H. Degradation of crosslinked unsaturated polyesters in sub-critical water. *Polym Degrad Stab* 2007;92:317–22.
- [22] Iwaya T, Tokuno S, Sasaki M, Goto M, Shibata K. Recycling of fiber reinforced plastics using depolymerization by solvothermal reaction with catalyst. *J Mater Sci* 2008;43:2452–6.
- [23] Pintero-Hernanz R, Dodds C, Hyde J, Garcia-Serna J, Poliakov M, Lester E, et al. Chemical recycling of carbon fibre reinforced composites in near critical and supercritical water. *Compos Part A* 2008;39:454–61.
- [24] Pintero-Hernanz R, Garcia-Serna J, Dodds C, Hyde J, Poliakov M, Jose Cocero M, et al. Chemical recycling of carbon fibre composites using alcohols under subcritical and supercritical conditions. *J Supercrit Fluids* 2008;46:83–92.
- [25] Wang H, Liu Y, Li Z, Zhang X, Zhang S, Zhang Y. Glycolysis of poly(ethylene terephthalate) catalyzed by ionic liquids. *Eur Polym J* 2009;45:1535–44.
- [26] Yuyan L, Guohua S, Linghui M. Recycling of carbon fibre reinforced composites using water in subcritical conditions. *Mater Sci Eng A* 2009;520:179–83.
- [27] Nakagawa T, Matsugi S, Hirota S, Miyazaki T, Yano H, Shibata K, et al. Enhanced and horizontal recycling of FRP using subcritical water. In: International symposium on supercritical fluids (ISSF); 18–20 may 2009. Arcachon, France.
- [28] Bai Y, Wang Z, Feng L. Chemical recycling of carbon fibers reinforced epoxy resin composites in oxygen in supercritical water. *Mater Des* 2010;31:999–1002.
- [29] Okajima I, Araya K, Hiramatsu M, Sako T. Chemical recycling of carbon fiber reinforced plastic with sub- or supercritical fluids. In: Proc. 9th international symposium on supercritical fluids (ISSF); 18–20 may 2009. Arcachon, France.
- [30] Kamimura A, Akinari Y, Watanabe T, Yamada K, Tomonaga F. Efficient chemical recycling of waste fiber-reinforced plastics: use of reduced amounts of dimethylaminopyridine and activated charcoal for the purification of recovered monomer. *J Mater Cycles Waste Manag* 2010;12:93–7.
- [31] Sakuma M, Koyama M, Fukuda H. Establishment of CFRP recycling method processable under atmospheric pressure. In: Proc. 18th international conference on composite materials (ICCM-18); 21–26 August 2011. Jeju, Korea.
- [32] Oliveux G, Bailleul JL, Le Gal La Salle E. Chemical recycling of glass fibre reinforced composites using subcritical water. *Compos Part A* 2012;43:1809–18.
- [33] Elghazzaoui H. Contribution    l'  tude de la d  gradation des composites carbone/  poxy par solvolys   dans l'eau subcritique et supercritique en vue de leur recyclage [Ph.D. Thesis]. France: Universit   de Nantes; 2012.
- [34] Okajima I, Watanabe K, Sako T. Chemical recycling of carbon fiber reinforced plastic with supercritical alcohol. *J Adv Res Phys* 2012;3:1–4.
- [35] Liu Y, Liu J, Jiang Z, Tang T. Chemical recycling of carbon fibre reinforced epoxy resin composites in subcritical water: Synergistic effect of phenol and KOH on the decomposition efficiency. *Polym Degrad Stab* 2012;97:214–20.
- [36] Knight CC, Zeng C, Zhang C, Wang B. Recycling of woven carbon-fibre-reinforced polymer composites using supercritical water. *Environ Technol* 2012;33:639–44.
- [37] Feraboli P, Kawakami H, Wade B, Gasco F, DeOto L, Masini A. Recyclability and reutilization of carbon fiber fabric/epoxy composites. *J Compos Mater* 2012;46:1459–73.
- [38] Yang P, Zhou Q, Yuan XX, van Kasteren JMN, Wang YZ. Highly efficient solvolysis of epoxy resin using poly(ethylene glycol)/NaOH systems. *Polym Degrad Stab* 2012;97:1101–6.
- [39] Li J, Xu PL, Zhu YK, Ding JP, Xue LX, Wang YZ. A promising strategy for chemical recycling of carbon fiber/thermoset composites: self-accelerating decomposition in a mild oxidative system. *Green Chem* 2012;14:3260–3.
- [40] Xu PL, Li J, Ding JP. Chemical recycling of carbon fibre/epoxy composites in a mixed solution of peroxide hydrogen and N,N-dimethylformamide. *Compos Sci Technol* 2013;82:54–9.
- [41] Oliveux G, Bailleul JL, Le Gal La Salle E, Lefevre N, Biotteau G. Recycling of glass fibre reinforced composites using subcritical hydrolysis: reaction mechanisms and kinetics, influence of the chemical structure of the resin. *Polym Degrad Stab* 2013;98:785–800.
- [42] Onwudili JA, Yildirim E, Williams PT. Catalytic hydrothermal degradation of carbon reinforced plastic wastes for carbon fibre and chemical feedstock recovery. *Waste Biomass Valorization* 2013;4:87–93.
- [43] Yildirim E, Onwudili JA, Williams PT. Recovery of carbon fibres and production of high quality fuel gas from the chemical recycling of carbon fibre reinforced plastic wastes. *J Supercrit Fluids* 2014;92:107–14.
- [44] Dandy LO, Oliveux G, Wood J, Jenkins MJ, Leeke GA. Accelerated degradation of polyetheretherketone (PEEK) composite materials for recycling applications. *Polym Degrad Stab* 2015;112:52–62.
- [45] Wood K. Carbon fiber reclamation: going commercial. High-performance Composites Mag March 2010. <http://www.compositesworld.com/articles/carbon-fiber-reclamation-going-commercial> [last accessed February 2014].
- [46] Final summary report of the EURECOMP project Recycling thermoset composites of the SST. 2009–2012., http://www.transport-research.info/Upload/Documents/201301/20130116_145654_17343_EURECOMP_FinalSummaryReport_Sep2012.pdf [last accessed February 2014].
- [47] Oliveux G, Dandy LO, Leeke GA. Current status of recycling of fibre reinforced polymers: Review of technologies, reuse and resulting properties. *Prog Mater Sci* 2015;72:61–99.
- [48] White SR, Mather PT, Smith MJ. Characterization of the cure-state of DGEBA-DDS epoxy using ultrasonic, dynamic mechanical, and thermal probes. *Polym Eng Sci* 2012;42:51–67.
- [49] Jessop PG, Subramaniam B. Gas-expanded liquids. *Chem Rev* 2007;107:2666–94.
- [50] Yuan XZ, Li H, Zeng GM, Tong JY, Xie W. Sub- and supercritical liquefaction of rice straw in the presence of ethanol-water and 2-propanol-water mixture. *Energy* 2007;32:2081–8.