

# Rapid sintering of $\text{Li}_{6.5}\text{La}_3\text{Zr}_1\text{Nb}_{0.5}\text{Ce}_{0.25}\text{Ti}_{0.25}\text{O}_{12}$ for high density lithium garnet electrolytes with current induced in- situ interfacial resistance reduction.

Stockham, Mark; Dong, Bo; James, Matthew; Zhu, Pengcheng; Kendrick, Emma; Slater, Peter

DOI:  
[10.1039/D3YA00123G](https://doi.org/10.1039/D3YA00123G)

License:  
Creative Commons: Attribution (CC BY)

*Document Version*  
Peer reviewed version

*Citation for published version (Harvard):*  
Stockham, M, Dong, B, James, M, Zhu, P, Kendrick, E & Slater, P 2023, 'Rapid sintering of  $\text{Li}_{6.5}\text{La}_3\text{Zr}_1\text{Nb}_{0.5}\text{Ce}_{0.25}\text{Ti}_{0.25}\text{O}_{12}$  for high density lithium garnet electrolytes with current induced in-situ interfacial resistance reduction.', *Energy Advances*. <https://doi.org/10.1039/D3YA00123G>

[Link to publication on Research at Birmingham portal](#)

## General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

## Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact [UBIRA@lists.bham.ac.uk](mailto:UBIRA@lists.bham.ac.uk) providing details and we will remove access to the work immediately and investigate.

Download date: 12. May. 2024

# Energy Advances

Accepted Manuscript

This article can be cited before page numbers have been issued, to do this please use: M. P. Stockham, B. Dong, M. S. James, P. Zhu, E. Kendrick and P. R. Slater, *Energy Adv.*, 2023, DOI: 10.1039/D3YA00123G.



This is an Accepted Manuscript, which has been through the Royal Society of Chemistry peer review process and has been accepted for publication.

Accepted Manuscripts are published online shortly after acceptance, before technical editing, formatting and proof reading. Using this free service, authors can make their results available to the community, in citable form, before we publish the edited article. We will replace this Accepted Manuscript with the edited and formatted Advance Article as soon as it is available.

You can find more information about Accepted Manuscripts in the [Information for Authors](#).

Please note that technical editing may introduce minor changes to the text and/or graphics, which may alter content. The journal's standard [Terms & Conditions](#) and the [Ethical guidelines](#) still apply. In no event shall the Royal Society of Chemistry be held responsible for any errors or omissions in this Accepted Manuscript or any consequences arising from the use of any information it contains.

Rapid sintering of  $\text{Li}_{6.5}\text{La}_3\text{Zr}_1\text{Nb}_{0.5}\text{Ce}_{0.25}\text{Ti}_{0.25}\text{O}_{12}$  for high density lithium garnet electrolytes with current induced *in-situ* interfacial resistance reduction.

[View Article Online](#)  
DOI: 10.1039/D3TA00123G

M. P. Stockham<sup>1\*</sup>, B. Dong<sup>1,3</sup>, M.S. James<sup>1</sup>, P. Zhu<sup>2,3</sup>, E. Kendrick<sup>2,3</sup>, P.R. Slater<sup>1,3\*</sup>

<sup>1</sup>School of Chemistry, University of Birmingham, Birmingham B15 2TT. UK

<sup>2</sup>School of Metallurgy and Materials, University of Birmingham, Birmingham B15 2TT. UK

<sup>3</sup>The Faraday Institution, Quad One, Harwell Campus, Didcot OX11 0RA, UK

Correspondence to

M. P. Stockham/P. R. Slater

School of Chemistry, University of Birmingham, Birmingham B15 2TT. UK



## Abstract

View Article Online  
DOI: 10.1039/D3YA00123G

A primary target of energy storage is the all solid state battery, however finding a suitable solid state electrolyte has proven troublesome. Lithium garnet materials are promising solid state electrolytes with high room temperature conductivity, a wide electrochemical window, high chemical stability with Li metal and have minimal hazards. However, lithium garnets suffer from slow, energy demanding synthesis, rapid proton exchange (leading to high interfacial resistance between the garnet and electrodes), mechanical instabilities with Li metal and require specific handling methods to achieve the highest performing materials (such as full processing under Ar). Here we report a Ti/Ce co-doped high entropy lithium garnet material with four B site dopants, with the formula  $\text{Li}_{6.5}\text{La}_3\text{Zr}_1\text{Nb}_{0.5}\text{Ce}_{0.25}\text{Ti}_{0.25}\text{O}_{12}$ . This material benefits from rapid simultaneous sintering and densification directly from the starting materials, allowing formation of dense pellets in <1hr at 1100°C using only a standard, cheap, muffle furnace.  $\text{Li}_{6.5}\text{La}_3\text{Zr}_1\text{Nb}_{0.5}\text{Ce}_{0.25}\text{Ti}_{0.25}\text{O}_{12}$  also has high conductivity (0.5 mS cm<sup>-1</sup> at 25°C), scalability and insensitivity to both rapid furnace ramp rates and long dwell times. There is also an indication of unusual behaviour towards limiting lithium dendrite propagation, which is also discussed.



## Introduction

Safe, long-lasting portable energy storage is an elusive goal. Lithium-ion batteries (LIB) are the device of choice for use in secondary, rechargeable, batteries, owing to their high energy density, low self-discharge, long life (compared to other options) and extended cycling stability<sup>1, 2</sup>. Yet LIBs remain far from reaching their theoretical potential and pose serious safety concerns, while a rechargeable lithium metal battery with high cyclability remains elusive. LIB safety problems generally arise from the liquid based electrolytes, such as LiPF<sub>6</sub> in ethylene carbonate and dimethyl carbonate. These electrolytes are flammable, toxic, have limited electrochemical windows and are unstable with Li metal<sup>1, 3-21</sup>. These electrolytes, therefore, require optimisation or replacement for the next leap in energy storage.

Solid state batteries (SSB) are thought to overcome most limitations in current LIBs<sup>5, 22-26</sup>. However, current SSBs remain confined mostly to small scale laboratory work, as finding a suitable solid state electrolyte (SSE) has proved troublesome. The issues primarily relate to either poor ionic mobility or limited electrochemical windows, however are further complicated by long/complex synthesis and poor interfacial contact to the electrodes. This poor interfacial contact leads to a resistance too high for battery operation, abrupt potential changes, and increasingly poorer contact due to volume changes during cell operation<sup>27-35</sup>. Therefore, full SSBs have yet to be deployed on a large scale, with the exception of micro-batteries, such as those based upon lithium phosphorus oxynitride, which have been commercially available for some time<sup>36</sup>.

Of the available SSEs, lithium garnet type materials have received significant attention, owing to their well-established wide electrochemical window and (after considerable work) ionic conductivity rivalling that of current liquid electrolytes at room temperature (0.1 - 1 mS cm<sup>-1</sup>)<sup>37-41</sup>. These materials are also chemically stable with Li metal, but they are susceptible to Li dendrite propagation through grain boundaries, although this can be substantially improved with increased SSE density, high stack pressures and low interfacial resistance<sup>42-48</sup>. Lithium garnets, however, often require time consuming synthesis, followed by densification processes, which can take several days. The best performing garnets in the literature also need handling solely within an Ar atmosphere to fully prevent proton exchange, which arises from thermodynamic instabilities in air (associated with the high Li content<sup>37, 49</sup>. Therefore, synthesis often lacks scalability and is usually confined to the < 4g level.

Ideal garnets have the general formula A<sub>3</sub>B<sub>2</sub>X<sub>3</sub>O<sub>12</sub> (e.g. A = Fe, Mg, B = Al, Cr, Fe, and X = Si, Fe, Al, Ga)<sup>50-53</sup>. In Li<sub>3</sub> garnets, e.g. Li<sub>3</sub>La<sub>3</sub>Te<sub>2</sub>O<sub>12</sub>, lithium fully occupies the 24d tetrahedral site and shows minimal Li ion mobility<sup>52, 54</sup>. System modifications by addition of lower valent cations permit increased Li content



to maintain charge neutrality. This gives increased conductivity with lithium occupying additional interstitial octahedral sites in a disordered fashion<sup>51, 53, 55, 56</sup>. Li garnets can accommodate 7 Li per formula unit (*pfu*), but this results in full Li site occupation and Li ordering (to reduce short Li-Li distances). This gives an elongation of an axis in the cubic cell forming the thermodynamically stable tetragonal system<sup>57-61</sup>. Tetragonal garnets have 7 Li *pfu* and poor conductivity with the  $I4_1/acd$  space group (no. 142)<sup>57-60</sup> whereas cubic garnets have <7 Li *pfu* and show high conductivity commonly with  $la\bar{3}d$  (no. 230) symmetry, although  $\bar{I}43d$  (no.220) has been proposed for  $Ga_xLi_{7-3x}La_3Zr_2O_{12}$  (Ga-LLZO)<sup>53, 62, 63</sup>.  $Li_{6.95}La_3Zr_{1.95}Nb_{0.05}O_{12}$  has also been reported with orthorhombic symmetry, space group *Ibca*<sup>64</sup>. Irrespectively, most lithium garnet reports detail cubic systems where Li content is between ~6.2-6.6 *pfu* as this maximises the Li content (and subsequent disorder) while maintaining some vacant interstitial sites for an effective migration pathway<sup>37, 45, 51, 55-57, 65-80</sup>.

Much work has focused on single dopant strategies, such as Al/Ga-LLZO, however only a small number of reports focus upon higher entropy lithium garnets, where multiple cations have been substituted onto a single site (where a high entropy metal oxide is, generally, considered to be a single-phase material with  $\geq 5$  elements *pfu*). Such increased entropic factors could be harmonious with the highly entropic cubic, high Li content garnet systems. This would promote increased disorder which may yield better conductivity, rapid synthesis, or better cell performance, some of which have been shown in recent reports<sup>81-83</sup>.

Prior work has shown that Ce doping in LLZO enables lower interfacial resistance between the Li metal and the garnet ( $388 \Omega \text{ cm}^2$ ), likely due to partial  $Ce^{4+}$  reduction<sup>61</sup>. We also recently reported on some high entropy garnet systems, and the ease at which they can form. We suggested that, with  $Ga_{0.2}Li_{5.75}La_{2.5}Nd_{0.5}Nb_{0.35}Ta_{0.3}Ce_{0.1}Zr_{0.75}Hf_{0.25}Ti_{0.25}O_{12}$ , the use of the Ti dopant should be examined further due to prior literature reports of dendrite resistance, high relative density pellets (95%), good ionic conductivity ( $0.2 \text{ mS cm}^{-1}$  at room temperature) and favourable interfacial wetting between the Li metal and Ti doped garnets<sup>81, 84-86</sup>. Therefore, the aim of this work was to build upon prior studies and combine the low interfacial resistance afforded by  $Ce^{4+}$  and the favourable performance properties reported for  $Ti^{4+}$  doping into a new dual doped high entropy garnet system, with aims to improve sintering, densification and conductivity.

Herein, an easy to synthesise Li garnet is presented, with the formula  $Li_{6.5}La_3Zr_1Nb_{0.5}Ce_{0.25}Ti_{0.25}O_{12}$  (LTC). LTC was designed to take advantage of a high entropy type approach *via* a multi-element doping strategy on the B site (rather than a single dopant for cubic phase stabilisation, such as Nb in a tetragonal LLZO type system). LTC enables a fast synthesis route to a high conductivity garnet, requiring only 15 - 60 minutes to form dense pellets, directly from the starting materials, and uses only conventional muffle furnaces placed in a dry room. LTC is insensitive to heating rates, forming



similar performing SSE membranes when heated at  $2^{\circ}\text{C min}^{-1}$  or at  $40^{\circ}\text{C min}^{-1}$  (furnace limit). Furthermore, the high ionic conduction in LTC ( $1.1 \text{ mS cm}^{-1}$  at  $45^{\circ}\text{C}$ , 88% density) does not noticeably degrade if heated for  $>1\text{h}$ . Mostly pure LTC can form in as little as 5 mins at  $1100^{\circ}\text{C}$ , whereas powder synthesis can be accomplished at  $950^{\circ}\text{C}/1\text{h}$  in air. The rapid simultaneous synthesis and densification results are not mirrored when preparing garnets using Ce or Ti as a single dopant, nor in reports detailing the single dopants elsewhere<sup>86-88</sup>. LTC shows excellent cycling stability, and a wide electrochemical window.

LTC was also designed to avoid Li site substituted dopants (such as Al/Ga), which exsolve to the grain boundary during heating and are unstable in contact with Li metal. These have been reported prior to undergo reversible short circuits during cell cycling, whereupon soft short circuits are removed by cell resting. This causes the garnet cations to be reduced *via* Li metal, which oxidises Li and removes the dendrite/s, with this attributed to the non-negligible electronic conductivity of lithium garnet materials<sup>89</sup>. This problem, however, could be tailored towards more rapid removal of lithium metal short circuits *via* dopant strategies. This could assist in dendrite removal before cell failure, and could be especially helpful if used as an interlayer in an all solid state cell. The reversible short circuit behaviour and in-situ changes to area specific resistance in LTC was, therefore, assessed in this work by time resolved impedance spectroscopy and X-ray absorption near edge structure.



## Methods

View Article Online  
DOI: 10.1039/D3YA00123G

### Synthesis

$\text{Li}_{6.5}\text{La}_3\text{Zr}_1\text{Nb}_{0.5}\text{Ce}_{0.25}\text{Ti}_{0.25}\text{O}_{12}$  (LTC) was prepared via the solid-state route from stoichiometric quantities of  $\text{Li}_2\text{CO}_3$  ( $\geq 99\%$ , Sigma),  $\text{La}_2\text{O}_3$  (99.9%, Sigma),  $\text{Nb}_2\text{O}_5$  (99.9%, Alfa Aesar),  $\text{ZrO}_2$  ( $>99\%$  Alfa Aesar),  $\text{TiO}_2$  (99.6%, Alfa Aesar) and  $\text{CeO}_2$  (99.9%, Acros Organics) in air. A 40% mol excess of lithium was added to compensate for lithium loss during high temperature sintering. All powders were ball milled for 1 hr with  $\text{ZrO}_2$  balls (350 rpm) with hexane. The powders were heated to  $950^\circ\text{C}$  (powder) or pelletised and heated  $1100^\circ\text{C}$  (1 h) at the fastest possible ramp rate in air ( $100^\circ\text{C min}^{-1}$ ) and within a dry room ( $40^\circ\text{C min}^{-1}$ ) in Carbolite ELF11/6 or CWF13/3 furnaces respectively. 10 mm pellets were pressed to 0.5 - 1 ton for  $\sim 1$  min from the starting materials. The dry room had a dewpoint between  $-45^\circ\text{C}$  to  $-64^\circ\text{C}$  (the elimination of humidity is desirable to prepare good quality garnet samples, as it is well established moisture can be an issue in the synthesis of Li garnet systems)<sup>90-92</sup>. Singularly Ce, Ti doped  $\text{Li}_{6.5}\text{La}_3\text{Zr}_{1.25}\text{Nb}_{0.5}\text{Ce}_{0.25}\text{O}_{12}$  and  $\text{Li}_{6.5}\text{La}_3\text{Zr}_{1.25}\text{Nb}_{0.5}\text{Ti}_{0.25}\text{O}_{12}$  were synthesised in the same manner but required two and four hours respectively to obtain similarly dense pellets.

All samples were stored in an argon glove box to prevent proton-Li exchange<sup>71, 93-96</sup>. Scanning electron microscopy (SEM) was performed on a Philips XL30 FEG instrument, with the elemental distribution confirmed by the corresponding Oxford Inca 300 energy dispersive X-ray (EDX) attachment. Pellets were polished with silicon carbide sandpaper from 800 to 4000 grit to form a flat surface. Additional SEM/EDX was performed on unpolished pellets and powder (available in the SI) using a benchtop Hitachi TM4000plus instrument. Here, elemental analysis was undertaken *via* an AZtecOne X-stream2 energy dispersive X-ray spectrometer. SEM/EDX pellets or powders were secured to the SEM stub by carbon tape. Phase analysis was performed by X-ray diffraction (XRD) using a Bruker D8 diffractometer with a Cu X-ray source. Experimental pellet densities were determined and compared to theoretical values from Rietveld refinement results (performed using GSAS II software)<sup>97</sup>. 3D visualisations of the crystal structure used Vesta<sup>98</sup>.

### Impedance Spectroscopy

Post-sintering, the pellets were polished and were sputtered with Au using an Agar Automatic Sputter coater with a 40mA current for 60 seconds, (or until a clearly visible gold coating was present). The pellets were protected from short circuit by adhesive tape. The sputtered pellets were then secured in an MTI split cell for room temperature impedance spectroscopy measurements, which were performed using a Solartron 1260 impedance analyser from 1 Hz to 10 MHz with a 20 mV potential. Variable temperature measurements were undertaken in a Genlab Classic oven from 19 –  $64^\circ\text{C}$ , with





at least 30-minute rest periods once obtaining the set temperature. Temperature accuracy was confirmed via a Fluke 51 II external thermocouple.

## Cell assembly

All cell tests were performed on a biologic VMP3 or SP50 instrument. Li|LTC|Li symmetric cells (> 9 cells) were assembled in an Ar glove box. Firstly, the pellets (~1 mm thickness) were polished using silicon carbide sandpaper from 240 to 4000 grit, then lithium metal foil was applied to each side of the pellet. The cell was then heated to 175 °C under a constant pressure for 1 h using a commercially and readily available steel 3-way G clamp as reported prior<sup>99</sup> and was secured under light pressure via hand tightening the clamp. The cell was subsequently secured within an MTI split test cell. Cells were examined *via* impedance spectroscopy before (and after) cell testing from 10 MHz to 0.1 Hz with a 20 mV potential on a Solartron 1260 impedance analyser. LTC Cells were analysed on an open lab bench (non-air conditioned) with small temperature fluctuations between 17-23°C for the critical current density (CCD), in increments of 10  $\mu\text{A cm}^{-2}$ . Cells were also assembled in a similar manner for long term Li stripping and plating analysis at 49°C, see figure S8.

Au|LTC|Li cells, for cyclic voltammetry (C.V.), were formed by polishing an LTC pellet as above and hand pressing the pellet into Li foil in an Ar glovebox. The cell was placed in a MTI Split cell with Au foil as the working electrode. Cyclic voltammetry was subsequently run from -0.4 to 10 V at a scan rate of 1  $\text{mV s}^{-1}$ .



## Results and discussion

View Article Online  
DOI: 10.1039/D3YA00123G

### X-Ray diffraction results

The powder X-ray diffraction (XRD) patterns of the LTC garnet materials sintered at 950°C (powder) and 1100°C (pellet) for 1h are shown in figure 1. Both were indexed on the  $la\bar{3}d$  space group as per other garnet materials without Ga (or Fe) Li site substitution<sup>62, 100</sup>. Rietveld refinements were based upon the structural model from Hamao *et al.*<sup>101</sup>. Considering the scattering similarities between Zr and Nb these were set to the intended ratios. As Zr and Nb occupancies could not be refined, Ce and Ti occupancies were also set to the intended ratio (which corresponded to the homogeneity seen within the EDX images gathered from the pellet surface, see later). Table 1 reports the calculated lattice parameters and an example refinement is shown in figure S1. Lattice parameters were 12.9389(6) Å for the powder sintered at 950°C and 12.9477(2) Å for the densified pellet at 1100°C (88% relative density). This is in line with other garnets with similarly high Li content on the  $la\bar{3}d$  type symmetry, and slightly larger than reported for the singly doped garnet  $\text{Li}_{6.5}\text{La}_3\text{Zr}_{1.5}\text{Ta}_{0.5}\text{O}_{12}$ <sup>101</sup>, which can be attributed to the presence of the larger Ce.

Considering the rapid speed, additional investigations into the optimum sintering/densification time were undertaken. LTC pellets were prepared and heated to 1100°C for 5, 15, 30, 45 and 60 minutes, see figure 2 and table 1. It was determined that garnet phases form in as little as 5 mins, with lattice parameters of 12.9404(7) Å being only slightly reduced compared to 1h. However, those phases sintered for 5 min had broad peaks, and were not uniformly densified with only a dense inner core surrounded by loose powders. Such pellets had relative densities of 80% but were thin and brittle. Nonetheless, this is an impressive density value for only 5 minutes sintering.

Pellets which were heated for  $\geq 15$  minutes did not require removal of any excess powder and formed denser membranes. These samples showed sharp, highly crystalline, diffraction peaks and gave lattice parameters similar to sintering for 1h. The peaks were mostly garnet related; however, some minor unknown impurities were present which could not be fully identified. These are attributed to partial sintering of the starting materials, with some peaks indexed to Li-Nb-O phases of varying stoichiometries. These impurity peaks remained until  $\geq 45$ mins, after which pure garnet type symmetry was observed. Relative densities for pellets sintered for  $\geq 15$  minutes ranged from 83-88%, the maximum of which was obtained at 1h. Sintering beyond 1h gave little difference in density, therefore subsequent pellets were sintered for 1h. Attempts were made to reduce the Li mol excess to 5, 10 or 20%, however pellet densification was much reduced by comparison and only a dense pellet



core, encapsulated by less dense powders, was observed. This suggests that the Li excess is also acting as an additional sintering aid.

Therefore, maximal pellet densities for these samples using conventional muffle furnaces is ~88% at 1100°C (similar densities were also achieved under N<sub>2</sub>/O<sub>2</sub> and no additional benefits were found when heating >1100°C). This is in line with our previous work conducted under similar experimental procedures for other garnet systems<sup>68-70, 99, 102</sup>, however these reports required sintering the powder for ~12h followed by densification for ~12h in either air or N<sub>2</sub>/O<sub>2</sub> (even with comparable Li excess as reported here. Or the addition of other sintering aids, e.g. LiF) and were more sensitive to heating rates. This is also true of the majority of reports elsewhere<sup>37, 41, 78, 87, 92, 101, 103-105</sup>. The sintering and densification behaviour of LTC, however, is considerably quicker and LTC has high ionic conductivity compared to similar reports (see later for impedance spectroscopy)<sup>68-70, 81, 99, 102, 106</sup>.

It is not clear why LTC has such rapid densification and sintering. It could perhaps rely on the increased disorder of the B site, which is host to four separate elements. This could enable greater entropic contributions to the cubic lithium garnet and thus provide the additional contribution to drive more rapid synthesis. However, it appears that some form of reactive sintering is crucial, as powder synthesis followed by densification was significantly more troublesome (1200 °C for 4 - 6 hours) and gave marginally poorer room temperature ionic conductivity (~0.1 mS cm<sup>-1</sup>). The rapid densification of LTC is reminiscent of liquid sintering, whereby the low melting point of a particular compound (Li<sub>2</sub>CO<sub>3</sub> here, with a 40% excess) can enable formation of a dense ceramic, and this is supported by the poorer densification observed when using a lower Li excess. However, when Ti or Ce is used singularly with Li<sub>6.5</sub>La<sub>3</sub>Zr<sub>1.25</sub>Nb<sub>0.5</sub>M<sub>0.25</sub>O<sub>12</sub> (M = Ti, Ce) (also with 40% Li excess) the synthesis was quick yet densification took several hours, see later. Therefore, although liquid sintering is a possibility to explain the rapid densification, its dependence on an Li<sub>2</sub>CO<sub>3</sub> excess remains unclear.

LTC was also proven to be scalable to at least 15g (the volume limit of the milling pot) under the same procedure. Increased Li content beyond 6.5 *pfu* was attempted, in the form of Li<sub>6.6</sub>La<sub>3</sub>Nb<sub>0.4</sub>Zr<sub>1</sub>Ti<sub>0.35</sub>Ce<sub>0.25</sub>O<sub>12</sub> and Li<sub>6.7</sub>La<sub>3</sub>Nb<sub>0.3</sub>Zr<sub>1</sub>Ti<sub>0.45</sub>Ce<sub>0.25</sub>O<sub>12</sub>. However, this yielded impurities, such as CeO<sub>2</sub>, which were unable to be removed, see figure S2.



Table 1. Lattice parameters, relative density, conductivity, capacitance values and dielectric constants for the analysed materials, where LT and LC correspond to the use of Ti and Ce as single dopants.

LTC Sample (mins)	Lattice Parameters (Å)	$\rho_{\text{rel}}$ (%)	$\sigma$ (mS cm <sup>-1</sup> )	$C_{\text{bulk}}$ (F/cm) (pF)	$\epsilon_r$
<b>Powder</b>	12.9389(6)	-	-	-	-
<b>5</b>	12.9404(7)	80	-	-	-
<b>15</b>	12.9492(6)	84	0.30 (26°C)	4.75	54
<b>30</b>	12.9490(4)	86	0.39 (27°C)	5.57	63
<b>45</b>	12.9507(5)	83	0.35 (24°C)	4.69	53
<b>60</b>	12.9477(2)	88	0.42 (24°C)	5.64	64
<b>180</b>	12.9446(2)	86	0.37 (22°C)	4.29	48
<b>720</b>	12.9539(1)	87	0.38 (22°C)	4.87	55
<b>LT</b>	12.9138(9)	86	0.33 (22°C)	4.77	54
<b>LC</b>	12.9760(14)	84	0.31 (22°C)	5.91	66



## SEM/EDX

The sintered pellet (1100 °C) was analysed *via* SEM and EDX to assess the microstructural features and to confirm elemental content. The SEM images show a dense pellet structure with an absence of discernible grain boundaries, with the corresponding EDX indicating the expected elemental distribution (see figure 3). Although the pellet has well connected individual grains; clear voids are present. Therefore, magnification was increased to examine these voids more closely. Here, the EDX, while indicating a relatively homogenous distribution of elements, shows higher concentrations of Ti around the grain boundary. It is unclear why this is so, however this could relate to some incomplete synthesis, or dopant exsolution in this region. Additional SEM and EDX images are shown in the SI for the unpolished pellet surface (which shows individual grains, see figure S3) and of the LTC powder when synthesised at 950°C (figure S4).



## Conductivity

View Article Online  
DOI: 10.1039/D3YA00123G

The room temperature conductivity of LTC was assessed by impedance spectroscopy for each pellet dwell time > 5 mins. Densities of the pellets ranged from 83-88% and were unable to be improved by times > 1h, higher temperature, slower heating rates or under  $N_2/O_2$ , see table 1.

A typical Nyquist plot with Au blocking electrodes is shown in figure 4, with the associated capacitance bode plot available in the SI. All LTC materials demonstrated a single resistivity contribution which is attributed to overlapping bulk and grain boundary contributions. Therefore, all plots were fit with a single parallel R/CPE element, see figure 4. The spectroscopic C plot (see figure S5) shows a high frequency plateau corresponding to capacitance in the  $pF\ cm^{-1}$  range from which dielectric constants of 48-64 were calculated (based on the permittivity of free space of  $8.854 \times 10^{-14}\ F\ cm^{-1}$ ). This corresponds to the data obtained from the equivalent circuit models and is the expected response for bulk oxide materials<sup>76, 107-109</sup>. The spike observed at low frequency relates to the Au electrode double layer, which blocks Li diffusion giving capacitive behaviour due to space-charge layers.

LTC materials sintered for 1h reached a maximum conductivity of  $0.4\ mS\ cm^{-1}$  at  $21^\circ C$  and  $1.1\ mS\ cm^{-1}$  at  $45.5^\circ C$ . Those sintered between the 15-60 minutes saw marginal changes in conductivity (the 5-minute membrane was too thin to be studied), see table 1. Beyond 1h density was similar, and conductivity degraded only slightly. Therefore, LTC is a garnet system that does not require specific handling requirements to form similarly performing membranes. Variable temperature measurements were also taken on pellets sintered for 1h, with the Arrhenius plots displayed in figure 5. These gave an activation energy of 0.34 eV over the temperature range of 19 – 64 °C.

Overall LTC is amongst the most conductive garnet system we have obtained within our laboratory and compares favourably to other reports of highly conducting systems elsewhere with similar densities and complex compositions<sup>82, 83, 86, 110, 111</sup>, but is easy to handle, quick to synthesise/densify and potentially scalable. This, therefore, indicates if this material were able to be synthesised and then sintered fully under Ar (with no intermediate air exposure), which would eliminate any surface  $Li_2CO_3$  as per work here<sup>37, 45</sup>, performance could potentially be further improved. However, if the large Li excess is facilitating high membrane porosity, hot pressing during heating may additionally be required for increased density. These approaches were, unfortunately, unable to be tested in the facilities available in our lab.



## Electrochemical testing

### Cyclic Voltammetry

To confirm the electrochemical stability window of the LTC materials, Au/LTC/Li cells were constructed and analysed via cyclic voltammetry (C.V.), see figure 6. LTC demonstrates an outstanding voltage stability of at least 10 V (vs Li/Li<sup>+</sup>) (the maximum voltage of the VMP3). A small peak is present at ~ 0.5 V, attributed to Au-Li alloying<sup>76</sup>. Outside of this the current response is flat, which indicates negligible redox activity and no indication of Ti<sup>4+</sup> reduction in the presence of Li metal. This is higher than previous reports, which indicate stability up to ~6V, further highlighting the potential of LTC materials for use in high voltage cells<sup>104, 112, 113</sup>. However, the large stripping and plating peaks could be masking dopant instabilities. This was assessed further by X-ray absorbance near edge spectroscopy (XANES), see later.



## Symmetrical Cell Testing

View Article Online  
DOI: 10.1039/D3YA00123G

To assess the critical current density (CCD), symmetrical Li/LTC/Li cells were assembled and analysed. CCD enables characterisation of the current density at which a soft or hard short circuit grows. A soft short circuit gives stable electronic pathways (for example along grain boundaries) that do not connect electrodes and, thus, a significant ionic current can still pass. This reduces cell resistance compared to the pristine sample. Comparatively, a hard short circuit connects electrodes and gives a large cell resistance drop to 0  $\Omega$  (although some small ohmic resistance would still be observed experimentally).

Low CCDs in lithium garnets have been reported to relate to the number of grain boundaries/larger grains/grain orientation<sup>114, 115</sup>, grain/grain boundary electrical properties<sup>45, 115-119</sup>, microstructure<sup>120, 121</sup> and grain boundary compositional differences (compared to the bulk)<sup>45, 117, 122-124</sup>. Whereas high density/low porosity<sup>42, 125, 126</sup>, low Li metal/garnet resistance<sup>45, 127-129</sup> and high ionic mobility (intrinsically linked with temperature)<sup>45, 130-132</sup> have been suggested to suppress dendrite growth.

Pristine cells were first analysed by IS to assess the Li/LTC area specific resistance (ASR). This gave values between 320-400  $\Omega \text{ cm}^2$ . This is similar to our prior reports on Ce doping, hence confirming the strategic use of Ce in low quantities to reduce interfacial resistance<sup>61</sup>. To confirm the correct assignment of the Li/Garnet interface in the impedance spectrum, Au sputtered pellets (used for conductivity) are overlaid in figure S9.

CCD measurements were then undertaken, whereupon LTC showed stable ohmic current–voltage behaviour up to 140  $\mu\text{A cm}^{-2}$ , with mostly flat voltage profiles but with some deviation from a square profile. This is attributed to non-uniform current distribution from imperfect interfacial contact between Li and the garnet, see figure 7a. However, a small voltage drop occurs at 140  $\mu\text{A cm}^{-2}$  followed by the onset of an erratic voltage profile, yet no clear/sharp voltage drop (as expected with a soft or a hard short circuit) is observed. This behaviour continued as the current density increased, see figure 7a. Therefore, LTC was cycled until 200  $\mu\text{A cm}^{-2}$  and analysed by IS. The impedance spectrum showed minimal changes to the LTC bulk and grain boundary contributions (compared to the pristine cell), see figure 7b. This suggests no short circuit nor any reversible short circuit behaviour, as reported elsewhere<sup>89</sup>. However, the low frequency Li/garnet interface region showed a reduced ASR from 380  $\Omega \text{ cm}^2$  (pristine cell) to 250  $\Omega \text{ cm}^2$ . As no short circuit was observed, CCD analysis was resumed until 300  $\mu\text{A cm}^{-2}$ . At this point the cell was analysed by IS again, whereupon no changes to the bulk/GB contributions were again observed, but ASR had further reduced to 161  $\Omega \text{ cm}^2$ . These data indicate cycling at certain current densities can initiate some form of a current induced ASR reduction in LTC (which could also account for the slightly decreased potential when cycling  $\geq 140 \mu\text{A cm}^{-2}$ ).





CCD measurements were then resumed until a large overpotential occurred (to the maximum tester voltage) at  $660 \mu\text{A cm}^{-2}$ . This automatically terminated the cell testing. Post CCD analysis by IS showed a large interfacial resistance ( $> 29\,000 \Omega \text{ cm}^2$ ), which indicates complete interfacial breakdown, see figure 7c. This could be dopant related and is discussed more later.

To assess if LTC was susceptible to the reversible short circuit behaviour previously reported by Ping *et al.*, and to confirm if this was a separate reaction from the observed ASR reduction at lower current densities, symmetrical LTC cells were assembled and cycled at  $500 \mu\text{A cm}^{-2}$ , see figure 8a. This value was chosen based upon the CCD results in figure 7a, as this is prior to complete cell degradation but is where the voltage profile becomes increasingly unstable. During the first  $500 \mu\text{A cm}^{-2}$  cycle, voltage initially increased before seeing a slow voltage drop, possibly indicative of short circuit behaviour. However, upon Immediate impedance analysis after one  $500 \mu\text{A cm}^{-2}$  cycle, no large resistance reduction was observed. This contrasts with the work from Ping *et al.*. However, the spectrum does potentially suggest short circuit propagation through the grain boundary, where some decreased resistance was observed, see figure 8b. This could indicate LTC had reversible short-circuit behaviour, but that the short circuit recovery process is more rapid compared to the Al-Ta doped LLZO analysed by Ping *et al.* (effectively removing Li dendrites before the IS measurements could be made). Therefore, IS was repeated continuously over the course of 1h and the cell gradually increased in resistance, recovering to the pristine cell value in 32 minutes. Within  $\approx 1\text{h}$  the impedance spectrum of the pellet stabilised with marginally increased resistance, particularly in the Li/Garnet interface region. This suggests similar short circuit reversal trends to those obtained by Ping *et al.* where the reversibility was ascribed to garnet cation reduction which, thus, oxidises Li and removes the short circuit<sup>89</sup>. However, the behaviour observed with LTC still appears to lack a clear indication of a soft or hard short circuit.

The  $500 \mu\text{A cm}^{-2}$  cell cycling was then restarted for 31 further cycles, see figure 9. The voltage profile initially mimicked the first cycle (further indicating LTC had chemically reacted with any Li dendrites), before again dropping to a consistent lower voltage. After 31 cycles, IS analysis was again conducted. Here, a short circuit in the expected manner (large reduction of the bulk/GB components) was observed, with repeated impedance showing only marginal recovery. However, after a 24hr rest the short circuit had been removed. This, therefore, confirms the reversible short circuit behaviour described by Ping *et al.* for Al, Ta-doped garnets.

However, the reversible short circuit in lithium symmetrical cells described by Ping *et al.* began at  $200 \mu\text{A cm}^{-2}$  and consistently had a noticeable reduction in the bulk/GB contributions within the impedance spectra after a single cycle. Here, at similar (and higher current densities), the CCD of LTC



showed an initial reduction in the ASR with no change in the bulk/GB contribution. Furthermore, direct cycling of pristine cells at  $500 \mu\text{A cm}^{-2}$  did not show a clear short circuit until >30 cycles (or dendrites were so rapidly removed after a single cycle that IS could not be captured). This, therefore, indicates the unusual electrochemical behaviour of LTC cannot be ascribed solely to the reversible short circuit behaviour described by Ping *et al.*. The dopants in LTC could be increasing the short circuit reversibility kinetics (which could be beneficial as an interlayer in a full solid state cell, where Li dendrites could be neutralised before cell failure). Therefore, to understand the dopant specific effects, the differences between garnet samples, with only Nb+Ce, or Nb+Ti dopants, were investigated further.

### Dopant Assessment

To assess the electrochemical properties (and the favourable synthesis/densification) of LTC, the Ti and Ce dopants were investigated individually. Firstly,  $\text{Li}_{6.5}\text{La}_3\text{Zr}_{1.25}\text{Nb}_{0.5}\text{Ti}_{0.25}\text{O}_{12}$  (LT) and  $\text{Li}_{6.5}\text{La}_3\text{Zr}_{1.25}\text{Nb}_{0.5}\text{Ce}_{0.25}\text{O}_{12}$  (LC) were synthesised and characterised as above, see figure S6 and S7. LT and LC were found to rapidly form phase pure powders as for LTC, but neither demonstrated the rapid densification properties of LTC; LT required four hours to form a dense pellet, whereas LC required at least two hours. Irrespective of heating regime, the relative density LT and LC were inferior to LTC, as was conductivity. This suggests both Ti and Ce are required for optimum sintering/densification and conductivity. This is further suggested by reports elsewhere where Ti or Ce was used singularly as cubic stabilising dopant, where long synthesis/densification times were required<sup>70, 86, 87, 110</sup>.

CCD testing of LT showed that the system did not have a low ASR value (observed value was 1000–2000  $\Omega \text{ cm}^2$ ), see figure S10. This is contradictory to other reports, which reported that Ti based systems enabled a low interfacial resistance. These works, however, employed heating of Li metal beyond  $180^\circ\text{C}$  to melt onto the interface in conditions where proton exchange could be more readily controlled<sup>110</sup>. This did not affect the CCD testing of LT in this work as, in all cases, irrespective of ASR, no clear CCD limit was observed. The voltage profile became non-square at  $280 \mu\text{A cm}^{-2}$ , but there was no voltage drop. The voltage continued to increase until the cell tester maximum voltage was reached, see figure S10. At the end, IS showed interfacial breakdown in LT cells. This breakdown relates to the lack of short circuit giving no easy path for higher currents. Therefore, interfacial void formation arises due to Li stripping at higher current densities, which degrades the interfacial contact between the Li and garnet. No indication of current induced ASR was found with LT.

LC gave an ASR of  $328 \Omega \text{ cm}^2$ , and was also examined to determine the CCD limit (see figure S11). LC obeyed ohmic current–voltage type behaviour up to  $120 \mu\text{A cm}^{-2}$ , whereupon a small voltage drop occurred, similar to LTC cells. Analysis *via* impedance spectroscopy after the  $260 \mu\text{A cm}^{-2}$  step showed no short circuit but an ASR reduction from  $328 \Omega \text{ cm}^2$  (pristine) to  $90 \Omega \text{ cm}^2$  was observed. At  $360 \mu\text{A}$



$\text{cm}^{-2}$  a clear short circuit was present (removal of the bulk/GB resistive component). This was further confirmed at  $600 \mu\text{A cm}^{-2}$ . Impedance analysis indicated the short circuit did not recover, with only marginal changes noted over similar timeframes, therefore LC was distinct from LTC. This is further confirmed by the absence of interfacial breakdown at higher current densities.

Considering the analysis on LC and LT, it can be confirmed that both Ce and Ti are required for the rapid synthesis/densification and improved conductivity (compared to the single dopants). Conversely, the reduction in ASR is related to the Ce dopant only. However, results suggest that the pairing of Ti and Ce is still required to prevent a hard short circuit at higher current densities and to enable enhanced short circuit reversibility, although the reasons behind this remain unclear.

Our previous work using Ce doped LLZO has shown a reduction in ASR in pristine symmetrical Li cells, with this attributed to the formation of interfacial  $\text{Ce}_4\text{O}_7$ <sup>61</sup>, although *in-situ* improvements to ASR were not assessed. Nonetheless, it is logical to conclude a similar reaction could be present with LTC, perhaps forming a mixed Ce-Ti-O phase. This is not demonstrated in the CV results, however, it could be hidden by the large Li stripping and plating peaks, see figure 6. Therefore, further analysis of oxidation states was undertaken by XANES on freshly prepared and cycled LTC pellets.

### X-ray absorption near edge structure

XANES does not show surface-based phenomena, however no proton-controlled environment was available to analyse the LTC interface by X-ray photoelectron spectroscopy. Nonetheless, powder was obtained from the interface and the bulk of the pellet to ascertain if any clear differences were present based upon proximity to Li metal.  $\text{Ti}_2\text{O}_3$ , anatase  $\text{TiO}_2$  and  $\text{CeO}_2$  references were used for comparison, see figure 10 and 11.

Data obtained from the Ti K edge in LTC suffered from severe interference from the strong La L3 absorption at 5491 eV, see figure 10. This suppressed the LTC Ti K edge peaks considerably, but a doublet is present at 4987 and 5001 eV across all LTC samples. These peaks are consistent in position and characteristics across the cycled and fresh LTC samples. This doublet corresponds more closely to the Ti K edge peak positions of the  $\text{TiO}_2$  reference. There is also a pre-edge peak in LTC at 4970 eV (absent in  $\text{Ti}_2\text{O}_3$ ), which is similar to reports elsewhere<sup>133-135</sup>. This suggests  $\text{Ti}^{4+}$  presence in LTC, but it is not conclusive due to the La interference and the difference in peak profiles arising from the comparison to anatase type  $\text{TiO}_2$ , see figure 10. However, if the XANES spectra are compared to  $\text{Ti}^{4+}$  orthosilicate garnets reported in the literature, such as schorlomite and andradite, LTC has similar peak profiles, positions and pre-edge characteristics<sup>136, 137</sup>. Irrespectively, the peaks at 4987 and 5001 eV can be identified as the region corresponding to Ti in the LTC samples. Here, it can be seen the Ti



peak positions and characteristics do not change between cycled and fresh LTC samples, which indicates no change of Ti during galvanostatic cycling.

Examination of the Ce L edges suffered slightly from La L2 edge interference, however absorption peaks for Ce are much clearer compared to Ti. These show the expected presence of  $\text{Ce}^{4+}$  within the freshly sintered materials, with a peak doublet at 5731 and 5736 eV. This corresponds to the  $\text{CeO}_2$  reference at 5730 and 5737 eV. However, post cycled pellets lacked these peaks, with a singular peak appearing at 5726 eV. This shift to lower energy indicates reduction of  $\text{Ce}^{4+}$  to a 3+ state. No  $\text{Ce}^{3+}$  reference was available to test, however,  $\text{Ce}^{3+}$  reports elsewhere, with compounds such as  $\text{CeF}_3$  and  $\text{Ce}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$ , also show a sharp singular peak in this region that is assigned to a trivalent Ce species<sup>138-141</sup>. Therefore, this suggests that Ce is being reduced during Li stripping and plating beyond a surface reaction, penetrating into the bulk and throughout the pellet. This confirms the previous work by Dong *et al.*, whereupon Ce reduction was suggested to occur in  $\text{Li}_7\text{La}_3\text{Zr}_{2-x}\text{Ce}_x\text{O}_{12}$  materials<sup>61</sup>.

The XANES data, therefore, supports the reduction of Ce in the garnet structure during cycling, with experimental evidence also confirming the ASR reduction during CCD analysis requires Ce. Therefore, as Ce is reduced from  $\text{Ce}^{4+}$  to  $\text{Ce}^{3+}$ , a corresponding oxidation to Li metal is likely occurring which neutralises dendrite formation at the Li/garnet interface, which fills voids and reduces the interfacial resistance. However, once the current density reaches a critical point, dendrites will then start to penetrate the pellet. However, the Ce reduction could aid in the recovery process through the bulk/GB and remove dendrites more rapidly than non-Ce doped garnets. This could account for the lack of clear short circuit after cycling pellets at  $500 \mu\text{A cm}^{-2}$ , however the full electrochemical effects of the Ce dopant require further study.

It would appear that that Ti is required to prevent a hard short circuit forming, which then enables interfacial breakdown at high current densities. Therefore, the data suggests that Ti and Ce are both required to give reduced ASR, for low interfacial resistance, and to improve the ability of the lithium garnet to reverse a short circuit during symmetrical cell cycling. However, further studies are needed to confirm the exact mechanisms, for example by *in-situ* symmetrical cycling using SEM and Li sensitive EDS. In particular, a cross section studied during Li dendrite growth would be valuable so that morphological and chemical changes could be monitored once cycling has stopped, and the cell is at rest. This however, is not currently available for our SEM facility.



## Conclusions

In summary, a new co-doped Ti/Ce garnet material ( $\text{Li}_{6.5}\text{La}_3\text{Zr}_1\text{Nb}_{0.5}\text{Ce}_{0.25}\text{Ti}_{0.25}\text{O}_{12}$  (LTC)) has been synthesised, and rapidly densified in a single step. LTC demonstrated easy synthesis, requiring only 15 – 60 minutes to form dense membranes directly from the starting materials, although > 45 mins was required for increased phase purity. If only the powder is required, a similarly rapid synthesis can be achieved at 950°C. It is also suggested that much faster heating rates could be employed, yielding more rapid synthesis, allowing the potential for further synthesis scale up into a continuous process. LTC was shown to be somewhat more robust than comparable singly doped garnets, as overall performance does not require specific handling, for example heating rate and/or heating times past 1h yielded similar results. Such absence of specificity gives the potential for LTC ideal to be used within a commercial environment. We have also demonstrated that single use of Ce or Ti in these garnets does not generate the same properties, and it is the combination of both which enables the ease of handling in LTC

It was also shown that LTC presents somewhat unusual Li dendrite resistance properties during symmetrical cell cycling. Here, medium current densities were shown to initiate an ASR reduction but did not show any reversible short circuit behaviour (under similar cycling regimes), as reported in other work. This is suggested to relate to the reduction of  $\text{Ce}^{4+}$  to  $\text{Ce}^{3+}$ , as confirmed by the XANES data. However, it was also experimentally shown that Ti is required to prevent hard short circuits from which the cell cannot easily recover from, therefore indicating the pairing of Ce and Ti has enabled increased dendrite reversibility kinetics compared to the singular dopants.

This report was primarily aimed at showing a high entropy garnet system which could be formed rapidly using only conventional muffle furnace sintering. However, the as complexity in garnet compositions increase, and interest in highly entropic materials progresses, so does the complexity of the electrochemistry of cell operation. In particular, the effect of the Ti dopant on lithium dendrites requires further work to understand, as does the influence of Ce. Therefore, more work is required to understand the LTC materials such as Li sensitive EDS or by further analysis *via* surface sensitive techniques (such as XPS). This would require facilities which can transfer samples under vacuum to avoid proton exchange and to allow assessment of the chemomechanical phenomena.

## Conflicts of interest

There are no conflicts of interest to declare.



## Acknowledgements

View Article Online  
DOI: 10.1039/D3YA00123G

We would like to thank the University of Birmingham for the studentship funding of Mark Stockham and Matthew James, and the EPSRC for funding the GENESIS project (under EP/ R024006/1) and the EPSRC Capital Award for Core Equipment (EP/T02349X/1). This work is supported by the Faraday Institution funded Nextrode (FIRG015) and CATMAT (FIRG016) Projects. We thank the Diamond Light Source for the award of beam time as part of the Energy Materials Block Allocation Group SP14239.



Figures

View Article Online  
DOI: 10.1039/D3YA00123G

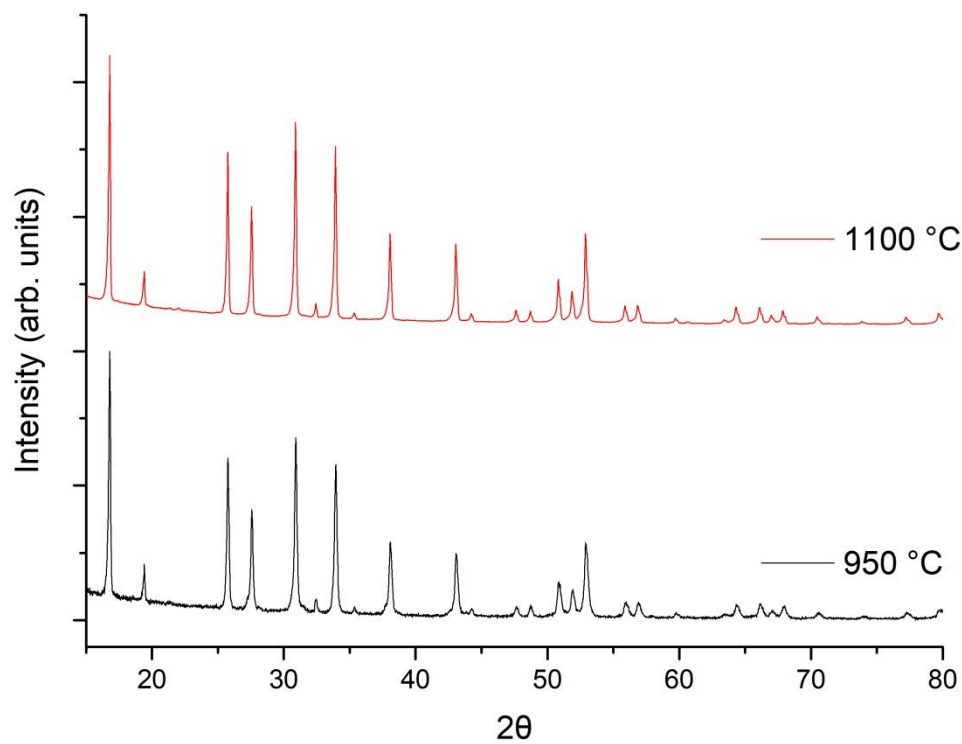


Figure 1. XRD patterns of LTC sintered in powder form (950°C, 100°C min<sup>-1</sup>) and as a pellet (1100°C, 40°C min<sup>-1</sup>). Both samples were sintered for 1h and demonstrate pure garnet (*Ia $\bar{3}d$* ) type symmetry. In both cases heating rates were the maximum available for the furnace model.



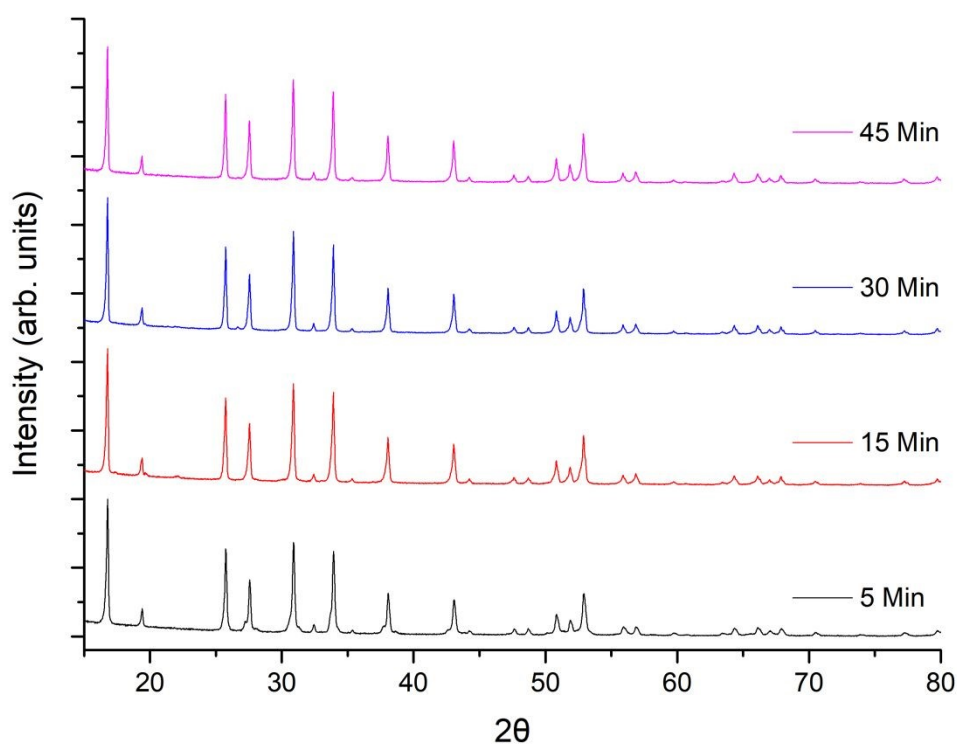


Figure 2. XRD patterns of LTC sintered pellet form at 1100°C for different time intervals. All patterns demonstrate garnet type symmetry but sharp, crystalline, peaks only appear  $\geq 15$  minutes.





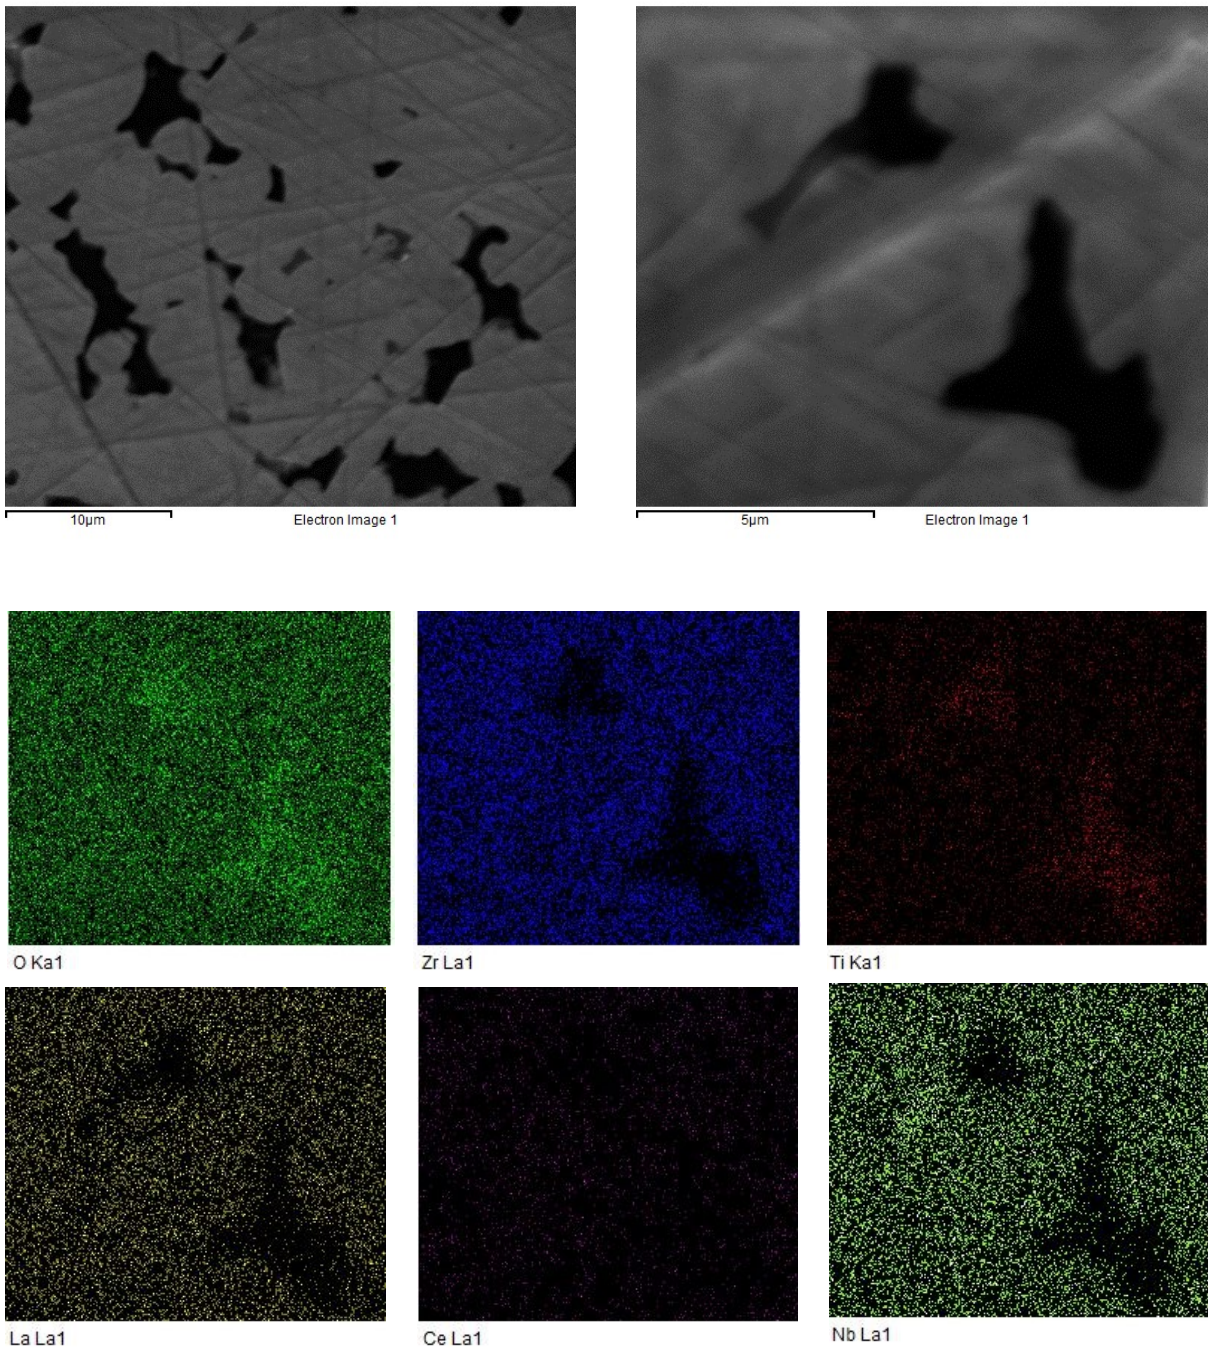


Figure 3. SEM images of polished pellet surface at two different magnification levels showing a dense pellet microstructure with no visible grain boundaries, however some voids are present. EDX is also shown, demonstrating concentrated areas of Ti in the pores.



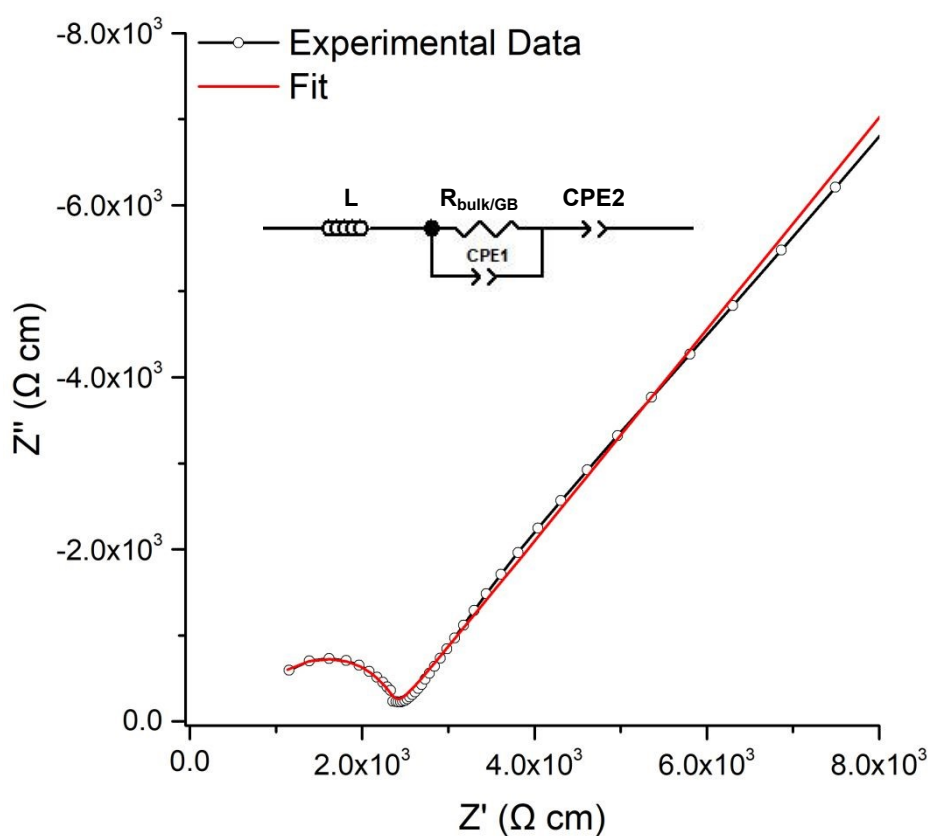


Figure 4. Typical Nyquist impedance plot of LTC, which was fit to the equivalent circuit in the top left.

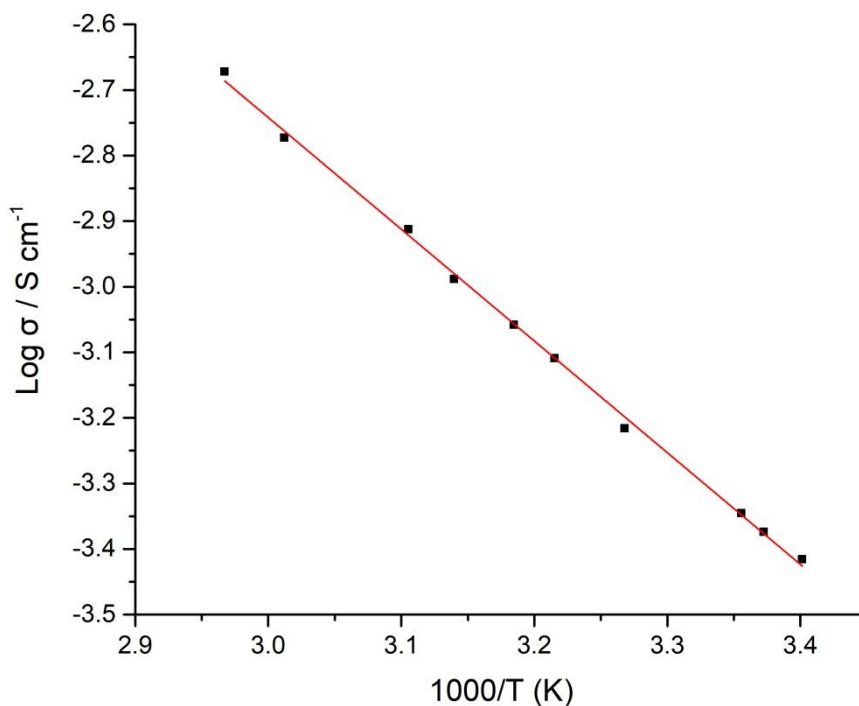


Figure 5. Arrhenius plot of LTC over the temperature range of 19 – 64 °C (activation energy = 0.34 eV).





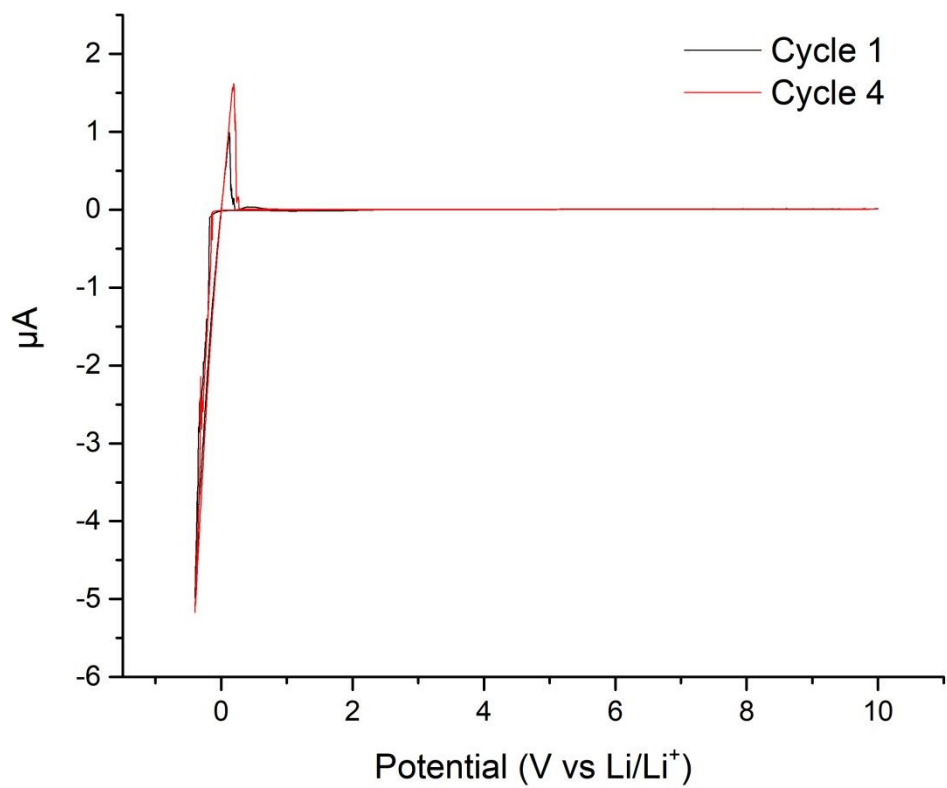


Figure 6. Cyclic voltammetry of LTC at room temperature using an Au/LTC/Li cell.

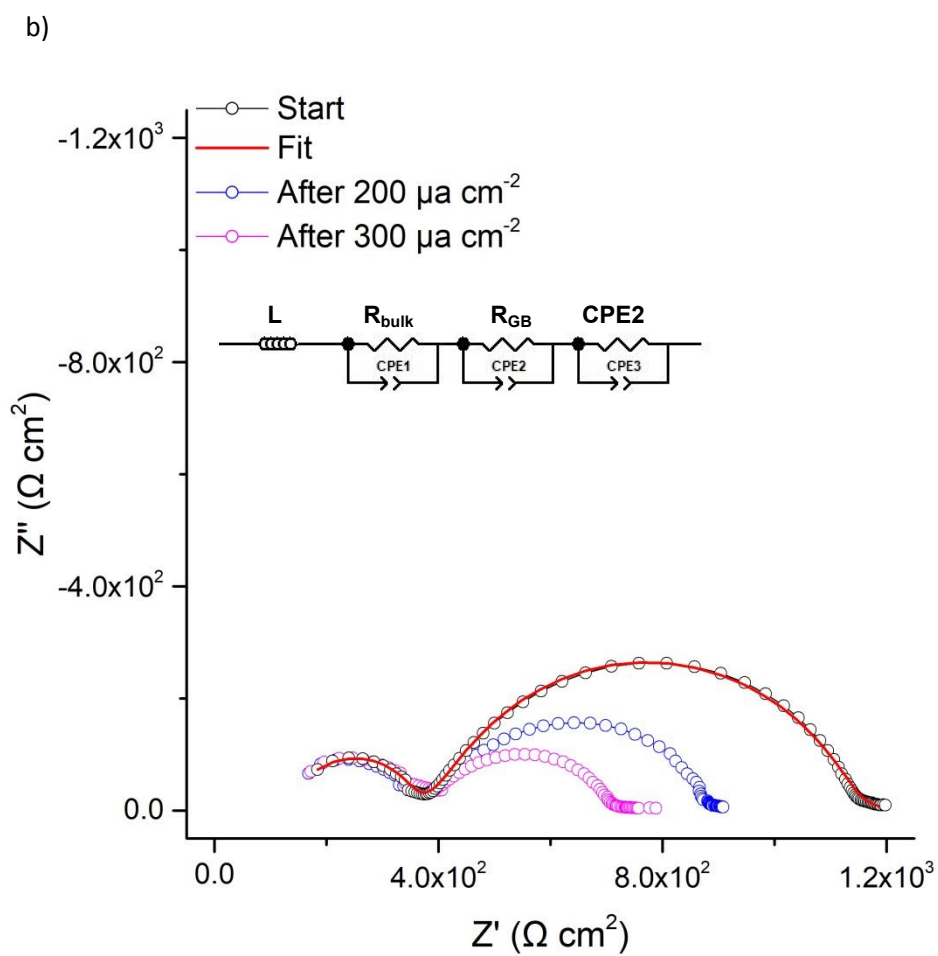

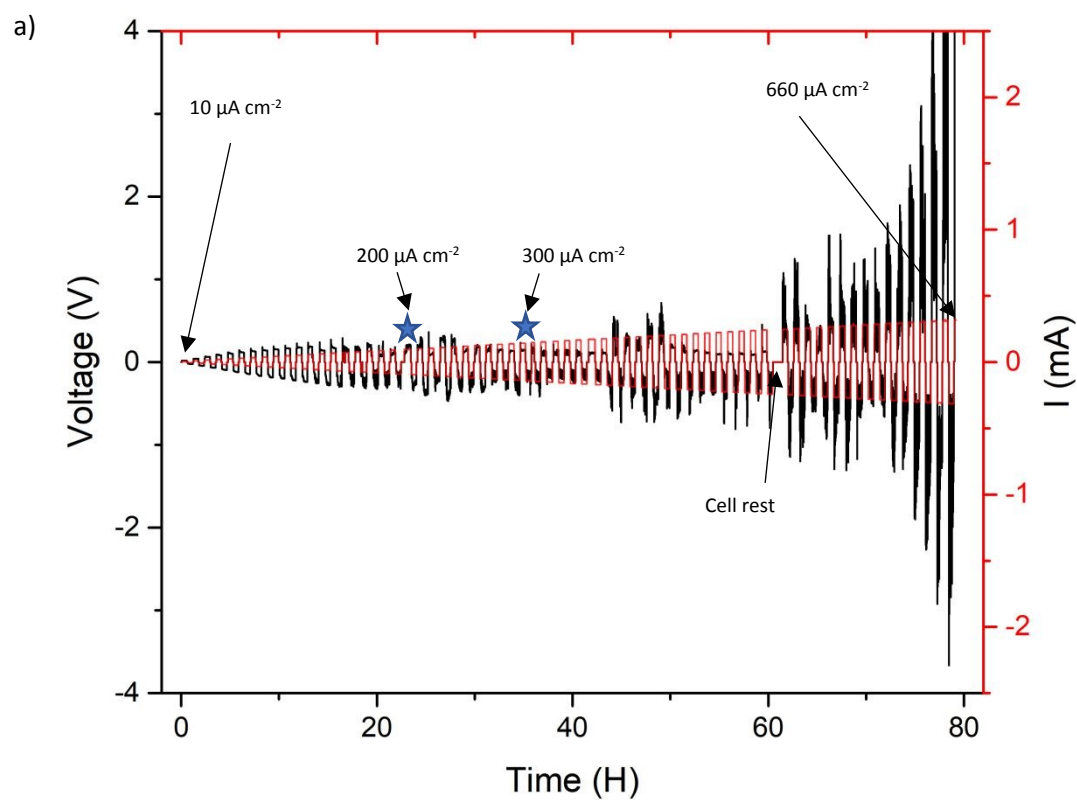

c)

View Article Online  
DOI: 10.1039/D3YA00123G

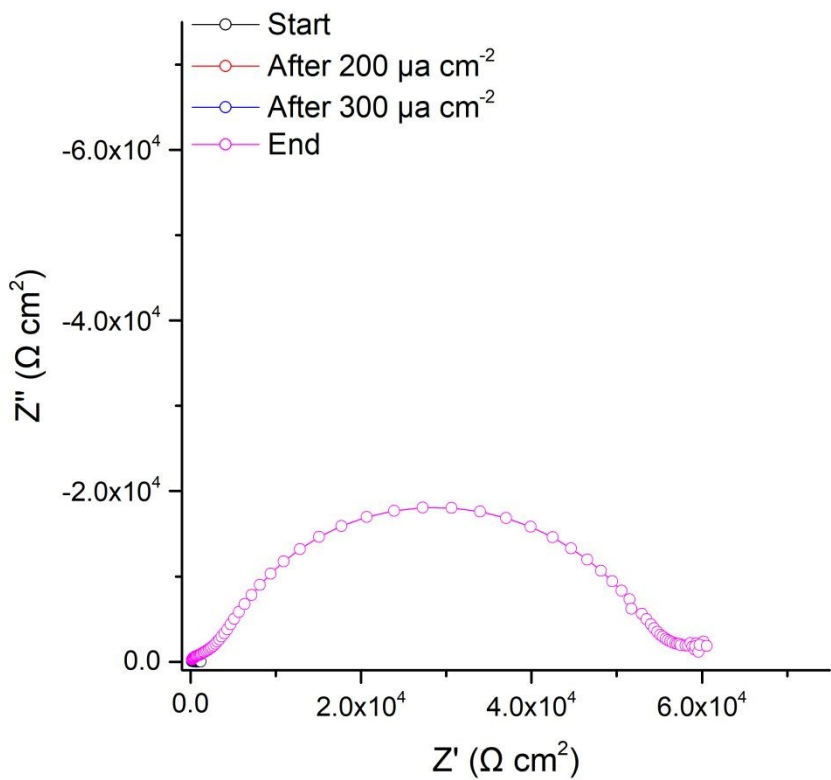


Figure 7. Symmetry cell impedance spectra and CCD measurements where a) is the CCD data measured in increments of  $10 \mu\text{A cm}^{-2}$ , stars indicate where cell was stopped for impedance analysis. b) is the overlaid impedance spectrums during the CCD testing at different current densities at room temperature and c) the same as figure 7b but with final impedance spectrum showing interfacial degradation upon cell failure (additional long term cycling, at differing current densities, is available in figure S8.)







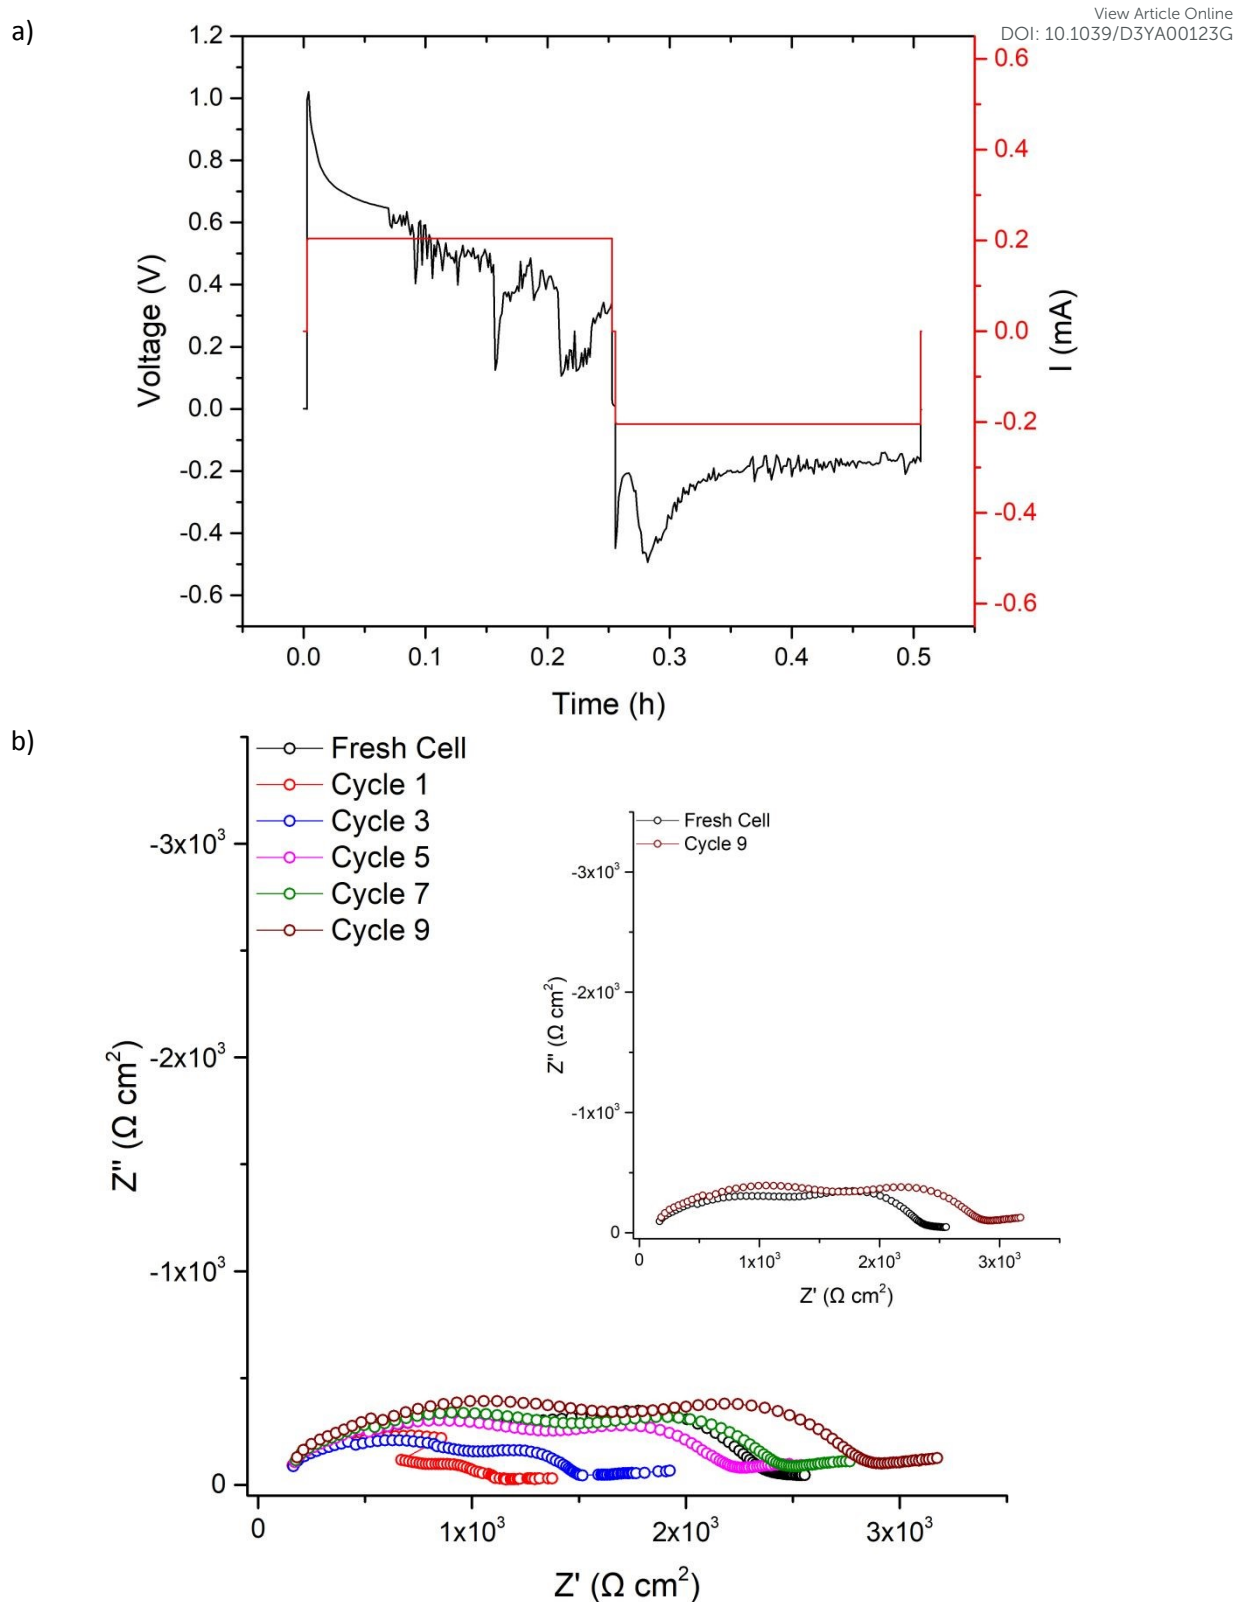



Figure 8. Results for the LTC cell was cycled at  $500 \mu\text{A cm}^{-2}$  for a) one cycle with the corresponding impedance analysis in b). Cycle 1 was taken 2 minutes after, as sample needed to be transported to the Solartron impedance analyser to collect data. Time difference between subsequent impedance cycles is 3 minutes, which is the length of each scan. Time difference between cycle 7 and 9 is 90 minutes.



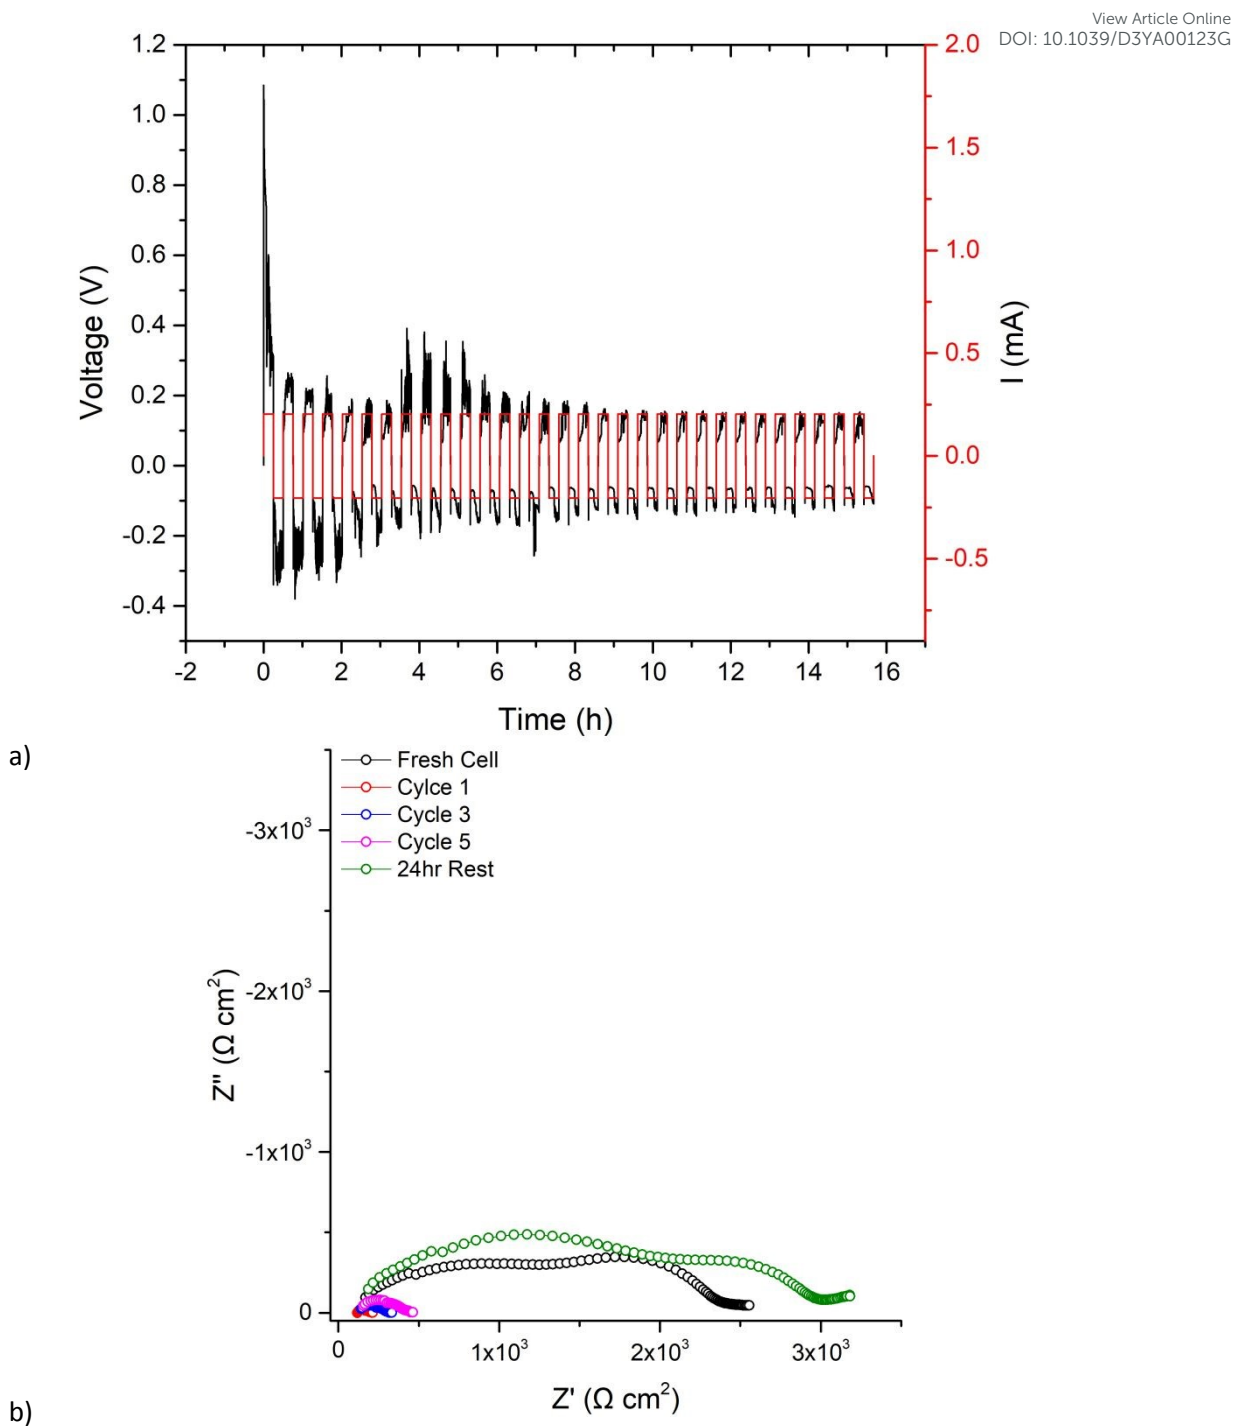

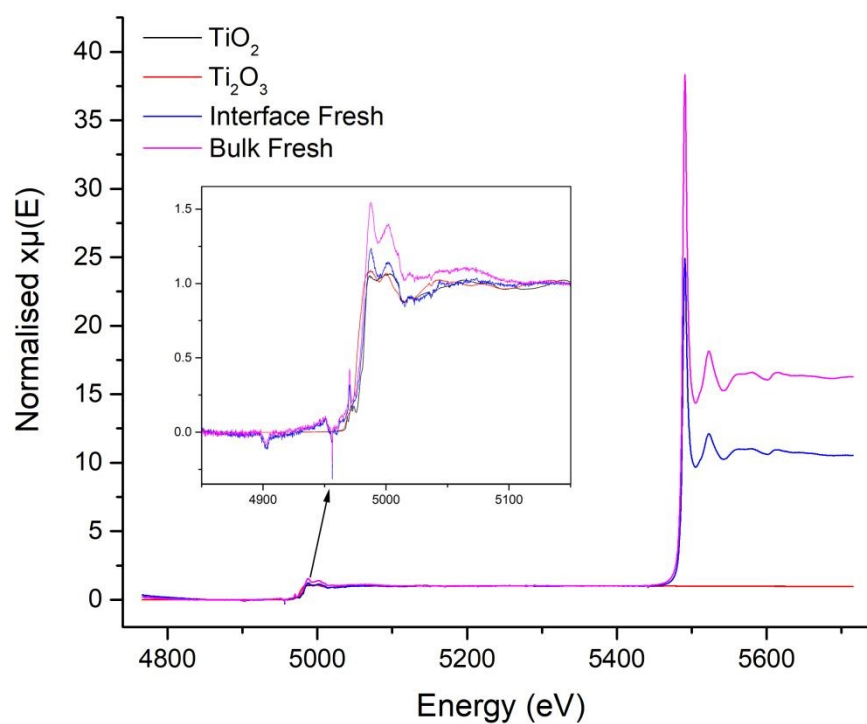


a)

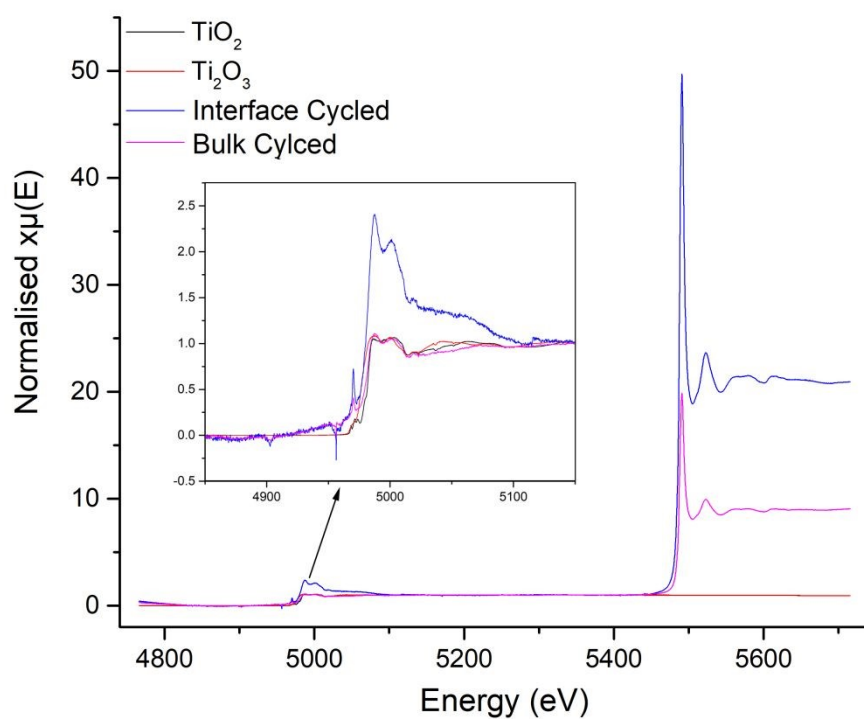


b)





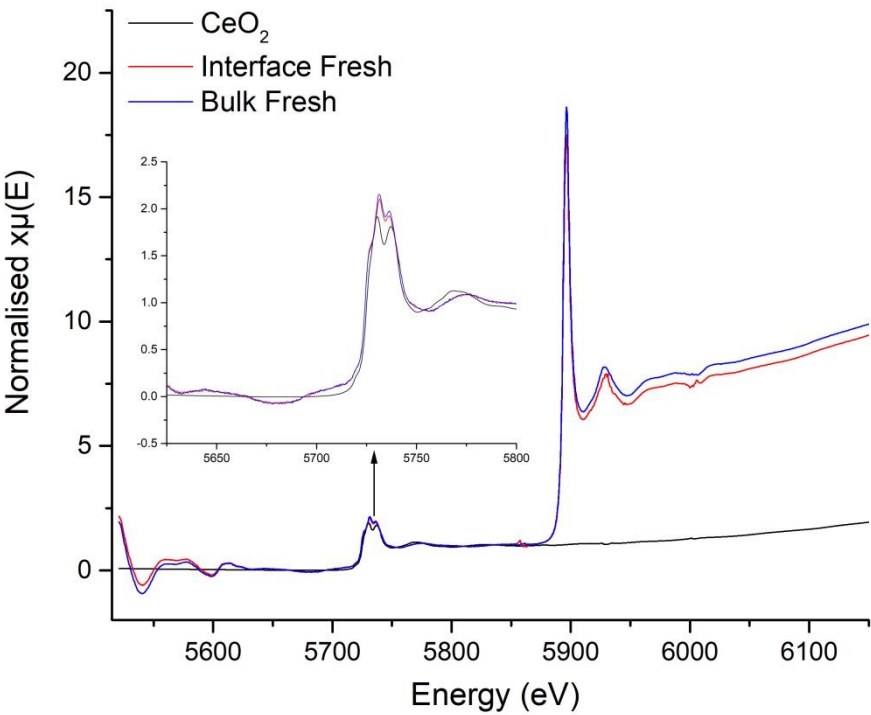

a)

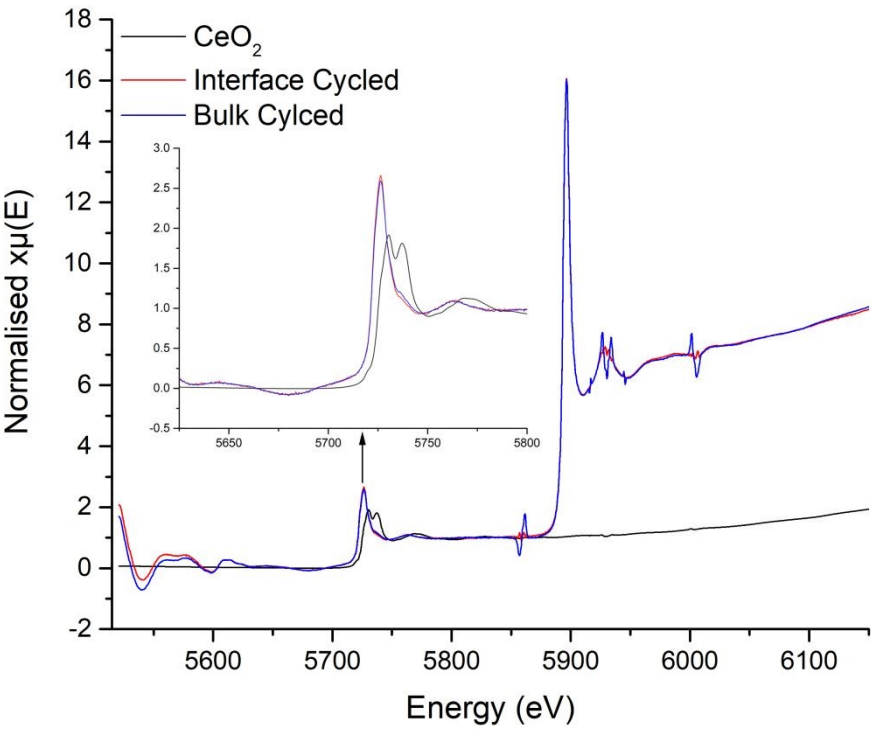

b)



## References

1. J. M. Tarascon and M. Armand, *Nature*, 2001, **414**, 359.
2. M. Armand and J. M. Tarascon, *Nature*, 2008, **451**, 652.
3. C.-X. Zu and H. Li, *Energy & Environmental Science*, 2011, **4**, 2614-2624.
4. M. Park, X. Zhang, M. Chung, G. B. Less and A. M. Sastry, *Journal of Power Sources*, 2010, **195**, 7904-7929.
5. V. Thangadurai and W. Weppner, *Ionics*, 2006, **12**, 81-92.
6. H. Yang, C. Guo, A. Naveed, J. Lei, J. Yang, Y. Nuli and J. Wang, *Energy Storage Materials*, 2018, **14**, 199-221.
7. C. Yang, K. Fu, Y. Zhang, E. Hitz and L. Hu, *Advanced Materials*, 2017, **29**, 1701169.
8. T. Kim, W. Song, D.-Y. Son, L. K. Ono and Y. Qi, *Journal of Materials Chemistry A*, 2019, **7**, 2942-2964.
9. B. Scrosati, J. Hassoun and Y. Sun, *Lithium-ion batteries. A look into the future*, 2011.
10. W. Xu, J. Wang, F. Ding, X. Chen, E. Nasybulin, Y. Zhang and J.-G. Zhang, *Energy & Environmental Science*, 2014, **7**, 513-537.
11. A. Väyrynen and J. Salminen, *The Journal of Chemical Thermodynamics*, 2012, **46**, 80-85.
12. C. Julien, A. Mauger, A. Vijn and K. Zaghib, *Lithium Batteries: Science and Technology*, Springer International Publishing, 2015.
13. J. B. Goodenough and K.-S. Park, *Journal of the American Chemical Society*, 2013, **135**, 1167-1176.
14. N. Nitta, F. Wu, J. T. Lee and G. Yushin, *Materials Today*, 2015, **18**, 252-264.
15. A. Lewandowski and A. Świdorska-Mocek, *Journal of Power Sources*, 2009, **194**, 601-609.
16. H. Wu, D. Zhuo, D. Kong and Y. Cui, *Nature Communications*, 2014, **5**, 5193.
17. Y. Kato, S. Hori, T. Saito, K. Suzuki, M. Hirayama, A. Mitsui, M. Yonemura, H. Iba and R. Kanno, *Nature Energy*, 2016, **1**, 16030.
18. V. A. Agubra and J. W. Fergus, *Journal of Power Sources*, 2014, **268**, 153-162.
19. L. Wang, Z. Zhou, X. Yan, F. Hou, L. Wen, W. Luo, J. Liang and S. X. Dou, *Energy Storage Materials*, 2018, **14**, 22-48.
20. V. Etacheri, R. Marom, R. Elazari, G. Salitra and D. Aurbach, *Energy & Environmental Science*, 2011, **4**, 3243-3262.
21. X. Shen, H. Liu, X.-B. Cheng, C. Yan and J.-Q. Huang, *Energy Storage Materials*, 2018, **12**, 161-175.
22. H. Duan, H. Zheng, Y. Zhou, B. Xu and H. Liu, *Solid State Ion.*, 2018, **318**, 45-53.
23. J. Li, C. Ma, M. Chi, C. Liang and N. J. Dudney, *Advanced Energy Materials*, 2015, **5**, 1401408.
24. F. Zheng, M. Kotobuki, S. Song, M. O. Lai and L. Lu, *Journal of Power Sources*, 2018, **389**, 198-213.
25. Y. Zheng, Y. Yao, J. Ou, M. Li, D. Luo, H. Dou, Z. Li, K. Amine, A. Yu and Z. Chen, *Chemical Society Reviews*, 2020, **49**, 8790-8839.
26. J. Fang Wu, Z. Zou, B. Pu, L. Ladenstein, S. Lin, W. Xie, S. Li, B. He, Y. Fan, W. K. Pang, H. M. R. Wilkening, X. Guo, C. Xu, T. Zhang, S. Shi and J. Liu, *Advanced Materials*, 2023, **n/a**, 2303730.
27. U. Roy, N. A. Fleck and V. S. Deshpande, *Extreme Mechanics Letters*, 2021, **46**, 101307.
28. J. A. Lewis, F. J. Q. Cortes, Y. Liu, J. C. Miers, A. Verma, B. S. Vishnugopi, J. Tippens, D. Prakash, T. S. Marchese, S. Y. Han, C. Lee, P. P. Shetty, H.-W. Lee, P. Shevchenko, F. De Carlo, C. Saldana, P. P. Mukherjee and M. T. McDowell, *Nature Materials*, 2021, **20**, 503-510.
29. J. G. Kim, B. Son, S. Mukherjee, N. Schuppert, A. Bates, O. Kwon, M. J. Choi, H. Y. Chung and S. Park, *Journal of Power Sources*, 2015, **282**, 299-322.
30. W. Luo, Y. Gong, Y. Zhu, Y. Li, Y. Yao, Y. Zhang, K. Fu, G. Pastel, C.-F. Lin, Y. Mo, E. D. Wachsman and L. Hu, *Advanced Materials*, 2017, **29**, 1606042.
31. L. Cheng, C. H. Wu, A. Jarry, W. Chen, Y. Ye, J. Zhu, R. Kostecki, K. Persson, J. Guo, M. Salmeron, G. Chen and M. Doeff, *ACS Appl. Mater. Interfaces*, 2015, **7**, 17649-17655.



32. R. Sudo, Y. Nakata, K. Ishiguro, M. Matsui, A. Hirano, Y. Takeda, O. Yamamoto and N. Imanishi, *Solid State Ion.*, 2014, **262**, 151-154.
33. B. Chen, C. Xu and J. Zhou, *J. Electrochem. Soc.*, 2018, **165**, A3946-A3951.
34. Y. Zhu, X. He and Y. Mo, *Journal of Materials Chemistry A*, 2016, **4**, 3253-3266.
35. G. L. Gregory, H. Gao, B. Liu, X. Gao, G. J. Rees, M. Pasta, P. G. Bruce and C. K. Williams, *Journal of the American Chemical Society*, 2022, **144**, 17477-17486.
36. T. Wu, W. Dai, M. Ke, Q. Huang and L. Lu, *Advanced Science*, 2021, **8**, 2100774.
37. C. Bernuy-Lopez, W. Manalastas, J. M. Lopez del Amo, A. Aguadero, F. Aguesse and J. A. Kilner, *Chemistry of Materials*, 2014, **26**, 3610-3617.
38. X. Huang, T. Xiu, M. E. Badding and Z. Wen, *Ceramics International*, 2018, **44**, 5660-5667.
39. T. Thompson, J. Wolfenstine, J. L. Allen, M. Johannes, A. Huq, I. N. David and J. Sakamoto, *Journal of Materials Chemistry A*, 2014, **2**, 13431-13436.
40. A. Ramzy and V. Thangadurai, *ACS Appl. Mater. Interfaces*, 2010, **2**, 385-390.
41. S. Hu, Y.-F. Li, R. Yang, Z. Yang and L. Wang, *Ceramics International*, 2018, **44**, 6614-6618.
42. Y. Ren, Y. Shen, Y. Lin and C.-W. Nan, *Electrochemistry Communications*, 2015, **57**, 27-30.
43. F. Flatscher, M. Philipp, S. Ganschow, H. M. R. Wilkening and D. Rettenwander, *Journal of Materials Chemistry A*, 2020, **8**, 15782-15788.
44. R. H. Brugge, F. M. Pesci, A. Cavallaro, C. Sole, M. A. Isaacs, G. Kerherve, R. S. Weatherup and A. Aguadero, *Journal of Materials Chemistry A*, 2020, **8**, 14265-14276.
45. Federico M. Pesci, R. H. Brugge, A. K. O. Hekselman, A. Cavallaro, R. J. Chater and A. Aguadero, *Journal of Materials Chemistry A*, 2018, **6**, 19817-19827.
46. W. Chang, R. May, M. Wang, G. Thorsteinsson, J. Sakamoto, L. Marbella and D. Steingart, *Nature Communications*, 2021, **12**, 6369.
47. X. Zhang, Q. Xiang, S. Tang, A. Wang, X. Liu and J. Luo, *Nano Letters*, 2020, **20**, 2871-2878.
48. H. Yan, K. Tantratian, K. Ellwood, E. T. Harrison, M. Nichols, X. Cui and L. Chen, *Advanced Energy Materials*, 2021, **n/a**, 2102283.
49. H. Zheng, G. Li, J. Liu, S. Wu, X. Zhang, Y. Wu, H. Zhu, X. Huang, H. Liu and H. Duan, *Energy Storage Materials*, 2022, **49**, 278-290.
50. A. F. Wells, *Structural inorganic chemistry*, Clarendon Press, 1984.
51. V. Thangadurai, S. Adams and W. Weppner, *Chemistry of Materials*, 2004, **16**, 2998-3006.
52. E. J. Cussen and T. W. S. Yip, *Journal of Solid State Chemistry*, 2007, **180**, 1832-1839.
53. E. J. Cussen, *Chemical Communications*, 2006, DOI: 10.1039/B514640B, 412-413.
54. M. P. O'Callaghan, D. R. Lynham, E. J. Cussen and G. Z. Chen, *Chemistry of Materials*, 2006, **18**, 4681-4689.
55. V. Thangadurai, H. Kaack and W. J. F. Weppner, *Journal of the American Ceramic Society*, 2004, **86**, 437-440.
56. R. Murugan, V. Thangadurai and W. Weppner, *Angewandte Chemie International Edition*, 2007, **46**, 7778-7781.
57. C. A. Geiger, E. Alekseev, B. Lazic, M. Fisch, T. Armbruster, R. Langner, M. Fechtelkord, N. Kim, T. Pettke and W. Weppner, *Inorganic Chemistry*, 2011, **50**, 1089-1097.
58. J. Awaka, N. Kijima, K. Kataoka, H. Hayakawa, K.-i. Ohshima and J. Akimoto, *Journal of Solid State Chemistry*, 2010, **183**, 180-185.
59. J. Awaka, N. Kijima, H. Hayakawa and J. Akimoto, *Journal of Solid State Chemistry*, 2009, **182**, 2046-2052.
60. J. Percival, E. Kendrick, R. I. Smith and P. R. Slater, *Dalton Transactions*, 2009, DOI: 10.1039/b907331k, 5177-5181.
61. B. Dong, S. R. Yeandel, P. Goddard and P. R. Slater, *Chemistry of Materials*, 2020, **32**, 215-223.
62. R. Wagner, G. J. Redhammer, D. Rettenwander, A. Senyshyn, W. Schmidt, M. Wilkening and G. Amthauer, *Chemistry of Materials*, 2016, **28**, 1861-1871.
63. J. Percival and P. R. Slater, *Solid State Communications*, 2007, **142**, 355-357.
64. K. Kataoka and J. Akimoto, *Inorganic Chemistry*, 2020, **59**, 14376-14381.

View Article Online  
DOI: 10.1039/D3YA00123G



65. R. Murugan, V. Thangadurai and W. Weppner, *Applied Physics A*, 2008, **91**, 615-620.
66. M. A. Howard, O. Clemens, E. Kendrick, K. S. Knight, D. C. Apperley, P. A. Anderson and P. R. Slater, *Dalton transactions (Cambridge, England : 2003)*, 2012, **41**, 12048-12053.
67. J. L. Allen, J. Wolfenstine, E. Rangasamy and J. Sakamoto, *Journal of Power Sources*, 2012, **206**, 315-319.
68. B. Dong, L. L. Driscoll, M. P. Stockham, E. Kendrick and P. R. Slater, *Solid State Ion.*, 2020, **350**, 115317.
69. M. P. Stockham, B. Dong, M. S. James, Y. Li, Y. Ding and P. R. Slater, *Dalton Transactions*, 2021, **50**, 2364-2374.
70. B. Dong, M. P. Stockham, P. A. Chater and P. R. Slater, *Dalton Transactions*, 2020, **49**, 11727-11735.
71. M. A. Howard, O. Clemens, E. Kendrick, K. S. Knight, D. C. Apperley, P. A. Anderson and P. R. Slater, *Dalton Transactions*, 2012, **41**, 12048-12053.
72. S. Narayanan and V. Thangadurai, *Journal of Power Sources*, 2011, **196**, 8085-8090.
73. S. Narayanan, F. Ramezanipour and V. Thangadurai, *J. Phys. Chem. C*, 2012, **116**, 20154-20162.
74. M. Botros, R. Djenadic, O. Clemens, M. Möller and H. Hahn, *Journal of Power Sources*, 2016, **309**, 108-115.
75. J.-F. Wu, E.-Y. Chen, Y. Yu, L. Liu, Y. Wu, W. K. Pang, V. K. Peterson and X. Guo, *ACS Appl. Mater. Interfaces*, 2017, **9**, 1542-1552.
76. R. H. Brugge, J. A. Kilner and A. Aguadero, *Solid State Ion.*, 2019, **337**, 154-160.
77. X. Wang, J. Liu, R. Yin, Y. Xu, Y. Cui, L. Zhao and X. Yu, *Materials Letters*, 2018, **231**, 43-46.
78. J. Gai, E. Zhao, F. Ma, D. Sun, X. Ma, Y. Jin, Q. Wu and Y. Cui, *Journal of the European Ceramic Society*, 2018, **38**, 1673-1678.
79. R. Murugan, N. Janani, D. C and D. L, *Influence of Sintering Additives on Densification and Li+ Conductivity of Al Doped Li7La3Zr2O12 Lithium Garnet*, 2014.
80. V. Thangadurai and W. Weppner, *Journal of the American Ceramic Society*, 2005, **88**, 411-418.
81. M. P. Stockham, B. Dong and P. R. Slater, *Journal of Solid State Chemistry*, 2022, **308**, 122944.
82. S.-K. Jung, H. Gwon, H. Kim, G. Yoon, D. Shin, J. Hong, C. Jung and J.-S. Kim, *Nature Communications*, 2022, **13**, 7638.
83. C.-H. Kuo, A.-Y. Wang, H.-Y. Liu, S.-C. Huang, X.-R. Chen, C.-C. Chi, Y.-C. Chang, M.-Y. Lu and H.-Y. Chen, *APL Materials*, 2022, **10**, 121104.
84. Y. Zhang, F. Chen, J. Li, L. Zhang, J. Gu, D. Zhang, K. Saito, Q. Guo, P. Luo and S. Dong, *Electrochimica Acta*, 2018, **261**, 137-142.
85. C. Shao, Z. Yu, H. Liu, Z. Zheng, N. Sun and C. Diao, *Electrochimica Acta*, 2017, **225**, 345-349.
86. J. Gao, J. Zhu, X. Li, J. Li, X. Guo, H. Li and W. Zhou, *Advanced Functional Materials*, 2021, **31**, 2001918.
87. Z. Xu, X. Hu, B. Fu, K. Khan, J. Wu, T. Li, H. Zhou, Z. Fang and M. Wu, *Journal of Materiomics*, 2023, DOI: <https://doi.org/10.1016/j.jmat.2023.01.007>.
88. S. Saran, Y. R. Eker, Ş. Ateş, G. Çelik, H. Baveghar, O. M. Özkendir, Ü. Atav and W. Klysubun, *Advances in Applied Ceramics*, 2023, DOI: 10.1080/17436753.2023.2167680, 1-9.
89. W. Ping, C. Wang, Z. Lin, E. Hitz, C. Yang, H. Wang and L. Hu, *Advanced Energy Materials*, 2020, **10**, 2000702.
90. R. H. Brugge, A. K. O. Hekselman, A. Cavallaro, F. M. Pesci, R. J. Chater, J. A. Kilner and A. Aguadero, *Chemistry of Materials*, 2018, **30**, 3704-3713.
91. G. Larraz, A. Orera and M. L. Sanjuán, *Journal of Materials Chemistry A*, 2013, **1**, 11419-11428.
92. C. Galven, J. Dittmer, E. Suard, F. Le Berre and M.-P. Crosnier-Lopez, *Chemistry of Materials*, 2012, **24**, 3335-3345.
93. M. A. Howard, O. Clemens, K. S. Knight, P. A. Anderson, S. Hafiz, P. M. Panchmatia and P. R. Slater, *Journal of Materials Chemistry A*, 2013, **1**, 14013-14022.
94. M. A. Howard, O. Clemens, A. S. Parvathy, P. A. Anderson and P. R. Slater, *Journal of Alloys and Compounds*, 2016, **670**, 78-84.

View Article Online  
DOI: 10.1039/D3YA00123G



95. J. Percival, D. Apperley and P. R. Slater, *Solid State Ion.*, 2008, **179**, 1693-1696.
96. H. Peng, Y. Zhang, L. Li and L. Feng, *Solid State Ion.*, 2017, **304**, 71-74.
97. B. Toby and R. Dreele, *Journal of Applied Crystallography*, 2013, **46**, 544-549.
98. K. Momma and F. Izumi, *Journal of Applied Crystallography*, 2011, **44**, 1272-1276.
99. M. P. Stockham, B. Dong, M. S. James, Y. Li, Y. Ding, E. Kendrick and P. Slater, *Dalton Transactions*, 2021, DOI: 10.1039/D1DT02474D.
100. R. Wagner, G. J. Redhammer, D. Rettenwander, G. Tippelt, A. Welzl, S. Taibl, J. Fleig, A. Franz, W. Lottermoser and G. Amthauer, *Chemistry of Materials*, 2016, **28**, 5943-5951.
101. N. Hamao, K. Kataoka and J. Akimoto, *Li-ion conductivity and crystal structure of garnet-type  $\text{Li}_{6.5}\text{La}_3\text{M}_{1.5}\text{Ta}_{0.5}\text{O}_{12}$  ( $\text{M} = \text{Hf}, \text{Sn}$ ) oxides*, 2017.
102. M. P. Stockham, B. Dong, Y. Ding, Y. Li and P. R. Slater, *Dalton Transactions*, 2020, DOI: 10.1039/D0DT01497D.
103. Y.-T. Chen, A. Jena, W. K. Pang, V. K. Peterson, H.-S. Sheu, H. Chang and R.-S. Liu, *The Journal of Physical Chemistry C*, 2017, **121**, 15565-15573.
104. George V. Alexander, N. C. Rosero-Navarro, A. Miura, K. Tadanaga and R. Murugan, *Journal of Materials Chemistry A*, 2018, **6**, 21018-21028.
105. Y. V. Baklanova, A. P. Tyutyunnik, N. V. Tarakina, A. D. Fortes, L. G. Maksimova, D. V. Korona and T. A. Denisova, *Journal of Power Sources*, 2018, **391**, 26-33.
106. B. Dong, A. R. Haworth, S. R. Yeandel, M. P. Stockham, M. S. James, J. Xiu, D. Wang, P. Goddard, K. E. Johnston and P. R. Slater, *Journal of Materials Chemistry A*, 2022, **10**, 11172-11185.
107. D. Rettenwander, G. Redhammer, F. Preishuber-Pflügl, L. Cheng, L. Miara, R. Wagner, A. Welzl, E. Suard, M. M. Doeff, M. Wilkening, J. Fleig and G. Amthauer, *Chemistry of Materials*, 2016, **28**, 2384-2392.
108. A. Wachter-Welzl, J. Kirowitz, R. Wagner, S. Smetaczek, G. C. Brunauer, M. Bonta, D. Rettenwander, S. Taibl, A. Limbeck, G. Amthauer and J. Fleig, *Solid State Ion.*, 2018, **319**, 203-208.
109. S. Narayanan, A. K. Baral and V. Thangadurai, *Physical Chemistry Chemical Physics*, 2016, **18**, 15418-15426.
110. J. Zhu, X. Li, C. Wu, J. Gao, H. Xu, Y. Li, X. Guo, H. Li and W. Zhou, *Angewandte Chemie International Edition*, 2021, **60**, 3781-3790.
111. Z. Qin, Y. Xie, X. Meng, D. Qian, D. Mao, Z. Zheng, L. Wan and Y. Huang, *ACS Appl. Mater. Interfaces*, 2022, **14**, 40959-40966.
112. S. Ohta, T. Kobayashi and T. Asaoka, *Journal of Power Sources*, 2011, **196**, 3342-3345.
113. Y. Li, J.-T. Han, C.-A. Wang, H. Xie and J. B. Goodenough, *Journal of Materials Chemistry*, 2012, **22**, 15357-15361.
114. A. Sharafi, C. G. Haslam, R. D. Kerns, J. Wolfenstine and J. Sakamoto, *Journal of Materials Chemistry A*, 2017, **5**, 21491-21504.
115. L. Cheng, W. Chen, M. Kunz, K. Persson, N. Tamura, G. Chen and M. Doeff, *ACS Appl. Mater. Interfaces*, 2015, **7**, 2073-2081.
116. H.-K. Tian, Z. Liu, Y. Ji, L.-Q. Chen and Y. Qi, *Chemistry of Materials*, 2019, **31**, 7351-7359.
117. R. Raj and J. Wolfenstine, *Journal of Power Sources*, 2017, **343**, 119-126.
118. M. D. Tikekar, S. Choudhury, Z. Tu and L. A. Archer, *Nature Energy*, 2016, **1**, 16114.
119. Y. Song, L. Yang, W. Zhao, Z. Wang, Y. Zhao, Z. Wang, Q. Zhao, H. Liu and F. Pan, *Advanced Energy Materials*, 2019, **9**, 1900671.
120. R. Hongahally Basappa, T. Ito, T. Morimura, R. Bekarevich, K. Mitsuishi and H. Yamada, *Journal of Power Sources*, 2017, **363**, 145-152.
121. B. Xu, W. Li, H. Duan, H. Wang, Y. Guo, H. Li and H. Liu, *Journal of Power Sources*, 2017, **354**, 68-73.
122. S. Yu and D. J. Siegel, *Chemistry of Materials*, 2017, **29**, 9639-9647.
123. K. Ishiguro, H. Nemori, S. Sunahiro, Y. Nakata, R. Sudo, M. Matsui, Y. Takeda, O. Yamamoto and N. Imanishi, *J. Electrochem. Soc.*, 2014, **161**, A668-A674.





124. S. Yu and D. J. Siegel, *ACS Appl. Mater. Interfaces*, 2018, **10**, 38151-38158.
125. Y. Lu, X. Huang, Y. Ruan, Q. Wang, R. Kun, J. Yang and Z. Wen, *Journal of Materials Chemistry A*, 2018, **6**, 18853-18858.
126. M. B. Dixit, M. Regala, F. Shen, X. Xiao and K. B. Hatzell, *ACS Appl. Mater. Interfaces*, 2019, **11**, 2022-2030.
127. A. Sharafi, S. Yu, M. Naguib, M. Lee, C. Ma, H. M. Meyer, J. Nanda, M. Chi, D. J. Siegel and J. Sakamoto, *Journal of Materials Chemistry A*, 2017, **5**, 13475-13487.
128. R. H. Basappa, T. Ito and H. Yamada, *J. Electrochem. Soc.*, 2017, **164**, A666-A671.
129. S. Kim, C. Jung, H. Kim, K. E. Thomas-Alyea, G. Yoon, B. Kim, M. E. Badding, Z. Song, J. Chang, J. Kim, D. Im and K. Kang, *Advanced Energy Materials*, 2020, **10**, 1903993.
130. A. Sharafi, H. M. Meyer, J. Nanda, J. Wolfenstine and J. Sakamoto, *Journal of Power Sources*, 2016, **302**, 135-139.
131. N. J. Taylor, S. Stangeland-Molo, C. G. Haslam, A. Sharafi, T. Thompson, M. Wang, R. Garcia-Mendez and J. Sakamoto, *Journal of Power Sources*, 2018, **396**, 314-318.
132. G. V. Alexander, I. M. S and R. Murugan, *Ionics*, 2021, **27**, 4105-4126.
133. J. Kanchanawarin, W. Limphirat, P. Promchana, T. Sooknoi, T. Maluangnont, K. Simalaotao, A. Boonchun, P. Reunchan, S. Limpijumnong and J. T-Thienprasert, *Journal of Applied Physics*, 2018, **124**, 155101.
134. D. Mardare, A. Yildiz, R. Apetrei, P. Rambu, D. Florea, N. G. Gheorghe, D. Macovei, C. M. Teodorescu and D. Luca, *Journal of Materials Research*, 2012, **27**, 2271-2277.
135. H. Masai, H. Sakurai, A. Koreeda, Y. Fujii, T. Ohkubo, T. Miyazaki and T. Akai, *Scientific Reports*, 2020, **10**, 11615.
136. A. J. Berry, A. M. Walker, J. Hermann, H. S. C. O'Neill, G. J. Foran and J. D. Gale, *Chemical Geology*, 2007, **242**, 176-186.
137. M. R. Ackerson, N. D. Tailby and E. B. Watson, *American Mineralogist*, 2017, **102**, 173-183.
138. S. Phokha, S. Pinitsoontorn, P. Chirawatkul, Y. Poo-arporn and S. Maensiri, *Nanoscale Research Letters*, 2012, **7**, 425.
139. C. H. Booth, M. D. Walter, M. Daniel, W. W. Lukens and R. A. Andersen, *Physical Review Letters*, 2005, **95**, 267202.
140. M. Tella, M. Auffan, L. Brousset, E. Morel, O. Proux, C. Chanéac, B. Angeletti, C. Pailles, E. Artells, C. Santaella, J. Rose, A. Thiéry and J. Y. Bottero, *Environmental Science: Nano*, 2015, **2**, 653-663.
141. W. Yuan, Q. Ma, Y. Liang, C. Sun, K. V. L. V. Narayanachari, M. J. Bedzyk, I. Takeuchi and S. M. Haile, *Journal of Materials Chemistry A*, 2020, **8**, 9850-9858.

View Article Online  
DOI: 10.1039/D3YA00123G

