

# Dental Pulp Cell Behaviour in Biomimetic Environments

Cooper, Paul; Smith, Anthony; Shelton, Richard; J.G, Smith

DOI:

[10.1177/0022034515599767](https://doi.org/10.1177/0022034515599767)

License:

None: All rights reserved

*Document Version*

Peer reviewed version

*Citation for published version (Harvard):*

Cooper, P, Smith, A, Shelton, R & J.G, S 2015, 'Dental Pulp Cell Behaviour in Biomimetic Environments', *Journal of Dental Research*. <https://doi.org/10.1177/0022034515599767>

[Link to publication on Research at Birmingham portal](#)

## **Publisher Rights Statement:**

Copyright © 2015 by International & American Associations for Dental Research  
Final published version available online: <http://dx.doi.org/10.1177/0022034515599767>

Checked October 2015

## **General rights**

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

## **Take down policy**

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact [UBIRA@lists.bham.ac.uk](mailto:UBIRA@lists.bham.ac.uk) providing details and we will remove access to the work immediately and investigate.

## Dental Pulp Cell Behaviour in Biomimetic Environments

Journal:	<i>Journal of Dental Research</i>
Manuscript ID:	JDR-15-0391.R2
Manuscript Type:	Research Reports
Date Submitted by the Author:	n/a
Complete List of Authors:	Smith, James; University of Nottingham, Wolfson Centre for Stem Cells Smith, Anthony; University of Birmingham, School of Dentistry Shelton, Richard M; Univ of Birmingham, UK, Cooper, Paul; Univeristy of Birmingham, Dentistry
Keywords:	Dentin, Pulp Biology, Stem cell(s), Tissue Engineering
Abstract:	<p>There is emerging recognition of the importance of a physiologically relevant in vitro cell culture environment to promote maintenance of stem cells for tissue engineering and regenerative medicine purposes. In vivo, appropriate cellular cues are provided by local tissue extracellular matrix (ECM) and these are not currently recapitulated well in vitro using traditional cultureware. We therefore hypothesized that better replication of the in vivo environment for cell culture and differentiation could be achieved by culturing dental pulp cells with their associated ECM. Primary dental pulp cells were subsequently seeded onto pulp-derived ECM coated cultureware. While at up to 24-hours they exhibited the same level of adherence as those cells seeded on tissue culture treated surfaces, by 4-days cell numbers and proliferation rates were significantly decreased in cells grown on pulp ECM compared with controls. Analysis of stem cell and differentiation marker transcripts, as well as Oct 3/4 protein distribution, supported the hypothesis that cells cultured on ECM better maintained a stem cell phenotype compared with those cultured on standard tissue culture treated surfaces. Subsequent differentiation analysis of cells cultured on ECM demonstrated they exhibited enhanced mineralisation as determined by alizarin red staining and mineralised marker expression. Supplementation of a 3% alginate hydrogel with pulp ECM components and dental pulp cells followed by differentiation induction in mineralisation medium resulted in a time-dependent mineral deposition at the periphery of the construct, as demonstrated histologically and using micro-computed tomography analysis, which was reminiscent of tooth structure. In conclusion, data indicates that culture of pulp cells in the presence of ECM better replicates the in vivo environment maintaining a stem cell phenotype suitable for downstream tissue engineering applications.</p>

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

SCHOLARONE™  
Manuscripts

For Peer Review

# Dental Pulp Cell Behaviour in Biomimetic Environments

JG Smith<sup>1,3</sup>, AJ Smith<sup>1</sup>, RM Shelton<sup>2</sup> & PR Cooper<sup>1</sup>

<sup>1</sup>Oral Biology & <sup>2</sup>Biomaterials, School of Dentistry, College of Medical and Dental Sciences,  
University of Birmingham, Birmingham, B4 6NN, UK

<sup>3</sup>Wolfson Centre for Stem Cells, Tissue Engineering and Modelling, Centre for Biomolecular  
Sciences, University of Nottingham, Nottingham, NG7 2RD, UK

## Corresponding author:

Professor Paul Cooper

Oral Biology,

School of Dentistry,

The University of Birmingham,

St. Chad's Queensway,

Birmingham,

B4 6NN, UK

Direct Dial: +44 (0) 121 466 5526

FAX: +44 (0) 121 466 5491

Email: cooperpr@adf.bham.ac.uk

**Short title:** Dental pulp cell culture with extracellular matrix in 2D and 3D

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

26     **ABSTRACT**

27     There is emerging recognition of the importance of a physiologically relevant *in vitro* cell  
28     culture environment to promote maintenance of stem cells for tissue engineering and  
29     regenerative medicine purposes. *In vivo*, appropriate cellular cues are provided by local  
30     tissue extracellular matrix (ECM) and these are not currently recapitulated well *in vitro* using  
31     traditional cultureware. We therefore hypothesized that better replication of the *in vivo*  
32     environment for cell culture and differentiation could be achieved by culturing dental pulp  
33     cells with their associated ECM. Primary dental pulp cells were subsequently seeded onto  
34     pulp-derived ECM coated cultureware. While at up to 24-hours they exhibited the same  
35     level of adherence as those cells seeded on tissue culture treated surfaces, by 4-days cell  
36     numbers and proliferation rates were significantly decreased in cells grown on pulp ECM  
37     compared with controls. Analysis of stem cell and differentiation marker transcripts, as well  
38     as Oct 3/4 protein distribution, supported the hypothesis that cells cultured on ECM better  
39     maintained a stem cell phenotype compared with those cultured on standard tissue culture  
40     treated surfaces. Subsequent differentiation analysis of cells cultured on ECM demonstrated  
41     they exhibited enhanced mineralisation as determined by alizarin red staining and  
42     mineralised marker expression. Supplementation of a 3% alginate hydrogel with pulp ECM  
43     components and dental pulp cells followed by differentiation induction in mineralisation  
44     medium resulted in a time-dependent mineral deposition at the periphery of the construct,  
45     as demonstrated histologically and using micro-computed tomography analysis, which was  
46     reminiscent of tooth structure. In conclusion, data indicates that culture of pulp cells in the  
47     presence of ECM better replicates the *in vivo* environment maintaining a stem cell  
48     phenotype suitable for downstream tissue engineering applications.

49     **Key words:** Pulp, dentine, extracellular matrix, hydrogel, growth factor, doping

## INTRODUCTION

Different populations of mesenchymal stem cells (MSCs) are described within the pulp including dental pulp stem cell (DPSC) (Gronthos et al. 2000), stem cells from human exfoliated deciduous teeth (SHED) (Miura et al. 2003) and stem cells from the apical papilla (SCAP) (Sonoyama et al. 2006). The environment within the MSC niche is critical for regulating cell homeostasis, proliferation and differentiation (Burness and Sipkins 2010) and the extracellular matrix (ECM) of the pulp provides both biochemical and biomechanical cues. The dental pulp ECM is of a relatively gelatinous consistency and contains significant amounts of collagen (types I and III), proteoglycans and glycosaminoglycans (Tsuzaki et al. 1990), non-collagenous proteins including fibronectin, tenascin, osteonectin and osteopontin and many members of growth factor families. Indeed the regulation of dental tissue regeneration also involves signalling derived from its ECM with members of the TGF $\beta$  superfamily being directly implicated in stimulating dentinogenic repair (Smith et al. 2012a).

Several approaches have been utilised to isolate post-natal MSCs from dental and other tissues, with the simplest utilising standard cultureware adherence (Friedenstein et al. 1976). Heterogeneous populations of cells are subsequently isolated with MSC-like properties including clonogenicity and high proliferative capacity (Gronthos et al. 2000; Miura et al. 2003). Fluorescence-activated cell sorting (FACs) and magnetic activated cell sorting (MACs) are also routinely used for MSC isolation (Zannettino et al. 2007) with positive selection for STRO-1, CD105, c-kit, CD34 and low-affinity nerve-growth-factor receptor (LNGFR) and negative selection for CD31 and CD146 being used to isolate pulp MSCs (Yang et al. 2007; Nakashima et al. 2009; Zhang et al. 2006). Recent reports however demonstrate that MSCs also exhibit selective adhesion to surfaces coated with ECM-derived

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

73 molecules and subsequently cell adhesion to fibronectin coated cultureware has been  
74 proposed for pulp MSC enrichment (Waddington et al. 2009).

75 Dental tissue engineering strategies require biomimetic scaffolds, morphogens and  
76 progenitor cell populations to generate whole tooth or tooth component structures. **Studies**  
77 ***in vivo* have demonstrated tooth tissue formation by seeding DPSCs and SHED on scaffolds**  
78 **which exhibit similar properties to native pulp tissue, such as collagen and poly-L-lactic acid**  
79 **(Sumita et al. 2006; Cordeiro et al. 2008).** Doping of these structures with dental ECM  
80 derived morphogens has also been shown to promote differentiation and mineral  
81 deposition of encapsulated MSCs. Notably however many of these approaches rely on  
82 implantation in animal models to enable engineering dental tissue structures (**Chen et al.**  
83 **2015**; Zhang et al. 2006; Zheng et al. 2011).

84 **We subsequently hypothesised that dental ECM-coated cultureware may better**  
85 **recapitulate the *in vivo* environment and aid selection and maintenance of pulp MSCs from**  
86 **heterogeneous primary pulp cell populations. Furthermore we hypothesised that dental**  
87 **ECM-supplementation of a hydrogel scaffold may provide a more physiologically relevant**  
88 **environment for 3D dental tissue engineering. Furthermore the generation of robust *in vitro***  
89 **models may reduce the requirement for *in vivo* experimentation and the associated costs**  
90 **and constraints.**

## 97 MATERIALS & METHODS

### 98 *Isolation of Dental Tissue and Cells*

99 Bovine mandibular incisor teeth were from <2-month old male Holstein Friesian calves  
100 (Bates' Wholesale Butchers, Birmingham, UK). Maxillary and mandibular incisors were from  
101 100-120g Wistar Hannover rats (Charles River Laboratories, Welwyn Garden City, UK). Teeth  
102 were dissected from jaws and pulp was extirpated for ECM extraction and cell isolation.

### 104 *Extraction and Characterisation of Pulp Extracellular Matrix (pECM)*

105 Bovine incisor pulps were mechanically dissected (0.5–1mm<sup>3</sup> pieces) and combined with 1ml  
106 ice cold 0.5M NaCl (Sigma-Aldrich, Dorset, UK) extraction solution (pH 11.7) containing  
107 protease inhibitors, 25mM EDTA, 1mM phenylmethylsulphonyl fluoride and 5mM *N*-  
108 ethylmaleimide (Sigma-Aldrich, Dorset, UK) and 1.5mM sodium azide (VWR International,  
109 Lutterworth, UK). Tissue suspensions were homogenised on ice [Ultra-Turrax T8  
110 homogeniser (IKA Labortechnik, Staufen, Germany)] and agitated for 24 hours at 4°C.  
111 Centrifuged supernatants were removed and pellets re-suspended in 1ml 0.5M NaCl (Sigma-  
112 Aldrich, Dorset, UK). Re-suspending, homogenisation, agitation and pelleting was repeated  
113 in triplicate and supernatants pooled. Pulpal tissue was re-suspended in 1ml cold 0.1M  
114 tartaric acid solution (pH 2.0) (Hopkin & Williams Ltd, Birmingham, UK) and subjected to the  
115 same homogenisation, stirring and centrifugation protocol as described above (Bellon et al.  
116 1988). NaCl and tartaric acid soluble pECM extracts were dialysed (19mm tubing) against  
117 dH<sub>2</sub>O for 2-weeks at 4°C with daily water changes prior to lyophilisation.



1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

120     **Characterisation of pECM Components**

121     Lyophilised pECM (0.5mg) in lithium dodecyl sulphate buffer was denatured (105°C) with  
122     NuPAGE reducing agent. Samples were electrophoresed on NuPAGE 10% Bis-Tris gels and  
123     stained using the SilverXpress Silver kit (Life Technologies, East Lothian, UK).  
124             Non-collagenous proteins (NCPs) were assayed using Coomassie Brilliant Blue G-250  
125     (Sigma-Aldrich, Dorset, UK) with absorbance determined at 595nm using a UV/VIS  
126     Spectrometer (Philips, Colchester, UK) with a BSA standard (Bradford 1976). The dimethyl  
127     methylene blue assay was used to quantify glycosaminoglycans (GAGs) (Farndale et al.  
128     1986). The GAG chain, chondroitin-4-sulphate (Sigma-Aldrich, Dorset, UK), was used as  
129     standard with absorbance at 525nm. Collagen was assayed using Sirius Red (VWR  
130     International, Lutterworth, UK) in saturated Picric acid (Sigma- Aldrich, Dorset, UK)  
131     (Tullberg-Reinert and Jundt 1999). Absorbance values were determined at 490-570nm using  
132     an ELX800 Universal Microplate reader (Bio-tex Instruments, USA) with rat tail collagen  
133     type-I standard (Sigma- Aldrich, Dorset, UK).

135     **Primary Cell Culture**

136     Culture was in  $\alpha$ -MEM (Biosera, Nuaille, France), containing 2mM L-glutamine  
137     supplemented with 1% penicillin / streptomycin (all Sigma-Aldrich, Dorset, UK) and 10%  
138     foetal calf serum (Biosera, Nuaille, France). Primary pulp cells were isolated from rodent  
139     tissue by enzymatic disaggregation (Patel et al. 2009). Cells ( $2 \times 10^4$ ) were seeded on culture  
140     surfaces (Sarstedt, Leicester, UK) and viable cells counted using the trypan blue exclusion  
141     assay (Sigma-Aldrich, Dorset, UK).

One-ml of pECM (1 mg/ml) dissolved in PBS was used to coat 35mm<sup>2</sup> culture dishes (Sarstedt, Leicester, UK) by incubation at 4°C for 24 hours. Surfaces were washed in triplicate with PBS to remove unbound protein. Coating of culture surfaces were assessed using Coomassie Brilliant Blue G-250 (Bradford 1976). To induce mineralising lineage differentiation, culture media was supplemented with 10<sup>-7</sup>M dexamethasone, 10mM β-glycerophosphate, and 50µg/ml ascorbic acid (all Sigma-Aldrich, Dorset, UK) (Gronthos et al. 2000).

#### **Scanning Electron Microscopy (SEM)**

For fixation, surfaces were treated with 2.5% glutaraldehyde (Agar Scientific, Stansted, UK) in 0.1M sodium cacodylate buffer (Fisher Scientific, Loughborough, UK) for 30 minutes followed by dehydration by sequential 10 minute treatments in increasing concentrations (v/v) of ethanol followed by exposure to hexamethyl-disilazane (Sigma-Aldrich, Dorset, UK). Culture surfaces were attached to aluminium SEM stubs using Acheson electrodag (Agar Scientific, Stansted, UK) and sputter-coated with gold under vacuum (Emitech K550X). SEM images were obtained using an accelerating voltage of 10kV using a JSM-840A SEM (Joel, Welwyn Garden City, UK).

#### **High Content Cell Analysis (HCA) of OCT 3/4**

HCA was performed at Imagen Biotech (Manchester, UK). Pulp cells were fixed (30 minutes) with 10% paraformaldehyde (VWR International, Lutterworth, UK). Cells were incubated with Oct 3/4 primary antibody (Abcam, Milton, UK) diluted 1:100 in 0.1M phosphate buffer

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

164 pH7.8 with 0.1% BSA for 1-hour at room temperature. Cells were washed (3x) and incubated  
165 with goat anti-rabbit IgG secondary antibody conjugated to an Alexa-Fluor® 488 fluorescent  
166 label (VWR International, Lutterworth, UK) for 1-hour. ArrayScan High Content Screening  
167 (HCS) Imaging Cytometer and ArrayScan II Data Acquisition and Data Viewer 3.0 software  
168 (Fisher, Loughborough, UK) were used for analysis.

169

170 ***Alizarin Red Staining***

171 Cultures were fixed in 10% paraformaldehyde (VWR International, Lutterworth, UK) for 30  
172 minutes, washed with PBS alizarin red solution added (VWR International, Lutterworth, UK)  
173 (Gregory et al. 2004). Excess stain was removed with PBS and cultures de-stained in 10mM  
174 acetic acid. Stain was quantified at 405nm using an ELX800 Universal Microplate reader  
175 (Bio-Tex Instruments Inc, Houston, US) and compared with 40mM alizarin red stock  
176 solution.

177

178 ***Bromodeoxyuridine (BrdU) Proliferation Assay***

179 The 5-bromo-2-deoxy-uridine labelling and detection kit II (Roche Life Sciences, Burgess Hill,  
180 UK) was used. Medium was removed from cultures and replaced with 500µl BrdU labelling  
181 medium. After 60 minutes incubation, BrdU labelling medium was removed and dishes  
182 washed in triplicate with PBS. Cells were fixed (30% absolute ethanol/70% 50mM glycine)  
183 for 20 minutes at room temperature. Fluid was removed and samples incubated at -20°C for  
184 30 minutes. After PBS washing, 700µl anti-BrdU (kit reagent) was added to each dish for 30  
185 minutes at 37°C, surfaces were PBS washed. 700µl AP conjugate was added for 30 minutes

1  
2  
3 186 at 37°C. Dishes were washed with PBS before 700µl colour substrate was added for 30  
4  
5 187 minutes at room temperature. Proliferating cells incorporating BrdU into DNA were  
6  
7  
8 188 detected by positive antibody staining under a Nikon Eclipse TE300 microscope (Nikon,  
9  
10 189 Kingston, UK). A graticule was used to determine percentage of proliferating cells.  
11  
12  
13 190  
14

#### 15 191 ***Semi-quantitative RT-PCR Analysis***

16

17  
18 192 RNA was isolated using the QIAGEN RNeasy minikit (Qiagen, Manchester, UK). Cells were  
19  
20 193 lysed in RLT buffer and 70% (v/v) ethanol was added, vortexed and added to an RNeasy  
21  
22 194 mini-column. Bound RNA was washed with ethanol kit buffer prior to centrifugal drying.  
23  
24  
25 195 DNase treated RNA was collected in molecular grade water.  
26

27  
28 196 The QIAGEN Omniscript RT kit (Qiagen, Manchester, UK) was used to reverse  
29  
30 197 transcribe 1.5-2µg of RNA using oligo-dT primer (Life Technologies, Paisley, UK), Omniscript  
31  
32 198 reverse transcriptase and buffer, deoxynucleoside triphosphates (dNTPs), with RNase  
33  
34 199 inhibitor (Promega, Southampton, UK) at 37°C for 1 hour. Synthesized cDNA was cleaned on  
35  
36 200 Microcon YM-30 spin-baskets (Millipore, Livingston, UK). RNA and cDNA concentrations  
37  
38 201 were determined using a Biophotometer (Eppendorf, Stevenage, UK).  
39  
40

41 202 PCRs contained 50-100ng of cDNA, 12.5µl 2xREDTaq Ready mix (Sigma-Aldrich,  
42  
43 203 Dorset, UK), 1µl of 1µM forward primer (VWR International, Lutterworth, UK), 1µl of 1µM  
44  
45 204 reverse primer (Invitrogen, UK), and 12.5µl of water (VWR International, Lutterworth, UK).  
46  
47  
48 205 Primer and assay details are in **Supplementary Table 1**. A GeneAmp 2700 Thermocycler  
49  
50 206 (Applied Biosystems, Manchester, UK) was used with initial denaturation of 94°C for 5  
51  
52 207 minutes, 1 minute cycles of 94°C, denaturation for 20 seconds, annealing at 60/60.5°C for 20  
53  
54  
55 208 seconds, extension at 68°C for 20 seconds, and a final extension at 72°C for 10 minutes.  
56  
57  
58  
59  
60

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

209           Amplified products were analysed on 1.5% (w/v) agarose gels (Web Scientific, Crewe,  
210   UK) with images analysed with GeneTools software (Syngene, Cambridge, UK). Target gene  
211   expression was normalised to Glyceraldehyde-3-phosphate dehydrogenase.

212  
**213   Cell Encapsulation and Culture in Alginate Gels**

214   Low viscosity sodium-alginate (Sigma-Aldrich, Dorset, UK) was prepared at 1, 3 and 5% w/v  
215   in PBS/ $\alpha$ -MEM (1:1) and autoclaved at 121°C. Pulp cells were dispersed by pipetting  
216   throughout the alginate at  $5 \times 10^5$  cells/ml +/- pECM supplementation. Constructs were  
217   added dropwise into culture dishes (Sarstedt, Leicester, UK) containing 100mM  $\text{CaCl}_2$  and  
218   incubated at 37°C for 1 hour to form cross-linked spheres (Hunt et al. 2009). Spheres were  
219   washed (x3) in  $\alpha$ -MEM and re-suspended in control or lineage inductive media. Cells were  
220   released from alginate using 100mM tri-sodium citrate (Sigma-Aldrich, Dorset, UK).

221  
**222   Histological Analysis of Hydrogel Constructs**

223   Encapsulated cells were fixed within alginate by submersion in 10% v/v paraformaldehyde  
224   (VWR International, Lutterworth, UK) for 30 minutes. Fixed gels were progressively  
225   dehydrated in increasing concentrations of alcohol for 15 minutes each. Gels were  
226   submerged in 2 changes of xylene (VWR International, Lutterworth, UK) for 15 minutes. Gels  
227   were embedded in paraffin wax (Sakura, Thatcham, UK) and cooled to 5°C and 5 $\mu$ m sections  
228   stained with haematoxylin and eosin (H&E) (Surgipath Europe Ltd, Peterborough, UK).

231 ***Micro-Computed Tomography (MicroCT)***

232 Alginate constructs were scanned at 80kV, 100µA at an isotropic resolution of 4µm with  
233 camera exposure of 200ms, a rotation step of 0.3°, frame averaging of 4 and omission of an  
234 X-ray filter using a Skyscan 1172 MicroCT system (Bruker, Coventry, UK). Images were  
235 reconstructed using NRecon 1.6.2 software (Bruker, Coventry, UK). For thresholding a  
236 hydroxyapatite mineral phantom was used comprising of tetracalcium phosphate  
237 (TTCP)/dicalcium phosphate anhydrous (DCPA) powder and α-tricalcium phosphate (α-TCP)  
238 powder (Hofmann et al. 2007).

239

240 ***Statistical Analysis***

241 Paired student T-tests and one-way ANOVA with  $p < 0.05$  with a Tukey post hoc test was used  
242 to determine statistical significance compared with controls.

243

244

245

246

247

248

249

250

RESULTS

*Pulp cell cultures on pECM*

Triplicate pECM isolates demonstrated consistent protein content profiles and yields. Ratios of GAG, NCP and collagen yields for the pECM isolates were also consistent between extractions. Coating of cultureware was confirmed by Coomassie blue staining and SEM analysis (*Figure 1*). This cultureware coating approach enabled comparison with standard culturing approaches. Viable cells at 24 hours post-seeding on uncoated control and pECM coated cultureware demonstrated no significant differences. Day 5 cell numbers were significantly lower on pECM coated cultureware compared with control. Consistent with this, BrdU data indicated cells cultured on pECM coated cultureware exhibited significantly decreased proliferation compared with controls (*Figure 2*).

Gene expression analysis for mesenchymal and pluripotent stem cell markers indicated that in general markers of stem cell phenotype were more abundantly expressed in cultures maintained on pECM compared with controls. Expression of the odontogenic cell fate markers, DSPP and DMP, were relatively more abundant in pulp cells cultured on uncoated cultureware compared with cells grown on pECM (*Figure 3*). Nuclear versus cytoplasmic localisation data for the pluripotent transcription factor Oct 3/4 was consistent with gene expression analysis regarding molecular pluripotent cell phenotype. Cells cultured on pECM demonstrated increased levels (~50%) of nuclear Oct 3/4 compared with controls (~20%) supporting the notion that cell-ECM interactions maintain an undifferentiated phenotype (*Figure 3*).

#### 274 ***Differentiation analysis of pulp cells on ECM***

275 Two-weeks cell culture on pECM surfaces in the presence of mineralisation supplements  
276 resulted in an enhanced mineralising phenotype (**Figure 4**). Cell count data indicated that  
277 differences in quantitative staining were not due to variations in cell numbers. Similar  
278 profiles were observed at 3-weeks (data not shown). Gene expression analyses using  
279 markers of dental and mineralising cell differentiation indicated differential gene expression  
280 between control and differentiation conditions (**Figure 4B**).

281

#### 282 ***Pulp cells cultured in hydrogels containing pECM***

283 Studies of pulp cells encapsulated in 1%, 3% and 5% hydrogels with or without pECM  
284 indicated that at 2 weeks, while cell numbers did not increase, there was no significant loss  
285 of viability (**Figure S1**). Subsequently, pulp cells were encapsulated in 3% hydrogels  
286 containing pECM components which had previously demonstrated influence on MSC  
287 behaviour and exposed to mineralisation medium for up to 5-weeks while controls were  
288 cultured in unsupplemented medium. Inspection of 3D cultures indicated that  
289 mineralisation medium exposed cultures appeared visually opaque and microCT analysis  
290 confirmed deposition of a radiodense layer at the construct periphery. H&E analysis  
291 indicated increased protein deposition at the construct surfaces exposed to mineralisation  
292 medium that became more distinct with time and likely contributed to an increased  
293 mineralised matrix deposition (**Figure 5**).

294

295

296



**DISCUSSION**

Several stem/progenitor cell niches are reported within the postnatal dental pulp, including sites within the central pulp stroma and in perivascular regions. The heterogeneous nature of these niches implicates local tissue signals being important for their self-renewal, proliferation, differentiation, mobilization and homing (Yin and Li 2006). Within healthy tissues, progenitor/MSC niches are reportedly quiescent and slow cycling MSCs are located in close proximity to ECM rich regions which regulate their behaviour (Booth and Potten 2000; Bi et al. 2007). We therefore hypothesised that culture of pulp cells with pECM may better recreate the niche environment. While data potentially supported this hypothesis the enhanced stem cell phenotype may also be due to pECM attracting a specific population of progenitor cells. Alternatively, the results obtained may reflect the pECM maintaining the dental pulp cells in a more quiescent and undifferentiated state which may relate to the lower cell cycling rates which decrease cell densities and associated cell-cell interactions.

Interestingly, we have also found that bone marrow MSCs exhibit similar adherent and growth profiles on pECM (unpublished data). These data could indicate that the effect exerted by ECM may not be cell-type specific and that common regulatory signalling pathways exist between different MSC-types.

To characterise pECM extracts we have performed proteomic mass spectrometry and identified over 90 proteins present in these preparations (data not shown). Several molecules previously utilised for culture-surface coating for MSC selection, including fibronectin and collagen type-I (He et al. 2014; Waddington et al. 2009), were identified as being present. While these molecules may contribute to the cellular affects we observed, it is likely that more complex ECM interactions occur which generate a more relevant and comprehensive environment for regulating MSC behaviour. Our culture approach may

1  
2  
3 321 therefore provide a MSC biomimetic environment. Previously we have found that when  
4  
5 322 pECM was subjected to enzymatic degradation, modulation of cell proliferation was  
6  
7  
8 323 abolished (Smith et al. 2012b) indicating its integrity is important in regulating cell  
9  
10 324 behaviour. Conceivably this may reflect the role of the ECM *in vivo* during healing whereby  
11  
12 325 enzymatic activities of bacterial and host proteases during disease (Cooper et al. 2014) may  
13  
14 326 lead to the release of MSCs from their niche enabling their proliferation and differentiation  
15  
16  
17 327 (Schedin et al. 2000). This notion is also supported by previous studies demonstrating that  
18  
19 328 during standard culture expansion, MSC phenotype is lost (Patel et al. 2009). Surface  
20  
21 329 properties such as chemistry, topography and elastic modulus elicit biomechanical forces on  
22  
23 330 cells and substrates that exert these effects have been shown to be important in regulating  
24  
25 331 cellular events (Celiz et al. 2014; Fu et al. 2010; Trappmann et al. 2012). Indeed future  
26  
27 332 experiments which isolate physical effects on cells from biological effects could be  
28  
29 333 performed by coating culture plasticware with inert materials which solely change  
30  
31 334 cultureware surface topography in a similar manner to that observed due to ECM coating.  
32  
33 335 Furthermore comprehensive identification of factors important in the ECM which maintain  
34  
35 336 MSC-potency may have significant application in future tissue regenerative and engineering  
36  
37 337 strategies.

38  
39 338 The present study also demonstrated that mineralisation was enhanced when cells  
40  
41 339 were cultured in a physiologically relevant ECM-environment. While this may be due to the  
42  
43 340 initial maintenance of the MSC phenotype we have also noted that when cells originally  
44  
45 341 cultured on ECM were re-seeded on standard cultureware they did not demonstrate  
46  
47 342 enhanced alizarin red staining. Similarly the differentiation of pulp cells along adipogenic  
48  
49 343 lineages on standard cultureware compared with those maintained on ECM demonstrated  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

minimal differentiation differences (data not shown). These data also indicate the potential importance of the ECM in providing additional signals for differentiation.

Alginate hydrogels have previously been used to viably encapsulate many cell types and the manipulation of its modulus can influence dental cell differentiation, as such it was selected as a suitable material for the generation of an *in vitro* model of dental tissue engineering (Hunt et al. 2009; Smith et al. 2007; Kong et al. 2003). Furthermore we have previously shown that alginate hydrogels can provide a conducive environment in which dental repair can occur *in vitro* (Dobie et al. 2002). In our studies only cells adjacent to the outer surface of the construct contributed to a mineralised tissue which is consistent with our previous reports (Smith et al. 2012c). These outer surface effects could be due to differences in oxygen tension, reduced diffusion of mineralisation signals, and/or physical restriction of the more deeply encapsulated cells.

Data presented here indicates the potential importance and utility of generating biomimetic environments *in vitro*, both in 2D and 3D, for tissue engineering purposes. Further studies are however required to confirm the importance of the role of pulp ECM signalling within 3D environments as well as its relevance in animal model systems. Nevertheless our findings indicate that application of ECM may aid MSC-phenotype maintenance and subsequent differentiation, and that alginate hydrogel scaffolds doped with ECM may provide suitable models to study tooth development and regeneration, as well as having future clinical application.

**ACKNOWLEDGEMENTS**

We thank Gay Smith, Michelle Holder and Sue Finney for expert technical assistance. We thank Imagen Biotech for assistance with high content analysis. This research was supported by the School of Dentistry, University of Birmingham. The authors declare no potential conflicts of interest with respect to the authorship and/or publication of this article.

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

396       **REFERENCES**

397       Bellon G, Wegrowski J, Perreau C, Randoux A, Borel JP, Malgras A, Chastang F. 1988. A  
398       parallel between two techniques of extraction of connective tissue macromolecules.  
399       Anal Biochem. 175(1):263-273.

400       Bi Y, Ehirchiou D, Kilts TM, Inkson CA, Embree MC, Sonoyama W, Li L, Leet AI, Seo BM,  
401       Zhang L, Shi S, Young MF. 2007. Identification of tendon stem/progenitor cells and the  
402       role of the extracellular matrix in their niche. Nat Med. 13(10):1219-1227.

403       Booth C, Potten CS. 2000. Gut instincts: thoughts on intestinal epithelial stem cells. J Clin  
404       Invest. 105(11):1493-1499.

405       Bradford MM. 1976. A rapid and sensitive method for the quantitation of microgram  
406       quantities of protein utilizing the principle of protein-dye binding. Anal Biochem. 72:248-  
407       254.

408       Burness ML, Sipkins DA. 2010. The stem cell niche in health and malignancy. Semin  
409       Cancer Biol. 20(2):107-115.

410       Celiz AD, Smith JG, Langer R, Anderson DG, Winkler DA, Barrett DA, Davies MC, Young  
411       LE, Denning C, Alexander MR. 2014. Materials for stem cell factories of the future. Nat  
412       Mater. 13(6):570-9.

413       Chen G, Chen J, Yang B, Li L, Luo X, Zhang X, Feng L, Jiang Z, Yu M, Guo W, Tian W. 2015.  
414       Combination of aligned PLGA/Gelatin electrospun sheets, native dental pulp  
415       extracellular matrix and treated dentin matrix as substrates for tooth root regeneration.  
416       Biomaterials 52:56–70.

417       Cooper PR, Holder MJ, Smith AJ. 2014. Inflammation and regeneration in the dentin-pulp  
418       complex: a double-edged sword. J Endod. 40(4 Suppl):S46-51.

419       Cordeiro MM, Dong Z, Kaneko T, Zhang Z, Miyazawa M, Shi S, Smith AJ, Nor JE. 2008.  
420       Dental pulp tissue engineering with stem cells from exfoliated deciduous teeth. J Endod.  
421       34(8):962-969.

422       Dobie K, Smith G, Sloan AJ, Smith AJ. 2002. Effects of alginate hydrogels and TGF-β1 on  
423       human dental pulp repair *in vitro*. Connective Tissue Research 43(2-3):387-390.

424       Farndale RW, Buttle DJ, Barrett AJ. 1986. Improved quantitation and discrimination of  
425       sulphated glycosaminoglycans by use of dimethylmethylene blue. Biochim Biophys Acta.  
426       883(2):173-177.

427       Friedenstein AJ, Gorskaja JF, Kulagina NN. 1976. Fibroblast precursors in normal and  
428       irradiated mouse hematopoietic organs. Exp Hematol. 4(5):267-274.

- 429 Fu J, Wang YK, Yang MT, Desai RA, Yu X, Liu Z, Chen, CS. 2010. Mechanical regulation of  
430 cell function with geometrically modulated elastomeric substrates. *Nat Methods*.  
431 7(9):733-736.
- 432 Gregory CA, Gunn WG, Peister A, Prockop DJ. 2004. An Alizarin red-based assay of  
433 mineralization by adherent cells in culture: comparison with cetylpyridinium chloride  
434 extraction. *Anal Biochem*. 329(1):77-84.
- 435 Gronthos S, Mankani M, Brahimi J, Robey PG, Shi S. 2000. Postnatal human dental pulp  
436 stem cells (DPSCs) *in vitro* and *in vivo*. *Proc Natl Acad Sci USA*. 97(25):13625-13630.
- 437 He J, Su Y, Huang T, Jiang B, Wu F, Gu Z. 2014. Effects of material and surface functional  
438 group on collagen self-assembly and subsequent cell adhesion behaviors. *Colloids Surf B*  
439 *Biointerfaces*. 116:303-308
- 440 Hofmann MP, Gbureck U, Duncan CO, Dover MS, Barralet JE. 2007. Carvable calcium  
441 phosphate bone substitute material. *J Biomed Mater Res B Appl Biomater*. 83(1):1-8.
- 442 Hunt NC, Shelton RM, Grover L. 2009. An alginate hydrogel matrix for the localised  
443 delivery of a fibroblast/keratinocyte co-culture. *Biotechnol J*. 4(5):730-737.
- 444  
445 Kong HJ, Smith MK, Mooney DJ. 2003. Designing alginate hydrogels to maintain viability  
446 of immobilized cells. *Biomaterials*. 24(22):4023-4029.
- 447 Larmas M. 1972. Observations on endopeptidases in human carious dentin. *Scand J Dent*  
448 *Res*. 80(6):520-523.
- 449 Miura M, Gronthos S, Zhao M, Lu B, Fisher LW, Robey PG, Shi S. 2003. SHED: stem cells  
450 from human exfoliated deciduous teeth. *Proc Natl Acad Sci USA*. 100(10):5807-5812.
- 451 Nakashima M, Iohara K, Sugiyama M. 2009. Human dental pulp stem cells with highly  
452 angiogenic and neurogenic potential for possible use in pulp regeneration. *Cytokine*  
453 *Growth Factor Rev*. 20(5-6):435-440.
- 454 Patel M, Smith AJ, Sloan AJ, Smith G, Cooper PR. 2009. Phenotype and behaviour of  
455 dental pulp cells during expansion culture. *Arch Oral Biol*. 54(10):898-908.
- 456 Schedin P, Strange R, Mitrenga T, Wolfe P, Kaeck M. 2000. Fibronectin fragments induce  
457 MMP activity in mouse mammary epithelial cells: evidence for a role in mammary tissue  
458 remodeling. *J Cell Sci*. 113(5):795-806.
- 459 Smith AM, Harris JJ, Shelton RM, Perrie Y. 2007. 3D culture of bone-derived cells  
460 immobilised in alginate following light-triggered gelation. *J Control Release*. 119(1):94-  
461 101.

1  
2  
3 462 Smith AJ, Scheven BA, Takahashi Y, Ferracane JL, Shelton RM, Cooper PR. 2012a. Dentine  
4 463 as a bioactive extracellular matrix. Arch Oral Biol. 57(2):109-121.  
5  
6 464 Smith JG, Smith AJ, Shelton RM, Cooper PR. 2012b. Recruitment of dental pulp cells by  
7 465 dentine and pulp extracellular matrix components. Exp Cell Res. 318(18):2397-2406.  
8  
9 466 Smith AJ, Smith JG, Shelton RM, Cooper PR. 2012c. Harnessing the natural regenerative  
10 467 potential of the dental pulp. Dent Clin North Am. 56(3):589-601.  
11  
12  
13 468 Sonoyama W, Liu Y, Fang D, Yamaza T, Seo BM, Zhang C, Liu H, Gronthos S, Wang CY, Shi  
14 469 S, Wang S. 2006. Mesenchymal stem cell-mediated functional tooth regeneration in  
15 470 swine. PLoS ONE. 1:e79.  
16  
17  
18 471 Sumita Y, Honda MJ, Ohara T, Tsuchiya S, Sagara H, Kagami H, Ueda M. 2006.  
19 472 Performance of collagen sponge as a 3-D scaffold for tooth-tissue engineering.  
20 473 Biomaterials. 27(17):3238-3248.  
21  
22  
23 474 Takahashi K, Yamanaka S. 2006. Induction of pluripotent stem cells from mouse  
24 475 embryonic and adult fibroblast cultures by defined factors. Cell. 126(4):663-676.  
25  
26  
27 476 Tullberg-Reinert H, Jundt G. 1999. *In situ* measurement of collagen synthesis by human  
28 477 bone cells with a sirius red-based colorimetric microassay: effects of transforming  
29 478 growth factor beta2 and ascorbic acid 2-phosphate. Histochem Cell Biol. 112(4):271-276.  
30 479  
31 480 Trappmann B, Gautrot JE, Connelly JT, Strange DG, Li Y, Oyen ML, Cohen Stuart MA,  
32 481 Boehm H, Li B, Vogel V, Spatz JP, Watt FM, Huck WT. 2012. Extracellular-matrix tethering  
33 482 regulates stem-cell fate. Nat Mater. 11(7):642-9.  
34 483  
35 484 Tsuzaki M, Yamauchi M, Mechanic GL. 1990. Bovine dental pulp collagens:  
36 485 characterization of types III and V collagen. Arch Oral Biol. 35(3):195-200.  
37  
38  
39 486 Waddington RJ, Youde SJ, Lee CP, Sloan AJ. 2009. Isolation of distinct progenitor stem  
40 487 cell populations from dental pulp. Cells Tissues Organs. 189(1-4): 268-274.  
41 488  
42 489 Yang X, Zhang W, Van Den Dolder J, Walboomers XF, Bian Z, Fan M, Jansen JA. 2007.  
43 490 Multilineage potential of STRO-1+ rat dental pulp cells *in vitro*. J Tissue Eng Regen Med.  
44 491 1(2):128-35.  
45  
46  
47 492 Yin T, Li L. 2006. The stem cell niches in bone. J Clin Invest. 116(5):1195-1201.  
48  
49  
50 493 Zannettino AC, Paton S, Kortessidis A, Khor F, Itescu S, Gronthos S. 2007. Human  
51 494 multipotential mesenchymal/stromal stem cells are derived from a discrete  
52 495 subpopulation of STRO-1bright/CD34 /CD45(-)/glycophorin-A-bone marrow cells.  
53 496 Haematologica. 92(12):1707-1708.  
54  
55  
56  
57  
58  
59  
60

- 1  
2  
3 497 Zhang W, Walboomers XF, Van Kuppevelt TH, Daamen WF, Bian Z, Jansen JA. 2006. The  
4 498 performance of human dental pulp stem cells on different three-dimensional scaffold  
5 499 materials. *Biomaterials*. 27(33):5658-68.
- 7 500 Zheng L, Yang F, Shen H, Hu X, Mochizuki C, Sato M, Wang S, Zhang Y. 2011. The effect of  
8 501 composition of calcium phosphate composite scaffolds on the formation of tooth tissue  
9 502 from human dental pulp stem cells. *Biomaterials*. 32(29):7053-7059.
- 10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60



FIGURE LEGENDS

**Figure 1. Ai)** Image of 1D-PAGE analysis of the three replicate extracts of pulp ECM (pECM). 0.125mg of pECM was loaded in a NuPAGE 10% Bis-Tris gel, and visualised using SilverXpress Silver staining kit. 10µl of Mark12 molecular weight (MW) ladder was loaded as a weight reference. Protein extracts cover a range of sizes. **ii)** Colourimetric analysis of pECM extracts showing quantification (µg/mg ECM) of non-collagenous proteins (NCPs), glycosaminoglycans (GAGs) and soluble collagen content in the three separate pECM extractions. **B)** Coomassie blue staining of **i)** uncoated control and **ii)** pECM treated cultureware surfaces. Positive staining of coated dishes shows protein. **C)** Secondary electron photomicrographs from SEM of **i)** untreated culture polystyrene surfaces and **ii)** ECM treated cultureware at x100 magnification. Scale bars are shown. Images demonstrate a change in the surface appearance following ECM coating indicating that protein adsorption to treated surfaces.

**Figure 2.** Data showing the number of adherent primary dental pulp cells **A)** at 24-hours and **B)** at 4-days culture. Cells were seeded on control and pulp ECM (pECM) coated plasticware. No statistical differences were found in cell adhesion numbers after 24 hours. **C)** BrdU proliferation assay in primary dental pulp cell cultures. Cells were counted in 10-fields of view in replicate plates representing over 50% of the total stained area per culture. Data showed a significant decrease in the percentage of cells showing active proliferation in the pulp cell population cultured on pECM coated compared with non-coated cultureware. Standard deviation bars plotted, \* = P<0.05.

**Figure 3. A)** Gene expression analysis for **i)** dentinogenic markers, **ii)** mesenchymal / general stem cell markers, **iii)** pluripotent stem cell markers. Densitometric intensities were normalised against GAPDH and plotted as relative gene expression. Data demonstrated there were statistically significant lower levels of the dentinogenic markers DMP and DSPP when cultured on pulp ECM (pECM) compared with uncoated cultureware in pulp cell populations. The expression of mesenchymal / general and pluripotent stem cell markers was generally increased in cultures on pulp ECM compared with uncoated cultureware. **B)** ArrayScan HCS imaging cytometer (Cellomics, UK) high content analysis of primary pulp cells stained for OCT 3/4 after 4-days culture on uncoated control and pECM coated cultureware. \* =  $P < 0.05$  N=3. **i)** Representative images for OCT 3/4 stained images. N=10. **ii)** Graphical representation showing the percentage of cells in the population that stained positive for OCT3/4. Semi-quantitative data shows increased percentage levels of the population staining positive for OCT 3/4 after culture on pulp ECM compared with control uncoated cultureware surfaces. This work was undertaken at Imagen Biotech, Manchester, UK (<http://www.imagen-biotech.com/>).

**Figure 4. Analysis of pulp cell behaviour at two weeks under different culture conditions. A)** Representative images of alizarin red stained cultures and following quantification are provided. Parentheses with \* indicate between groups which demonstrate statistically significant differences. N=4. **B)** Semi-quantitative gene expression analysis for mineralisation associated transcripts. Levels were normalised to the GAPDH housekeeping gene and densitometric values plotted. Cell cultures analysed were: Unc.+CM = uncoated cultureware with control medium; Unc.+MM = uncoated culture cultureware with mineralisation




medium; pECM+CM = pulp ECM coated cultureware with control medium; pECM+MM = pulp ECM coated cultureware with mineralisation medium. Standard deviation bars plotted.

\* =  $P < 0.05$  as determined by ANOVA with a Tukey post hoc test. N=2.

**Figure 5.** Deposition of mineral on outer surfaces of alginate hydrogels containing pulp ECM components and cells after cultures exposure to control and mineralisation media. **A i)** Representative photographs, and microCT images for the **ii)** sagittal plane in 2D and **iii)** 3D reconstructions of the alginate gels, after 5-weeks culture. **B)** Analysis showing number of pixels above the intensity of the hydroxyapatite phantom mineral threshold in microCT scanned images of alginate gels. Data demonstrated that culture in mineralisation medium resulted in an increase in the number of pixels above the hydroxyapatite phantom mineral threshold density. **C)** Representative photomicrographs of histological sections of the 3% alginate gels containing pulp ECM components and primary pulp cells stained with haemotoxylin and eosin after culture in control medium and mineralisation medium for **i)** 2 weeks, **ii)** 3 weeks, **iii)** 4 weeks, and **iv)** 5 weeks. Images show increased staining on the outer surfaces of gels exposed to mineralisation medium. Scale bars are shown.

**Figure S1.** Viable cells released from different concentrations of alginate hydrogels in the presence or absence of pulp ECM molecules over a two week period. **A)** Photomicrographs of released primary pulp cells after culture for one week in different alginate gel conditions. **i)** 1% alginate gel, **ii)** 1% alginate gel with pECM molecules, **iii)** 3% alginate gel, **iv)** 3% alginate gel with pECM molecules, **v)** 5% alginate gel, and **vi)** 5% alginate gel with pECM

1  
2  
3 molecules. Phase contrast images are representative of cells released from all six gel  
4  
5 conditions showing that released cells could adhere to polystyrene surfaces and retained a  
6  
7 morphological appearance similar to that of controls. Scale bars are shown. **B)** The number  
8  
9 of viable cells released from the gels was determined by Trypan blue staining and standard  
10  
11 cell counts remained relatively constant over the two week period for all six culture  
12  
13 conditions. There was no statistical difference identified between viable cell numbers under  
14  
15 the culture conditions analysed. Standard deviation bars are shown. N=4.  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

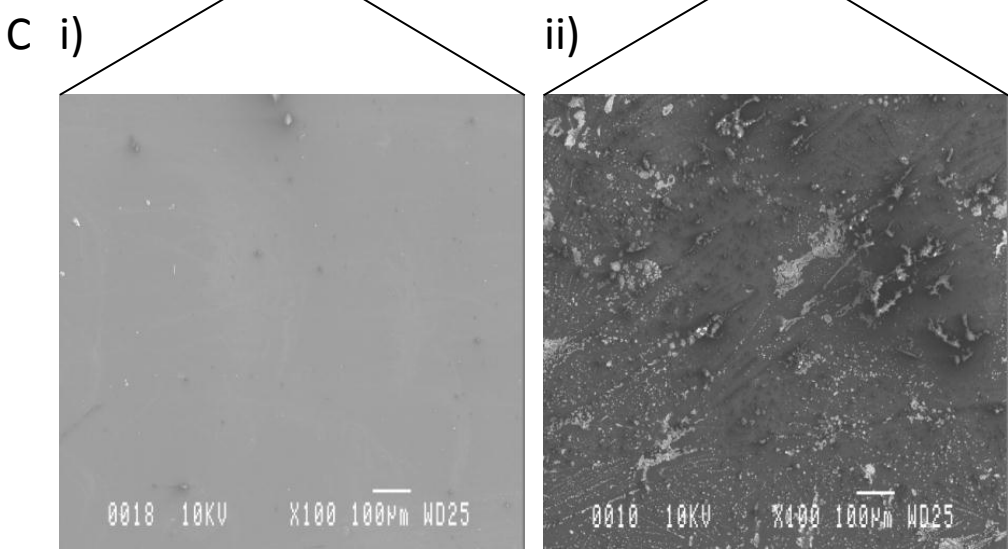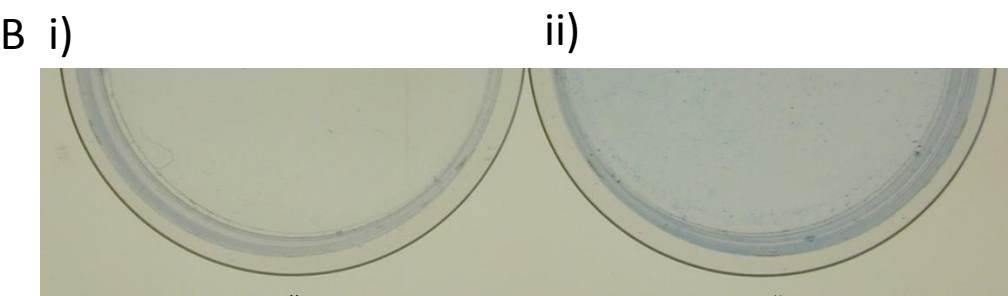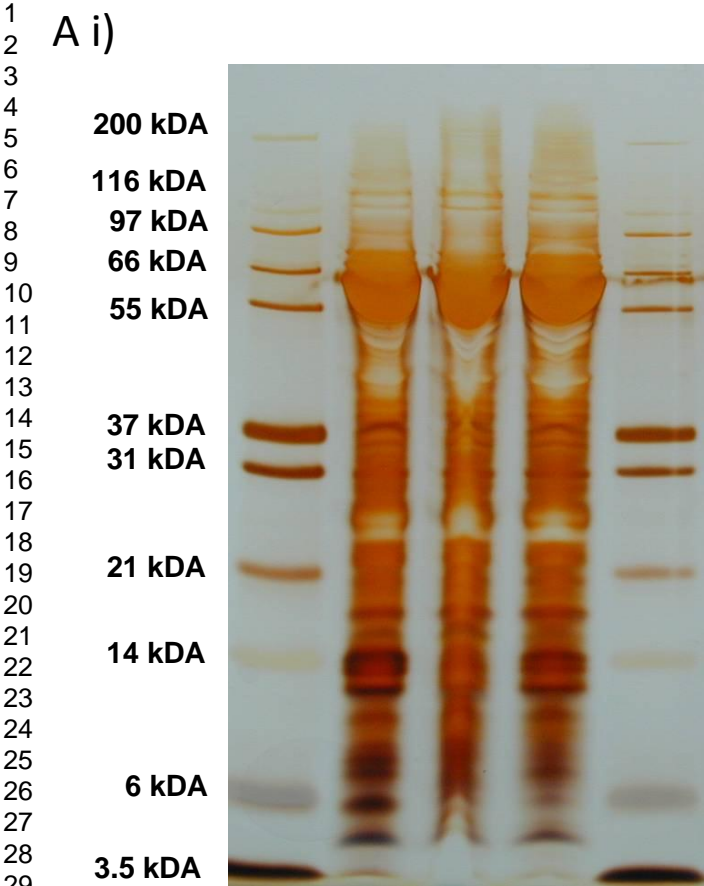


ii)


	ECM 1	ECM 2	ECM 3
NCPs	200.4	235.0	121.5
GAGs	16.1	19.6	11.4
Collagen	142.2	135.6	73.0

Fig 1

A

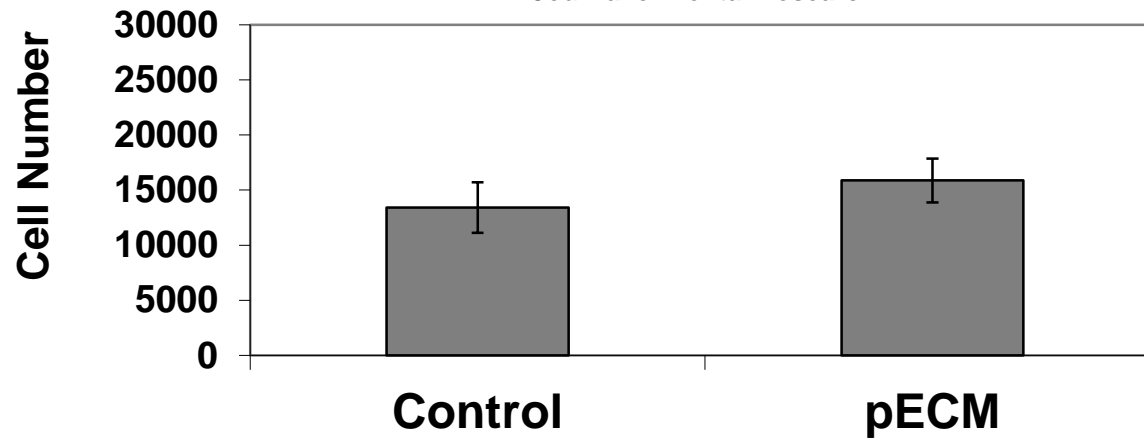

B

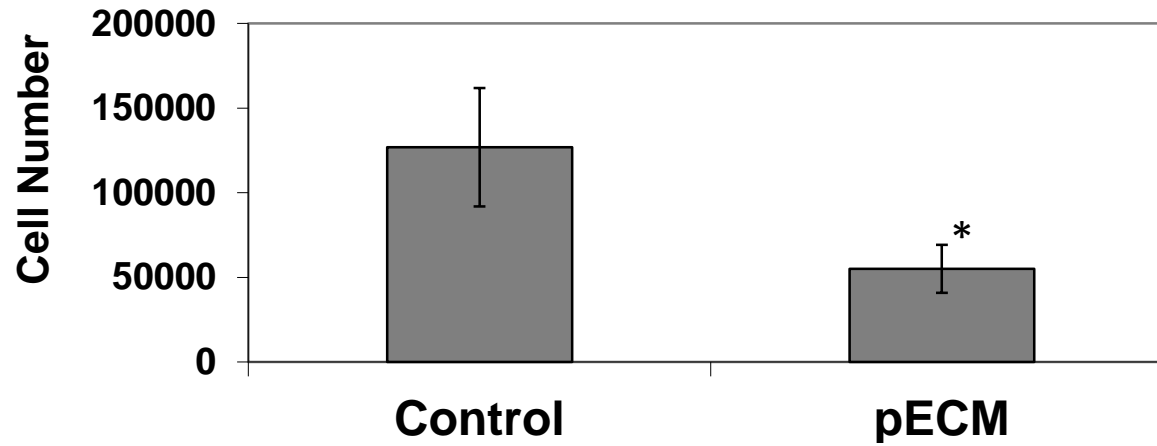

C












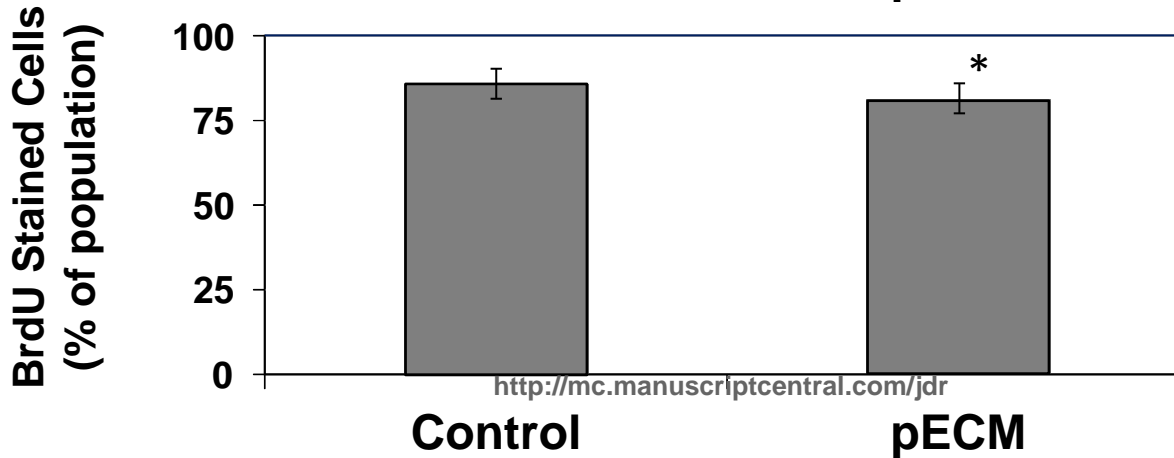


Fig 2

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42

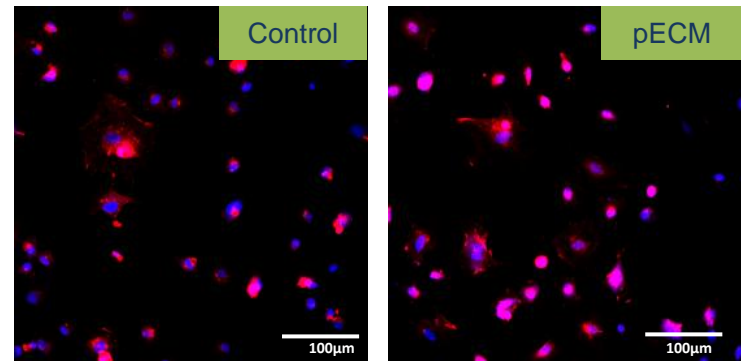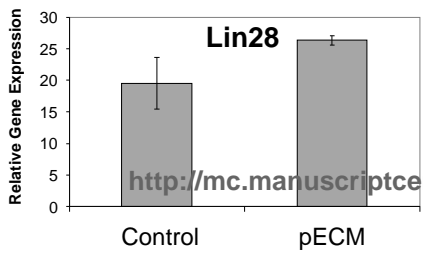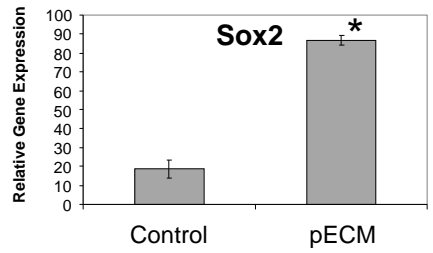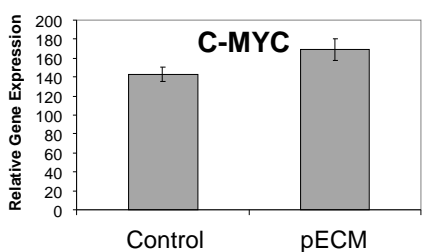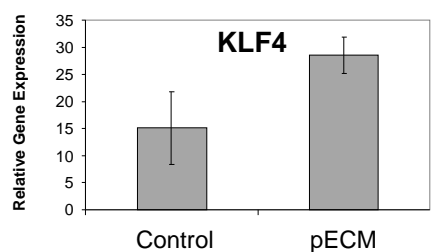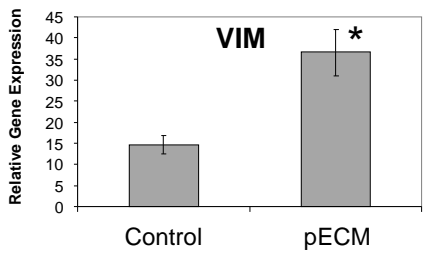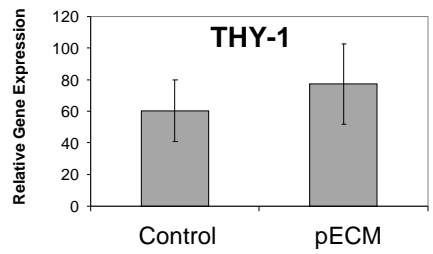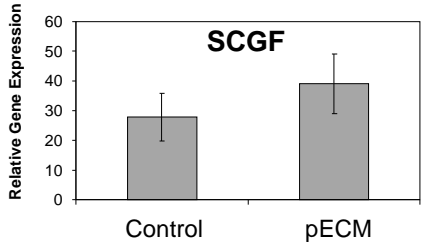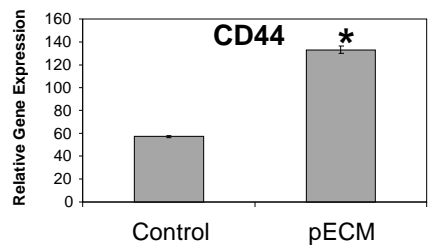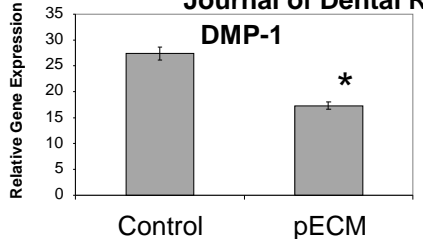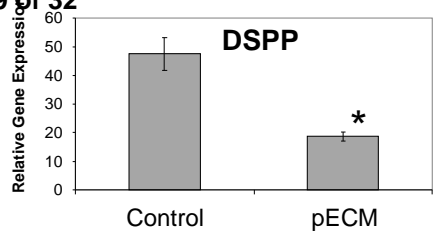

ii)


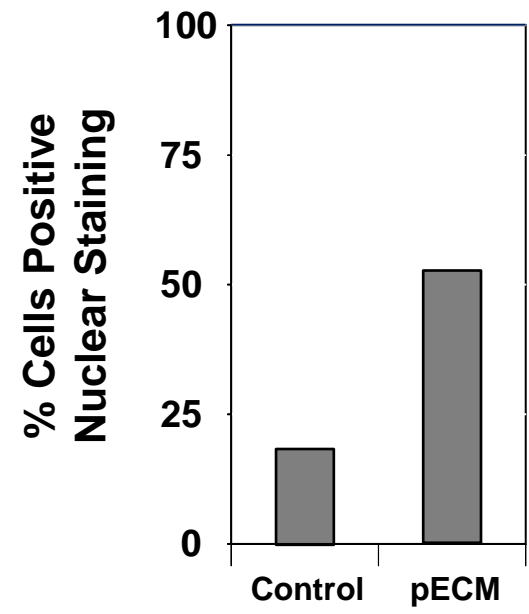


Fig 3

A

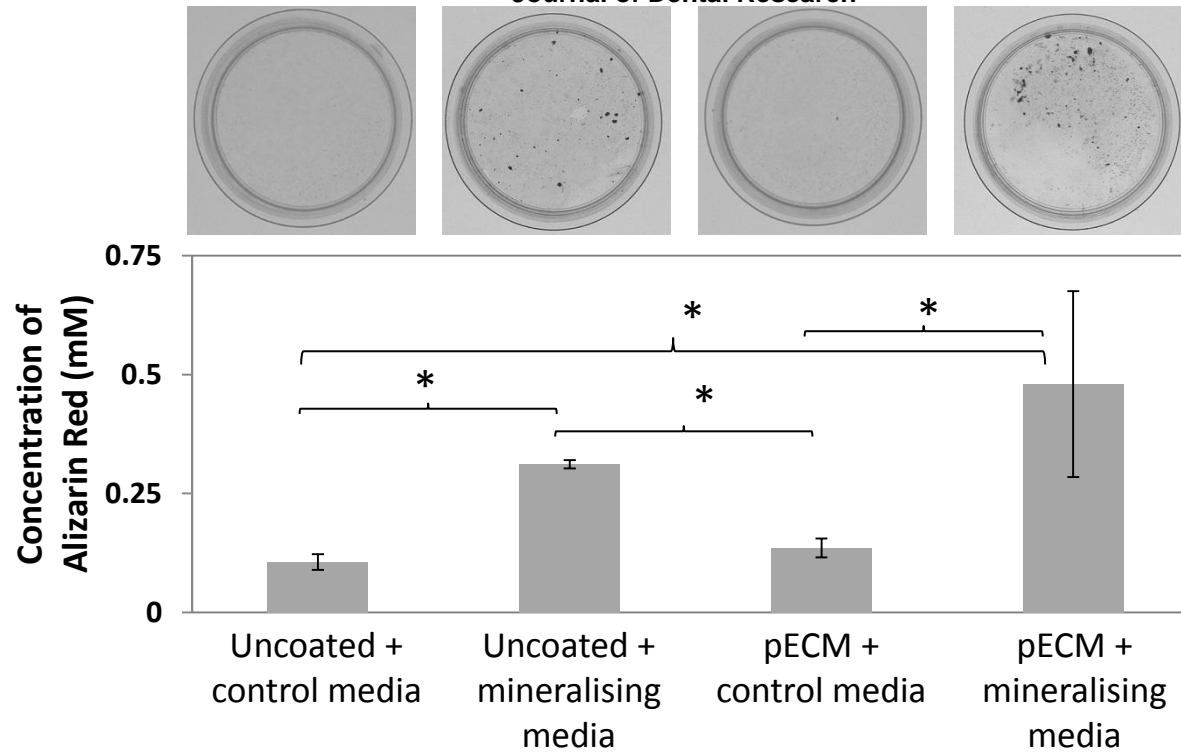

B

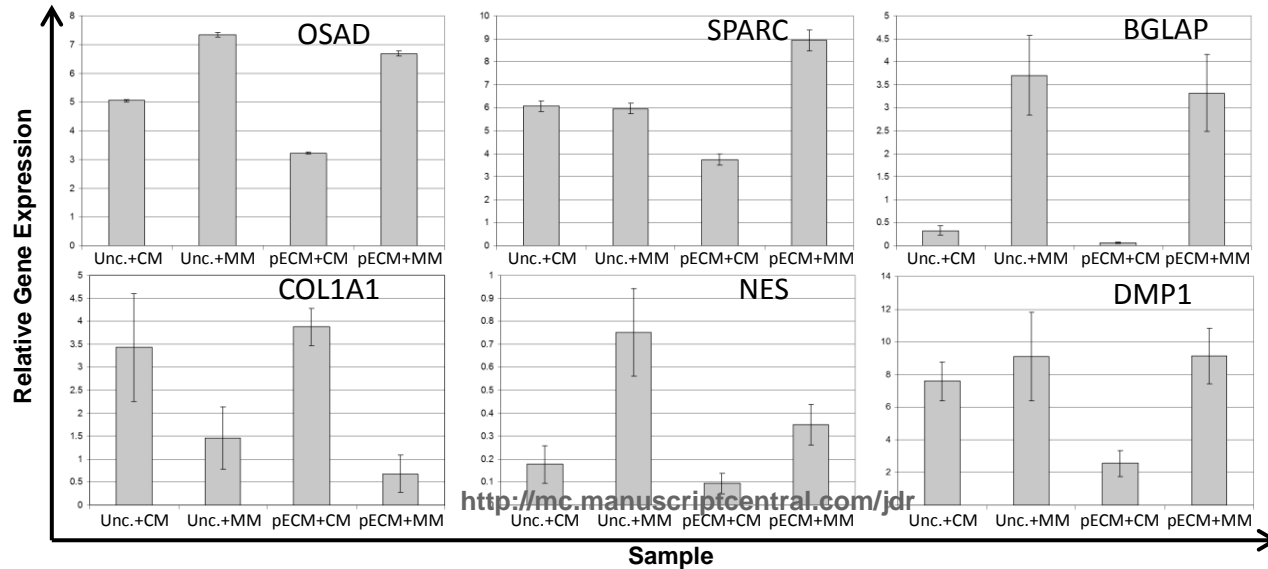


Fig 4



1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42




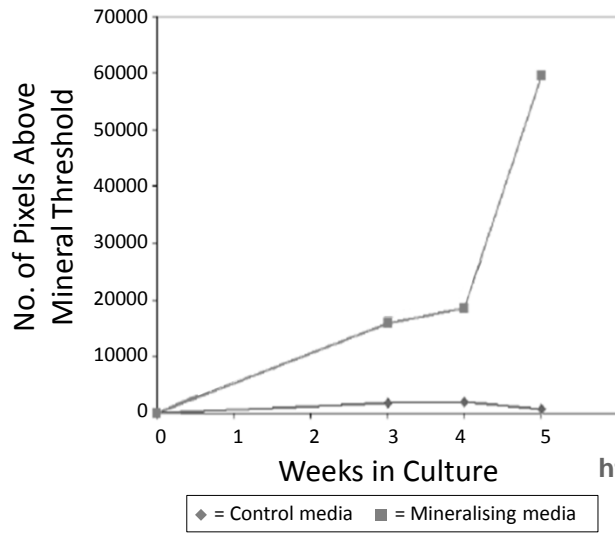


Fig 5


**Supplementary Table.** Rat gene identifiers and primer sequences used in PCR assays. Primers were designed from Genbank sequences using the Primer Blast programme; <http://www.ncbi.nlm.nih.gov/tools/primer-blast/>. Sequences were purchased from Invitrogen, UK. Forward (F) and reverse (R) primer.

Gene	Gene Symbol	Genbank Accession Number	Primer Sequences (5'→3')
Glyceraldehyde 3-phosphate dehydrogenase	GAPDH	NM_017008.4	F-CCC ATC ACC ATC TTC CAG GAG C R-CCA GTG AGC TTC CCG TTC AGC
Dentin sialophosphoprotein	DSPP	NM_012790.2	F-TGC ATT TTG AAG TGT CTC GC R-CCT CCT GTC TTG GTG TGG TT
Dentine matrix protein 1	DMP-1	NM_203493.3	F-CGG CTG GTG GTC TCT CTA AG R-CAT CAC TGT GGT GGT CCT TG
Osteocalcin	Bglap	NM_013414.1	F-TCC GCT AGC TCG TCA CAA TTG G R-CCT GAC TGC ATT CTG CCT CTC T
Osetonectin	SPARC	NM_012656.1	F-AAA CAT GGC AAG GTG TGT GA R-AGG TGA CCA GGA CGT TTT TG
Osteoadherin	Osad	NM_031817.1	F-AAC CTT AGC CAC AAC AAA ATT AA R-TTG CTT CAG TTT GTT ATG TCC
Nestin	Nes	NM_012987.1	F-CAT TTA GAT GCT CCC CAG GA R-AAT CCC CAT CTA CCC CAC TC
Collagen type I alpha	COL1A1	BC133728	F-GGG CAA GAC AGT CAT CGA AT R-TTG GTT TTT GGT CAC GTT CA
SRY-related HMG-box-2	Sox-2	NM_001109181.1	F-ATA CAA GGG AAT TGG GAG GG R-AAA CCC AGC AAG AAC CCT TT
Lin-28 homolog A	Lin28	NM_001109269	F-TTT CTT GTT TCC CCC AAA TG R-AGA GGG GCT GGT TGT AAG GT
Kruppel-like factor 4	Klf4	NM_053713	F-ATC ATGGTCAAGTTCCCAGC R-ACC AAG CAC CAT CGT TTA GG
Cellular Myelocytomatosis Oncogene	C-myc	BC091699	F-CTT ACT GAG GAA ACG GCG AG R-GCC CTA TGT ACA CCG GAA GA
Thymus cell antigen 1	Thy-1 / CD90	NM_012673.1	F-AAC CAG AAC CTT CGA CTG GA R-AGG AAG GAG AGG GAA AGC AG
Vimentin	Vim	NM_031140	F-AGA TCG ATG TGG ACG TTT CC R-GCA GGT CCT GGT ATT CAC G
Cluster of Differentiation 44	CD44	NM_012924.2	F-TGG GTT TAC CCA GCT GAA TC R-CTT GCG AAA GCA TCA ACA AA
Stem cell growth factor	SCGF	NM_001012459	F-CCT TTG AGC AGA GGA AGC AA R-TCA AGG TGC AGG TTG CAC TA

A

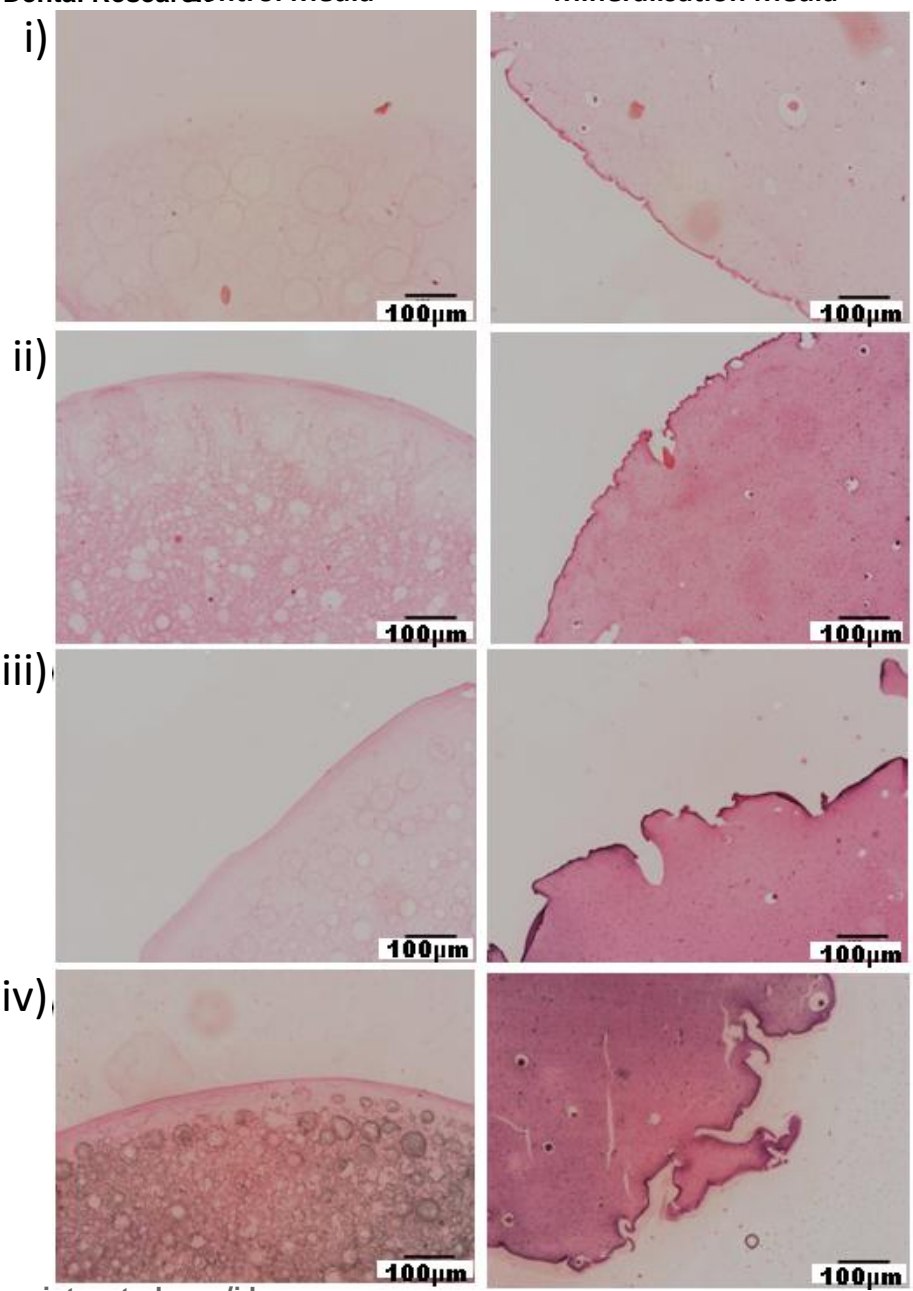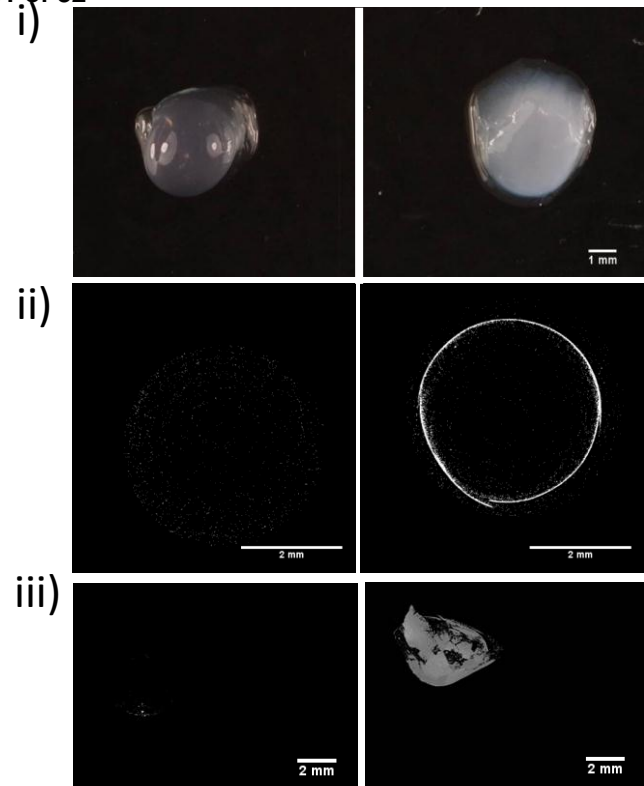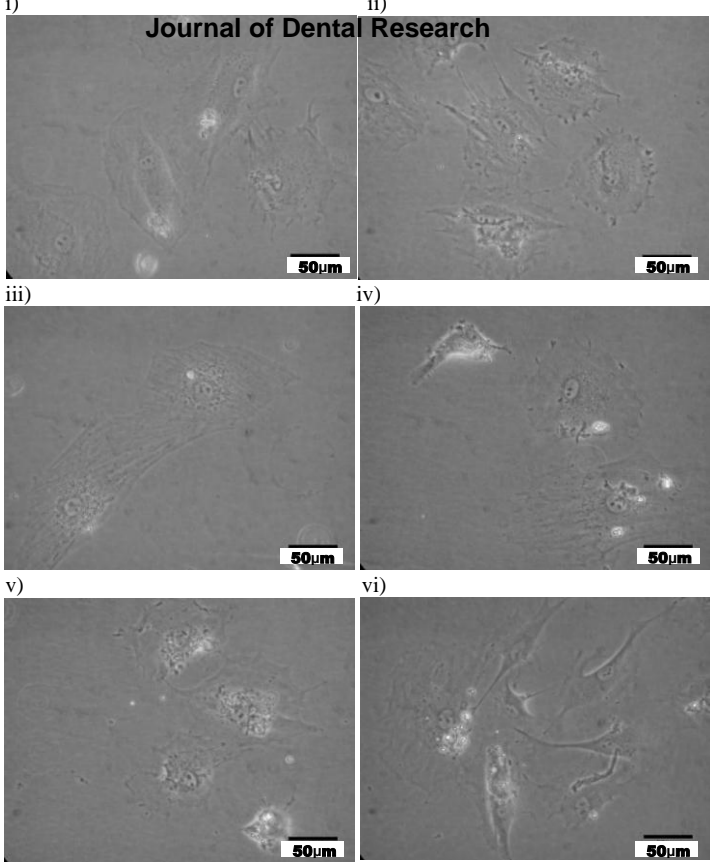

B

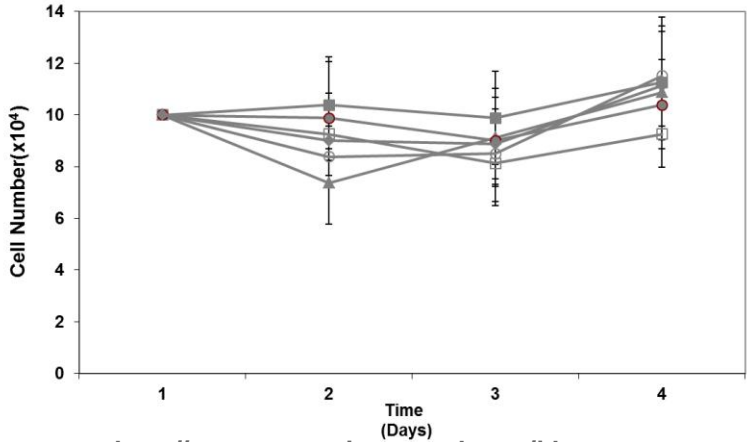

<http://mc.manuscriptcentral.com/jdr>

1% Alginate Gel 1% Alginate Gel containing pECM 3% Alginate Gel  
3% Alginate Gel containing pECM 5% Alginate Gel 5% Alginate Gel containing pECM