

Competing hydrostatic compression mechanisms in nickel cyanide

Adamson, J.; Lucas, Tim; Cairns, A.b.; Funnell, N.p.; Tucker, M.g.; Kleppe, A.k.; Hriljac, Joseph; Goodwin, A.I.

DOI:

[10.1016/j.physb.2015.09.027](https://doi.org/10.1016/j.physb.2015.09.027)

License:

Creative Commons: Attribution-NonCommercial-NoDerivs (CC BY-NC-ND)

Document Version

Peer reviewed version

Citation for published version (Harvard):

Adamson, J, Lucas, T, Cairns, AB, Funnell, NP, Tucker, MG, Kleppe, AK, Hriljac, J & Goodwin, AL 2015, 'Competing hydrostatic compression mechanisms in nickel cyanide', *Physica B - Physics of Condensed Matter*, vol. 479, pp. 35-40. <https://doi.org/10.1016/j.physb.2015.09.027>

[Link to publication on Research at Birmingham portal](#)

Publisher Rights Statement:

Eligibility for repository: Checked on 15/10/2015

General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

Take down policy


While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact UBIRA@lists.bham.ac.uk providing details and we will remove access to the work immediately and investigate.

Author's Accepted Manuscript

Competing Hydrostatic Compression Mechanisms in Nickel Cyanide

J. Adamson, T.C. Lucas, A.B. Cairns, N.P. Funnell, M.G. Tucker, A.K. Kleppe, J.A. Hriljac, A.L. Goodwin

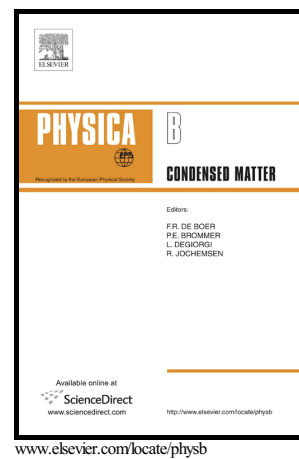

PII: S0921-4526(15)30239-8
DOI: <http://dx.doi.org/10.1016/j.physb.2015.09.027>
Reference: PHYSB309173

To appear in: *Physica B: Physics of Condensed Matter*

Received date: 17 July 2015
Revised date: 11 September 2015
Accepted date: 14 September 2015

Cite this article as: J. Adamson, T.C. Lucas, A.B. Cairns, N.P. Funnell, M.G. Tucker, A.K. Kleppe, J.A. Hriljac and A.L. Goodwin, Competing Hydrostatic Compression Mechanisms in Nickel Cyanide, *Physica B: Physics of Condensed Matter*, <http://dx.doi.org/10.1016/j.physb.2015.09.027>

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting galley proof before it is published in its final citable form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

Competing Hydrostatic Compression Mechanisms in Nickel Cyanide

J. Adamson^{a,b}, T. C. Lucas^c, A. B. Cairns^a, N. P. Funnell^a, M. G. Tucker^{d,e}, A. K. Kleppe^e, J. A. Hriljac^c, A. L. Goodwin^a^aDepartment of Chemistry, University of Oxford, Inorganic Chemistry Laboratory, South Parks Road, Oxford OX1 3QR, U.K.^bNational Institute of Chemical Physics and Biophysics, Akadeemia tee 23, 12618 Tallinn, Estonia^cSchool of Chemistry, University of Birmingham, Edgbaston, Birmingham B15 2TT, U.K.^dISIS Facility, Rutherford Appleton Laboratory, Harwell Oxford, Didcot, Oxfordshire OX11 0QX, U.K.^eDiamond Light Source, Chilton, Oxfordshire, OX11 0DE, U.K.**Abstract**

We use variable-pressure neutron and X-ray diffraction measurements to determine the uniaxial and bulk compressibilities of nickel(II) cyanide, Ni(CN)₂. Whereas other layered molecular framework materials are known to exhibit negative area compressibility, we find that Ni(CN)₂ does not. We attribute this difference to the existence of low-energy in-plane tilt modes that provide a pressure-activated mechanism for layer contraction. The experimental bulk modulus we measure is about four times lower than that reported elsewhere on the basis of density functional theory methods [*Phys. Rev. B* **83**, 024301 (2011)].

Keywords: compressibility mechanisms, high-pressure crystallography, negative area compressibility

1. Introduction

From a lattice dynamical perspective, molecular frameworks have provided an extraordinary number of interesting examples that challenge our understanding of how materials should respond to external stimuli such as temperature and pressure. Negative thermal expansion in the Zn(CN)₂ family [1, 2], pressure-induced and thermal amorphisation in metal–organic frameworks (MOFs) such as ZIF-8 [3, 4], and “breathing” transitions in the MIL-53 and MIL-101 systems are all popular examples [5, 6]. A related phenomenon to receive particular recent interest is that of negative compressibility, whereby a material actually expands in one or more directions under application of hydrostatic pressure [7, 8]. While it is now emerging that negative linear compressibility (NLC) might be somewhat more widespread amongst molecular frameworks and molecular crystals than originally thought [9], the much rarer property of negative area compressibility (NAC)—where a system reduces its volume by expanding simultaneously in two orthogonal directions—remains known to occur in only a handful of materials [10, 11, 12]. The development of a microscopic understanding of NAC and its lattice dynamical origins is crucial if we are ever to design improved NAC candidates for application in next-generation ferroelectric sensor technology [7].

Arguably the clearest lattice dynamical signature of NAC established to date is the existence of so-called Lifshitz modes in layered framework materials. These modes are low-energy vibrations of weakly-coupled layers in which atomic displacements are polarised perpendicular to the layer plane [Fig. 1]. The relationship with NAC arises from a combination of a large and negative elastic compliance S_{13} —linking interlayer compression with layer expansion—and a small value of the elastic constant C_{33} which reflects facile compression along the layer stacking axis. As a consequence, one design strategy for identifying

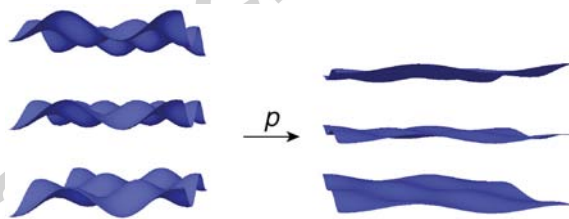


Figure 1: The Lifshitz instability in layered materials involves displacement of atoms within layers in a direction parallel to the layer stacking axis. Increased population of Lifshitz modes results in a reduction of the effective cross-sectional area of each layer, which couples to an expansion of the inter-layer separation. The Lifshitz mode is associated with negative area compressibility in cases where volume reduction under hydrostatic pressure results in rapid inter-layer collapse that couples with damping of the Lifshitz modes.

new NAC candidates has been to focus on layered systems with very weak inter-layer interactions, such as is observed in the key NAC system silver(I) tricyanomethanide [11].

It was in this context that we sought to study the high-pressure structural behaviour of nickel(II) cyanide, Ni(CN)₂. The structure of this material is described by stacked square layers, each assembled from square-planar Ni²⁺ ions connected via linear Ni–C–N–Ni linkages [Fig. 2] [13, 14]. The interaction between layers is considered to be weak on the basis of a number of observations. First, Ni(CN)₂ exhibits strong positive thermal expansion (PTE) behaviour along the layer stacking axis that is coupled to area negative thermal expansion (NTE) within the layer plane [13]; note the magnitude of thermal expansion is usually inversely proportional to the strength of bonding interactions [15]. Second, there is no long-range periodicity within the stacking arrangement, a structural feature which has also been associated with weak inter-layer interactions [14]. And, third, the phonon dispersion curves determined

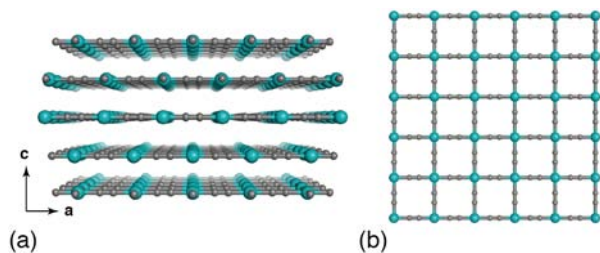


Figure 2: Representation of the structure of $\text{Ni}(\text{CN})_2$. (a) Square-grid layers are stacked along the c crystal axes. Successive layers are shifted by $\frac{1}{2}(100)$ lattice vectors. The existence of choice in this shift direction results in a loss of long-range periodicity along the stacking axis. (b) A single layer is assembled from square-planar Ni^{2+} cations (shown here in teal) connected via linear Ni-C-N-Ni linkages (C/N atoms shown in grey). The orientation of the cyanide ions is disordered throughout the structure. The view direction in (b) is parallel to the c axis.

using density functional theory (DFT) calculations reflect the existence of Lifshitz-like excitations [16]. So the established design criteria for NAC in molecular frameworks would suggest that $\text{Ni}(\text{CN})_2$ should be a prime candidate in which to observe the unusual phenomenon of NAC.

Here we apply a combination of variable-pressure neutron and X-ray powder diffraction measurements to determine experimentally the compressibility behaviour of $\text{Ni}(\text{CN})_2$ over the pressure range $0 < p < 2.5$ GPa. We find no evidence for NAC behaviour, a result we rationalise in terms of the existence of low-energy modes with negative Grüneisen parameters that compete with the Lifshitz modes in allowing volume collapse via layer densification. Subsequent to carrying out our measurements, a related study has appeared in the preprint literature [17]. The experimental results reported by us and by Ref. 17 are broadly similar; however our analysis differs in some important respects. In particular, we interpret our compressibility data in the context of the Grüneisen parameters associated with different types of NTE modes supported by the $\text{Ni}(\text{CN})_2$ structure. Our own paper is arranged as follows. We begin by describing the experimental methods used in our study. We then present the pressure-dependent lattice parameter variation we observe experimentally and report the corresponding lattice and bulk compressibilities. Our manuscript concludes with a discussion of possible microscopic mechanisms responsible for this behaviour, placing our results in the context of previous studies of $\text{Ni}(\text{CN})_2$ and of other NAC materials.

2. Experimental Methods

2.1. Synthesis

Powder samples of $\text{Ni}(\text{CN})_2$ were prepared according to either of two methods. The first method involved heating $\text{Ni}(\text{CN})_2 \cdot 4\text{H}_2\text{O}$ (Alfa Aesar, >99%) under vacuum at 200°C for 24 h [13]. The dehydration process is coupled to a change in colour; the yellow product was stored in a vacuum desiccator to prevent rehydration. The second method involved reaction of aqueous solutions of nickel(II) nitrate (Sigma Aldrich, >99%) and potassium tetracyanonickelate(II) (Sigma Aldrich, >99%)

[18]. The precipitate formed was isolated by vacuum filtration, washed (H_2O) and dried to afford $\text{Ni}(\text{CN})_2 \cdot 4\text{H}_2\text{O}$. This product was dehydrated and stored as described above. Infrared spectroscopy measurements were performed on powder solid samples over the frequency range $600\text{--}4000\text{ cm}^{-1}$, and revealed two features: the CN stretch (2199.22 cm^{-1} , strong), and the Ni-CN stretch (605.96 cm^{-1} , medium) in accordance with previous reports [13, 18].

2.2. Variable-pressure neutron diffraction

Neutron diffraction measurements were carried out using the PEARL instrument at the ISIS neutron spallation source. Hydrostatic pressure was applied using a V4 Paris-Edinburgh press. A powdered sample of $\text{Ni}(\text{CN})_2$, prepared as described above, was loaded into a TiZr gasket together with a Pb pellet and fluorinert as pressure-transmitting medium. The gasket was positioned within a zirconia-toughened alumina anvil with a Los Alamos single toroidal profile. The sample was subjected to a series of eight force values that corresponded to hydrostatic pressures $0 < p < 0.78$ GPa. Pressures were calculated using the third-order Birch-Murnaghan equation of state known for Pb ($V_0 = 30.354\text{ \AA}^3$, $B_0 = 42.0$ GPa, $B' = 5.71$). Neutron scattering data were collected over the d -spacing range $0 < d < 4.1\text{ \AA}$. Constrained Rietveld refinements were used to extract unit cell parameters via the GSAS refinement package [19]. A crystallographic approximant to the “disorder stack” model reported in Ref. 14 was used as the basis of these refinements ($I4_1/amd$, $a \approx 4.9\text{ \AA}$, $c \approx 12.8\text{ \AA}$), together with a stacking-fault model as implemented in GSAS [19]. Our data were not sufficiently discriminating to allow robust refinement of positional parameters.

2.3. Variable-pressure synchrotron X-ray diffraction

Synchrotron X-ray diffraction measurements were carried out using the I15 beamline at the Diamond Light Source. A powdered sample of $\text{Ni}(\text{CN})_2$, prepared as described above, was loaded under a controlled atmosphere into a modified Merrill-Bassett diamond-anvil cell with diamond culets of $450\text{ }\mu\text{m}$. Silicone oil was used as pressure-transmitting medium. Ruby chips, evenly distributed in the pressure chamber, were used to measure the applied pressure according to the ruby fluorescence method [20, 21]. The variation in pressure values determined from different chips was found to be less than 0.1 GPa. For our measurements, five pressures over the range $0 < p < 2.5$ GPa were applied. The observed intensities were integrated as a function of 2θ using the software FIT2D [22, 23] in order to give one-dimensional diffraction profiles. A powder sample of CeO_2 was used to calibrate the beam centre and to determine the sample-to-detector distance. As for the neutron diffraction data, constrained Rietveld refinements were used to extract unit cell parameters via the GSAS refinement package [19]. The same structural model described above was used as the basis of these refinements, and again our data were not sufficiently discriminating to allow robust refinement of positional parameters.

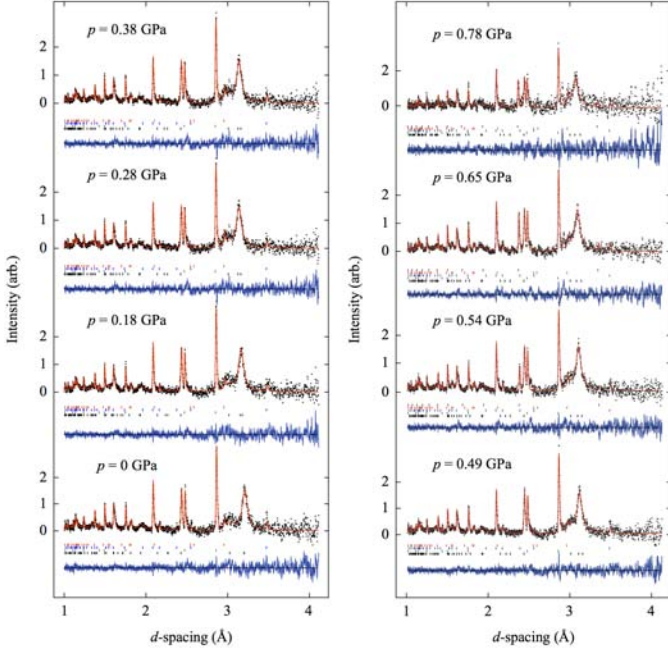


Figure 3: Variable-temperature time-of-flight neutron diffraction patterns collected for $\text{Ni}(\text{CN})_2$ together with fits obtained from Rietveld refinement. Data are shown as black markers; fit as a red line, and difference (data – fit) in blue. Tick marks are given for the various phases included in the fit: (bottom–top) $\text{Ni}(\text{CN})_2$, Pb , Al_2O_3 and ZrO_2 components of the zirconia-toughened alumina (ZTA) anvils, and (optionally) the high-pressure $\text{Ni}(\text{CN})_2$ phase.

3. Results

The time-of-flight neutron diffraction patterns and corresponding fits obtained from Rietveld refinement are shown in Fig. 3. The coexistence of contrasting sharp and broad reflections noted elsewhere [14] as evidence for stacking disorder is clearly visible in our newly-collected data and appears immune to the application of hydrostatic pressure. In contrast to the finding of Ref. 17 we do not find any evidence of a structural phase transition below 0.1 GPa: all data sets collected over the pressure range $0 < p < 0.5$ GPa are well fit using a structural model based on the ambient-pressure structure [14]. At pressures above 0.5 GPa we find a set of additional reflections that can be indexed (very tentatively) on the basis of a new $\text{Ni}(\text{CN})_2$ cell consistent with a defect Prussian blue architecture ($Im\bar{3}m, a \approx 4.8 \text{ \AA}$). In the absence of any noticeable discontinuity in the compressibility of the ambient phase we consider these additional peaks to arise from a slow first-order transition to a high-pressure phase that may be the $p > 0.7$ GPa phase postulated in Ref. 17. Given that only a handful of relatively-weak peaks contribute to this minor component of the diffraction pattern, we cannot have any real confidence in the structural model we have used for this phase in our Rietveld refinement. Nevertheless, the (meta-)stability of the ambient phase to higher pressures allows us to continue to study its compressibility behaviour over the entire pressure regime $0 < p < 2.5$ GPa.

The variation in lattice parameters extracted from our Rietveld fits to these neutron diffraction data—together with

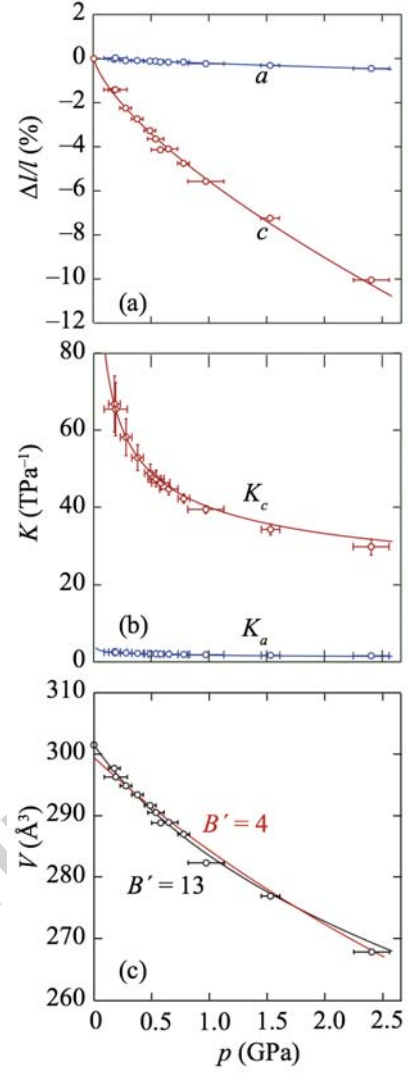


Figure 4: Compressibility behaviour of $\text{Ni}(\text{CN})_2$. (a) Relative change in lattice parameters under hydrostatic pressure: the mechanical response of the system is dominated by compression along c . (b) The corresponding linear compressibilities extracted from the empirical fit to the data in (a) according to Eq. (1). (c) The volume equation of state, shown with both second-order ($B' \equiv 4$) and third-order Birch-Murnaghan fits as described in the text.

those for the X-ray diffraction data (themselves not shown)—is shown in Fig. 4. What is immediately obvious is that the structural response to hydrostatic pressure is dominated by rapid collapse of the inter-layer separation, which corresponds to the c lattice parameter. By contrast the a parameter, which describes the $\text{Ni} \dots \text{Ni}$ separation within an individual square sheet, changes remarkably little under hydrostatic pressure. Of particular note is the absence of any increase in this parameter with pressure, which rules out NAC behaviour in $\text{Ni}(\text{CN})_2$.

The lattice parameter data were fitted in the program PASCAL [24] according to a set of empirical expressions of the form

$$\ell(p) = \ell_0 + \alpha(p - p_c)^\lambda, \quad (1)$$

as described in Ref. 25. The corresponding compressibilities, obtained via the isothermal pressure derivative of Eq. (1), are

shown in Fig. 4(b). Extreme deviations from linear behaviour are observed for the c axis compressibility at low pressures, which suggests strongly anharmonic inter-layer interactions. The linear compressibilities extracted from these fits over the entire pressure range $0 < p < 2.5$ GPa are

$$K_a = +1.8(2) \text{ TPa}^{-1}, \quad (2)$$

$$K_c = +45(2) \text{ TPa}^{-1}. \quad (3)$$

Hence $\text{Ni}(\text{CN})_2$ is essentially incompressible within the layer directions and is about as strongly compressible in a direction parallel to the layer stacking axis as the NAC material silver(I) tricyanomethanide ($K_\ell = +66(20) \text{ TPa}^{-1}$) [11].

A third-order Birch-Murnaghan equation of state [26] describes well the pressure-dependence of the unit cell volume [Fig. 4(c)]. The corresponding zero-pressure bulk modulus is determined as $B_0 = 11.7(1.8)$ GPa with a first pressure derivative $B' = 12(3)$. Taken together these values reflect a compliant material which rapidly stiffens on application of hydrostatic pressure [27]. Our values are consistent with other cyanides and layered molecular frameworks [11, 28] but contrast with those reported in Refs. 16, 17: $B_0 = 105(2)$ GPa ($0 < p < 0.1$ GPa; experiment), $15.4(2)$ GPa ($0.1 < p < 18$ GPa; experiment), and 63.4 GPa (DFT).

4. Discussion and Conclusions

There are two obvious questions posed by these results, and we proceed to answer these in turn. The first is why there might be such a discrepancy between the compressibility values determined here and those reported in Refs. 16 and 17. Whereas the second—and arguably the more important—concerns why $\text{Ni}(\text{CN})_2$ *does not* show NAC when its structure possesses all the design motifs thought to favour the phenomenon. Answering this particular question is key to informing future design strategies for targeting NAC behaviour in other materials.

With respect to the apparent discrepancies in compressibility amongst the various studies of the lattice dynamics of $\text{Ni}(\text{CN})_2$, we address first the difference between experimental and computational (DFT) results. The DFT study of Ref. 16 was always going to be difficult because the layer stacking sequence in $\text{Ni}(\text{CN})_2$ has no true periodicity along the stacking axis [14], and so the material structure is inconsistent with the presumption of crystallinity inherent to DFT methods. The work-around devised in that study was to use a modified layer stacking arrangement in which the layers were separated by twice their normal distance and placed directly above one another rather than offset by $\frac{1}{2}\langle 100 \rangle$ as known to occur in the real material. This meant that cell relaxation was not possible and the all-important compressibility in the c direction determined computationally is unlikely to have any physical meaning. Even if a different stacking arrangement had been implemented, it would likely have proven difficult for DFT to determine the correct compressibility given the non-negligible role of thermal fluctuations in modifying the elastic properties of cyanide frameworks with (strictly) linear M–C–N–M linkages [29].

Table 1: Comparison of compressibility behaviour of $\text{Ni}(\text{CN})_2$ determined using neutron and X-ray diffraction methods (our study) and neutron diffraction methods alone (Ref. 17).

	This study	Ref. 17	
K_a (TPa ⁻¹)	+1.8(2)	+2	+3.5
K_c (TPa ⁻¹)	+45(2)	+3.5	+45
B_0 (GPa)	11.7(1.8)	105(2)	15.4(2)
B'	12(3)	≡ 4	≡ 4
Pressure range (GPa)	0–2.5	0–0.1	0.2–2.0

The experimental data of Ref. 17 are much more consistent with our own results, with the exception of the compressibility behaviour at very lowest pressures $0 < p < 0.1$ GPa. It was reported that, over this pressure regime, very little change in the unit cell dimensions is observed but application of hydrostatic pressure (Ar gas) induces an irreversible shift in cyanide stretching frequencies that the authors of Ref. 17 associate with a transition in cyanide ordering. This process is difficult to rationalise in terms of the extremely small $p\Delta V$ driving force (ca 20 J mol⁻¹) and the absence of any variation in neutron scattering intensities as would be expected with the C/N sensitivity offered by the technique. We also find no evidence in our neutron scattering patterns for a difference in cyanide order between the ambient and high-pressure structures of $\text{Ni}(\text{CN})_2$. Given that the neutron and Raman scattering measurements of Ref. 17 were performed under different experimental conditions, and given the absence of a pressure marker in the low-pressure neutron scattering study, we suggest there is sufficient ambiguity regarding this low-pressure regime that the longer-range compressibilities over the pressure range $0 < p < 2.5$ GPa more likely reflect the true pressure response of $\text{Ni}(\text{CN})_2$ [Table 1].

Having established that $\text{Ni}(\text{CN})_2$ shows conventional (positive) area compressibility in the plane perpendicular to its stacking axis, we proceed to discuss how this observation might be consistent with the existence of Lifshitz modes in its lattice dynamics. These modes are characterised by a positive Grüneisen parameter

$$\gamma = -\frac{V}{\omega} \left(\frac{\partial \omega}{\partial V} \right)_T, \quad (4)$$

where ω is the mode frequency and V the unit cell volume.¹ Consequently as V decreases with increasing hydrostatic pressure, the value of ω increases and so the mode occupation number $n(\omega) \simeq k_B T / \hbar \omega$ decreases; this change in frequency is obvious in the spectroscopic measurements of Ref. 17. In other words, the degree of layer rippling is reduced at high pressures and the layer cross-sectional area $A = a^2$ might be expected to expand as a result.

But the $\text{Ni}(\text{CN})_2$ structure supports an additional type of low-energy phonon mode in which $[\text{Ni}(\text{C/N})_4]$ units rotate about

¹Note that the sign of γ is misassigned in Ref. 16 (likely as a result of the particular stacking approximation used), which explains why that study predicts volume NTE at low temperatures in contrast to the PTE behaviour observed experimentally [13].

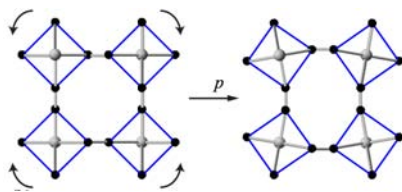


Figure 5: Representative in-plane tilt mode responsible for both area-NTE and positive area compressibility.

an axis parallel to the stacking axis [Fig. 5] [16, 30]. These in-plane tilts give rise to C/N displacements that are polarised within the layer plane and are related to the NTE mechanism thought to operate in the Prussian Blues [31, 32]. The corresponding Grüneisen parameters are now negative because population of these modes leads to volume reduction: while the a lattice parameter decreases as for the Lifshitz modes, this effect is no longer counterbalanced by a change in the stacking axis repeat c . Because $\gamma < 0$ the energy of these modes will decrease on application of pressure—*i.e.* their occupation numbers $n(\omega)$ will increase—leading to a contraction in cross-sectional area A and hence positive compressibility within the (a, b) plane. The absence of NAC in $\text{Ni}(\text{CN})_2$ would suggest that this second mechanism outweighs the Lifshitz mechanism for this material, but what is really needed for quantitative insight here is a computational study that takes into account the experimentally-observed stacking arrangement and allows interpretation of the inelastic neutron scattering results presented elsewhere [17]. One possible avenue would be the development of an *ab initio* force field that might then be used to drive finite-temperature molecular dynamics simulations, as has recently been carried out for $\text{Zn}(\text{CN})_2$ [33].

One further consideration that might be expected to play a role in the contrasting behaviour of $\text{Ni}(\text{CN})_2$ and silver(I) tricyanomethanide is that of ligand field effects. The silver(I) cation has a closed-shell d^{10} configuration, which is notoriously forgiving of variations in metal–ligand bonding geometries. By contrast, the nickel(II) cation has the open-shell d^8 configuration that is strongly stabilised by square planar coordination. Consequently, from a purely crystal field perspective, one might expect $\text{Ni}(\text{CN})_2$ to be less flexible, and hence its dynamics dictated more strongly by the usual bond compression mechanisms responsible for positive compressibility in ordinary materials. Any such crystal field effects should be even more pronounced in the related compounds $\text{Pd}(\text{CN})_2$ and $\text{Pt}(\text{CN})_2$, although the extent to which these two systems are actually isostructural with $\text{Ni}(\text{CN})_2$ remains contentious [34, 35].

In terms of materials design strategies for engineering new NAC systems, what are the lessons suggested by our study? Perhaps the most obvious is that the existence of Lifshitz modes in a layered material does not guarantee NAC. We have suggested elsewhere that a natural domain in which to search for NAC candidates is amongst materials that show area-NTE [11, 9]. What has emerged in our study is that the existence of area NTE is not necessarily diagnostic of NAC since there are competing NTE mechanisms—*e.g.* in-plane tilts—which will

contribute to NTE but will drive positive area compressibility under hydrostatic conditions. So in searching for layered NAC candidates, the strategy that emerges is to focus on systems where any low-energy in-plane modes are frustrated; *e.g.* via network interpenetration, as in silver(I) tricyanomethanide itself [11].

Acknowledgements

We gratefully acknowledge financial support from ESFUSA and St Anne’s College Oxford to J.A., from the E.R.C. (Grant 279705) to A.B.C., N.P.F. and A.L.G. and from the E.P.S.R.C. (Grant EP/G004528/2) to A.L.G. We are grateful to the ISIS and Diamond Light Source facilities for access to neutron and synchrotron beamtime, respectively.

References

- [1] D. Williams, D. E. Partin, F. J. Lincoln, J. Kouvetakis, M. O’Keeffe, The disordered crystal structures of $\text{Zn}(\text{CN})_2$ and $\text{Ga}(\text{CN})_3$, *J. Solid State Chem.* 134 (1997) 164–169.
- [2] A. L. Goodwin, C. J. Kepert, Negative thermal expansion and low-frequency modes in cyanide-bridged framework materials, *Phys. Rev. B* 71 (2005) 140301.
- [3] K. W. Chapman, G. J. Halder, P. J. Chupas, Pressure-induced amorphization and porosity modification in a metal–organic framework, *J. Am. Chem. Soc.* 131 (2009) 17546–17547.
- [4] T. D. Bennett, A. L. Goodwin, M. T. Dove, D. A. Keen, M. G. Tucker, E. R. Barney, A. K. Soper, E. G. Bithell, J.-C. Tan, A. K. Cheetham, Structure and properties of an amorphous metal–organic framework, *Phys. Rev. Lett.* 104 (2010) 115503.
- [5] C. Serre, C. Mellot-Draznieks, S. Surblé, N. Audebrand, Y. Filinchuk, G. Férey, Role of solvent-host interactions that lead to very large swelling of hybrid frameworks., *Science* 315 (5820) (2007) 1828–1831.
- [6] Q. Ma, Q. Yang, A. Ghoufi, G. Férey, C. Zhong, G. Maurin, Guest dependent pressure behavior of the flexible MIL-53(Cr): A computational exploration, *Dalton Trans.* 41 (2012) 3915–3919.
- [7] R. H. Baughman, S. Stafström, C. Cui, S. O. Dantas, Materials with negative compressibilities in one or more dimensions, *Science* 279 (1998) 1522–1524.
- [8] A. B. Cairns, J. Catafesta, C. Levelut, J. Rouquette, A. van der Lee, L. Peters, A. L. Thompson, V. Dmitriev, J. Haines, A. L. Goodwin, Giant negative linear compressibility in zinc dicyanoaurate, *Nature Mater.* 12 (3) (2013) 212–216.
- [9] A. B. Cairns, A. L. Goodwin, Negative linear compressibility, *Phys. Chem. Chem. Phys.* 17 (2015) 20449–20465.
- [10] I. Loa, K. Syassen, R. K. Kremer, U. Schwarz, M. Hanfland, Structural properties of NaV_2O_5 under high pressure, *Phys. Rev. B* 60 (1999) 6945–6948.
- [11] S. A. Hodgson, J. Adamson, S. J. Hunt, M. J. Cliffe, A. B. Cairns, A. L. Thompson, M. G. Tucker, N. P. Funnell, A. L. Goodwin, Negative area compressibility in silver(I) tricyanomethanide, *Chem. Commun.* 50 (2014) 5264–5266.
- [12] W. Cai, A. Gladysiak, M. Aniola, V. J. Smith, L. J. Barbour, A. Katrusiak, Giant negative area compressibility tunable in a soft porous framework material, *J. Am. Chem. Soc.* 137 (2015) 9296–9301.
- [13] S. J. Hibble, A. M. Chippindale, A. H. Pohl, A. C. Hannon, Surprises from a simple material—The structure and properties of nickel cyanide, *Angew. Chem. Int. Ed.* 46 (2007) 7116–7118.
- [14] A. L. Goodwin, M. T. Dove, A. M. Chippindale, S. J. Hibble, A. H. Pohl, A. C. Hannon, Aperiodicity, structure, and dynamics in $\text{Ni}(\text{CN})_2$, *Phys. Rev. B* 80 (2009) 054101.
- [15] J. M. Ogborn, I. E. Collings, S. A. Moggach, A. L. Thompson, A. L. Goodwin, Supramolecular mechanics in a metal–organic framework, *Chem. Sci.* 3 (10) (2012) 3011–3017.

- [16] R. Mittal, M. Zbiri, H. Schober, E. Marelli, S. J. Hibble, A. M. Chippindale, S. L. Chaplot, Relationship between phonons and thermal expansion in $\text{Zn}(\text{CN})_2$ and $\text{Ni}(\text{CN})_2$ from inelastic neutron scattering and *ab initio* calculations, *Phys. Rev. B* 83 (2011) 024301.
- [17] S. K. Mishra, R. Mittal, M. Zbiri, R. Rao, P. Goel, S. J. Hibble, A. M. Chippindale, T. Hansen, H. Schober, S. L. Chaplot, New insights into the compressibility and high-pressure stability of $\text{Ni}(\text{CN})_2$ from neutron diffraction, Raman spectroscopy and inelastic neutron scattering (2014) arXiv:1409.2305.
- [18] A. G. Sharpe, *The Chemistry of Cyano Complexes of the Transition Metals*, Academic Press, London, 1976.
- [19] A. C. Larson, R. B. von Dreele, General structure analysis system (GSAS), Tech. Rep. LAUR 86-748, Los Alamos National Laboratory (2000).
- [20] G. J. Piermarini, S. Block, J. D. Barnett, R. A. Forman, Calibration of the pressure dependence of the R_1 ruby fluorescence line to 195 kbar, *J. Appl. Phys.* 46 (1975) 2774–2780.
- [21] H. K. Mao, J. Xu, P. M. Bell, Calibration of the ruby pressure gauge to 800 kbar under quasi-hydrostatic conditions, *J. Geophys. Res.* 91 (1986) 4673–4676.
- [22] A. P. Hammersley, FIT2D: An introduction and overview, Tech. Rep. ESRF97HA02T, European Synchrotron Radiation Facility (1997).
- [23] A. P. Hammersley, S. O. Svensson, M. Hanfland, A. N. Fitch, D. Häusermann, Two-dimensional detector software: From real detector to idealised image or two-theta scan, *High Press. Res.* 14 (1996) 235–248.
- [24] M. J. Cliffe, A. L. Goodwin, PASCAL: A principal-axis strain calculator for thermal expansion and compressibility determination, *J. Appl. Cryst.* 45 (2012) 1321–1329.
- [25] A. L. Goodwin, D. A. Keen, M. G. Tucker, Large negative linear compressibility of $\text{Ag}_3\text{Co}(\text{CN})_6$, *Proc. Natl. Acad. Sci., U.S.A.* 105 (48) (2008) 18708–18713.
- [26] F. D. Murnaghan, The compressibility of media under extreme pressures, *Proc. Natl. Acad. Sci., U.S.A.* 30 (1944) 244–247.
- [27] C. Slebodnick, J. Zhao, R. Angel, B. E. Hanson, Y. Song, Z. Liu, R. J. Hemley, A high pressure study of $\text{Ru}_3(\text{CO})_{12}$ by X-ray diffraction, Raman and infrared spectroscopy, *Inorg. Chem.* 43 (2004) 5245–5252.
- [28] I. E. Collings, A. B. Cairns, A. L. Thompson, J. E. Parker, C. C. Tang, M. G. Tucker, J. Catafesta, C. Levelut, J. Haines, V. Dmitriev, P. Pattison, A. L. Goodwin, Homologous critical behavior in the molecular frameworks $\text{Zn}(\text{CN})_2$ and $\text{Cd}(\text{imidazolate})_2$, *J. Am. Chem. Soc.* 135 (2013) 7610–7620.
- [29] H. Fang, A. E. Phillips, M. T. Dove, M. G. Tucker, A. L. Goodwin, Temperature-dependent pressure-induced softening in $\text{Zn}(\text{CN})_2$, *Phys. Rev. B* 88 (2013) 144103.
- [30] A. L. Goodwin, Rigid unit modes and intrinsic flexibility in linearly bridged framework structures, *Phys. Rev. B* 74 (2006) 134302.
- [31] A. L. Goodwin, K. W. Chapman, C. J. Kepert, Guest-dependent negative thermal expansion in nanoporous Prussian Blue analogues $\text{M}(\text{II})\text{Pt}(\text{IV})(\text{CN})_6 \cdot x\{\text{H}_2\text{O}\}$ ($0 \leq x \leq 2$; $\text{M} = \text{Zn}, \text{Cd}$), *J. Am. Chem. Soc.* 127 (51) (2005) 17980–17981.
- [32] K. W. Chapman, P. J. Chupas, C. J. Kepert, Compositional dependence of negative thermal expansion in the Prussian Blue analogues $\text{M}(\text{II})\text{Pt}(\text{IV})(\text{CN})_6$ ($\text{M} = \text{Mn}, \text{Fe}, \text{Co}, \text{Ni}, \text{Cu}, \text{Zn}, \text{Cd}$), *J. Am. Chem. Soc.* 128 (2006) 7009–7014.
- [33] H. Fang, M. T. Dove, L. H. N. Rimmer, A. J. Misquitta, Simulation study of pressure and temperature dependence of the negative thermal expansion in $\text{Zn}(\text{CN})_2$, *Phys. Rev. B* 88 (2013) 104306.
- [34] S. J. Hibble, A. M. Chippindale, E. J. Bilbé, E. Marelli, P. J. Harris, A. C. Hannon, Structures of $\text{Pd}(\text{CN})_2$ and $\text{Pt}(\text{CN})_2$: Intrinsically nanocrystalline materials?, *Inorg. Chem.* 50 (2011) 104–113.
- [35] A. R. Overy, A. B. Cairns, M. J. Cliffe, M. G. Tucker, A. L. Goodwin, Design of crystal-like aperiodic solids with selective disorder–phonon coupling (2015) arXiv:1508.05909.