

Elastic modulus of concrete made with recycled aggregates

Lye, Chao; Dhir, Ravindra; Ghataora, Gurmel

DOI:

[10.1680/jstbu.15.00077](https://doi.org/10.1680/jstbu.15.00077)

License:

None: All rights reserved

Document Version

Publisher's PDF, also known as Version of record

Citation for published version (Harvard):

Lye, C, Dhir, R & Ghataora, G 2015, 'Elastic modulus of concrete made with recycled aggregates', *Institution of Civil Engineers. Proceedings. Structures and Buildings*. <https://doi.org/10.1680/jstbu.15.00077>

[Link to publication on Research at Birmingham portal](#)

Publisher Rights Statement:

Checked for eligibility: 29/01/2016. Copyright © ICE Publishing, all rights reserved.

General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact UBIRA@lists.bham.ac.uk providing details and we will remove access to the work immediately and investigate.

Elastic modulus of concrete made with recycled aggregates

1 Chao-Qun Lye BSc


PhD Student, School of Civil Engineering, University of Birmingham, Edgbaston, UK

2 Ravindra K. Dhir OBE, BSc, PhD, CEng, MIMMM, HonFICT, HonFICI, FGS

Professor, School of Civil Engineering, University of Birmingham, Edgbaston, UK (Corresponding author: r.k.dhir@dundee.ac.uk)

3 Gurmel S. Ghataora BEng, PhD, MIMMM, MMGS, MIGS, MILT

Senior Lecturer, School of Civil Engineering, University of Birmingham, Edgbaston, UK



A global literature search, in the English medium, on the modulus of elasticity of concrete made with recycled aggregates revealed coarse recycled concrete aggregate (RCA) to be most widely reported, covering 284 publications from 42 countries since 1977 and yielding a 14 500 data matrix for systematic analysis, evaluation and synthesis. The modulus of elasticity of concrete was found to decrease at a decreasing rate with increasing coarse RCA content, giving an average 16% reduction at full natural aggregate replacement. This reduction was found to be dependent on concrete strength, becoming smaller with increasing strength. The relationship between modulus of elasticity and cube strength based on the literature data was compared with Eurocode 2, showing the modulus of elasticity of concrete made with normal aggregate falling from being just below quartzite rock at 100 MPa to limestone rock at 60 MPa concrete strength; for concrete made with 100% coarse RCA, the comparable rock types were found to be limestone and sandstone, respectively. An empirical method for estimating, in conjunction with Eurocode 2, the modulus of elasticity of concrete made with coarse RCA and sustainable measures to compensate for the reduction in the modulus of elasticity are proposed.

1. Introduction

1.1 Background

A great deal has been said about sustainability and, accordingly, the need to maximise the use of recycled and secondary materials. Indeed, the construction industry globally is expected to play a major role in driving this agenda. However, in the final analysis, the acceptance of these materials in practice will depend on real understanding of their performance so that they can be used effectively and appropriately, with confidence and without undue risk.

In the field of concrete construction, billions of tonnes of natural aggregates (NAs) are used per annum worldwide and it is claimed that a significant amount of these can be replaced by recycled aggregates (RAs) arising from construction demolition and excavation. However, in order to adopt the use of RA in concrete construction confidently, it is important that the performance of this material in concrete is well understood and engineers are sufficiently confident in specifying it routinely.

After strength, engineers need to know the deformation properties of concrete, both in the form of load-dependent properties such as the modulus of elasticity and creep and load-independent properties such as shrinkage. Adhered mortar on RA is accepted to lower the modulus of elasticity of concrete made from RAs when compared with corresponding concrete made with virgin NAs but, beyond this, there is no consensus and the information available in the published literature is generally fragmented and design engineers, as well as the standards, remain sceptical about adopting the use of RA in structural concrete. This has hindered progress in establishing the responsible use of RAs in concrete construction.

A series of systematic literature review projects is being undertaken by the authors in order to investigate the effect of RA on the deformation properties of concrete, including the modulus of elasticity, creep and shrinkage. This paper, one of three in the series, deals with the subject of the modulus of elasticity of concrete made with RAs.

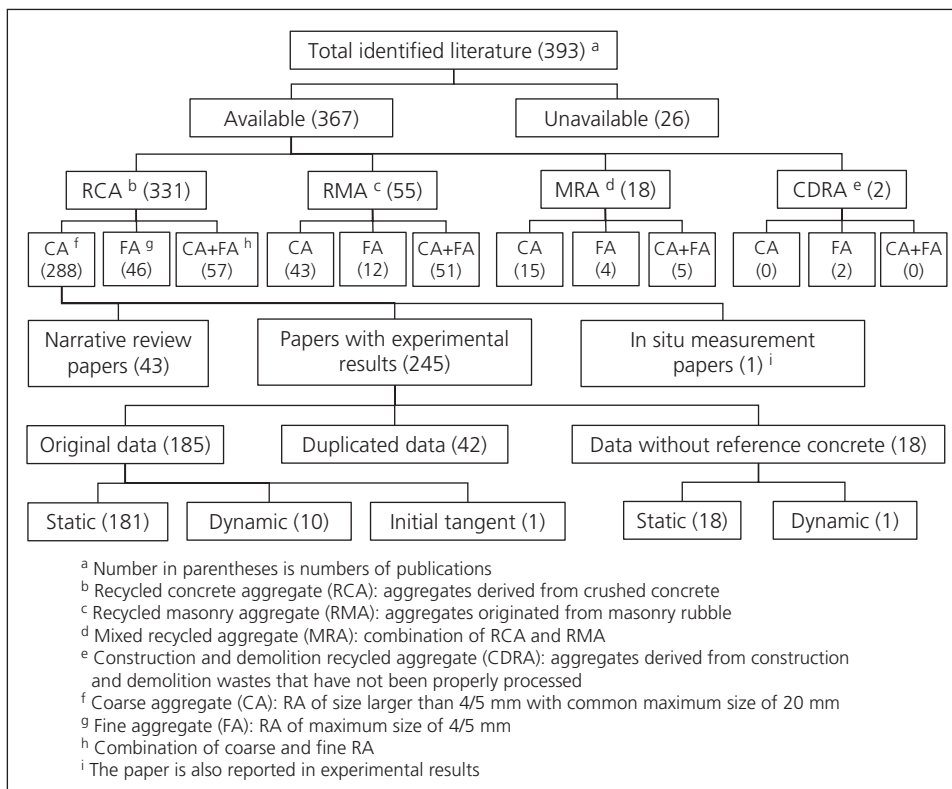


Figure 1. Distribution of publication data from the literature search

1.2 Aims and objectives

The main aim of this study is to systematically analyse, evaluate and synthesise globally published data on the modulus of elasticity of concrete made with RA in relation to that of concrete made with NA and thereby facilitate measures that could be taken to develop its use in practice. It should also help to establish what is known and avoid repetitive research and, instead, direct valuable resources to the information that is still needed.

2. Outline of approach adopted

A near-exhaustive global literature search, but limited to the English medium, was conducted using combinations of keywords defining and elaborating the subject area considered using many sources, such as the American Concrete Institute, American Society of Civil Engineers and Institution of Civil Engineers libraries and engineering village, Google, Google Scholar, Science Direct, Scopus, Springer Link, Taylor & Francis Online and Wiley Online Library.

The search yielded a total of 393 publications, grouped into various categories, as shown in Figure 1. Based on the main composition of RA used, the sourced literature was, in the first place, separated into four RA types (Silva *et al.*, 2014), as described in Figure 1. It can be seen that the use of recycled

concrete aggregate (RCA) as NA replacement has been the subject of investigation of most (90%) and the coarse fraction size has been most commonly used.

Based on material resource availability and potential for use considerations, coarse RCA was selected as the main subject of this project and the relevant published literature was classified into the following three categories (Figure 1).

- Narrative review papers, which present previous research on the modulus of elasticity of concrete made with coarse RCA; these also include codes and proposed specifications.
- Papers with experimental results, in which test data were obtained from dedicated cast specimens, analysed, evaluated and discussed by the researchers of the studies themselves. A further breakdown was also made in which
 - the data available for the modulus of elasticity of RCA concrete and that of the corresponding reference NA concrete are original
 - similar data are reported in more than one publication from the total identified literature
 - the modulus of elasticity of RCA concrete is original but the corresponding information for reference NA concrete is not available.

Measurements of modulus of elasticity in terms of static, dynamic and initial tangent were also separated.

- (c) Papers reporting in situ measurements – the data were obtained from specimens cored from actual concrete structures that had been in service for a period of time.

As the vast majority of the results present the static modulus of elasticity, this narrowed down the research focus of this project to the effect of using coarse RCA as NA replacement on the static modulus of elasticity of concrete. For this, the data used were sourced from 284 publications from review, experimental results and in situ measurement papers (Figure 1), covering over 39 years since 1977 (Figure 2) and originating from 42 countries (Figure 3). Only these 284 publications are listed as references used at the end of the paper.

3. Overview of the literature

From the 43 publications of a review nature, two groups were created based on the origin of the information

- group 1: established organisations, codes and proposed specifications (as listed in Table 1)
- group 2: individual researchers (Agrela *et al.*, 2013; Ajdukiewicz, 2005; Balazs *et al.*, 2008; Behera *et al.*, 2014; de Brito and Alves, 2010; de Brito and Robles, 2010; Dhir *et al.*, 2011; Franklin and Gumedde, 2014; Kukadia *et al.*, 2014; Li, 2008a, 2008b; Marinkovic *et al.*, 2012; McNeil and Kang, 2013; Nixon, 1978; Park *et al.*, 2015; Poon *et al.*, 2003; Ramachandran, 1981; Rao *et al.*, 2007; Safiuddin *et al.* 2013; Safiuddin *et al.*, 2011; Xiao *et al.*, 2006a, 2012a, 2012b).

Given that the main observations of the two groups are broadly the same, only the suggested relative decrease and multiplying factor of modulus of elasticity of RCA concrete with respect to NA concrete from group 1 are compiled as an example in Table 1, which shows the following.

- In general, the use of RCA reduces the modulus of elasticity of RCA concrete as compared with NA concrete, with 100% RCA use giving a reduction of 6–40% (30% on average). At 20% RCA use, one publication suggests the modulus of elasticity remains similar to that of the NA concrete. As expected, at equal water/cement (w/c) ratios, RCA concrete has a lower modulus of elasticity than the corresponding reference NA concrete.
- A multiplying factor of 0.80 has been suggested for concrete made with 100% RCA with concrete strength in the range 37–60 MPa and 0.95 for concrete strength within the range 20–30 MPa. No multiplying factor is required for concrete made with 20% RCA content and, for high-quality RCA, a multiplying factor may also not be necessary for up to 100% RCA replacement of NA.
- Even though the data in the literature are, in the main, limited to 100% RCA replacement of NA, there is a suggestion that the reduction in modulus of elasticity of concrete containing RCA will be affected by the RCA content and RCA properties such as aggregate density and water absorption. Additionally, the literature suggests that the RCA performance relative to NA in concrete can be influenced by its w/c ratio and design strength.

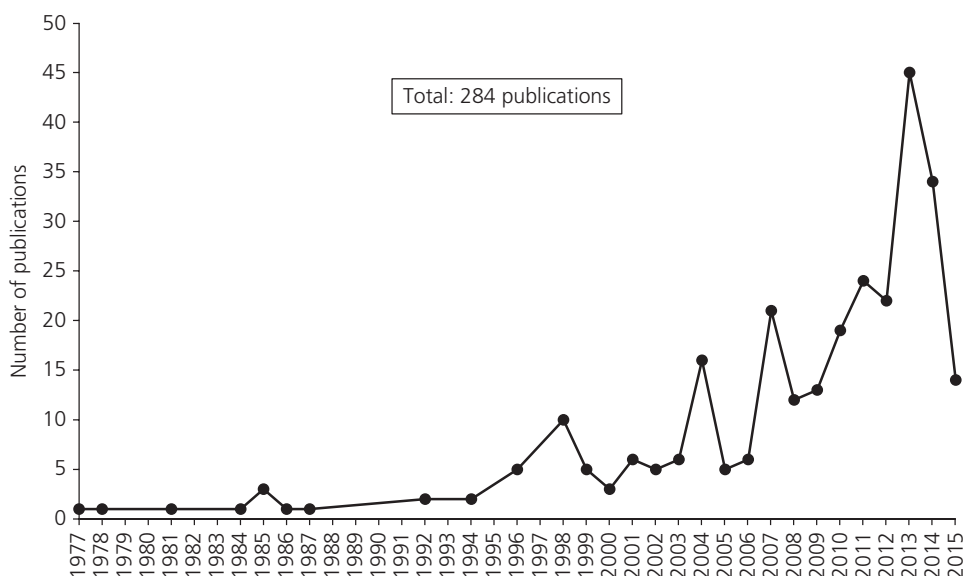


Figure 2. Distribution of publication per year

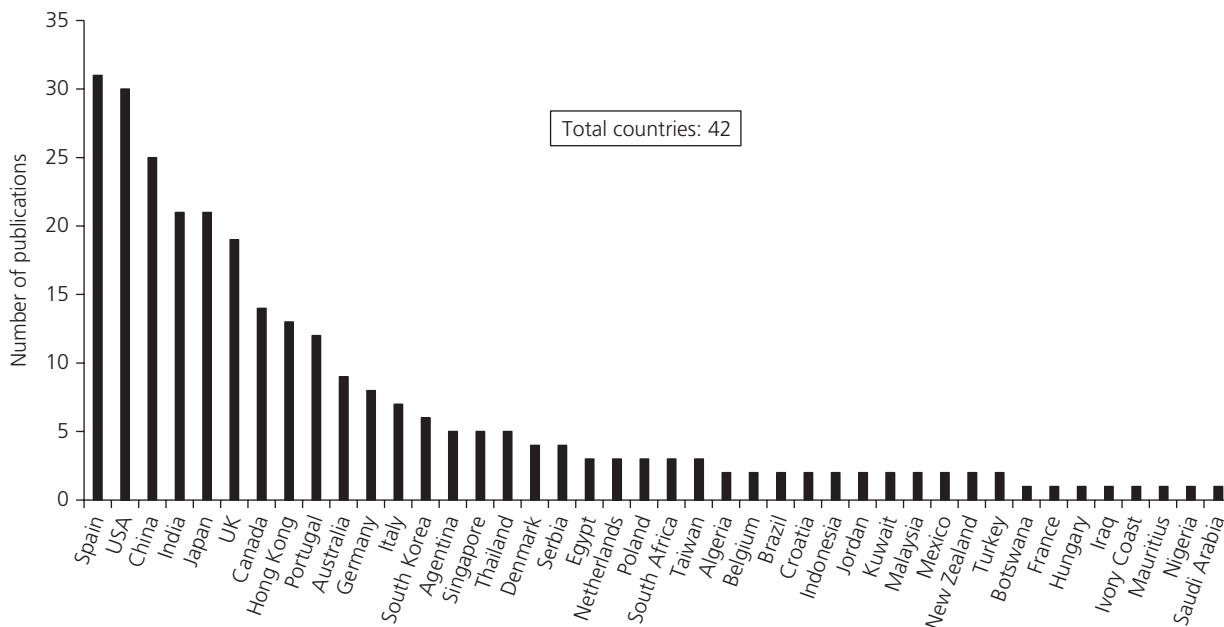


Figure 3. Distribution of country of publication (based on first author)

4. Systematic analysis and evaluation of published data

4.1 Variations in modulus of elasticity tests

Except for the publications with duplicate data, experimental variations in measuring the modulus of elasticity of the test concrete in the literature were categorised into four main groups under the headings of RCA properties, test method, specimen type and curing conditions, as summarised in Table 2 and described in the following.

4.1.1 RCA properties

Of the three basic aggregate properties (specific gravity/density, water absorption and grading), although used in designing concrete mixes, information on the specific gravity and density of RCA in the sourced literature for this study was found to be surprisingly lacking. The water absorption of RCA is reported to be in the range of 3.0–5.9%, which more or less reflects the amount of the adhered cement paste commonly remaining on RCA.

Given that the grading of the aggregates used can greatly influence the performance of concrete, the literature was first screened for aggregate grading in terms of RCA grading being (i) similar or different to the corresponding reference NA or (ii) information of RCA and/or NA was not provided. This showed that only a small number of studies (16%) used the same gradings of both RCA and NA, thus avoiding potential dissimilarity in aggregate packing between the resulting RCA and NA concrete. Surprisingly, 20% of the studies did not

control the aggregate grading and 64% of studies were indifferent to providing grading data for the aggregates used.

As each NA type has its own properties, RCAs are not only affected by the amount of adhered cement paste but also their parent rock type. Thus, in comparing the performance of RCAs with NAs, the same origin material would be ideal for eliminating the effect of the base aggregate material factor. About 18% of the studies reported using NA and RCA having the same original rock base. Of the remaining vast majority of studies, this information was not provided while a few reported that the parent rock of RCA and NA was known to be different.

The moisture condition of the RCA used appears to vary, with about 32% reporting it to be in a saturated surface dry (SSD) state (including pre-saturation), 4% stating air-dry or oven-dry state, 19% not stating but reporting that additional water was added for compensation during mixing and the rest providing no information on moisture condition.

Thus, in dealing with analysis and evaluation of the data, the assumption was made that, ideally, the discrepancies noted above would have been minimal and not significant enough to affect the accuracy of comparison between the data of concrete made with RCA and the corresponding reference NA concrete.

4.1.2 Test method

Almost half of the sourced literature stated the standard test method used to determine the modulus of elasticity of

Reference	Number of references used	Elastic modulus of RA concrete wrt NA concrete		Remarks	
		20% RCA	100% RCA		
Relative performance					
CCAA (2008)	n.a.	n.a.	n.a.	At equal w/c, RCA concrete has lower elastic modulus than NA concrete	
Australia	Sagoe-Crentsil and Brown (1998) (CSIRO)	n.a.	n.a.	≤ 40% lower	
New Zealand	Chisolm (2011) (CCANZ)	n.a.	n.a.	6–33% lower	
Netherlands	Gerardu and Hendriks (1985)(Rijkswaterstaat)	3	n.a.	≤ 15% lower	
Spain	TFSCCS (2004)	n.a.	No change	20–40% lower	
Switzerland	OT 70085 (2006) (reported by de Brito and Saikia (2013))	n.a.	n.a.	20% lower	
	ACI (2001)	1	n.a.	10–33% lower	For 0.45–0.79 w/c ratio
	Anderson <i>et al.</i> (2009) (WSDoT)	1	n.a.	20–40% lower	At equal w/c ratio
	Burke <i>et al.</i> (1992) (INDoT)	2	n.a.	≤ 33% lower	n.a.
USA	Dam <i>et al.</i> (2011) (MDoT)	1	n.a.	10–33% lower	n.a.
	Dam <i>et al.</i> (2012) (NCPTC)	1	n.a.	≤ 30% lower	n.a.
	PCA (2002)	1	n.a.	35% lower	n.a.
	USACE (2004)	n.a.	n.a.	35% lower	n.a.
n.a.	Hansen, 1985, 1992 (Rilem TC 37-DRC)	12	n.a.	≤ 40% lower	n.a.
n.a.	Vazquez, 2013 (Rilem TC 217-PRE)	5	n.a.	n.a.	Elastic modulus decreases as RCA increases
Multiplying factor on RCA concrete					
Belgium	Belgium (not dated) (reported by Vyncke and Rousseau (1994))	n.a.	n.a.	0.80	For RCA with >2100 kg/m ³ dry density, <9% water absorption and max. strength of 37 MPa
Netherlands	CUR-VB (1994) (reported by de Vries (1996))	n.a.	1.00	0.95	For 20–30 MPa concrete
Spain	EHE-08 (2010)	n.a.	1.00	0.80	For 30–50 MPa concrete
n.a.	Rilem TC121 (1994), Hendriks and Henrichsen (1996)	n.a.	n.a.	0.80	For RCA with ≥2000 kg/m ³ dry density, ≤ 10% water absorption and max. strength of 60 MPa
				1.00	For RCA with ≥2400 kg/m ³ dry density, ≤ 3% water absorption and no strength limit

n.a. = not applicable

Table 1. Relative decrease of elastic modulus and multiplying factor for RCA concrete with respect to NA concrete from various organisations and specifications

Parameter	Variable	Number of studies	Parameter	Variable	Number of studies		
RCA properties			Curing conditions				
Specific gravity	<2.3	10	Exposure	Moist	138		
	2.30–2.49	63		Air	3		
2.50–2.69	36	Not given		56			
Density (SSD): kg/m ³	Not given	172	Duration: d	≤ 14	23		
	<2400	11		15–30	110		
	2400–2490	32		>30	8		
	≥ 2500	21	Temperature: °C	Not given	59		
	Not given	218		20–25	58		
Water absorption: %	< 3	27		25–30	14		
	3–5.9	141	40	1			
	6–10	50	Not given	125			
	Not given	63	RH: %	90–100	123		
Grading	Similar	45		50–80	4		
	Different	55	Not given	71			
	Not given	181	Table 2. Continued				
Parent aggregate	Similar	50	concrete, with ASTM C 469 being more common than any other, followed by BS 1881:121. However, the remainder of publications, especially those from Spain, did not provide any information on the test procedure.				
	Different	2	4.1.3 Specimen type				
	Not given	229	Cylinder specimens of various dimensions with height-to-diameter ratios of 2–3 were the most commonly used in determining the modulus of elasticity of the test concrete mixes, with a few studies using prisms.				
Moisture condition when in use	SSD	89	4.1.4 Curing conditions				
	Air dry	9	Moist curing with relative humidity (RH) of 90–100% and temperature 20–30°C for a duration of up to 30 d was the most commonly used in the reported studies. The effect of curing per se has not been the subject of study in the reported literature.				
	Oven dry	4	4.2 Effect of coarse RCA as NA replacement				
	Not given but water added	52	Data on static modulus of elasticity reported in 181 out of 223 studies (excluding 42 duplicate papers) of the sourced literature are plotted in Figure 4. This contains 1311 sets of results with the modulus of elasticity of concrete made with RCA expressed in relative terms to concrete made with NA. Each data point in Figure 4 has been slightly displaced both horizontally and/or vertically in order to avoid overlapping more than one data point at the same location. To visualise distribution of the data, box-and-whisker plots were created at each RCA replacement level and the outliers thus determined. For the purpose of regression analysis, the following data were excluded.				
Test method	Not given	127	■ Cases where the modulus of elasticity of concrete made with RCA was higher than the corresponding concrete made with NA as, like-for-like with adhered cement paste,				
	ASTM C 469 (USA)	36					
		BS 1881:121 (UK)	19				
		LNEC E397 (Portugal)	7				
		DIN 1048 (Germany)	6				
		UNE 83-316 (Spain)	6				
		JIS A 1149 (Japan)	5				
		IS 516 (India)	3				
		UNI 6556 (Italy)	3				
		Others	13				
		Not given	98				
		Specimen type (shape and dimension: mm)	Cylinder ($\varnothing \times h$)	131			
			• 75 × 150	4			
• 100 × 200			42				
• 100 × 250	1						
• 100 × 300	1						
• 120 × 240	1						
• 120 × 360	1						
• 150 × 250	1						
• 150 × 300	59						
• 160 × 320	2						
• Not given	19						
Prism ($l \times w \times h$)	8						
• 100 × 100 × 300	3						
• 100 × 100 × 400	2						
• 150 × 150 × 300	2						
• Not given	1						
Not given	57						

Table 2. Compilation of test parameters of modulus of elasticity of RCA concrete in the literature

- Cases where the modulus of elasticity of concrete made with RCA was higher than the corresponding concrete made with NA as, like-for-like with adhered cement paste,

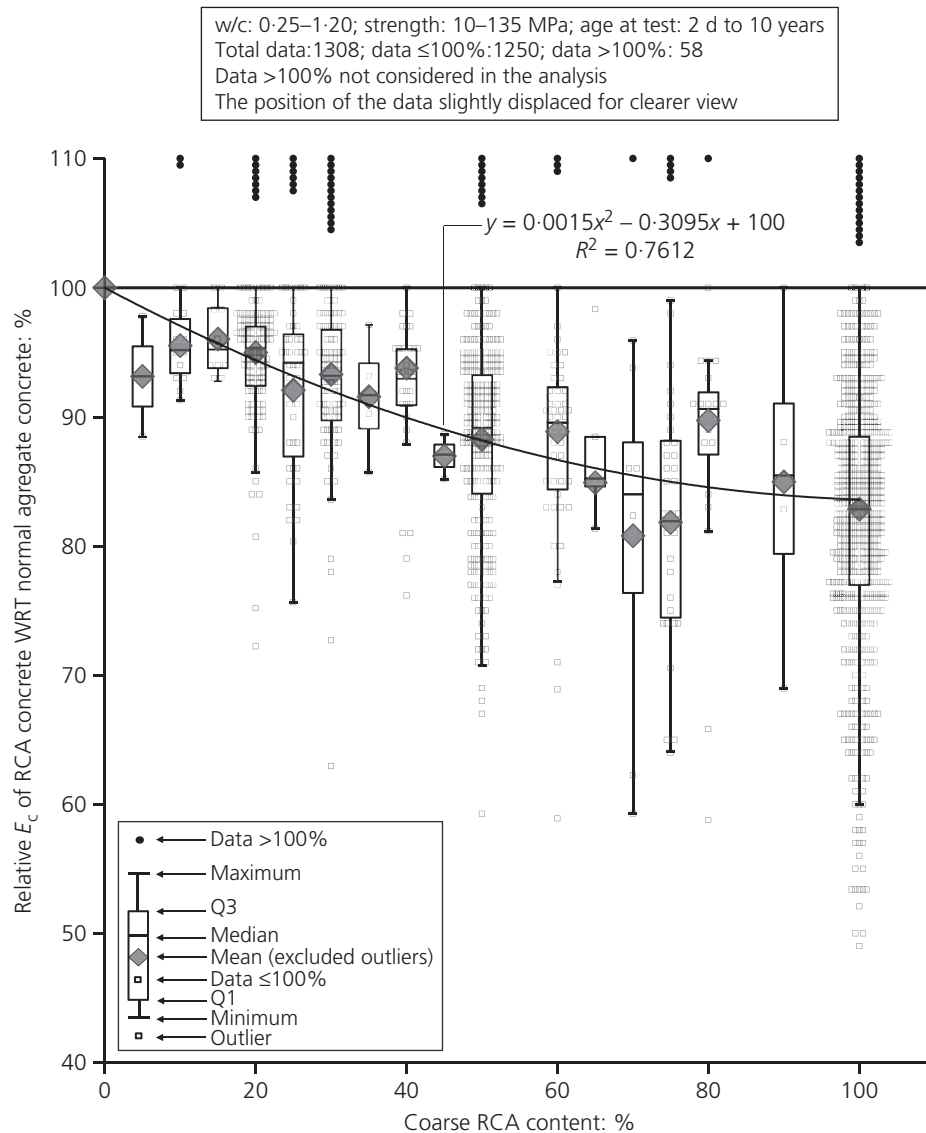


Figure 4. Relative change of modulus of elasticity of coarse RCA with respect to corresponding reference NA in concrete. Data taken from Ahmad *et al.* (1996), Ahmed and Vidyadhara (2013), Ajdukiewicz and Kliszczewicz (2002, 2007), Akbarnezhad *et al.* (2011), Arezoumandi *et al.* (2015), Arundeb *et al.* (2011), Barbudo *et al.* (2013), Beltran *et al.* (2014), Brand *et al.* (2013a, 2013b), Bravo *et al.* (2015), Bretschneider and Ruhl (1998), Butler *et al.* (2013a, 2013b), Cadarsa and Ramchiriter (2014), Castano *et al.* (2009), Casuccio *et al.* (2008), Cervantes *et al.* (2007), Chen (2013), Chen *et al.* (2003a, 2003b, 2014), Choi and Yun (2012, 2013), Collery *et al.* (2015), Corinaldesi (2010, 2011), Corinaldesi *et al.* (2011), Cui *et al.* (2015), Dapena *et al.* (2011), de Juan and Gutierrez (2004), de Oliveira and Vazquez (1996), de Oliveira *et al.* (2004), de Pauw *et al.* (1998), Deshpande *et al.* (2009), Dhir and Paine (2004, 2007), Dhir *et al.* (1999, 2004a), Dilbas *et al.* (2014), Dillmann (1998), Domingo-Cabo *et al.* (2009, 2010), Dosho (2007), Duan and Poon (2014), Duan *et al.* (2013), Eguchi *et al.* (2007), Ekolu *et al.* (2010), Etxeberria *et al.* (2006, 2007a, 2007b),

Fahmy *et al.* (2011, 2012), Fan *et al.* (2014), Fathifazl and Razaqpur (2013), Fathifazl *et al.* (2009a, 2009b, 2009c), Ferreira *et al.* (2011), Folino and Xargay (2014), Fonseca *et al.* (2011), Frondistou-Yannas (1977), Garcia-Navarro *et al.* (2010), Geng *et al.* (2015), Go *et al.* (2007), Gomes and de Brito (2007, 2009), Gomes *et al.* (2014), Gomez-Soberon (2002, 2003), Gomez-Soberon *et al.* (2001, 2002), Gonzalez-Corominas and Etxeberria (2014), Gonzalez-Fonteboa and Martinez-Abella (2004, 2005, 2008), Gonzalez-Fonteboa *et al.* (2011a, 2011b), Grubl *et al.* (1999), Guardian *et al.* (2014), Guo *et al.* (2014), Haitao and Shizhu (2015), Hansen and Boegh (1985), Haque *et al.* (2014), Henry *et al.* (2011), Ho *et al.* (2013), Huda and Shahria Alam (2014, 2015), Ignjatovic *et al.* (2013), Imamoto *et al.* (2004), Inoue *et al.* (2012), Ishiyama *et al.* (2010), Ismail and Ramli (2014), James *et al.* (2011), Kang *et al.* (2014), Kenai *et al.* (2002, 2005), Kenanawati *et al.* (2013), Kerkhoff and Siebel (2001), Khayat and Sadati (2014), Kheder and Al-Windawi (2005), Kikuchi *et al.* (1998), Kim *et al.* (2012), Kiuchi (2001), Kiuchi and Horiuchi

the former cannot give a higher value (i.e. >100%). This accounted for 4.4% of the total data population (i.e. 58 out of 1311 results).

- Outliers determined using the box-and-whisker plots; these amounted to 3.4% of the total data (i.e. 45 results).

A polynomial regression was obtained, giving the best correlation of 0.7612. Overall, and without reference to the RCA properties and concrete strength, this suggests that the modulus of elasticity of concrete made with RCA relative to NA decreases at a decreasing rate with increasing RCA content, reaching a maximum average reduction of 16% at 100% RCA replacement level, and the corresponding values for 20% and 50% RCA replacements being 5% and 12%, respectively.

This finding of 16% reduction in modulus of elasticity for 100% RCA concrete is close to the multiplying factor of 0.80 suggested within the restricted range of aggregate density and water absorption and concrete strength given by (see Table 1)

- the Code on Structural Concrete (EHE-08) of the Spanish Ministry of Development (MdF, 2010)
- recommendations from pilot projects and research work in the Netherlands (as reported by de Vries (1996))
- recommendations from a working group initiated by the Ministry of the Environment and Infrastructure in Belgium (year unknown) (as reported by Vyncke and Rousseau (1994)).
- specifications proposed by Rilem Technical Committee 121 (Rilem TC121, 1994).

As shown in Table 1, similar results are found in technical reports of various organisations and committees based in North America, Europe, Australia and New Zealand published over the period 1986–2012. However, in these cases the relative

reduction of modulus of elasticity was generally in the range 20–40% for 100% RCA concrete.

However, at 20% RCA level, while Figure 4 shows a reduction of 5% in the modulus of elasticity of concrete, reports from Spain (Eguchi *et al.*, 2007; TFSCCS, 2004) and the Netherlands (de Vries, 1996) (Table 1) suggest no change in the modulus of elasticity of concrete at this replacement level. The fact that Figure 4 is based on a vast amount of results sourced from literature published over a period of 39 years and involving RCA characteristics and content and concrete mixes varying over a large range, the reduction in the modulus of elasticity of concrete with the use of RCA is likely to be more representative.

4.3 Effect of RCA on modulus of elasticity in different strength grades of concrete

In order to further analyse the data in Figure 4, the same data were categorised into six different strength groups based on the measured strength of NA concrete, ranging from 15 to 130 MPa, as shown in Figures 5(a)–5(f). In preparing Figure 5

- cylinder strength was converted into cube strength using a factor of 1.25 given in BS EN 12504-1 (BSI, 2009).
- where the specimen type was not indicated in the publications, cube strength was assumed
- data with relative modulus of elasticity values of RCA concrete higher than 100% were excluded in calculation of mean results.

Figures 5(a)–5(f) show that, while the form of the trendlines is essentially similar, collectively the trendlines show that the reduction in modulus of elasticity of RCA concrete relative to NA concrete becomes smaller with increasing concrete strength. To visualise this effect clearly and prepare it for use in practice, the data plotted in Figure 5 were regrouped into

(2003), Knaack and Kurama (2011, 2012, 2013a, 2013b, 2015), Knights (1999), Konin and Kouadio (2012), Kou and Poon (2008, 2013, 2015), Kou *et al.* (2004, 2007, 2008, 2012), Koulouris *et al.* (2004), Kumutha and Vijai (2010), Li *et al.* (2012), Limbachiya (2004, 2010), Limbachiya *et al.* (1998, 2000, 2004, 2012a, 2012b), Liu *et al.* (2011), Lo *et al.* (2013), López-Gayarre *et al.* (2009, 2011), Malesev *et al.* (2010), Manzi *et al.* (2011, 2013a, 2013b), Maruyama *et al.* (2004), Mathew *et al.* (2013), Meinhold *et al.* (2001), Mellman *et al.* (1999), Mendes *et al.* (2004), Mohamad *et al.* (2014), Motwani *et al.* (2013), Nishigori and Sakai (2012), Obla *et al.* (2007), Ong *et al.* (2010), Padmini *et al.* (2009), Paine *et al.* (2009), Park (1999), Paul and van Zijl (2012, 2013), Pecur *et al.* (2015), Pedro *et al.* (2014), Pepe *et al.* (2014), Pickel *et al.* (2014), Poon and Kou (2004, 2010), Poon *et al.* (2006), Prasad and Kumar (2007), Purushothaman *et al.* (2014), Qasrawi (2014), Qasrawi and Marie (2013), Rahal (2007), Rao and Madhavi (2013), Rao *et al.* (2010, 2011a, 2011b),

Rasheeduzzafar and Khan (1984), Ravindrarajah (1996, 2012), Ravindrarajah and Tam (1985), Ravindrarajah *et al.* (1987), Razaqpur *et al.* (2010), Roos (1998), Safiuddin *et al.* (2011), Sakata and Ayano (2000), Salehlamein *et al.* (2015), Salem and Burdette (2001), Salem *et al.* (2003), Sarhat and Sherwood (2013), Sato *et al.* (2007), Schulz (1986), Sheen *et al.* (2013), Sivakumar *et al.* (2014), Soares *et al.* (2014), Somna *et al.* (2012a, 2012b), Surya *et al.* (2013), Suryawanshi *et al.* (2015), Tam *et al.* (2007b, 2013), Tangchirapat *et al.* (2008, 2010, 2013), Teranishi *et al.* (1998), Thomas *et al.* (2013, 2014a, 2014b), Tsujino *et al.* (2007), Ueno *et al.* (2013), Ujike (2000), Uygunoglu *et al.* (2014), Verian *et al.* (2013), Vieira *et al.* (2011), Vyas and Bhatt (2013), Wagih *et al.* (2013), Waleed and Canisius (2007), Wang *et al.* (2013b), Wardeh *et al.* (2015), Xiao *et al.* (2005, 2006b, 2015), Yang *et al.* (2008a, 2008b, 2010, 2012), Yin *et al.* (2010), Yun (2010), Zega and Di Maio (2006, 2009, 2011)

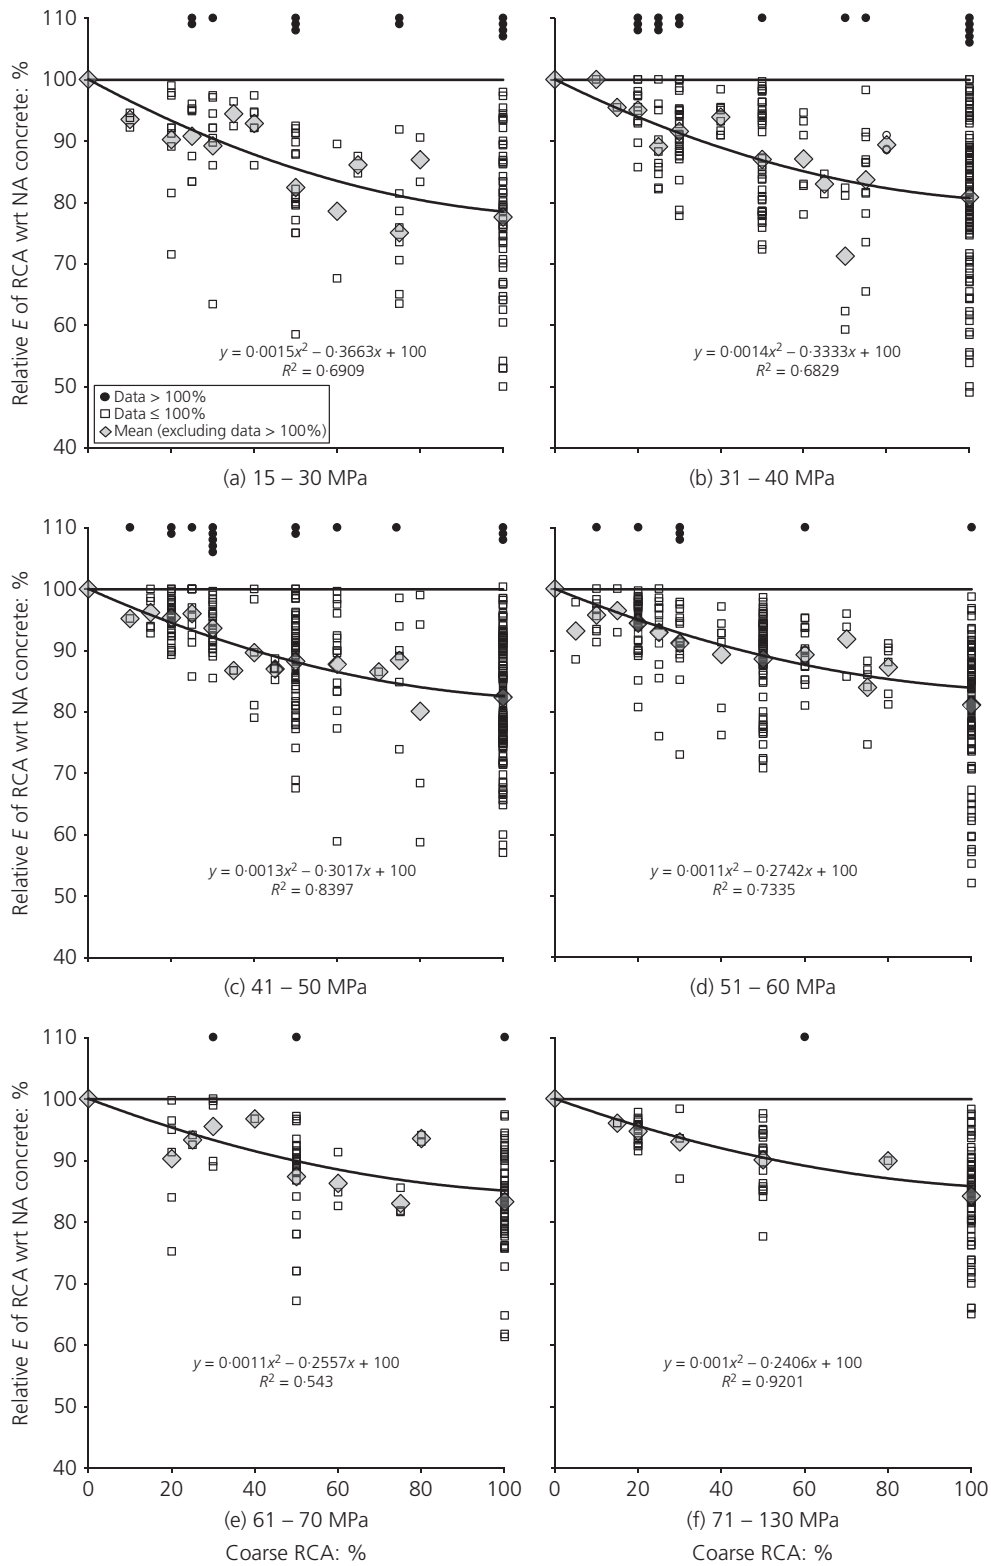


Figure 5. Relative change of modulus of elasticity of coarse RCA with respect to corresponding reference NA in concretes of different strength ranges

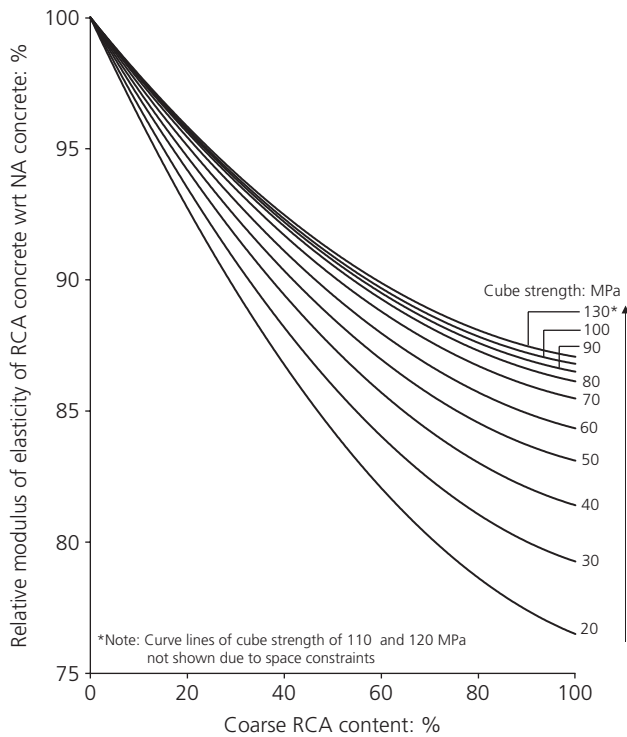


Figure 6. Compilation of relative elastic modulus of coarse RCA concrete with respect to NA concrete for different strength groups

strength increments of 10 MPa ranging from 20 MPa to 130 MPa and the family of curves thus produced is shown in Figure 6. This figure clearly shows the above-mentioned decreasing trend of modulus of elasticity of RCA concrete with increasing strength, albeit opposite to the suggestion made by de Vries (1996). This can be explained in terms of coarse aggregate volume decreasing with increasing concrete strength. In the case of RCA concrete, there is proportionately less adhered mortar, giving rise to a relatively smaller reduction in the modulus of elasticity of RCA concrete.

4.4 Relationship between modulus of elasticity and compressive strength

It is known that the modulus of elasticity of concrete increases with strength but, because RCA has relatively low stiffness compared with the corresponding NA, the increase in modulus of elasticity of RCA concrete would be lower than that in a corresponding reference NA concrete. In order to visualise this in graphical form, the published experimental data of modulus of elasticity for both NA concrete and RCA concrete are plotted against the corresponding cube strength in Figure 7.

The data used to produce Figure 7 were extracted from the sourced literature of 199 publications categorised in Figure 1 under the groupings of ‘original data’ (references as listed for

Figure 4) and ‘data without reference concrete’ (Akhtar and Akhtar, 2014; Bhikshma and Manipal, 2012; Hossain and Sohji, 2004; Jimenez *et al.*, 2013; Morohashi and Sakurada, 2007; Morohashi *et al.*, 2007; Olanike, 2014; Paine and Dhir, 2010; Pecur *et al.*, 2013; Radonjanin *et al.*, 2013; Salem *et al.*, 2001; Song *et al.*, 2015; Tam and Tam, 2008; Tam *et al.*, 2006, 2007a; Wang *et al.*, 2013a; Wu *et al.*, 2013; Yanagi *et al.*, 1998), initially rendering a total data population of 2008, from which 54 results (2.7% of the total) were excluded for reasons such as

- the specimens were subjected to elevated temperature after moist curing for 28 d followed by a pre-conditioning period, resulting in low modulus of elasticity values
- very high or low modulus of elasticity values that could not be justified.

The cube strength data used in developing the plots in Figure 7 were either as given in the literature or were converted from the given cylinder strength using a multiplying factor of 1.25 as given in BS EN 12504-1 (BSI, 2009).

For comparison purposes, the modulus of elasticity of concretes made with different NAs (i.e. basalt, quartzite, limestone and sandstone) as obtained from Eurocode 2 (BSI, 2004) are also shown in Figure 7. Although some papers identified the nature of the rock type of the NAs used (commonly limestone and granite), this was not sufficient for use in any further analysis. Interestingly, however, the trendlines for NAs fall within the sandstone and limestone values when the strength was less than 60 MPa and between limestone and quartzite values for strength higher than 60 MPa.

To see the effect of RCA replacement level on the modulus of elasticity of concrete, the trendlines in Figures 7(a)–7(f) are plotted together in Figure 8. This shows that, as RCA content increases, the trendline moves towards to the values of concrete made with sandstone: at 100% RCA content and a cube strength of 35 MPa, the modulus of elasticity of RCA concrete would be similar to that of concrete made with coarse sandstone aggregate.

5. Estimation of modulus of elasticity of RCA concrete

The modulus of elasticity of RCA concrete for a given characteristic cube strength of 15–105 MPa and coarse RCA content of 0–100% can be estimated using Figure 9 in conjunction with Eurocode 2 (BSI, 2004), which is required to obtain the corresponding modulus of elasticity of NA concrete to start the process.

In developing Figure 9, the analysis of the published data used previously for Figures 5 and 6 was adopted in conjunction with the coefficient of variation of 12.5% given in ACI 301-05 (ACI, 2005) for fair construction quality control for calculating

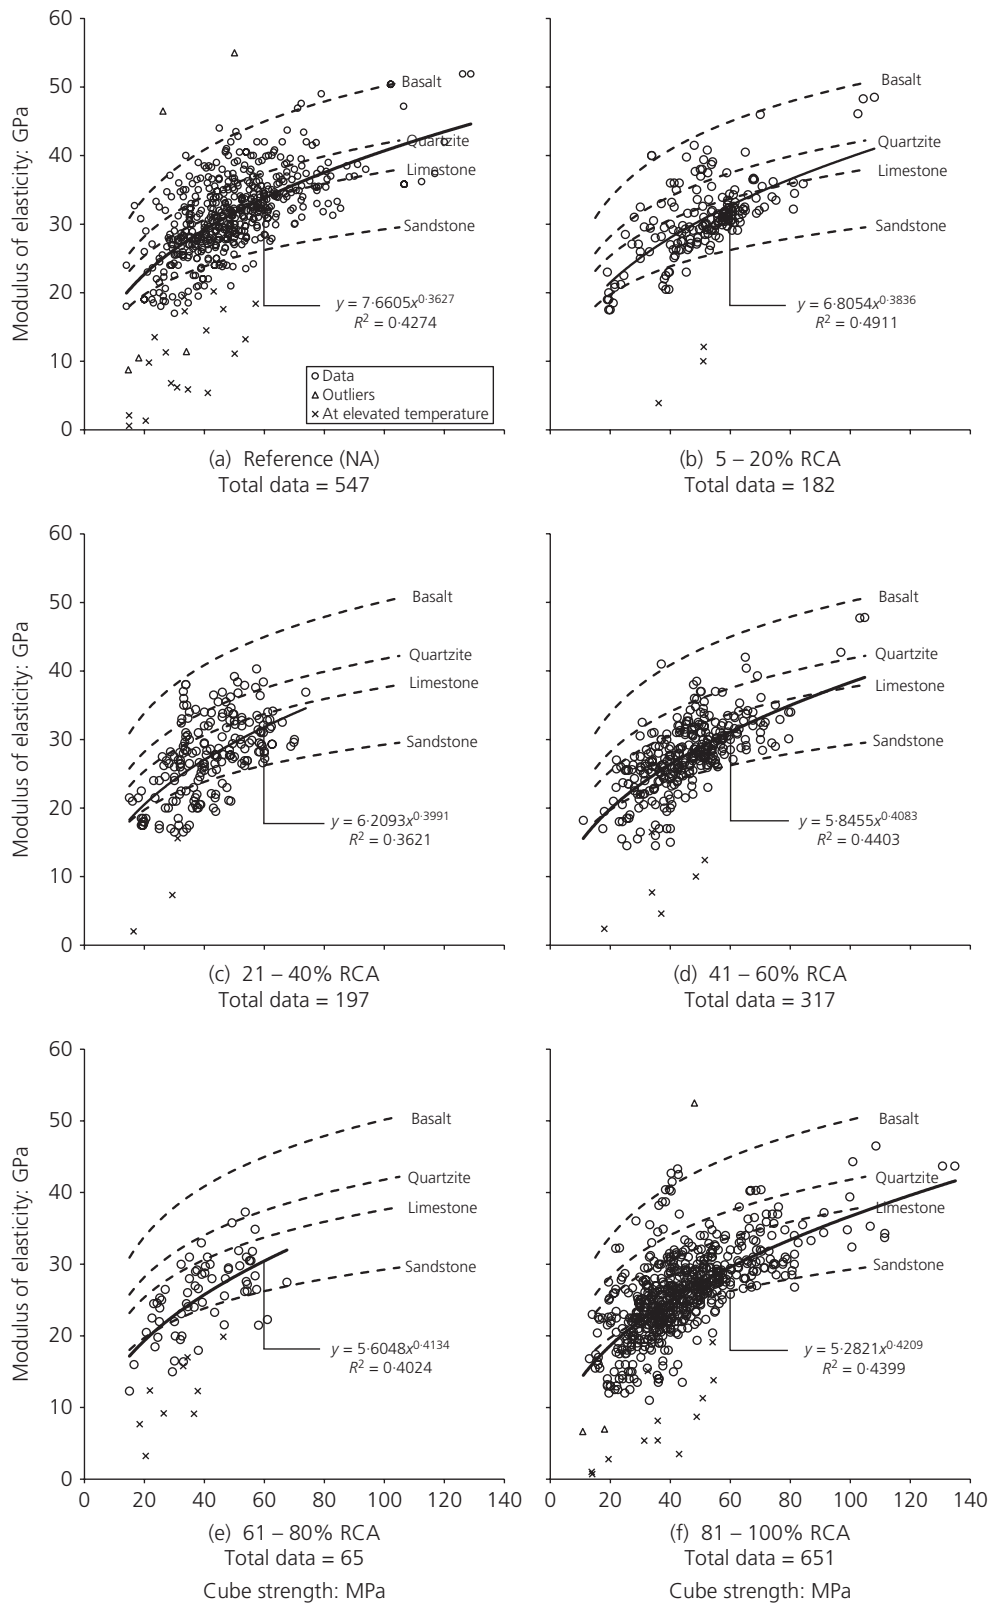


Figure 7. Modulus of elasticity and mean cube strength of RCA concrete for different RCA contents

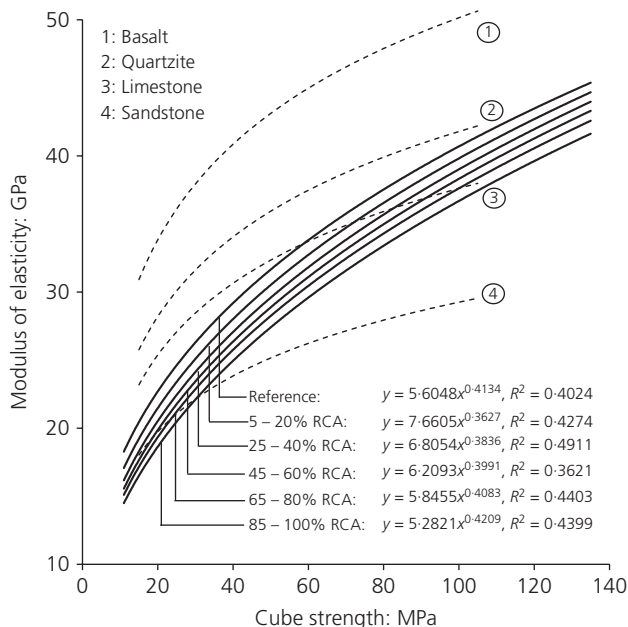


Figure 8. Compilation of modulus of elasticity and cube strength of concrete for different RCA contents

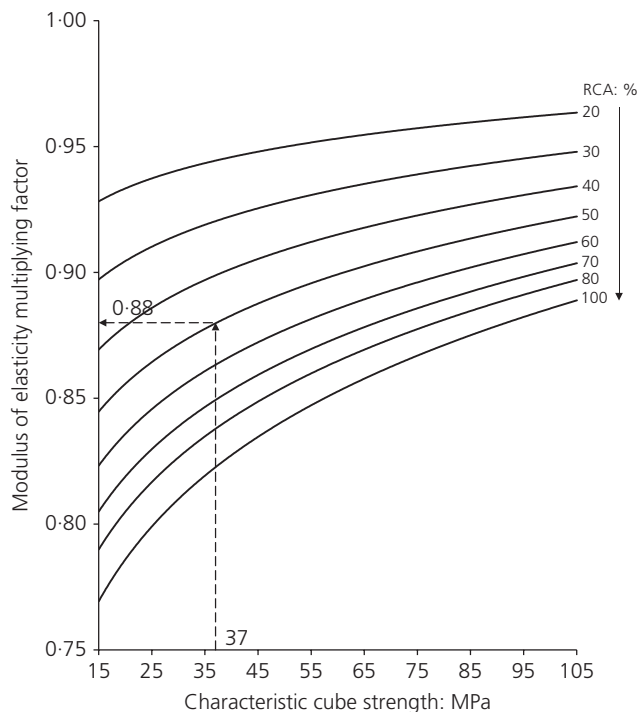


Figure 9. Proposed modulus of elasticity multiplying factors for RCA concretes of different characteristic cube strengths

the characteristic strengths of the measured strength data reported in the literature.

For ease of use of Figure 9 in practice, Table 3 gives conversion factors for estimating the modulus of elasticity of RCA concrete for a given characteristic cube strength in line with Eurocode 2 and coarse RCA content.

The following steps show how Figure 9 can be used to estimate the modulus of elasticity of RCA concrete.

- Step 1: Determine the modulus of elasticity of NA concrete. For example, according to Eurocode 2, concrete made with coarse basalt, quartzite, limestone or sandstone aggregate of designed characteristic cube strength of 37 MPa is estimated to have a modulus of elasticity of 42.9 GPa, 33.0 GPa, 29.7 GPa or 23.1 GPa, respectively.
- Step 2: Determine the multiplying factor required for RCA concrete. If 50% of the NA is replaced by RCA of a similar rock type for concrete with a characteristic cube strength of 37 MPa, Figure 9 suggests that a modulus of elasticity multiplying factor of 0.88 is required.
- Step 3: Estimate the modulus of elasticity of RCA concrete. By applying the multiplying factor to the modulus of elasticity of coarse natural basalt, quartzite, limestone or sandstone aggregate concrete, the estimated modulus of elasticity of corresponding to 50% RCA concrete is 37.8 GPa, 29.0 GPa, 26.1 GPa or 20.3 GPa, respectively.

6. Methods proposed to enhance the modulus of elasticity of RCA concrete

In order to enhance the modulus of elasticity of coarse RCA concrete and thereby improve its potential for specifying for use in structural concrete by engineers as a sustainable construction material, two simple and not so dissimilar methods involving mix adjustments of RCA concrete are proposed.

6.1 Cement paste reduction

For a given w/c ratio and workability, Dhir *et al.* (2006) showed that a reduction in cement content, by as much as 30%, could be realised by using water-reducing admixtures, leading to an increase in modulus of elasticity ranging from 8% to 17% (a mean of 12%). The fines content of the mix was maintained with the use of filler aggregate.

Using the previous examples discussed in Section 5, if the cement content of the concrete made with 50% RCA is reduced by 30%, the modulus of elasticity of the revised RCA concrete is almost similar to that of the corresponding reference NA concrete, as shown by

$$E_{R50} = 1.12 \times 0.88E_N = 0.99E_N$$

where E_{R50} is the modulus of elasticity of concrete made with 50% RCA and 30% cement reduction and E_N is the modulus of elasticity of concrete made with NA.

Modulus of elasticity multiplying factor for RCA concrete

RCA: %	Characteristic cube strength: MPa													
	15	20	25	30	37	45	50	55	60	67	75	85	95	105
20	0.93	0.93	0.94	0.94	0.94	0.95	0.95	0.95	0.95	0.96	0.96	0.96	0.96	0.97
30	0.90	0.90	0.91	0.91	0.92	0.93	0.93	0.93	0.93	0.94	0.94	0.95	0.95	0.95
40	0.87	0.88	0.89	0.89	0.90	0.91	0.91	0.91	0.92	0.92	0.93	0.93	0.93	0.94
50	0.84	0.85	0.86	0.87	0.88	0.89	0.89	0.90	0.90	0.91	0.91	0.92	0.92	0.93
60	0.82	0.83	0.84	0.85	0.86	0.87	0.88	0.88	0.89	0.89	0.90	0.91	0.91	0.92
70	0.80	0.82	0.83	0.84	0.85	0.86	0.87	0.87	0.88	0.88	0.89	0.90	0.90	0.91
80	0.79	0.80	0.82	0.83	0.84	0.85	0.86	0.86	0.87	0.88	0.88	0.89	0.90	0.90
100	0.76	0.78	0.80	0.81	0.82	0.84	0.84	0.85	0.86	0.86	0.87	0.88	0.89	0.90

Table 3. Modulus of elasticity multiplying factors for RCA concretes with selected characteristic cube strengths, as shown in Figure 9

Concrete made with 100% NA		Concrete made with 50% coarse RCA	
		Method 1: cement paste reduction	Method 2: increase in design strength
Rock type	Modulus of elasticity: GPa ^a	Modulus of elasticity: GPa	Additional strength required: MPa
Basalt	42.9	42.3	13.0
Quartzite	33.0	32.5	10.0
Limestone	29.7	29.2	9.0
Sandstone	23.1	22.7	7.0

^aAt characteristic cube strength of 37 MPa

Table 4. Modulus of elasticity and additional strength required of concrete made with 50% RCA from the proposed methods

The modulus of elasticity values for NA concrete made with different rock types and the corresponding 50% RCA concrete are given in Table 4. This 30% reduction of cement and water content in a mix is considered to be the maximum water reduction level that can be realised with water-reducing admixtures, suggesting that this method can only offer a maximum 50% RCA as NA replacement without compromising the modulus of elasticity of the concrete produced.

In revising the mix design of RCA concrete, high-range water-reducing admixtures such as polycarboxylate ether based superplasticisers can be considered. This is equally effective as

a normal water-reducing admixture but a relatively low dose is required. The use of fly ash as filler would be preferable as its use can additionally offer some improvement in workability.

6.2 Increase in design strength

Another method to enhance the modulus of elasticity would be to increase the design strength of the RCA concrete. The additional strength required for matching the modulus of elasticity of RCA concrete with that of NA concrete, for designing concrete with up to 100% RCA content and 20–45 GPa modulus of elasticity, is shown in Figure 10. This figure was produced from the previously used data in Figures 7 and 8 with measured strength data converted into characteristic strength by applying a coefficient of variation of 12.5% as used previously in developing Figure 9.

Following the previous example, to achieve a similar modulus of elasticity of 37 MPa characteristic cube strength concrete made with different NA rock types, when 50% of the aggregate is replaced with coarse RCA, Figure 10 shows that the strength of the RCA concrete needs to be increased by 7–13 MPa depending on the modulus of elasticity of NA concrete, as shown in Table 4.

This additional strength can be obtained by reducing the water content of the concrete by using a water-reducing admixture, thereby reducing the w/c ratio of the concrete and resulting in higher strength (Dhir *et al.*, 2004b, 2006), or by increasing the cement content to achieve the same effect. Of the two options, the former would be preferable on the grounds of sustainability as it uses less Portland cement. However, as the maximum water reduction is unlikely to be greater than 30%, the additional strength resulting from such an approach is also limiting and could be expected to limit the increase in strength

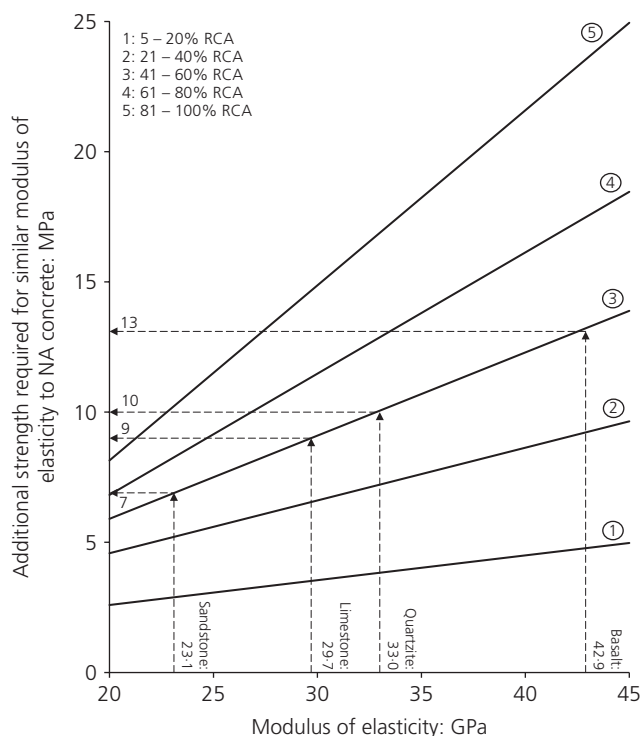


Figure 10. Additional strength required for concrete made with different coarse RCA contents to achieve similar modulus of elasticity to NA concrete

to a maximum of 10 MPa, depending on the properties of the constituent materials and mix design used. Thus, when higher additional strength is required due to an increase in RCA replacement level and the targeted modulus of elasticity, it can only be achieved through increasing the cement content of a mix.

Given the above, it would appear that, at present, the use of coarse RCA without having to increase cement content is likely to be limited to the maximum 50% replacement of NA as engineers endeavour to balance concrete performance requirements, the sustainability benefits that can be gained with the use of RAs and the extent to which concrete design can be manipulated.

7. Conclusions

Consolidation of 393 publications on the modulus of elasticity of concrete made with recycled aggregates identified from a near-exhaustive global literature search (limited to the English medium) revealed the following.

- The effect of coarse recycled concrete aggregate (RCA) on the static modulus of elasticity of concrete is most commonly reported, with 284 identified works published since 1977.

- Data on the modulus of elasticity of concretes made with fine RCA, mixtures of coarse and fine RCA, and other types and sizes of recycled aggregate (e.g. recycled masonry aggregate (RMA), mixed recycled aggregate (MRA) and construction and demolition recycled aggregate (CDRA)) have also been reported, but on a relatively very small scale.
- Technical reports produced by established organisations reveal that the use of coarse RCA in place of natural aggregate (NA) in concrete reduces its modulus of elasticity, with the level of reduction depending on RCA content and its properties, as well as mix design parameters such as w/c ratio and compressive strength.

Narrowing the focus to the effect of coarse RCA on the static modulus of elasticity of concrete, data from the 284 publications published since 1977 were systematically analysed, evaluated and synthesised. The main points to emerge from this analysis are as follows.

- The modulus of elasticity of RCA concrete relative to a corresponding reference NA concrete decreases at a decreasing rate with increasing RCA content, with a mean of 16% reduction at 100% RCA content, which is close to the modulus of elasticity multiplying factor of 0.80 suggested by some organisations. At 20% RCA content, rather than no change in modulus of elasticity suggested by some works, a slight reduction (5% on average) was calculated from the overall data population analysed.
- The reduction in modulus of elasticity of RCA concrete relative to NA concrete also decreases with an increase in the design strength of concrete, with a mean of 22% to 14% reduction at 100% RCA content in the lowest to highest strength groups, respectively.
- Plotting cube strength against modulus of elasticity and comparing it with values given in Eurocode 2 for concrete made with different NA rock types in decreasing aggregate stiffness order (namely basalt, quartzite, limestone and sandstone), the trendline of NA concrete for the published literature was found to be within the range of values for concrete made with quartzite and sandstone. The trendline of RCA concrete moved towards to concrete made with sandstone aggregate with increasing RCA content, and almost matched it at 100% RCA content for concrete strength up to 35 MPa.
- For a given characteristic cube strength and RCA content, the modulus of elasticity of RCA concrete can be estimated with the use of proposed multiplying factors developed from the published data in conjunction with a code of practice such as Eurocode 2.

Two simple and not so dissimilar methods involving mix adjustments of coarse RCA concrete have been proposed to enhance its modulus of elasticity, making it more appealing to specifying engineers for use in structural concrete.

- Achieving a reduction in cement paste, the water and cement contents of a mix can be reduced by the same proportion for a given w/c ratio. The workability and fines content can be maintained with the use of a water-reducing admixture and filler.
- Achieving an increase in strength by reducing the w/c ratio, it is recommended to reduce only the water content of a mix with the use of a water-reducing admixture, rather to increase its cement content. A method for estimating the additional strength required for RCA concrete at a given modulus of elasticity and RCA content has been proposed.

REFERENCES

- ACI (American Concrete Institute) (2001) ACI 555-01: Removal and reuse of hardened concrete. American Concrete Institute, Farmington Hills, MI, USA.
- ACI (2005) ACI 301-05: Specifications for structural concrete. American Concrete Institute, Farmington Hills, MI, USA.
- Agrela F, Alaejos P and de Juan MS (2013) Properties of concrete with recycled aggregates. In *Handbook of Recycled Concrete and Demolition Waste* (Pacheco-Torgal F, Tam VWY, Labrincha JA *et al.* (eds)). Woodhead Publishing, Cambridge, UK, pp. 304–329.
- Ahmad SH, Fisher D and Sackett K (1996) *Properties of Concrete made with North Carolina Recycled Coarse and Fine Aggregates*. Center for Transportation Engineering Studies, North Carolina State University, Raleigh, NC, USA, Report FWS/NC/96-07.
- Ahmed MS and Vidyadhara HS (2013) Experimental study on strength behaviour of recycled aggregate concrete. *International Journal of Engineering Research and Technology* **2(10)**: 76–82.
- Ajdkiewicz A (2005) The place of concrete in sustainable civil engineering in Poland. *Beton- und Stahlbetonbau* **100(7)**: 633–641.
- Ajdkiewicz A and Kliszczewicz A (2002) Influence of recycled aggregates on mechanical properties of HS/HPC. *Cement and Concrete Composites* **24(2)**: 269–279.
- Ajdkiewicz A and Kliszczewicz A (2007) Comparative tests of beams and columns made of recycled aggregate concrete and natural aggregate concrete. *Journal of Advanced Concrete Technology* **5(2)**: 259–273.
- Akbarnezhad A, Ong KCG, Zhang MH, Tam CT and Foo TWJ (2011) Microwave-assisted beneficiation of recycled concrete aggregates. *Construction and Building Materials* **25(8)**: 3469–3479.
- Akhtar JN and Akhtar MN (2014) Enhancement in properties of concrete with demolished waste aggregate. *GE-International Journal of Engineering Research* **2(9)**: 73–83.
- Anderson KW, Uhlmeier JS and Russell M (2009) *Use of Recycled Concrete Aggregate in PCCP: Literature Search*. Washington State Department of Transportation (WSDoT), Olympia, WA, USA, Research report WA-RD 726.1.
- Arezoumandi M, Smith A, Volz JS and Khayat KM (2015) An experimental study on flexural strength of reinforced concrete beams with 100% recycled concrete aggregate. *Engineering Structures* **88**: 154–162.
- Arundeb G, Saroj M and Somnath G (2011) Direct compressive strength and elastic modulus of recycled aggregate concrete. *International Journal of Civil and Structural Engineering* **2(1)**: 292–304.
- Balazs G, Kausay T and Simon TK (2008) Technical guidelines for recycled aggregate concrete in Hungary. *Concrete Structures* **25(2)**: 45–55.
- Barbudo A, de Brito J, Evangelista L, Bravo M and Agrela F (2013) Influence of water-reducing admixtures on the mechanical performance of recycled concrete. *Journal of Cleaner Production* **59**: 93–98.
- Behera M, Bhattacharyya SK, Minocha AK, Deoliya R and Maiti S (2014) Recycled aggregate from C&D waste & its use in concrete – a breakthrough towards sustainability in construction sector: a review. *Construction and Building Materials* **68**: 501–516.
- Beltran MG, Barbudo A, Agrela F, Galvin AP and Jimenez JR (2014) Effect of cement addition on the properties of recycled concretes to reach control concretes strengths. *Journal of Cleaner Production* **79**: 124–133.
- Bhikshma V and Manipal K (2012) Study on mechanical properties of recycled aggregate concrete containing steel fibres. *Asian Journal of Civil Engineering (Building and Housing)* **13(2)**: 155–164.
- Brand AS, Amirkhanian AN and Roesler JR (2013a) Load capacity of concrete slabs with recycled aggregates. *Proceedings of Airfield and Highway Pavement 2013, Los Angeles, CA, USA*, pp. 307–320.
- Brand AS, Amirkhanian AN and Roesler JR (2013b) Flexural Capacity of Rigid Pavement Concrete Slabs with Recycled Aggregates. Illinois Center for Transportation, University of Illinois, Champaign, IL, USA, Report ICT-13-018.
- Bravo M, de Brito J, Pontes J and Evangelista L (2015) Mechanical performance of concrete made with aggregates from construction and demolition waste recycling plants. *Journal of Cleaner Production* **99**: 59–74, <http://dx.doi.org/10.1016/j.jclepro.2015.03.012>.
- Bretschneider A and Ruhl M (1998) The influence of recycled aggregate on the compressive strength and the elastic modulus of concrete. See <http://www.b-i-m.de/public/TUdmassiv/dacon98ruehl.htm> (accessed 18/06/2016).
- BSI (2004) BS EN 1992: Eurocode 2. Design of concrete structures – part 1-1: general rules and rules for buildings. BSI, London, UK.
- BSI (2009) BS EN 12504-1: Testing concrete in structures. Cored specimens. Taking, examining and testing in compression. BSI, London, UK.
- Burke TT, Cohen MD and Scholer CF (1992) *Synthesis Study on the Use of Concrete Recycled from Pavements and Building*

- Rubble in the Indiana Highway System*. Purdue University and Indiana Department of Transportation JHRP (INDoT), West Lafayette, IN, USA, Report FHWA/IN/JHRP-92-15.
- Butler L, West JS and Tighe SL (2013a) Effect of recycled concrete coarse aggregate from multiple sources on the hardened properties of concrete with equivalent compressive strength. *Construction and Building Materials* **47**: 1292–1301.
- Butler L, West JS and Tighe SL (2013b) Towards the classification of recycled concrete aggregates: influence of fundamental aggregate properties on recycled concrete performance. *Journal of Sustainable Cement-Based Materials* **3**(2): 140–163.
- Cadessa AS and Ramchiriter M (2014) Use of recycled concrete aggregates in structural concrete in Mauritius. *Journal of Emerging Trends Engineering and Applied Sciences* **6**(1): 71–81.
- Castano JO, Domingo A, Lazaro C and Lopez-Gayarre F (2009) A study on drying shrinkage and creep of recycled concrete aggregate. *Proceedings of International Association for Shell and Spatial Structures (IASS) Symposium – Evolution and Trends in Design, Analysis and Construction of Shell and Spatial Structures, Valencia, Spain*, pp. 2955–2964.
- Casuccio M, Torrijos MC, Giaccio G and Zerbino R (2008) Failure mechanism of recycled aggregate concrete. *Construction and Building Materials* **22**(7): 1500–1506.
- CCAA (Cement, Concrete and Aggregates Australia) (2008) *Use of Recycled Aggregates in Construction*. Cement, Concrete and Aggregates Australia, Mascot, NSW, Australia, pp. 1–25.
- Cervantes V, Roesler J and Bordelon A (2007) *Fracture and Drying Shrinkage Properties of Concrete Containing Recycled Concrete Aggregate*. Department of Civil and Environmental Engineering, University of Illinois, Champaign, IL, USA, Technical Note 34.
- Chen B (2013) Basic mechanical properties and microstructural analysis of recycled concrete. *Journal of Wuhan University of Technology Materials Science* **28**(1), 104–109.
- Chen GM, He YH, Yang H, Chen JF and Guo YC (2014) Compressive behaviour of steel fibre reinforced recycled aggregate concrete after exposure to elevated temperatures. *Construction and Building Materials* **71**: 1–15.
- Chen HJ, Yen T and Chen KH (2003a) The use of building rubbles in concrete and mortar. *Journal of the Chinese Institute of Engineers* **26**(2): 227–236.
- Chen HJ, Yen T and Chen KH (2003b) Use of building rubbles as recycled aggregates. *Cement and Concrete Research* **33**(1): 125–132.
- Chisolm D (2011) *Best Practice Guide for the Use of Recycled Aggregates in New Concrete*. Cement and Concrete Association of New Zealand (CCANZ), Wellington, New Zealand, TR14.
- Choi WC and Yun HD (2012) Compressive behaviour of reinforced concrete columns with recycled aggregate under uniaxial loading. *Engineering Structures* **41**: 285–293.
- Choi WC and Yun HD (2013) Long-term deflection and flexural behaviour of reinforced concrete beams with recycled aggregate. *Materials and Design* **51**: 742–750.
- Collery DJ, Kelvin PA and Dhir RK (2015) Establishing rational use of recycled aggregates in concrete: a performance-related approach. *Magazine of Concrete Research* **67**(11): 559–574.
- Corinaldesi V (2010) Mechanical and elastic behaviour of concretes made of recycled-concrete coarse aggregates. *Construction and Building Materials* **24**(9): 1616–1620.
- Corinaldesi V (2011) Structural concrete prepared with coarse recycled concrete aggregate: from investigation to design. *Advances in Civil Engineering* **2011**: 1–6.
- Corinaldesi V, Letelier V and Moriconi G (2011) Behaviour of beam–column joints made of recycled-aggregate concrete under cyclic loading. *Construction and Building Materials* **25**(4): 1877–1882.
- Cui H, Shi X, Memon S, Xing F and Tang W (2015) Experimental study on the influence of water absorption of recycled coarse aggregates on properties of the resulting concretes. *Journal of Materials in Civil Engineering* **27**(4): 9.
- Dam TV, Smith K, Truschke C and Vitton S (2011) *Using Recycled Concrete in MDoT's Transportation Infrastructure – Manual of Practice*. Michigan Department of Transportation (MDOT), Lansing, MI, USA, Report RC-1544.
- Dam TV, Taylor P, Fick G et al. (2012) *Sustainable Concrete Pavements: A Manual of Practice*. National Concrete Pavement Technology Center (NCPTC), Iowa State University, Ames, IA, USA, pp. 1–112.
- Dapena E, Alaejos P, Lobet A and Perez D (2011) Effect of recycled sand content on characteristics of mortars and concretes. *Journal of Materials in Civil Engineering* **23**(4): 414–422.
- de Brito J and Alves F (2010) Concrete with recycled aggregates: Portuguese experimental research. *Materials and Structures* **43**(1): 35–51.
- de Brito J and Robles R (2010) Recycled aggregate concrete (RAC) methodology for estimating its long-term properties. *Indian Journal of Engineering & Materials Sciences* **17**(6): 449–462.
- de Brito J and Saikia N (2013) *Recycled Aggregate in Concrete: Use of Industrial, Construction and Demolition Waste*. Springer, London, UK.
- de Juan MS and Gutierrez PA (2004) Influence of recycled aggregate quality on concrete properties. *Proceedings of International Rilem Conference on the Use of Recycled Materials in Buildings and Structures, Barcelona, Spain*, pp. 545–553.
- de Oliveira MB and Vazquez E (1996) The influence of retained moisture in aggregates from recycling on the properties of new hardened concrete. *Waste Management* **16**(1–3): 113–117.

- de Oliveira MJ, de Assis CS and Terni AW (2004) Study on compressed stress, water absorption and modulus of elasticity of produced concrete made by recycled aggregate. *Proceedings of International Rilem Conference on the Use of Recycled Materials in Buildings and Structures, Barcelona, Spain*, pp. 634–642.
- de Pauw P, Thomas P, Vyncke J and Desmyter J (1998) Shrinkage and creep of concrete with recycled materials as coarse aggregates. *Proceedings of International Symposium on Sustainable Construction: Use of Recycled Concrete Aggregate, London, UK*, pp. 213–225.
- de Vries P (1996) Concrete re-cycled: crushed concrete aggregate. In *Concrete for Environment Enhancement and Protection. Proceedings of International Conference on Concrete in the Service of Mankind, Dundee, UK* (Dhir RK and Dyer TD (eds)). E&FN Spon, London, UK, pp. 121–130.
- Deshpande Y, Hiller JE and Shorkey CJ (2009) Volumetric stability of concrete using recycled concrete aggregates. In *Proceedings of International Symposium on Brittle Matrix Composites 9, Warsaw, Poland* (Brandt AM, Olek J and Marshall IH (eds)). Woodhead Publishing, Cambridge, UK, pp. 301–312.
- Dhir RK and Paine K (2004) Suitability and practicality of using coarse RCA in normal and high strength concrete. *Proceedings of 1st International Conference on Sustainable Construction: Waste Management, Singapore*, pp. 108–123.
- Dhir RK and Paine K (2007) *Performance-Related Approach to Use of Recycled Aggregates*. Waste and Resources Action Programme (WRAP), Banbury, UK, Project AGG0074.
- Dhir RK, Limbachiya MC and Leelawat T (1999) Suitability of recycled concrete aggregate for use in BS 5328 designated mixes. *Proceedings of the Institution of Civil Engineers – Structures and Buildings* **134**(3): 257–274, <http://dx.doi.org/10.1680/istbu.1999.31568>.
- Dhir RK, Dyer TD and Paine KA (2004a) Dismantling barriers: roles for research in realising markets for construction and demolition wastes. *Proceedings of 1st International Conference on Sustainable Construction: Waste Management, Singapore*, pp. 1–22.
- Dhir RK, McCarthy MJ, Zhou S and Tittle PAJ (2004b) Role of cement content in specifications for concrete durability: cement type influences. *Proceedings of the Institution of Civil Engineers – Structures and Buildings* **157**(2): 113–127, <http://dx.doi.org/10.1680/stbu.2004.157.2.113>.
- Dhir RK, McCarthy MJ, Tittle PAJ and Zhou S (2006) Role of cement content in specifications for concrete durability: aggregate type influences. *Proceedings of the Institution of Civil Engineers – Structures and Buildings* **159**(4): 229–242, <http://dx.doi.org/10.1680/stbu.2006.159.4.229>.
- Dhir RK, Paine KA, de Brito J et al. (2011) Use of recycled and secondary aggregates in concrete: an overview. *Proceedings of International UKIERI Concrete Congress on New Developments in Concrete Construction, Delhi, India*, pp. 157–182.
- Dilbas H, Simsek M and Cakir O (2014) An investigation on mechanical and physical properties of recycled aggregate concrete (RAC) with and without silica fume. *Construction and Building Materials* **61**: 50–59.
- Dillmann R (1998) Concrete with recycled concrete aggregates. In *Proceedings of International Symposium on Sustainable Construction on Use of Recycled Concrete Aggregate, London, UK* (Dhir RK, Henderson NA and Limbachiya MC (eds)). Thomas Telford, London, UK, pp. 239–254.
- Domingo-Cabo A, Lazaro C, Lopez-Gayarre F et al. (2009) Creep and shrinkage of recycled aggregate concrete. *Construction and Building Materials* **23**(7): 2545–2553.
- Domingo-Cabo A, Lazaro C, Lopez-Gayarre F, Serrano-Lopez MA and Lopez-Colina C (2010) Long term deformations by creep and shrinkage in recycled aggregate concrete. *Materials and Structures* **43**(8): 1147–1160.
- Dosho Y (2007) Development of a sustainable concrete waste recycling system. *Journal of Advanced Concrete Technology* **5**(1): 27–42.
- Duan ZH and Poon CS (2014) Properties of recycled aggregate concrete made with recycled aggregates with different amounts of old adhered mortars. *Materials and Design* **58**: 19–29.
- Duan ZH, Kou SC and Poon CS (2013) Using artificial neural networks for predicting the elastic modulus of recycled aggregate concrete. *Construction and Building Materials* **44**: 524–532.
- Eguchi K, Teranishi K, Nakagome A et al. (2007) Application of recycled coarse aggregate by mixture to concrete construction. *Construction and Building Materials* **21**(7): 1542–1551.
- Ekolu SO, Makama LN and Shuluuka WP (2010) Influence of different recycled aggregate types on strength and abrasion resistance properties of concrete. In *Proceedings of 3rd International Conference on Concrete Repair, Rehabilitation and Retrofitting III, Cape Town, South Africa* (Alexander MG, Beuhausen HD, Dehn F and Moyo P (eds)). Taylor & Francis, London, UK, pp. 193–198.
- Ettxeberria M, Vazquez E and Mari A (2006) Microstructure analysis of hardened recycled aggregate concrete. *Magazine of Concrete Research* **58**(10): 683–690.
- Ettxeberria M, Mari AR and Vazquez E (2007a) Recycled aggregate concrete as structural material. *Materials and Structures* **40**(5): 529–541.
- Ettxeberria M, Vazquez E, Mari A and Barra M (2007b) Influence of amount of recycled coarse aggregates and production process on the properties of recycled aggregate concrete. *Cement and Concrete Research* **37**(5): 735–742.
- Fahmy W, Heneidy E, Ali E and Agwa I (2011) Mechanical properties of concrete containing recycled concrete aggregates subjected to different fire durations. *Journal of Engineering Sciences* **39**(5): 1005–1019.
- Fahmy W, Heneidy E, Ali E and Agwa I (2012) Performance of concrete containing crushed waste concrete exposed to

- different fire temperatures. *International Journal of Civil and Structural Engineering* **3(1)**: 9–22.
- Fan Y, Xiao J and Tam VWY (2014) Effect of old attached mortar on the creep of recycled aggregate concrete. *Structural Concrete* **15(2)**: 169–178.
- Fathifazl G and Razaqpur AG (2013) Creep rheological models for recycled aggregate concrete. *ACI Materials Journal* **110(2)**: 115–125.
- Fathifazl G, Abbas A, Razaqpur AG *et al.* (2009a) New mixture proportioning method for concrete made with coarse recycled concrete aggregate. *ASCE Materials Journal* **21(10)**: 601–611.
- Fathifazl G, Razaqpur AG, Isgor OB *et al.* (2009b) Shear strength of steel reinforced recycled concrete beams without stirrups. *Magazine of Concrete Research* **61(7)**: 387–400.
- Fathifazl G, Razaqpur AG, Isgor OB *et al.* (2009c) Flexural performance of steel reinforced recycled concrete (RRC) beams. *ACI Structural Journal* **106(6)**: 858–867.
- Ferreira L, de Brito J and Barra M (2011) Influence of pre-saturation of recycled coarse concrete aggregates on structural concrete's mechanical and durability properties. *Magazine of Concrete Research* **63(1)**: 1–11.
- Folino P and Xargay H (2014) Recycled aggregate concrete – mechanical behaviour under uniaxial and triaxial compression. *Construction and Building Materials* **56**: 21–31.
- Fonseca N, de Brito J and Evangelista L (2011) The influence of curing conditions on the mechanical performance of concrete made with recycled concrete waste. *Cement and Concrete Composites* **33(6)**: 637–643.
- Franklin SO and Gumede MT (2014) Studies on strength and related properties of concrete incorporating aggregates from demolished wastes: part 1 – a global perspective. *Open Journal of Civil Engineering* **4(4)**: 311–317.
- Frondestou-Yannas S (1977) Waste concrete as aggregate for new concrete. *ACI Materials Journal* **74(8)**: 373–376.
- Garcia-Navarro J, de Guzman A and Cervantes M (2010) A study on the mix design and fundamental properties of pre-cast concrete artefacts prepared with coarse and fine recycled aggregates. Proceedings of 12th International Symposium on Environmental Issues and Waste Management in Energy and Mineral Production, Prague, pp. 1–6.
- Geng Y, Wang T and Chen J (2015) Time-dependent behaviour of recycled aggregate concrete-filled steel tubular columns. *Journal of Structural Engineering* **141(10)**: 1–12.
- Gerardu JJA and Hendriks CF (1985) *Recycling of Road Pavement Materials in the Netherlands*. Rijkswaterstaat, The Hague, Netherlands, Rijkswaterstaat Communications No. 38.
- Go SS, Yoo DR, Lee HC, Lee G and Park YC (2007) A study on the physical properties of hard concrete mixing various type of recycled aggregate. In Portugal SB07: Sustainable Construction, Materials and Practices: Challenge of the Industry for the New Millennium (Bragança L, Pinheiro M, Jalali S *et al.* (eds)). IOS Press, Amsterdam, the Netherlands, pp. 826–833.
- Gomes M and de Brito J (2007) Structural concrete with incorporation of coarse recycled concrete and ceramic aggregates. In Portugal SB07: Sustainable Construction, Materials and Practices: Challenge of the Industry for the New Millennium (Bragança L, Pinheiro M, Jalali S *et al.* (eds)). IOS Press, Amsterdam, the Netherlands, pp. 887–894.
- Gomes M and de Brito J (2009) Structural concrete with incorporation of coarse recycled concrete and ceramic aggregates: durability performance. *Materials and Structures* **42(5)**: 663–675.
- Gomes M, de Brito J and Bravo M (2014) Mechanical performance of structural concrete with the incorporation of coarse recycled concrete and ceramic aggregates. *Journal of Materials in Civil Engineering* **26(10)**: 1–10.
- Gomez-Soberon JM (2002) Porosity of recycled concrete with substitution of recycled concrete aggregate: an experimental study. *Cement and Concrete Research* **32(8)**: 1301–1311.
- Gomez-Soberon JM (2003) Relationship between gas adsorption and the shrinkage and creep of recycled aggregate concrete. *Cement, Concrete and Aggregates* **25(2)**: 42–48.
- Gomez-Soberon JM, Aguyo L and Vazquez E (2001) Repercussions on concrete permeability due to recycled concrete aggregate. In *Proceedings of 3rd CANMET/ACI International Symposium on Sustainable Development of Cement and Concrete, San Francisco, CA, USA* (Malhotra VM (ed.)). American Concrete Institution, Farmington Hills, MI, USA, pp. 181–195.
- Gomez-Soberon JM, Gomez-Soberon JC and Gomez-Soberon LA (2002) Shrinkage and creep of recycled concrete interpreted by the porosity of their aggregate. In *Proceedings of Sustainable Concrete Construction, Dundee, UK* (Dhir RK, Dyer TD and Halliday JE (eds)). Thomas Telford, London, UK, pp. 563–576.
- Gonzalez-Corominas A and Etxeberria M (2014) Experimental analysis of properties of high performance recycled aggregate concrete. *Construction and Building Materials* **68**: 127–134.
- Gonzalez-Fonteboa B and Martinez-Abella F (2004) Shear strength of concrete with recycled aggregates. *Proceedings of International Rilem Conference on the Use of Recycled Materials in Building and Structures, Barcelona, Spain*, pp. 887–893.
- Gonzalez-Fonteboa B and Martinez-Abella F (2005) Recycled aggregates concrete: aggregate and mix properties. *Materiales De Construccion* **55(279)**: 53–66.
- González-Fonteboa B and Martínez-Abella F (2008) Concretes with aggregates from demolition waste and silica fume: materials and mechanical properties. *Building and Environment* **43(4)**: 429–437.

- Gonzalez-Fonteboa B, Martinez-Abella F, Carro Lopez D and Seara-Paz S (2011a) Stress–strain relationship in axial compression for concrete using recycled saturated coarse aggregate. *Construction and Building Materials* **25(5)**: 2335–2342.
- Gonzalez-Fonteboa B, Martinez-Abella F, Eiras-López J and Seara-Paz S (2011b) Effect of recycled coarse aggregate on damage of recycled concrete. *Materials and Structures* **44(10)**: 1759–1771.
- Grubl P, Ruhl M and Bührer M (1999) *Evaluation of Modulus of Elasticity of Concrete with Recycled Aggregate*. See <http://www.b-i-m.de/public/tudmassiv/damcon99grueblbruehl.htm> (assessed 20/04/2015).
- Guardian H, Garcia-Alcocel E, Baeza-Brotons F, Garcés P and Zornoza E (2014) Corrosion behaviour of steel reinforcement in concrete with recycled aggregates, fly ash and spent cracking catalyst. *Materials* **7(4)**: 3176–3179.
- Guo Y, Zhang J, Chen G and Xie Z (2014) Compressive behaviour of concrete structures incorporating recycled concrete aggregates, rubber crumb and reinforced with steel fibre, subjected to elevated temperatures. *Journal of Cleaner Production* **72**: 193–203.
- Haitao Y and Shizhu T (2015) Preparation and properties of high-strength recycled concrete in cold areas. *Materiales de Construcción* **65(318)**: 1–6.
- Hansen TC (1985) Recycled aggregates and recycled aggregate concrete second state-of-the-art report developments 1945–1985. *Materials and Structures* **19(3)**: 201–246.
- Hansen TC (1992) *Recycled Aggregates and Recycled Aggregate Concrete*. Rilem Report 6: Recycling of Demolished Concrete and Masonry, Taylor & Francis, London, UK, pp. 1–138.
- Hansen TC and Boegh E (1985) Elasticity and drying shrinkage of recycled aggregate concrete. *Journal of the American Concrete Institute* **82(5)**: 648–652.
- Haque M, Al-Yaqout A, Sreekala V and El-Hawary M (2014) Characteristics of recycled aggregate concretes produced in Kuwait: a case study. *Journal of Engineering Research* **2(4)**: 16–31.
- Hendriks C and Henriksen A (1996) Concrete with Recycled Aggregates. In *15th Congress of IABSE Congress of Structural Engineering in Consideration of Economy*. Environment and Energy, Copenhagen, Denmark, pp. 465–472.
- Henry M, Pardo G, Nishimura T and Kato Y (2011) Balancing durability and environmental impact in concrete combining low-grade recycled aggregates and mineral admixtures. *Resources, Conservation and Recycling* **55(11)**: 1060–1069.
- Ho N, Lee Y, Lim W et al. (2013) Efficient utilization of recycled concrete aggregate in structural concrete. *Journal of Materials in Civil Engineering* **25(3)**: 318–327.
- Hossain MZ and Sohji I (2004) A study on mechanical properties of cementitious composites with various recycled aggregates. *Proceedings of 29th Conference on Our World in Concrete and Structures, Singapore*, pp. 373–380.
- Huda S and Shahria Alam M (2014) Mechanical behaviour of three generations of 100% repeated recycled coarse aggregate concrete. *Construction and Building Materials* **65**: 574–582.
- Huda S and Shahria Alam M (2015) Mechanical and freeze-thaw durability properties of recycled aggregate concrete made with recycled coarse aggregate. *Journal of Materials in Civil Engineering* **27(10)**: 1–9.
- Ignjatovic I, Marinkovic SB, Miskovic ZM and Savic AR (2013) Flexural behaviour of reinforced recycled aggregate concrete beams under short-term loading. *Materials and Structures* **46(6)**: 1045–1059.
- Imamoto K, Kiruma Y, Nagayama M and Tamura H (2004) Deflections and cracks in recycled coarse aggregate concrete members processed by decompression and rapid release. *Proceedings of Rilem International Symposium on Environment-Conscious Materials and Systems for Sustainable Development, Koriyama, Japan*, pp. 171–177.
- Inoue S, Iizasa S, Wang D et al. (2012) Concrete recycling by pulsed power discharge inside concrete. *International Journal of Plasma Environmental Science & Technology* **6(2)**: 183–188.
- Ishiyama T, Takasu K and Matsufuji Y (2010) Strength property of concrete using recycled aggregate and high-volume fly ash. In *Challenges, Opportunities and Solutions in Structural Engineering and Construction* (Ghafoori N (ed)). Taylor & Francis, London, UK, pp. 557–562.
- Ismail S and Ramli M (2014) Mechanical strength and drying shrinkage properties of concrete containing treated coarse recycled concrete aggregates. *Construction and Building Materials* **68**: 726–739.
- James MN, Choi W and Abu-Lebdeh T (2011) Use of recycled aggregate and fly ash in concrete pavement. *American Journal of Engineering and Applied Science* **4(2)**: 201–208.
- Jimenez C, Aponte D, Vazquez E, Barra M and Vails S (2013) Equivalent mortar volume (EMV) method for proportioning recycled aggregate concrete: validation under the Spanish context and its adaptation to bolomey methodology for concrete proportioning. *Materiales De Construcción* **63(311)**: 341–360.
- Kang THK, Kim W, Kwak YK and Hong SG (2014) Flexural testing of reinforced concrete beams with recycled concrete aggregates. *ACI Structural Journal* **111(3)**: 607–616.
- Kenai S, Debieb F and Azzouz L (2002) Mechanical properties and durability of concrete made with coarse and fine recycled concrete aggregates. In *Proceedings of International Conference on Sustainable Concrete Construction, Dundee, UK* (Dhir RK, Henderson NA and Limbachiya MC (eds)). Thomas Telford, London, UK, pp. 383–392.
- Kenai S, Debieb F and Azzouz L (2005) Performance of concrete made with recycled concrete and brick aggregates. *Proceedings of Inter American Conference on*

- Non Conventional Materials and Technologies in Ecological and Sustainable Construction, Rio de Janeiro, Brazil*, pp. 471–478.
- Kencanawati NN, Iizasa S and Shigeishi M (2013) Fracture process and reliability of concrete made from high grade recycled aggregate using acoustic emission technique under compression. *Materials and Structures* **46(9)**: 1441–1448.
- Kerkhoff B and Siebel E (2001) Properties of concrete with recycled aggregates. *Beton* **2**: 47–58.
- Khayat K and Sadati S (2014) *Recycled Concrete Aggregate: Field Implementation at the Stan Musial Veterans Memorial Bridge*. Center for Transportation Infrastructure and Safety, Rolla, MO, USA, Technical report NUTC R332.
- Kheder GF and Al-Windawi S (2005) Variation in mechanical properties of natural and recycled aggregate concrete as related to the strength of their binding mortar. *Materials and Structures* **38(7)**: 701–709.
- Kikuchi M, Doshio Y, Miura T and Narikawa M (1998) Application of recycled aggregate concrete for structural concrete: part 1 – experimental study on the quality of recycled aggregate and recycled aggregate concrete. In *Proceedings of International Symposium on Sustainable Construction: Use of Recycled Concrete Aggregate, London, UK* (Dhir et al. (eds)). Thomas Telford, London, UK, pp. 55–68.
- Kim Y, Sim J and Park C (2012) Mechanical properties of recycled aggregate concrete with deformed steel re-bar. *Journal of Marine Science and Technology* **20(3)**: 274–280.
- Kiuchi T (2001) A study on the recycle concrete by using type III recycled coarse aggregate. *Memoirs of the Faculty of Engineering, Osaka City University* **42**: 31–40.
- Kiuchi T and Horiuchi E (2003) An experimental study on recycled concrete by using high quality recycled coarse aggregate. *Memoirs of the Faculty of Engineering, Osaka City University* **44**: 37–44.
- Knaack AM and Kurama YC (2011) Design of normal strength concrete mixtures with recycled concrete aggregates. *Proceedings of the ASCE 2011 World Environmental and Water Resources Congress, Palm Springs, CA, USA*, pp. 3068–3079.
- Knaack AM and Kurama YC (2012) Rheological and mechanical behaviour of concrete mixtures with recycled concrete aggregates. In *Proceedings of the 2012 Structures Congress, Chicago, IL, USA* (Carrato J and Burns J (eds)). ASCE, Reston, VA, USA, pp. 2257–2267.
- Knaack AM and Kurama YC (2013a) Design of concrete mixtures with recycled concrete aggregates. *ACI Materials Journal* **110(5)**: 483–492.
- Knaack AM and Kurama YC (2013b) Service load–deflection behaviour of reinforced concrete beams with recycled concrete aggregate. *Proceedings of ASCE Structure Congress on Bridging Your Passion with Your Profession, Pittsburgh, PA, USA*, pp. 2705–2716.
- Knaack AM and Kurama YC (2015) Behaviour of reinforced concrete beams with recycled concrete coarse aggregates. *Journal of Structural Engineering, Special Issue: Sustainable Building Structures* **141(3)**: 1–12.
- Knights JC (1999) Making the most of marginal aggregates. In *Proceedings of International Conference of Utilizing Ready-Mixed Concrete and Mortar, Dundee, UK* (Dhir RK and Limbachiya MC (eds)). Thomas Telford, London, UK, pp. 45–56.
- Konin A and Kouadio DM (2012) Mechanical and abrasion resistance of recycled aggregates concrete in relation to the cement content. *Modern Applied Science* **6(1)**: 88–96.
- Kou SC and Poon CS (2008) Mechanical properties of 5 year old concrete prepared with recycled aggregates obtained from three different sources. *Magazine of Concrete Research* **60(1)**: 57–64.
- Kou SC and Poon CS (2013) Long-term mechanical and durability properties of recycled aggregate concrete prepared with the incorporation of fly ash. *Cement & Concrete Composites* **37**: 12–19.
- Kou SC and Poon CS (2015) Effect of the quality of parent concrete on the properties of high performance recycled aggregate concrete. *Construction and Building Materials* **77**: 501–508.
- Kou SC, Poon CS and Chan D (2004) Properties of steam cured recycled aggregate fly ash concrete. *Proceedings of International Conference on the Use of Recycled Materials in Buildings and Structures, Barcelona, Spain*, pp. 590–599.
- Kou SC, Poon CS and Chan D (2007) Influence of fly ash as a cement replacement on the hardened properties of recycled aggregate concrete. *Journal of Materials in Civil Engineering* **19(9)**: 709–717.
- Kou SC, Poon CS and Chan D (2008) Influence of fly ash as a cement addition on the hardened properties of recycled aggregate concrete. *Materials and Structures* **41(7)**: 1191–1201.
- Kou SC, Poon CS and Wan HW (2012) Properties of concrete prepared with low-grade recycled aggregates. *Construction and Building Materials* **36**: 881–889.
- Koulouris A, Limbachiya MC, Fried AN and Roberts JJ (2004) Use of recycled aggregate in concrete application: case studies. In *Proceedings of International Conference on Sustainable Waste Management and Recycling: Construction Demolition Waste, London, UK* (Limbachiya MC and Roberts JJ (eds)). Thomas Telford, London, UK, pp. 245–258.
- Kukadia VJ, Gajjar RK and Parkeh DN (2014) Performance of recycled concrete aggregates – new era for use in construction – a literature review. *International Journal for Scientific Research and Development* **2(10)**: 312–319.
- Kumutha R and Vijai K (2010) Strength of concrete incorporating aggregates recycled from demolition waste. *Journal of Engineering and Applied Sciences* **5(5)**: 64–71.
- Li X (2008a) Recycling and reuse of waste concrete in China – part I material behaviour of recycled aggregate concrete. *Resources, Conservation and Recycling* **53(1–2)**: 36–44.

- Li X (2008b) Recycling and reuse of waste concrete in China – part II. Structural behaviour of recycled aggregate concrete and engineering applications. *Resources, Conservation and Recycling* **53**(3): 107–112.
- Li W, Xiao J, Sun Z and Shah SP (2012) Failure processes of modelled recycled aggregate concrete under uniaxial compression. *Cement and Concrete Composites* **34**(10): 1148–1158.
- Limbachiya MC (2004) Coarse recycled aggregates for use in new concrete. *Proceedings of the Institution of Civil Engineers – Engineering Sustainability* **157**(2): 99–106.
- Limbachiya MC (2010) Recycled aggregates: production, properties and value-added sustainable applications. *Journal of Wuhan University of Technology – Materials Science* **25**(6): 1011–1016.
- Limbachiya MC, Leelawat T and Dhir RK (1998) RCA concrete: a study of properties in the fresh state, strength development and durability. In *Proceedings of International Conference on the Use of Recycled Concrete Aggregates* (Dhir RK, Henderson NA and Limbachiya MC (eds)). Thomas Telford, London, UK, pp. 227–237.
- Limbachiya MC, Leelawat T and Dhir RK (2000) Use of recycled concrete aggregate in high-strength concrete. *Materials and Structures* **33**(9): 574–580.
- Limbachiya MC, Koulouris A, Roberts JJ and Fried AN (2004) Performance of recycled aggregate concrete. *Proceedings of Rilem International Symposium on Environment – Conscious Materials and Systems for Sustainable Development*, Koriyama, Japan, pp. 127–136.
- Limbachiya MC, Meddah MS and Ouchagour Y (2012a) Performance of Portland/silica fume cement concrete produced with recycled concrete aggregate. *ACI Materials Journal* **109**(1): 91–100.
- Limbachiya MC, Meddah MS and Ouchagour Y (2012b) Use of recycled concrete aggregate in fly-ash concrete. *Construction and Building Materials* **27**(1): 439–449.
- Liu Q, Xiao J and Sun Z (2011) Experimental study on the failure mechanism of recycled concrete. *Cement and Concrete Research* **41**(10): 1050–1057.
- Lo CY, Chowdhury SH and Doh JH (2013) Recycled aggregate concrete prepared with water-washed aggregates – an investigative study. In *Proceedings of 22nd Australasian Conference on the Mechanics of Structures and Materials, Materials to Structures: Advancement through Innovation* (Samali B, Attard MM and Song C (eds)). Taylor & Francis, London, UK, pp. 1143–1146.
- López-Gayarre F, Serna P, Domingo-Cabo A, Serrano-López MA and López-Colina C (2009) Influence of recycled aggregate quality and proportioning criteria on recycled concrete properties. *Waste Management* **29**(12): 3022–3028.
- López-Gayarre F, López-Colina C, Serrano-López MA, García Taengua E and López Martínez A (2011) Assessment of properties of recycled concrete by means of a highly fractioned factorial design of experiment. *Construction and Building Materials* **25**(10): 3802–3809.
- Malesev M, Radonjanin V and Marinkovic S (2010) Recycled concrete as aggregate for structural concrete production. *Sustainability* **2**(5): 1204–1225.
- Manzi S, Mazzotti C and Bignozzi MC (2011) Concrete demolition waste: sustainable source for structural concrete. *Proceedings of 2nd Workshop on The New Boundaries of Structural Concrete*, Ancona, Italy, pp. 39–46.
- Manzi S, Mazzotti C and Bignozzi MC (2013a) Effect of adhered mortar of recycled concrete aggregates on long-term concrete properties. *Proceedings of 3rd International Conference on Sustainable Construction Materials and Technologies*, Kyoto, Japan, pp. 1–9.
- Manzi S, Mazzotti C and Bignozzi MC (2013b) Short and long-term behaviour of structural concrete with recycled concrete aggregate. *Cement and Concrete Composites* **37**: 312–318.
- Marinkovic S, Ignjatovic I, Radonjanin V and Malesev M (2012) Recycled aggregate concrete for structural use – an overview of technologies, properties and applications. In *ACES Workshop on Innovative Materials and Techniques in Concrete Construction* (Fardis MN (ed.)). Springer, Dordrecht, the Netherlands, pp. 115–130.
- Maruyama I, Sogo M, Sogabe T, Sato R and Kawai K (2004) Flexural properties of reinforced recycled concrete beams. *Proceedings of International Rilem Conference on the Use of Recycled Materials in Buildings and Structures, Barcelona, Spain*, pp. 526–535.
- Mathew P, Baby V, Sahoo D and Joseph G (2013) Manually recycled coarse aggregate from concrete waste – a sustainable substitute for customary coarse aggregate. *American Journal of Engineering Research* **3**: 34–38.
- McNeil K and Kang THK (2013) Recycled concrete aggregates: a review. *International Journal of Concrete Structures and Materials* **7**(1): 61–69.
- MdF (Ministerio de Fomento) (2010) EHE-08: Code on structural concrete. Ministerio de Fomento, Madrid, Spain.
- Meinhold U, Mellmann G and Maultzsch M (2001) *Performance of High-grade Concrete with Full Substitution of Aggregates by Recycled Concrete*. ACI, Farmington Hills, MI, USA, ACI SP-202, pp. 85–96.
- Mellman G, Meinhold U and Maultzsch M (1999) Processed concrete rubble for the reuse as aggregates. In *Proceedings of International Symposium, Exploiting Wastes in Concrete, Dundee, UK* (Dhir RK and Jappy TG (eds)). Thomas Telford, London, UK, pp. 171–178.
- Mendes T, Morales G and Carbonari G (2004) Study on ARC's aggregate utilization recycled of concrete. *Proceedings of International Rilem Conference Use of Recycled Materials in Buildings and Structures, Barcelona, Spain*, pp. 629–635.
- Mohamad N, Samad AAA, Goh WI, Suffian S and Hizami MT (2014) The use of recycled aggregate in a development of

- reinforced concrete container as a retaining wall: preliminary study. *Advanced Materials Research* **831**: 153–157.
- Morohashi N and Sakurada T (2007) Researching recycled aggregate structural concrete for buildings. In *Proceedings of International Conference on Sustainable Construction Materials and Technologies, Coventry, UK*. Taylor & Francis, London, UK, pp. 63–67.
- Morohashi N, Sakurada T and Yanagibashi K (2007) Bond splitting strength of high-quality recycled concrete aggregate concrete beams. *Journal of Asian Architecture and Building Engineering* **6(2)**: 331–337.
- Motwani P, Rajendhiran RK, Elumalai A and Santhi AS (2013) High strength concrete using recycled aggregate. *International Journal of Applied Engineering Research* **8(9)**: 2501–2505.
- Nishigori W and Sakai K (2012) Complete recycling of demolished concrete with low environmental loads. In *Proceedings of 9th fib International PhD Symposium in Civil Engineering* (Muller HS and Acosta HF (eds)). KIT Scientific, Karlsruhe, Germany, pp. 411–418.
- Nixon PJ (1978) Recycled concrete as an aggregate for concrete – a review. *Materials and Structures* **11(5)**: 371–378.
- Obla K, Kim H and Lobo C (2007) *Crushed Returned Concrete as Aggregates for New Concrete*. National Ready Mix Concrete Association, National Ready Mixed Concrete Association, Silver Spring, MD, USA.
- Olanike AO (2014) Taguchi experimental approach to laboratory evaluation of static modulus of elasticity of recycled aggregate concrete. *Global Journal of Engineering, Design and Technology* **3(1)**: 88–91.
- Ong G, Akbarnezhad A, Zhang MH *et al.* (2010) Mechanical properties of concrete incorporating microwave-treated recycled concrete aggregates. *Proceedings of 35th Conference on Our World in Concrete and Structures, Singapore*, pp. 1–8.
- Padmini AK, Ramamurthy K and Mathews MS (2009) Influence of parent concrete on the properties of recycled aggregate concrete. *Construction and Building Materials* **23(2)**: 829–836.
- Paine KA and Dhir RK (2010) Recycled aggregates in concrete: a performance-related approach. *Magazine of Concrete Research* **62(7)**: 519–530.
- Paine KA, Collyer DJ and Dhir RK (2009) Strength and deformation characteristics of strength concrete containing coarse recycled and manufactured aggregates. *Proceedings of 11th International Conference on Non-conventional Materials and Technologies, Bath, UK*, pp. 1–9.
- Park SG (1999) *Recycled concrete construction rubble as aggregate for new concrete*. Building Research Association of New Zealand. Study Report SR 86, Judgeford, New Zealand.
- Park WJ, Noguchi T, Shin SH and Oh DY (2015) Modulus of elasticity of recycled aggregate concrete. *Magazine of Concrete Research* **67(11)**: 585–591.
- Paul SC and van Zijl G (2012) Strength of recycled aggregate concrete for structural uses. In *Proceedings of 3rd International Conference on Concrete Repair, Rehabilitation and Retrofitting III, Cape Town, South Africa* (Alexander MG, Beushausen HD, Dehn F and Moyo P (eds)). Taylor & Francis, London, UK, pp. 1340–1346.
- Paul SC and van Zijl G (2013) Mechanical and durability properties of recycled concrete aggregate for normal strength structural concrete. *International Journal of Sustainable Construction Engineering & Technology* **4(1)**: 89–103.
- PCA (Portland Cement Association) (2002) *Recycled concrete for reinforced concrete?* Portland Cement Association, Skokie, IL, USA, pp. 5–6.
- Pecur IB, Stirmer N and Milovanovic B (2013) Durability properties of recycled aggregate concrete. *Proceedings of Rilem International Workshop on Performance-Based Specification and Control of Concrete Durability, Zagreb, Croatia*, pp. 191–198.
- Pecur IB, Stirmer N and Milovanovic B (2015) Recycled aggregate concrete for nearly zero-energy buildings. *Magazine of Concrete Research* **67(11)**: 575–584.
- Pedro D, de Brito J and Evangelista L (2014) Performance of concrete made with aggregates recycled from precasting industry waste: influence of the crushing process. *Materials and Structures*, pp. 1–12, <http://dx.doi.org/10.1617/s11527-014-0456-7>.
- Pepe M, Toledo Filho R, Koenders E and Martinelli E (2014) Alternative processing procedures for recycled aggregates in structural concrete. *Construction and Building Materials* **69**: 124–132.
- Pickel D, Tighe S and West J (2014) Evaluation of recycled concrete aggregate for usage in highway and municipal concrete applications. *Proceedings of Green Technologies Session of the 2014 Conference of the Transportation Association of Canada, Montreal, Quebec*, pp. 1137–1156.
- Poon CS and Kou SC (2004) Properties of steam cured recycled aggregate concrete. In *Proceedings of International Conference on Construction Demolition Waste, London, UK* (Limbachiya MC and Roberts JJ (eds)). Thomas Telford, London, UK, pp. 1–12.
- Poon CS and Kou SC (2010) Properties of cementitious rendering mortar prepared with recycled fine aggregates. *Journal of Wuhan University of Technology* **25(6)**: 1053–1056.
- Poon CS, Azhar S and Kou SC (2003) Recycled aggregates for concrete applications. *Proceedings of Materials Science and Technology in Engineering Conference – Now, New and Next, Hong Kong*, pp. 1–16.
- Poon CS, Kou SC and Chan D (2006) Influence of steam curing on hardened properties of recycled aggregate concrete. *Magazine of Concrete Research* **58(5)**: 289–299.

- Prasad MLV and Kumar PR (2007) Mechanical properties of fibre reinforced concretes produced from building demolished waste. *Journal of Environmental Research and Development* **2(2)**: 180–187.
- Purushothaman R, Amirthavalli R and Karan L (2014) Influence of treatment methods on the strength and performance characteristics of recycled aggregate concrete. *Journal of Materials in Civil Engineering* **27(5)**: 1–7, doi: 10.1061/(ASCE)MT.1943-5533.0001128.
- Qasrawi H (2014) The use of steel slag aggregate to enhance the mechanical properties of recycled aggregate concrete and retain the environment. *Construction and Building Materials* **54**: 298–304.
- Qasrawi H and Marie I (2013) Towards better understanding of concrete containing recycled concrete aggregate. *Advances in Materials Science and Engineering* **2013**: 1–8.
- Radonjanin V, Malesev M, Marinkovic S and Al Malty AES (2013) Green concrete aggregate concrete. *Construction and Building Materials* **47**: 1503–1511.
- Rahal K (2007) Mechanical properties of concrete with recycled coarse aggregate. *Building and Environment* **42(1)**: 407–415.
- Ramachandran VS (1981) *Waste and By-Products as Concrete Aggregates*. National Research Council, Ottawa, Canada, CBD-215.
- Rao A, Jha KM and Misra S (2007) Use of aggregates from recycled construction and demolition waste in concrete. *Resources, Conservation and Recycling* **50(1)**: 71–81.
- Rao DVP and Madhavi M (2013) A study on partially used recycled coarse aggregate cement concrete. *Asian Journal of Civil Engineering* **14(6)**: 917–933.
- Rao MC, Bhattacharyya S and Barai SV (2010) Influence of recycled aggregate on mechanical properties of concrete. *Proceedings of 5th Civil Engineering Conference in the Asian Region and Australasian Structural Engineering Conference*, Sydney, Australia, pp. 749–754.
- Rao MC, Bhattacharyya SK and Barai SV (2011a) Influence of field recycled coarse aggregate on properties of concrete. *Materials and Structures* **44(1)**: 205–220.
- Rao MC, Bhattacharyya SK and Barai SV (2011b) Behaviour of recycled aggregate concrete under drop weight impact load. *Construction and Building Materials* **25(1)**: 69–80.
- Rasheeduzzafar IB and Khan A (1984) Recycled concrete – a source for new aggregate. *Cement, Concrete and Aggregates* **6(1)**: 17–27.
- Ravindrarajah RS (1996) Effects of using recycled concrete as aggregate on the engineering properties of concrete. *Proceedings of National Symposium on the Use of Recycled Materials in Engineering Construction*, Sydney, Australia, pp. 147–152.
- Ravindrarajah RS (2012) High-strength self-compacting concrete for sustainable construction. In *Proceedings of 22nd Australasian Conference on the Mechanics of Structures and Materials, Materials to Structures: Advancement through Innovation* (Samali B, Attard MM and Song C (eds)). Taylor & Francis, London, UK, pp. 1021–1025.
- Ravindrarajah RS and Tam CT (1985) Properties of concrete made with crushed concrete as coarse aggregate. *Magazine of Concrete of Research* **37(130)**: 29–38.
- Ravindrarajah RS, Loo YH and Tam CT (1987) Recycled concrete as fine and coarse aggregates in concrete. *Magazine of Concrete Research* **39(141)**: 214–220.
- Razaqpur A, Fathifazl G, Isgor B et al. (2010) How to produce high quality concrete mixes with recycled concrete aggregate. *Proceedings of 2nd International Conference on Waste Engineering and Management, Shanghai, China*, pp. 11–35.
- Rilem TC121 (1994) Specifications for concrete with recycled aggregates. *Materials and Structures* **27(9)**: 557–559.
- Roos F (1998) Verification of the dimensioning values for concrete with recycled concrete aggregates. In *Proceedings of International Conference on the Use of Recycled Concrete Aggregates, London, UK* (Dhir RK, Henderson NA and Limbachiya MC (eds)). Thomas Telford, London, UK, pp. 309–320.
- Safiuddin M, Alengaram UJ, Salam MA et al. (2011) Properties of high-workability concrete with recycled concrete aggregate. *Materials Research* **14(2)**: 248–255.
- Safiuddin M, Alengaram U, Rahman MM, Salam MA and Jumaat MZ (2013) Use of recycled concrete aggregate in concrete: a review. *Journal of Civil Engineering and Management* **19(6)**: 796–810.
- Sagoe-Crentsil K and Brown T (1998) *Guide for Specification of Recycled Concrete Aggregates (RCA) for Concrete Production*. CSIRO, Building, Construction and Engineering, East Melbourne, Victoria, Australia.
- Sakata K and Ayano T (2000) Improvement of concrete with recycled aggregate. *Proceedings of 5th Canmet/ACI International Conference on Durability of Concrete*, Barcelona, Spain, vol. II, pp. 1089–1108.
- Salehlamein FR, Solikin M and SriSunarjono I (2015) Effect of recycled coarse aggregate on concrete properties. *International Journal of Innovative Research in Science, Engineering and Technology* **4(1)**: 19060–19068.
- Salem RM and Burdette EG (2001) Role of chemical and mineral admixtures on physical properties and frost resistance of recycled aggregate concrete. *ACI Materials Journal* **95(5)**: 558–563.
- Salem RM, Burdette EG and Jackson NM (2001) Interrelationship of physical properties of concrete made with recycled aggregates. *Proceedings of the Transportation Research Board 82nd Annual Meeting*, Washington, DC, USA, pp. 1–20.
- Salem RM, Burdette EG and Jackson NM (2003) Resistance to freezing and thawing of recycled aggregate concrete. *ACI Materials Journal* **100(3)**: 216–221.
- Sarhat S and Sherwood E (2013) Residual mechanical response of recycled aggregate concrete after exposure to elevated

- temperatures. *Journal of Materials in Civil Engineering* **25(11)**: 1721–1730.
- Sato R, Maruyama I, Sogabe T and Sogo M (2007) Flexural behaviour of reinforced recycled concrete beams. *Journal of Advanced Concrete Technology* **5(1)**: 43–61.
- Schulz RR (1986) West Germany must learn from long experience. *Batiment International, Building Research and Practice* **14(3)**: 154–159.
- Sheen YN, Wang HY, Juang YP and Le DH (2013) Assessment on the engineering properties of ready-mixed concrete using recycled aggregates. *Construction and Building Materials* **45**: 298–305.
- Silva RV, de Brito J and Dhir RK (2014) Properties and composition of recycled aggregates from construction and demolition waste suitable for concrete production. *Construction and Building Materials* **65**: 201–217.
- Sivakumar N, Muthukumar S, Sivakumar V, Gowtham D and Muthuraj V (2014) Experimental studies on high strength concrete by using recycled coarse aggregate. *International Journal of Engineering and Science* **4(1)**: 27–36.
- Soares D, de Brito J, Ferreira J and Pacheco J (2014) Use of coarse recycled aggregates from precast concrete rejects: mechanical and durability performance. *Construction and Building Materials* **71**: 263–272.
- Somna R, Jaturapitakkul C, Chalee W and Rattanachu P (2012a) Effect of the water to binder ratio and ground fly ash on properties of recycled aggregate concrete. *Journal of Materials in Civil Engineering* **24(1)**: 16–22.
- Somna R, Jaturapitakkul C, Rattanachu P and Chalee W (2012b) Effect of ground bagasse ash on mechanical and durability properties of recycled aggregate concrete. *Materials and Design* **36**: 597–603.
- Song X, Wiao P and Wen H (2015) Recycled aggregate concrete enhanced with polymer aluminium sulfate. *Magazine of Concrete Research* **67(10)**: 496–502.
- Surya M, Kanta Rao VVL and Lakshmy P (2013) Recycled aggregate concrete for transportation infrastructure. *Procedia – Social and Behavioral Sciences* **104**: 1158–1167.
- Suryawanshi SR, Singh B and Bhargava P (2015) Characterization of recycled aggregate concrete. *Advances in Structural Engineering* **3**: 1813–1822.
- Tam CT, Ong KCG, Akbarnezhad A and Zhang MH (2013) Research on recycled concrete aggregates at NUS. *Electronic Journal of Structural Engineering* **13(1)**: 21–30.
- Tam V and Tam CM (2008) Diversifying two-stage mixing approach (TSMA) for recycled aggregate concrete: TSMA_s and TSMA_{sc}. *Construction and Building Materials* **22(10)**: 2068–2077.
- Tam V, Gao XF and Tam CM (2006) Comparing performance of modified two-stage mixing approach for producing recycled aggregate concrete. *Magazine of Concrete Research* **58(7)**: 477–484.
- Tam V, Tam CM and Le KN (2007a) Removal of cement mortar remains from recycled aggregate using pre-soaking approaches. *Resources, Conservation and Recycling* **50(1)**: 82–101.
- Tam V, Tam CM and Wang Y (2007b) Optimization on proportion for recycled aggregate in concrete using two-stage mixing approach. *Construction and Building Materials* **21(10)**: 1928–1939.
- Tangchirapat W, Buranasing R, Jaturapitakkul C and Chindaprasirt P (2008) Influence of rice husk-bark ash on mechanical properties of concrete containing high amount of recycled aggregates. *Construction and Building Materials* **22(8)**: 1812–1819.
- Tangchirapat W, Buranasing R and Jaturapitakkul C (2010) Use of high fineness of fly ash to improve properties of recycled aggregate concrete. *Journal of Materials in Civil Engineering* **22(6)**: 565–571.
- Tangchirapat W, Rattanashotinunt C, Buranasing R and Jaturapitakkul C (2013) Influence of fly ash on slump loss and strength of concrete fully incorporating recycled concrete aggregates. *Journal of Materials in Civil Engineering* **25(2)**: 243–251.
- Teranishi K, Dosho Y, Narikawa M and Kikuchi M (1998) Application of recycled aggregate concrete for structural concrete. Part 3 – production of recycled aggregate by real-scale plant and quality of recycled aggregate concrete. In *Proceedings of International Conference on the Use of Recycled Concrete Aggregates* (Dhir RK, Henderson NA and Limbachiya MC (eds)). Thomas Telford, London, UK, pp. 143–156.
- TFSCCS (Task Force of the Standing Committee of Concrete of Spain) (2004) Draft of Spanish regulations for the use of recycled aggregate in the productions of structural concrete. *Proceedings of International Rilem Conference on the Use of Recycled Materials in Buildings and Structures, Barcelona, Spain*, pp. 511–525.
- Thomas C, Setien J, Polanco JA, Alaejos P and Sanchez de Juan M (2013) Durability of recycled aggregate concrete. *Construction and Building Materials* **40**: 1054–1065.
- Thomas C, Sosa I, Setien J, Polanco JA and Cimentada A (2014a) Evaluation of the fatigue behaviour of recycled aggregate concrete. *Journal of Cleaner Production* **65**: 397–405.
- Thomas C, Setien J, Polanco JA, Lombillo I and Cimentada A (2014b) Fatigue limit of recycled aggregate concrete. *Construction and Building Materials* **52**: 146–154.
- Tsujino M, Noguchi T, Tamura M, Kanematsu M and Maruyama I (2007) Application of conventionally recycled coarse aggregate to concrete structure by surface modification treatment. *Journal of Advanced Concrete Technology* **5(1)**: 13–25.
- Ueno A, Ishida M, Ohno K and Uji K (2013) Properties of extremely dry concrete made with eco-cement and recycled coarse aggregate. *Proceedings of 3rd International Conference on Sustainable Construction Materials and Technologies, Kyoto, Japan*, pp. 1–9.
- Ujike I (2000) A study on air and water permeability of concrete using aggregate recycled from crushed concrete.

- Proceedings of Rilem/CIB/ISO International Symposium, Integrated Life-Cycle Design of Materials and Structures, Helsinki, Finland*, pp. 194–198.
- USACE (U.S. Army Corps of Engineers) (2004) *Reuse of Concrete Materials from Building Demolition*. Department of the Army, Washington, DC, USA, Public Works technical bulletin 200-1-27.
- Uygunoglu T, Topcu IB and Celik AG (2014) Use of waste marble and recycled aggregates in self-compacting concrete for environmental sustainability. *Journal of Cleaner Production* **84**: 691–700.
- Vazquez E (2013) *Progress of Recycling in the Built Environment*. Final Report of Rilem Technical Committee 217-PRE. Springer, Dordrecht, the Netherlands.
- Verian KPN, Whiting NM, Olek J, Jain J and Snyder MB (2013) *Using Recycled Concrete as Aggregate in Concrete Pavements to Reduce Materials Cost*. Joint Transportation Research Program, Indiana Department of Transportation and Purdue University, West Lafayette, Indiana, USA, Report FHWA/IN/JTRP-2013/18.
- Vieira JPB, de Brito J and Correia JR (2011) Post-fire mechanical properties of concrete made with recycled concrete coarse aggregates. *Cement and Concrete Research* **41(5)**: 533–541.
- Vyas CM and Bhatt DR (2013) Evaluation of modulus of elasticity for recycled coarse aggregate concrete. *International Journal of Engineering Science and Innovative Technology* **2(1)**: 26–29.
- Vyncke J and Rousseau E (1994) Recycling of construction and demolition waste in Belgium: actual situation and future evolution. In *Proceedings of 3rd International Rilem Symposium, Demolition and Reuse of Concrete and Masonry*, Odense, Denmark (Lauritzen EK (ed.)). E&FN Spon, London, UK, pp. 60–74.
- Wagih AM, El-Karmoty HZ, Ebid M and Okba SH (2013) Recycled construction and demolition concrete waste as aggregate for structural concrete. *Housing and Building National Research Center* **9(3)**: 193–200.
- Waleed N and Canisius TDG (2007) *Engineering Properties of Concrete Containing Recycled Aggregates*. Waste and Resources Action Programme (WRAP), Banbury, UK, Project code AGG0079-002.
- Wang HL, Wang JJ, Sun XY and Jin WL (2013a) Improving performance of recycled aggregate concrete with superfine pozzolanic powders. *Journal of Central South University* **20(12)**: 3715–3722.
- Wang WL, Kou SC and Xing F (2013b) Deformation properties and direct shear of medium strength concrete prepared with 100% recycled coarse aggregates. *Construction and Building Materials* **48**: 187–193.
- Wardeh G, Ghorbel E and Gohmart H (2015) Mix design and properties of recycled aggregate concretes: applicability of Eurocode 2. *International Journal of Concrete Structures and Materials* **9(1)**: 1–20.
- Wu B, Liu C and Yang Y (2013) Size effect on compressive behaviours of normal-strength concrete cubes made from demolished concrete blocks and fresh concrete. *Magazine of Concrete Research* **65(19)**: 1155–1167.
- Xiao J, Li J and Zhang C (2005) Mechanical properties of recycled aggregate concrete under uniaxial loading. *Cement and Concrete Research* **35(6)**: 1187–1194.
- Xiao J, Li J and Zhang C (2006a) On relationships between the mechanical properties of recycled aggregate concrete: an overview. *Materials and Structures* **39**: 655–664.
- Xiao J, Sun Y and Falkner H (2006b) Seismic performance of frame structures with recycled aggregate concrete. *Engineering Structures* **28(1)**: 1–8.
- Xiao J, Li W and Poon CS (2012a) Recent studies on mechanical properties of recycled aggregate concrete in China – a review. *Science China Technological Sciences* **55(6)**: 1643–1480.
- Xiao J, Li W, Fan Y and Huang X (2012b) An overview of study on recycled aggregate concrete in China (1996–2011). *Construction and Building Materials* **31**: 364–383.
- Xiao J, Fan Y and Tam VWY (2015) On creep characteristics of cement paste, mortar and recycled aggregate concrete. *European Journal of Environmental and Civil Engineering* **19(10)**: 1234–1252.
- Yanagi K, Kasai Y, Kaga S and Abe M (1998) Experimental study on the applicability of recycled aggregate concrete to cast in place concrete pile. In *Proceedings of International Conference on the Use of Recycled Concrete Aggregates* (Dhir RK, Henderson NA and Limbachiya MC (eds)). Thomas Telford, London, UK, pp. 359–370.
- Yang DJ, Hao YH and Wang TC (2010) Experimental research on recycled aggregate concrete for highway pavement. In *Proceedings of 10th International Conference of Chinese Transportation Professionals, Integrated Transportation Systems: Green, Intelligent, Reliable, Beijing, China* (Wei H, Wang Y, Rong J and Weng J (eds)). ASCE, Reston, VA, USA, pp. 2913–2919.
- Yang F, Lin H and Xin W (2008a) Concrete shrinkage and creep in recycled aggregate concrete-filled steel tubes. *Advances in Structural Engineering* **11(4)**: 383–396.
- Yang KH, Chung HS and Ashour AF (2008b) Influence of type and replacement level of recycled aggregates on concrete properties. *ACI Materials Journal* **105(3)**: 289–296.
- Yang YF, Ma GL and Wang J (2012) Experimental studies on recycled aggregate concrete filled stainless steel tube stub columns. In *Proceedings of 14th International Symposium on Tubular Structures, London, UK* (Gardner L (ed.)). Taylor & Francis, London, UK, pp. 383–389.
- Yin J, Chi Y, Gong S and Zou W (2010) Research and application of recycled aggregate concrete. In *Proceedings of Sessions of GeoShanghai 2010 of Paving Materials and Pavement Analysis, Shanghai, China* (Huang B, Tutumluer E, Al-Qadi IL, Prozzi J and Shu X (eds)). American Society of Civil Engineers, Reston, VA, USA, pp. 162–168.

-
- Yun HD (2010) Effects of recycled coarse aggregate replacement levels on the mechanical properties of RAC. In *Proceedings of 6th International Conference on Concrete under Severe Conditions, Yucatan, Mexico* (Castor-Borges P, Moreno EI, Sakai K, Gjørsv O and Banthia N (eds)). Taylor & Francis, Leiden, the Netherlands, pp. 1585–1592.
- Zega C and Di Maio AA (2011) Recycled concretes made with waste ready-mix concrete as coarse aggregate. *Journal of Materials in Civil Engineering* **23(3)**: 281–286.
- Zega CJ and Di Maio AA (2006) Recycled concrete exposed to high temperatures. *Magazine of Concrete Research* **58(10)**: 675–682.
- Zega CJ and Di Maio AA (2009) Recycled concrete made with different natural coarse aggregates exposed to high temperature. *Construction and Building Materials* **23(5)**: 2047–2052.

WHAT DO YOU THINK?

To discuss this paper, please email up to 500 words to the editor at journals@ice.org.uk. Your contribution will be forwarded to the author(s) for a reply and, if considered appropriate by the editorial panel, will be published as discussion in a future issue of the journal.

Proceedings journals rely entirely on contributions sent in by civil engineering professionals, academics and students. Papers should be 2000–5000 words long (briefing papers should be 1000–2000 words long), with adequate illustrations and references. You can submit your paper online via www.icevirtuallibrary.com/content/journals, where you will also find detailed author guidelines.