

Charge collection and field profile studies of heavily irradiated strip sensors for the ATLAS inner tracker upgrade

ATLAS Collaboration

DOI:

[10.1016/j.nima.2016.04.035](https://doi.org/10.1016/j.nima.2016.04.035)

License:

Creative Commons: Attribution-NonCommercial-NoDerivs (CC BY-NC-ND)

Document Version

Peer reviewed version

Citation for published version (Harvard):

ATLAS Collaboration 2016, 'Charge collection and field profile studies of heavily irradiated strip sensors for the ATLAS inner tracker upgrade', *Nuclear Instruments & Methods in Physics Research. Section A. Accelerators, Spectrometers, Detectors*. <https://doi.org/10.1016/j.nima.2016.04.035>

[Link to publication on Research at Birmingham portal](#)

General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.


Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact UBIRA@lists.bham.ac.uk providing details and we will remove access to the work immediately and investigate.

Charge Collection and Field Profile Studies of Heavily Irradiated Strip Sensors for the ATLAS Inner Tracker Upgrade

K. Hara, P.P. Allport, M. Baca, J. Broughton, A. Chisholm, K. Nikolopoulos, S. Pyatt, J.P. Thomas, J.A. Wilson, J. Kierstead, P. Kuczewski, D. Lynn, M. Arratia, L.B.A. Hommels, M. Ullan, I. Bloch, I.M. Gregor, K. Tackmann, A. Trofimov, E. Yildirim, M. Hauser, K. Jakobs, S. Kuehn, K. Mahboubi, R. Mori, U. Parzefall, A. Clark, D. Ferrere, S. Gonzalez Sevilla, J. Ashby, A. Blue, R. Bates, C. Buttar, F. Doherty, T. McMullen, F. McEwan, V. O'Shea, S. Kamada, K. Yamamura, Y. Ikegami, K. Nakamura, Y. Takubo, Y. Unno, R. Takashima, A. Chilingarov, H. Fox, A.A. Affolder, G. Casse, P. Dervan, D. Forshaw, A. Greenall, S. Wonsak, M. Wormald, V. Cindro, G. Kramberger, I. Mandić, M. Mikuž, I. Gorelov, M. Hoferkamp, P. Palni, S. Seidel, A. Taylor, K. Toms, R. Wang, N.P. Hessey, N. Valencic, K. Hanagaki, Z. Dolezal, P. Kodys, J. Bohm, M. Mikestikova, A. Bevan, G. Beck, C. Milke, M. Domingo, V. Fadeyev, Z. Galloway, D. Hibbard-Lubow, Z. Liang, H.F.-W. Sadrozinski, A. Seiden, K. To, R. French, P. Hodgson, H. Marin-Reyes, K. Parker, O. Jinnouchi, K. Hara, K. Sato, K. Sato, M. Hagihara, S. Iwabuchi, J. Bernabeu, J.V. Civera, C. Garcia, C. Lacasta, S. Marti i. Garcia, D. Rodriguez, D. Santoyo, C. Solaz, U. Soldevila

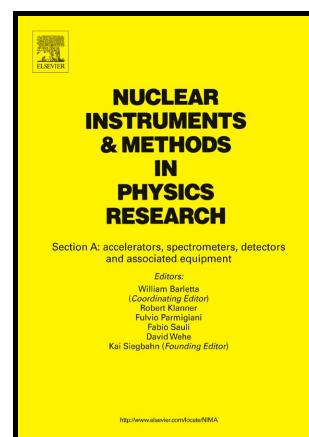

www.elsevier.com/locate/nima

PII: S0168-9002(16)30207-8
DOI: <http://dx.doi.org/10.1016/j.nima.2016.04.035>
Reference: NIMA58817

To appear in: *Nuclear Inst. and Methods in Physics Research, A*

Received date: 20 November 2015

Revised date: 12 April 2016

Accepted date: 12 April 2016

Cite this article as: K. Hara, P.P. Allport, M. Baca, J. Broughton, A. Chisholm,

K. Nikolopoulos, S. Pyatt, J.P. Thomas, J.A. Wilson, J. Kierstead, P. Kuczewski, D. Lynn, M. Arratia, L.B.A. Hommels, M. Ullan, I. Bloch, I.M. Gregor, K. Tackmann, A. Trofimov, E. Yildirim, M. Hauser, K. Jakobs, S. Kuehn, K. Mahboubi, R. Mori, U. Parzefall, A. Clark, D. Ferrere, S. Gonzalez Sevilla, J. Ashby, A. Blue, R. Bates, C. Buttar, F. Doherty, T. McMullen, F. McEwan, V. O'Shea, S. Kamada, K. Yamamura, Y. Ikegami, K. Nakamura, Y. Takubo, Y. Unno, R. Takashima, A. Chilingarov, H. Fox, A.A. Affolder, G. Casse, P. Dervan, D. Forshaw, A. Greenall, S. Wonsak, M. Wormald, V. Cindro, G. Kramberger, I. Mandić, M. Mikuž, I. Gorelov, M. Hoferkamp, P. Palni, S. Seidel, A. Taylor, K. Toms, R. Wang, N.P. Hessey, N. Valencic, K. Hanagaki, Z. Dolezal, P. Kodys, J. Bohm, M. Mikestikova, A. Bevan, G. Beck C. Milke, M. Domingo, V. Fadeyev, Z. Galloway, D. Hibbard-Lubow, Z. Liang, H.F.-W. Sadrozinski, A. Seiden, K. To, R. French, P. Hodgson, H. Marin-Reyes, K. Parker, O. Jinnouchi, K. Hara, K. Sato, K. Sato, M. Hagihara, S. Iwabuchi, J. Bernabeu, J.V. Civera, C. Garcia, C. Lacasta, S. Marti i. Garcia, D. Rodriguez, D. Santoyo, C. Solaz and U. Soldevila, Charge Collection and Field Profile Studies of Heavily Irradiated Strip Sensors for the ATLAS Inner Tracker Upgrade, *Nuclear Inst. and Methods in Physics Research, A* <http://dx.doi.org/10.1016/j.nima.2016.04.035>

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting galley proof before it is published in its final citable form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain

Charge Collection and Field Profile Studies of Heavily Irradiated Strip Sensors for the ATLAS Inner Tracker Upgrade

K. Hara^{x,y,*}, P.P. Allport^a, M. Baca^a, J. Broughton^a, A. Chisholm^a, K. Nikolopoulos^a, S. Pyatt^a, J.P. Thomas^a, J.A. Wilson^a, J. Kierstead^b, P. Kuczewski^b, D. Lynn^b, M. Arratia^c, L.B.A. Hommels^c, M. Ullan^d, I. Bloch^e, I.M. Gregor^e, K. Tackmann^e, A. Trofimov^e, E. Yildirim^e, M. Hauser^f, K. Jakobs^f, S. Kuehn^f, K. Mahboubi^f, R. Mori^f, U. Parzefall^f, A. Clark^g, D. Ferrere^g, S. Gonzalez Sevilla^g, J. Ashby^h, A. Blue^h, R. Bates^h, C. Buttar^h, F. Doherty^h, T. McMullen^h, F. McEwan^h, V. O'Shea^h, S. Kamadaⁱ, K. Yamamuraⁱ, Y. Ikegami^j, K. Nakamura^j, Y. Takubo^j, Y. Unno^j, R. Takashima^k, A. Chilingarov^l, H. Fox^l, A.A. Affolder^m, G. Casse^m, P. Dervan^m, D. Forshaw^{m,1}, A. Greenall^m, S. Wonsak^m, M. Wormald^m, V. Cindroⁿ, G. Krambergerⁿ, I. Mandićⁿ, M. Mikužⁿ, I. Gorelov^o, M. Hoferkamp^o, P. Palni^o, S. Seidel^o, A. Taylor^o, K. Toms^o, R. Wang^o, N.P. Hessey^p, N. Valencic^p, K. Hanagaki^{q,j}, Z. Dolezal^r, P. Kodys^r, J. Bohm^s, M. Mikestikova^s, A. Bevan^t, G. Beck^t, C. Milke^u, M. Domingo^u, V. Fadeyev^u, Z. Galloway^u, D. Hibbard-Lubow^u, Z. Liang^u, H. F.-W. Sadrozinski^u, A. Seiden^u, K. To^u, R. French^v, P. Hodgson^v, H. Marin-Reyes^v, K. Parker^v, O. Jinnouchi^w, K. Hara^{x,y}, K. Sato^x, K. Sato^{x,y}, M. Hagihara^x, S. Iwabuchi^x, J. Bernabeu^z, J.V. Civera^z, C. Garcia^z, C. Lacasta^z, S. Marti i Garcia^z, D. Rodriguez^z, D. Santoyo^z, C. Solaz^z, U. Soldevila^z

^aSchool of Physics and Astronomy, University of Birmingham, Birmingham B15 2TT, United Kingdom

^bBrookhaven National Laboratory, Physics Department and Instrumentation Division, Upton, NY 11973-5000, USA

^cCavendish Laboratory, University of Cambridge, JJ Thomson Avenue, Cambridge CB3 0HE, United Kingdom

^dCentro Nacional de Microelectronica (IMB-CNM, CSIC), Campus UAB-Bellaterra, 08193 Barcelona, Spain

^eDESY, Notkestrasse 85, 22607 Hamburg, Germany

^fPhysikalisches Institut, Universität Freiburg, Hermann-Herder-Str. 3, D-79104 Freiburg, Germany

^gDPNC, University of Geneva, 24, Quai Ernest-Ansermet, CH-1211 Geneve 4, Switzerland

^hSUPA- School of Physics and Astronomy, University of Glasgow, Glasgow G12 8QQ, United Kingdom

ⁱSolid State Div., Hamamatsu Photonics K.K., 1126-1, Ichino-cho, Higashi-ku, Hamamatsu-shi, Shizuoka 435-8558, Japan

^jInstitute of Particle and Nuclear Study, KEK, Oho 1-1, Tsukuba, Ibaraki 305-0801, Japan

^kDepartment of Science Education, Kyoto University of Education, Kyoto 612-8522, Japan

^lPhysics Department, Lancaster University, Lancaster LA1 4YB, United Kingdom

^mOliver Lodge Laboratory, Department of Physics, University of Liverpool, Oxford St., Liverpool L69 7ZE, United Kingdom

ⁿJožef Stefan Institute and Department of Physics, University of Ljubljana, Ljubljana, Slovenia

^oDepartment of Physics and Astronomy, University of New Mexico, MSC07 4220, 1919 Lomas Blvd. NE, Albuquerque, NM 87131, USA

^pNikhef, Science Park 105, 1098 XG Amsterdam, Netherlands

^qDepartment of Physics, Osaka University, Machikaneyama-cho 1-1, Toyonaka-shi, Osaka 560-0043, Japan

^rCharles University in Prague, Faculty of Mathematics and Physics, V Holesovickach 2, Prague 8, Czech Republic

^sAcademy of Sciences of the Czech Republic, Institute of Physics, Na Slovance 2, 18221 Prague 8, Czech Republic

^tSchool of Physics and Astronomy, Queen Mary University of London, London E1 4NS, United Kingdom

^uSanta Cruz Institute for Particle Physics (SCIPP), University of California, Santa Cruz, CA 95064, USA

^vDepartment of Physics and Astronomy, The University of Sheffield, Hicks Building, Hounsfield Road, S3 7RH Sheffield, United Kingdom

^wInstitute of Science and Engineering, Tokyo Institute of Technology, Ookayama 2-12-1, Meguro-ku, Tokyo 152-8551, Japan

^xInstitute of Pure and Applied Sciences, University of Tsukuba, Tsukuba, Ibaraki 305-8751, Japan

^yCenter for Integrated Research in Fundamental Science and Engineering, University of Tsukuba, Tsukuba, Ibaraki 305-8571 Japan

^zIFIC/CSIC-UVEG, Ed. Inst. Investigacion, PO Box 22085, 46071 Valencia, Spain

Abstract

The ATLAS group has evaluated the charge collection in silicon microstrip sensors irradiated up to a fluence of $1 \times 10^{16} \text{ n}_{\text{eq}}/\text{cm}^2$, exceeding the maximum of $1.6 \times 10^{15} \text{ n}_{\text{eq}}/\text{cm}^2$ expected for the strip tracker during the high luminosity LHC (HL-LHC) period including a safety factor of 2. The ATLAS12, n^+ -on-p type sensor, which is fabricated by Hamamatsu Photonics (HPK) on float zone (FZ) substrates, is the latest barrel sensor prototype. The charge collection from the irradiated $1 \times 1 \text{ cm}^2$ barrel test sensors has been evaluated systematically using penetrating β -rays and an Alibava readout system. The data obtained at different measurement sites are compared with each other and with the results obtained from the previous ATLAS07 design. The results are very consistent, in particular, when the deposit charge is normalized by the sensor's active thickness derived from the edge transient current technique (edge-TCT) measurements. The measurements obtained using β -rays are verified to be consistent with the measurements using an electron beam. The edge-TCT is also effective for evaluating the field profiles across the depth. The differences between the irradiated ATLAS07 and ATLAS12 samples have been examined along with the differences among the samples irradiated with different radiation sources: neutrons, protons, and pions. The studies of the bulk properties of the devices show that the devices can yield a sufficiently large signal for the expected fluence range in the HL-LHC, thereby acting as precision tracking sensors.

Keywords: high luminosity Large Hadron Collider, microstrip sensor, charge collection, edge transient current technique, field profile

Preprint submitted to Nuclear Instruments and Methods A

April 12, 2016

1. Introduction

The ATLAS experiment [1] at the Large Hadron Collider (LHC) is due to undergo phased detector upgrades in accordance with the planned accelerator upgrades. The instantaneous beam luminosity after the Phase-II upgrade of the LHC, termed the HL-LHC (high luminosity LHC) [2], is expected to reach $5 \times 10^{34} \text{ cm}^{-2} \text{ s}^{-1}$ and deliver a total of 3000 fb^{-1} of collisions at a center-of-mass energy of 14 TeV. The ATLAS inner detector is subjected to a major upgrade to cope with these significant increases in the instantaneous and integrated luminosities. A new all-semiconductor type inner tracker (ITk) [3] [4] [5] composed of pixel and microstrip layers will be installed. As described in the Letter of Intent (LoI) [6] the microstrip detector is constructed of five barrel layers and seven discs in each of the endcaps. The barrel strips in the three inner layers are 24 mm long while in the outer layers they are 48 mm long. The strip pitch is $74.5 \mu\text{m}$ in both cases. The length of the endcap strips varies from 17 mm to 59 mm depending on the radius. The strip length is chosen so as to maintain the average hit occupancy at less than 1% at the expected maximum instantaneous luminosity.

The particle fluence and total ionizing dose expected at the end of experiment's lifetime has been evaluated with a FLUKA simulation [7]: this simulation is based on the experience from the current detector where the agreement between simulation and measurement is within 20% [7]. The estimated maximum lifetime fluence values [7] are $5.3 \times 10^{14} \text{ n}_{\text{eq}}/\text{cm}^2$ in the 24 mm long barrel strips, $2.9 \times 10^{14} \text{ n}_{\text{eq}}/\text{cm}^2$ in the 48 mm long barrel strips, and $8.1 \times 10^{14} \text{ n}_{\text{eq}}/\text{cm}^2$ in the endcap. Here, the contributions of different kind of particles are translated into 1-MeV neutron equivalent values by taking into account the non-ionizing energy loss (NIEL) [8] factors in silicon. The particle composition (n, π, p) varies according to the location and is found to be (57%, 35%, 8%) and (73%, 19%, 8%) at the points with the largest fluence values in the 24 mm and 48 mm long barrel strips [9].

We have extensively studied the radiation hardness of Hamamatsu n^+ -on-p float-zone (FZ) strip sensors to predict the performance at the end of lifetime and determine if the collected charge is sufficiently large. Previous studies [10] using the ATLAS07 layout sensors [11] have shown that after irradiation to the HL-LHC fluence the charge is reduced. However, the signal-to-noise ratio is more than 15 at 500 V bias and thus, the detector remains as a precision tracker.

The ATLAS12A (A12A, for short) and ATLAS12M (A12M)[12] sensor layouts are the latest sensor designs implemented at the time of writing (2016). A12 main sensors have the axial strips only and A12M main sensors have the axial and stereo strips mixed. Different bulk resistivity and further design evolution compared to A07 sensors allow us to find effects that depend on them and further assure that the resistivity range expected in production is within the required specification. The bulk damage properties of these series were compared

with those of the ATLAS07 (A07) series, and the dependence of damage difference on the radiating particle type (neutron, proton, pion) was investigated. The collected charge values were evaluated by seven groups using identical Alibava [13] readout systems utilizing penetrating β rays emitted from ^{90}Sr . We extended the study to a 4.4-GeV electron beam to cross check if the β results are representative of the HL-LHC experiment.

The magnitudes of damage due to neutrons, protons and pions were found to be different for the same NIEL fluence of $5 \times 10^{14} \text{ n}_{\text{eq}}/\text{cm}^2$. The signal as a function of sensor depth was evaluated using an edge transient current technique (TCT) [14] to determine the field profile after these irradiations.

2. Samples, Irradiation, and Charge Collection Measurements

2.1. Samples

Hamamatsu utilizes 6" wafers for sensor fabrication. The $9.75 \times 9.75 \text{ cm}$ main sensor, which is surrounded by 24 pieces of $1.0 \times 1.0 \text{ cm}$ miniature sensors, is placed on each wafer. Only the miniature sensors are used in this study. The A07, A12A, and A12M sensors are fabricated on the same p-type wafer category FZp, where the resistivity was specified to be within 3 to 8 $\text{k}\Omega\text{cm}$. In practice, the typical sensor resistivity varied among the wafer production lots. Consequently, the full-depletion voltages are typically 200-220 V (4.3-4.7 $\text{k}\Omega\text{cm}$) for A07, 220 V for A12M, and 270-320 V (2.9-3.5 $\text{k}\Omega\text{cm}$) for A12A.

2.2. Irradiation

The samples were irradiated with neutrons at Ljubljana TRIGA Reactor [15], with 300-MeV pions at PSI, and with 23-, 27-, 70-, and 800-MeV protons at Karlsruhe, Birmingham, CYRIC (Tohoku University, Japan), and Los Alamos accelerators. The 1-MeV neutron equivalent fluence values were calculated using NIEL hardness factors [8].

As an exemplary irradiation setup, the scanning box and sample holder used at CYRIC are shown in the photograph (Fig. 1). There are fifteen sample slots in the box. The holder with the samples to be irradiated was pushed in remotely, and then the box was moved laterally to allow for uniform irradiation of the samples with the proton beam. The box was thermally insulated and liquid nitrogen was flushed through it to maintain a temperature of approximately -15°C . Aluminum foils were attached to the samples to obtain dosimetry using $\text{Al}^{27}(\text{p}, 3\text{pn})\text{Na}^{24}$ spallation reaction. For fluences in the range of 10^{12} - $10^{16} \text{ n}_{\text{eq}}/\text{cm}^2$, samples were irradiated from few minutes to six hours at a beam current ranging from 10 nA to 1 μA . The fluence uncertainty was approximately 10%, as determined from the uncertainty in the available spallation cross section. The irradiated samples were stored in a refrigerator immediately after a series of irradiation was completed.

2.3. Charge collection measurement technique and calibration

All the measurements reported here utilized the Alibava system [13] which uses a Beetle analogue readout chip with a field-programmable gate array (FPGA)-based readout. The Alibava

*Corresponding author. e-mail: hara@hep.px.tsukuba.ac.jp

¹Now at Syracuse University.

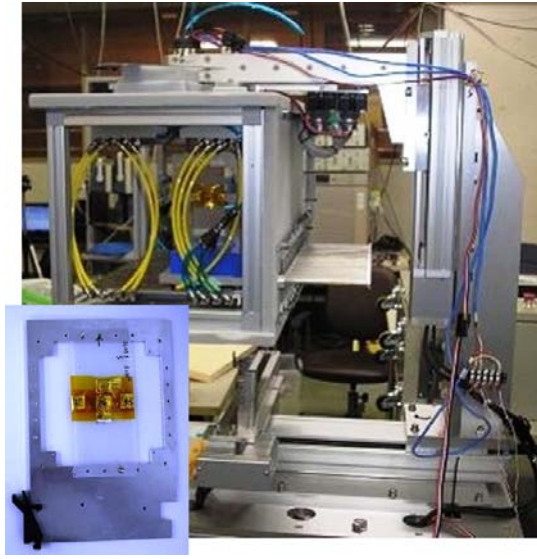


Fig. 1: Sample box used in the irradiation experiment at CYRIC. The bottom-left inset shows the sample holder to be inserted in the sample box.

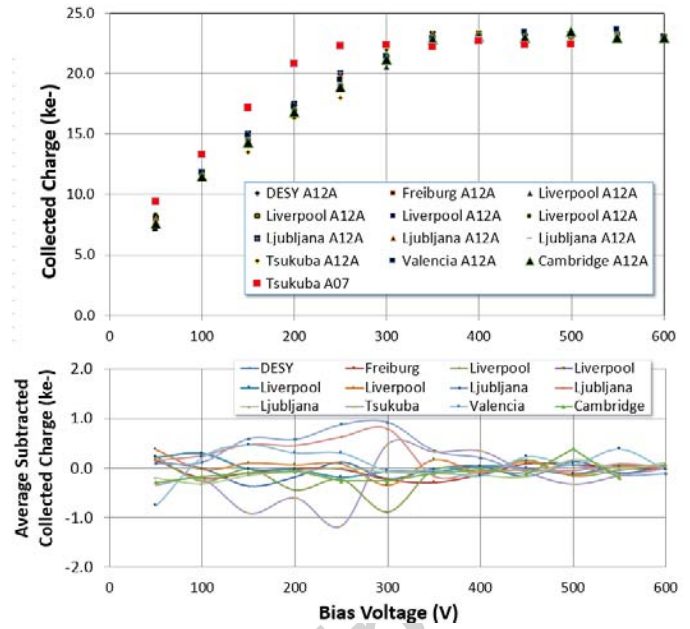


Fig. 2: (top) Collected charge vs. bias for non-irradiated samples measured at different sites. The charge is normalized to 23 ke⁻ for a sample with an active thickness of 300 μm. All samples are A12A except for one A07. (bottom) Average subtracted collected charge in ke⁻ for twelve A12A non-irradiated samples.

system digitizes charge while recording the trigger arrival time with respect to the clock cycle. Since a scintillating counter set underneath the sample triggers on the penetrating β particles generated through ^{90}Sr decay, the trigger timing is not always optimal with respect to the charge sampling timing. To be selected for the analysis, events were required to be within 5 ns of the trigger signal which resulted in the maximum collected charge. The collected charge of an event was determined by a clustering algorithm with a seed threshold of 3.5 times the channel's noise level and neighbor threshold of 1.5 times the noise. The collected charge for the sample at a given voltage was found by fitting of the cluster charge distribution with a Landau function convoluted with a Gaussian. The most probable cluster charge is defined as the collected charge. Instead of relying on the internal calibration of the Beetle, we have determined the calibration with non-irradiated samples assuming charge collection Q [e⁻] above depletion voltage to be

$$Q = \frac{d}{3.68} [190 + 16.3 \ln(d)]$$

for the measured active thickness d [μm] of the device [16]. Note that active thickness is typically 10 μm smaller than physical thickness, which is explained in Sec. 4.

Figure 2 shows the plot of collected charge vs. bias voltage measured for non-irradiated samples and at various measurement sites. Most of the curves are for A12A samples except for one corresponding to an A07. As explained previously the full depletion voltage of A07 is lower than that of the others but all the samples show identical collected charge above full depletion.

The average subtracted collected charge is plotted in Fig. 2 for the A12A sensors. Larger variations are only seen when not fully depleted: above depletion agreement is very good. Since different sites used different samples, any resistivity and thick-

ness variations within the production lead to changes in the normalization. Since he observed variation is less than 1 ke⁻ below full depletion and at most 0.3 ke⁻ above full depletion, these effects are minimal.

The samples were measured at low temperatures, around -20°C to suppress the leakage current induced by radiation. The actual temperatures were different among the measurement sites depending on the cooling system performance. Since the calibration of the Alibava system has a temperature dependence, charge calibration relying on non-irradiated sensors of known thickness, as described, enhances the reliability of charge measurement.

3. Results of Charge Collection Measurements

3.1. Annealing

The annealing properties of the samples irradiated to $\sim 10^{15}$ n_{eq}/cm² are quite different from those reported previously [17], especially at high bias voltages. Figure 3 shows the collected charge of the A12A and A12M sensors irradiated with protons to a fluence of 10^{15} n_{eq}/cm², measured as a function of annealing time at 60°C. The collected charge increases (beneficial annealing) up to 80 min, and then decreases for both samples at lower bias voltages. However, the collected charge of A12M stays almost constant at bias voltages of 900 V and 1000 V after 80 min. Similar trends as for A12M have been observed in another study [18] conducted on A07 sensors, where the samples were irradiated to 10^{15} n_{eq}/cm² by neutrons and pions. Owing to radiation-induced defects, the depletion depth decreases with radiation. Since depletion develops from the strip side and

the applied bias voltage is sustained in the depletion region, the field around the strips increases with irradiation and bias, reaching a region where avalanche multiplication occurs.

The magnitude of initial beneficial annealing is dependent on irradiation conditions such as irradiation rate [19]. Therefore a certain controlled annealing is preferred prior to comparing various types of irradiation data. Also in real experiments where the radiation rate is much smaller and beneficial annealing is taking place, results evaluated with controlled annealing are expected to represent actual characteristics in the real experiments. In the following, the results of charge collection measurement after controlled annealing for 80 min at 60°C are presented.

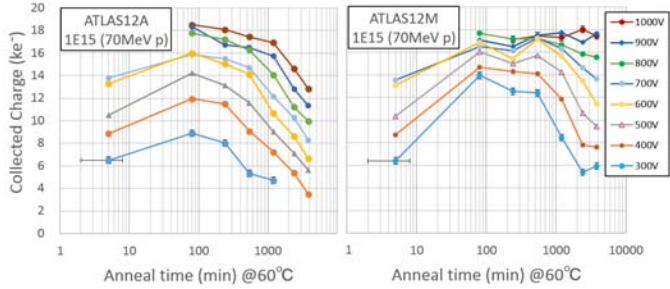


Fig. 3: Examples of annealing properties of A12A (left) and A12M (right). The samples were irradiated with protons to a fluence of $1 \times 10^{15} \text{ n}_{\text{eq}}/\text{cm}^2$.

3.2. Neutron and proton irradiation

Figure 4 shows the collected charge at 500 V and 900 V as a function of fluence for all neutron-irradiated A12A and A07 samples. As expected from [20] [21], there is a difference between A12A and A07 sensors observed below $5 \times 10^{14} \text{ n}_{\text{eq}}/\text{cm}^2$ due to the difference in the initial resistivity of the devices. At higher fluences, this effect is much reduced.

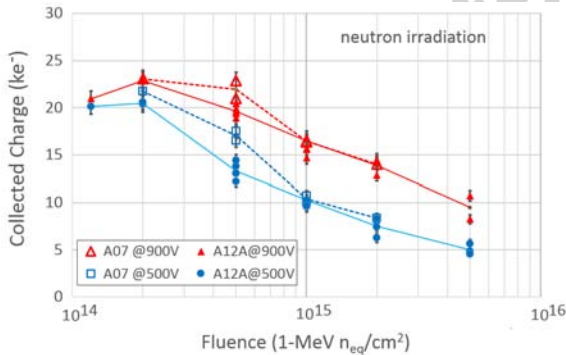


Fig. 4: Collected charge of neutron-irradiated samples measured at 500 V and 900 V. The lines connect the average data points separately for A07 and A12A samples.

All the data points measured for proton irradiated A12A samples are plotted for three bias voltage settings, 300, 500, and 900 V, in Fig. 5. No noticeable dependence on the source of proton irradiation or the charge collection measurement site was observed for these results.

In Fig. 6, the results of A12A are compared with those of A07 and A12M at 300 V, 500 V, and 900 V. Since the A12A

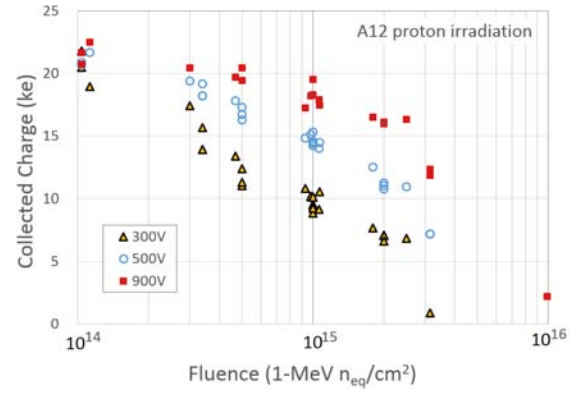


Fig. 5: Collected charge of proton irradiated A12A samples measured at 300, 500, and 900 V.

data points, as shown in Fig. 5, form specific bands, we take the averages if multiple data points are available, with the variations represented as uncertainty.

At 500 V, the difference among proton irradiated samples is substantially reduced, compared to that observed at 300 V, as expected for the different full depletion voltages. Moreover, the difference to the neutron-irradiated samples becomes small at 900 V as shown in the figure.

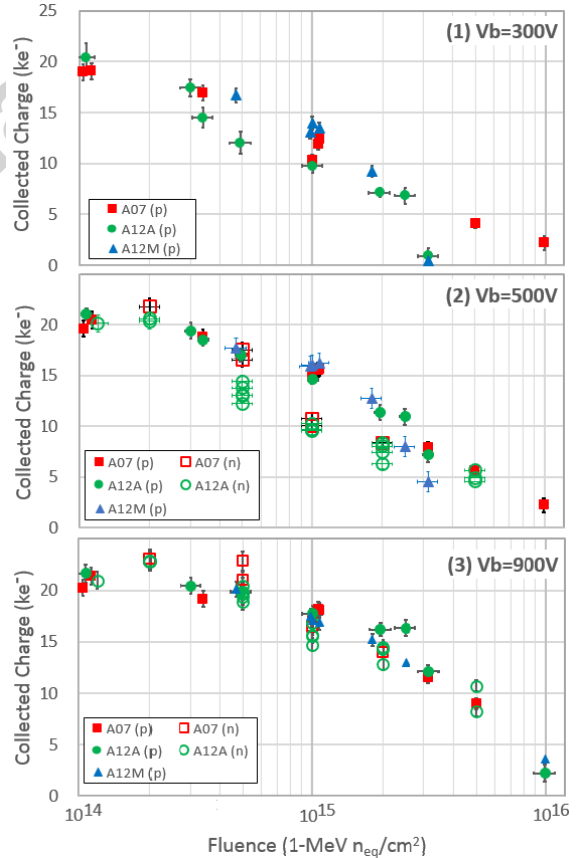


Fig. 6: Comparison of collected charge of proton-irradiated A07, A12A, and A12M samples, measured at (1) 300 V, (2) 500 V, and (3) 900 V. The A12A data points are the averages of the data shown in Fig. 5 with variations represented as uncertainty. The neutron data at 500 V and 900 V, as shown in Fig. 4, are also plotted.

3.3. Test beam evaluation of neutron-irradiated samples

The charge collection from a few neutron-irradiated samples was measured using a DESY 4.4 GeV electron beam. Two samples, read out with the Alibava system, were placed in the beam in between two beam tracker systems. The samples were cooled to $-25 \pm 3^\circ\text{C}$ by circulating cooled Silicone oil around them.

Figure 7 compares the charge distributions of the non-irradiated and $1 \times 10^{15} \text{ n}_{\text{eq}}/\text{cm}^2$ irradiated samples between the source and beam measurements. The distributions of cluster size, which is determined by the number of hit strips in a hit cluster, are also plotted. The charge distributions are consistent between the source and beam. The cluster size distributions are slightly wider for the source measurement, which can be explained by the incident angle and scattering effects of β rays.

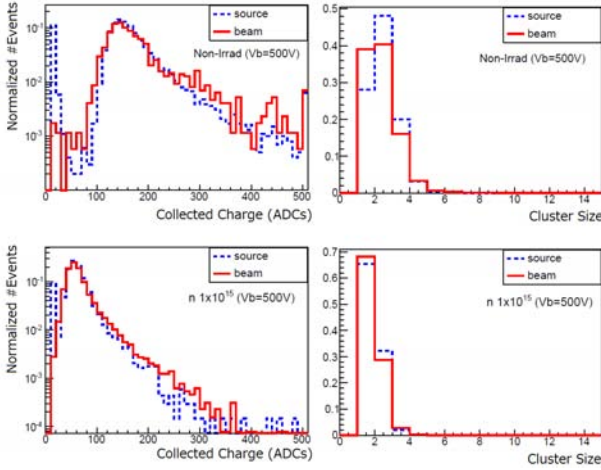


Fig. 7: Comparison of source (dashed) and beam (solid histograms) measurements of the non-irradiated (above) and $1 \times 10^{15} \text{ n}_{\text{eq}}/\text{cm}^2$ irradiated samples (below). Comparison of charge distributions and cluster size distributions at 500 V.

The most probable charge values are compared in Fig. 8 as a function of the detector bias for eight samples: two non-irradiated and six neutron-irradiated samples. Of the six samples, two were measured before being subjected to controlled annealing. The agreement between the two measurements is remarkable, although there is a slight tendency for the collected charge of the irradiated samples for the beam data to be 5-6% higher than that for the source data.

The results of this study with the electron beam verified that measurements using a ^{90}Sr β source can provide reliable values in estimation of collected charge for minimum-ionizing particles.

3.4. Comparison among proton, neutron, and pion irradiation

As discussed in Sec. 3.2, the reduction in charge collection is higher for neutrons than for protons at 500 V bias. A systematic comparison of the collected charge was carried out for the A12A samples of similar initial full depletion voltages irradiated with neutrons, 23-MeV protons (Karlsruhe), and 300-MeV pions (PSI) to the same NIEL fluence of $5 \times 10^{14} \text{ n}_{\text{eq}}/\text{cm}^2$. From Fig. 9, we observe that the collected charge is larger

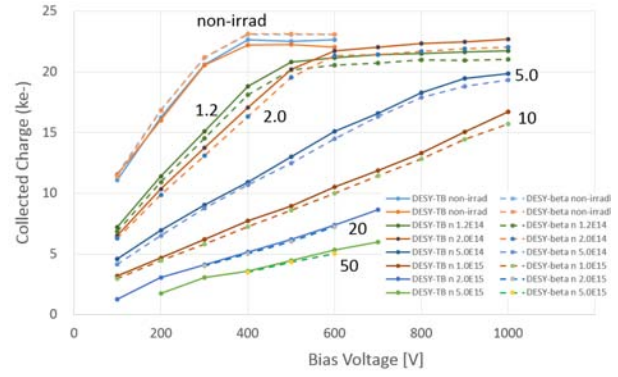


Fig. 8: Comparison of collected charge values between beam (solid line) - and source (dashed line) -measurements, shown as a function of bias. The samples are non-irradiated or irradiated with neutrons to the fluence denoted by the numbers shown next to the curves (the unit is $10^{14} \text{ n}_{\text{eq}}/\text{cm}^2$). The curves 20 and $50 \times 10^{14} \text{ n}_{\text{eq}}/\text{cm}^2$ are for the data before annealing.

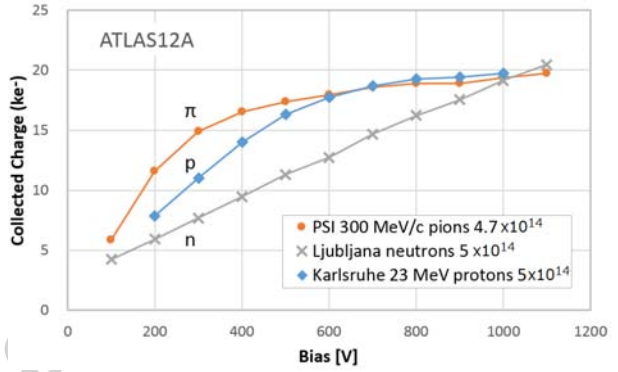


Fig. 9: Collected charge vs. bias of A12A samples irradiated with neutrons, protons, and pions to a fluence of $5 \times 10^{14} \text{ n}_{\text{eq}}/\text{cm}^2$.

for the pion-irradiated sample than for the proton- or neutron-irradiated samples. For a bias of 500 V or less, the difference is noticeably large.

The results clearly suggest that NIEL hypothesis is not suitable for the normalization of collectable charge at the concerned fluence level, which is typically $1 \times 10^{15} \text{ n}_{\text{eq}}/\text{cm}^2$.

The differences after irradiation are the main subject of the study presented in Sec. 4. We discuss the differences in the field profile along the depth instead in the full depletion voltages, since the irradiated sensors do not remain as a simple diode and characterization by the full depletion only is not appropriate.

3.5. Charge Collection at 500 V

Figure 10 plots the summary of neutron, proton, and pion irradiation measurements at 500 V including the measurements using the electron beam. The maximum operation voltage at the HL-LHC, expected in ATLAS, is 500 V, which is determined from the specifications of the available cables used in the present inner detector. At 500 V, all proton-irradiated samples, A07, A12A, and A12M show similar fluence dependences, while the collected charge is reduced for neutron-irradiated samples in the fluence range of $0.5\text{--}2 \times 10^{15} \text{ n}_{\text{eq}}/\text{cm}^2$ for A12A, and of $1\text{--}2 \times 10^{15} \text{ n}_{\text{eq}}/\text{cm}^2$ for A07 samples.

4. Field Profile Studies

In the transient current technique (TCT), transient currents on readout electrodes are induced by charge released in the detector by short laser pulses. The charge collection characteristics of the silicon detector can be investigated from the induced current pulses. The method, when the laser light is injected from the detector side, is effective in evaluating the active thickness and understanding the difference between the sensors and irradiation sources.

In an edge-TCT [14] study, an infrared laser of 1060 nm wavelength and 300 ps duration was injected from a polished side edge parallel to the strip direction. The induced current from one of the strips was measured using a high-speed amplifier and a 1.5 GHz oscilloscope, in which neighboring strips were set to the same potential as the readout strip to avoid disturbance of the electric field in the strip sensor. The laser was collimated to 8 μm (FWHM) underneath the readout strip. By scanning through the depth of the sensor the charge collection characteristics can be investigated as a function of sensor depth.

The induced current time profile is influenced by the number of generated charge carriers, carrier velocities, and carrier trapping along their paths. The current profile right after the laser injection can be expressed as [22]:

$$I(y, t \sim 0) \sim qE_w(y)[\bar{v}_e(y) + \bar{v}_h(y)]$$

where y denotes the depth location in the sensor, $E_w(y)$ is the weighting field in Ramo's theorem, q is the elementary charge, and \bar{v}_e and \bar{v}_h are electron and hole velocities, respectively. The time $t \sim 0$ condition in the equation is a result of the requirement that the current amplitude is measured immediately after carrier generation before trapping and before charges move significantly away from the location of the laser beam. When the laser beam is perpendicular to the strips, the weighting field is effectively constant because of the contributions of carriers drifting to the neighboring strips [14]. The current values at $t = 0.6$ ns was found to be adequate for measurement of the velocity sum, $\bar{v}_e(y) + \bar{v}_h(y)$ [22].

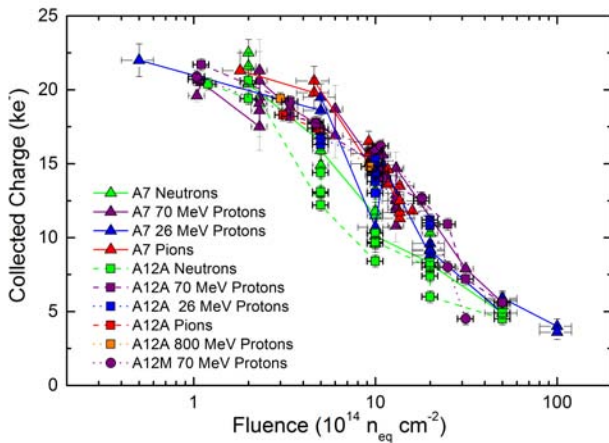


Fig. 10: Summary of collected charge measurements at 500 V for A07, A12A and A12M samples, shown separately for various irradiation sources.

Since velocities are expressed as the product of mobilities and the electric field, the electric field can be extracted simply by using $I(y, t \sim 0) \sim \bar{v}_e(y) + \bar{v}_h(y) = [\mu_e(E) + \mu_h(E)]E$, provided that the electric field is not very high, as velocity saturates with increasing electric field. The detailed analysis has been reported in a previous study [22].

The velocity sum, $\bar{v}_e(y) + \bar{v}_h(y)$, is plotted in Fig. 11 as a function of sensor depth for non-irradiated A07 and A12A samples at 200 V and 400 V. Here, the vertical scale is arbitrary but the sample areas in the same plot are normalized, since integration of the electric field ($\sim \bar{v}_e(y) + \bar{v}_h(y)$) over the depth gives the bias voltage, which is fixed. Since resistivity is different, the depth profile is different at 200 V, when A12A is not fully depleted. At 400 V both the sensors are fully depleted. Note that the full depths are slightly different between A07 and A12A. We conclude that the active depths are 10 μm smaller than the physical thickness of the A07 and A12A samples, which are 310 and 320 μm , respectively.

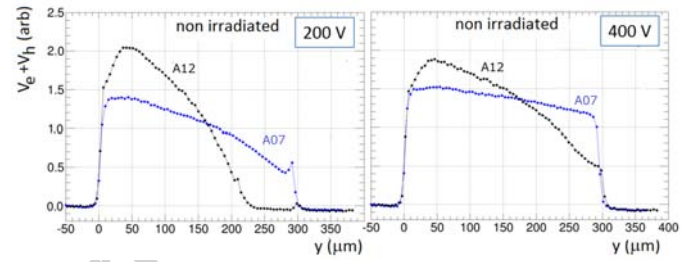


Fig. 11: Velocity-sum profiles of non-irradiated A07 and A12A samples at 200 V (left) and 400 V (right).

The velocity-sum profiles of neutron-irradiated A07 and A12A samples measured at 700 V are shown in Fig. 12. The field near the backside of A07 is substantially larger than that for A12A at $5 \times 10^{14} \text{ n}_{\text{eq}}/\text{cm}^2$ as expected, because of the different initial resistivities. The difference, however, diminishes at $2 \times 10^{15} \text{ n}_{\text{eq}}/\text{cm}^2$ irradiation, which can be explained by the fact that radiation-induced space charge dominates over the initial difference. Notably, non-zero velocity profiles near the backside are observed for both the samples at $2 \times 10^{15} \text{ n}_{\text{eq}}/\text{cm}^2$ irradiation. Such a profile is known as “double peak electric field profile” [23] [22], where the space charge in the detector changes sign. The carriers released by the generation current are trapped in defects, and subsequently, holes flow to the backplane, effectively changing the sign of the space charge near the backplane of the p-type bulk. Therefore the space charge concentration becomes zero at a certain depth. For both the sensors, zero charge concentration occurs at a depth of approximately 180 μm at 700 V at $2 \times 10^{15} \text{ n}_{\text{eq}}/\text{cm}^2$, and at approximately 250 μm for A12A only at $5 \times 10^{14} \text{ n}_{\text{eq}}/\text{cm}^2$.

The velocity-sum profiles of protons-, neutron-, and pion-irradiated A12A samples, measured at 300 V and 500 V, are compared in Fig. 13. At both the bias voltages, there are substantial non-zero contributions near the backside for the pion-irradiated samples. The profile reveals that the sample irradiated by pions to $5 \times 10^{14} \text{ n}_{\text{eq}}/\text{cm}^2$ is fully depleted at 500 V, while there is a substantial undepleted region in the neutron-irradiated sample at 500 V. The measured velocity-sum profiles agree with

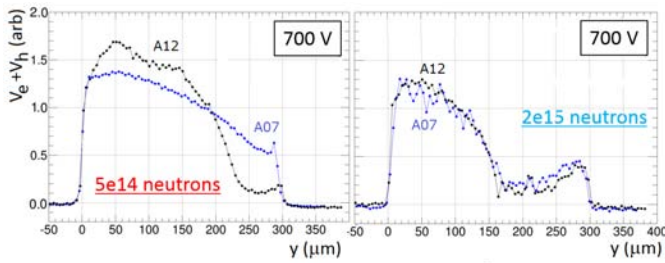


Fig. 12: Velocity-sum profiles of A07 and A12A samples at 700 V irradiated to a fluence of 5×10^{14} (left) and 2×10^{15} n_{eq}/cm^2 (right).

the charge collection difference shown previously (Fig. 9).

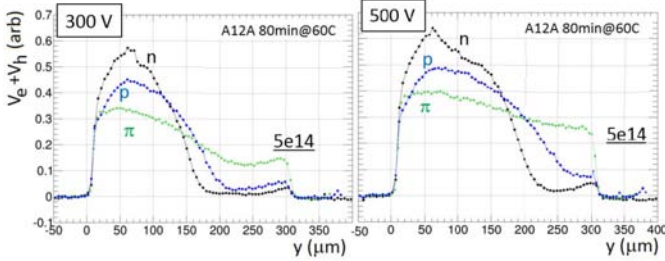


Fig. 13: Velocity-sum profiles of A12A samples irradiated with protons, neutrons, and pions to a fluence of 5×10^{14} n_{eq}/cm^2 measured at 300 V (left) and 500 V (right).

5. Conclusions

We extensively studied the charge collection from Hamamatsu p-bulk FZ sensors of 310–320 μm thickness using penetrating β rays. Highly consistent results were obtained by the seven groups that participated in the measurements. The results were further verified by independent measurements using an electron beam.

The difference in the charge collection between different sensor types, which is due to different initial resistivity, diminishes with the irradiation fluence and bias voltage. The effect depends on the particles used in the irradiation. For example, at 500 V, the samples irradiated with protons showed a small difference in charge collection, while those irradiated with neutrons showed a difference below 1×10^{15} n_{eq}/cm^2 .

The reduction in the charge collection is largest for neutron irradiation followed by that for 23-MeV proton irradiation. Damage caused by 300-MeV pions is the least for the same NIEL fluence.

The carrier velocity profiles across the depth were evaluated using an edge TCT. The profiles differ for different irradiating particles, neutrons, protons, and pions. The field near the backside is the largest for the pion-irradiated samples, which explains the largest charge collection observed for these samples.

The expected signal-to-noise ratios after the HL-LHC fluence can be evaluated using the ENC noise values of the readout electronics with corresponding wire-bonded sensors. Typical ENC noise values are 550 e^- for the barrel with 24 mm long strips connected, 720 e^- for the barrel with 48 mm connected,

and 650 e^- for the endcap module [24]. Assuming the safety factor of 2 and the neutron damage dominance, we arrive at conservative estimate for the lowest S/N value of 14. It is realized for endcap location.

The present studies have verified that the Hamamatsu p-bulk strip sensors are operational and provide precise particle tracking in the high-radiation environment expected in the HL-LHC.

6. Acknowledgements

The irradiations were performed: with protons at the University of Birmingham MC40 cyclotron, supported by the H2020 project AIDA-2020, GA number 654168, and the UK's Science and Technology Facilities Council, at Cyclotron and Radioisotope Center (CYRIC), Tohoku University, with Y. Sakemi, M. Ito, and T. Wakui, at the Karlsruhe Institute of Technology (KIT) by A. Dierlamm, supported by the Initiative and Networking Fund of the Helmholtz Association, contract HA-101 (Physics at the Terascale) and the European Commission under the FP7 Research Infrastructures project AIDA, Grant agreement no.262025, and at the LANSCE facility, Los Alamos National Laboratory; with neutrons at JSI TRIGA reactor in Ljubljana supported by the H2020 project AIDA-2020, GA no. 654168; with pions at Paul Scherrer Institut (PSI); and with γ 's at Brookhaven National Laboratory (BNL).

The research was supported and financed in part by CONICYT Becas Chile 72140349 and Cambridge Trust, the Ministry of Education, Youth and Sports of the Czech Republic (Grant No. LG13009), the German Federal Ministry of Education and Research, and the Helmholtz Association, the European Social Fund and by the Ministry of Science, Research and Arts, Baden-Wuerttemberg, Germany, the Japan Society for Promoting Science KAKENHI-A Grant number 20244038 and KAKENHI-C Grant number 20540291, the Ministry of Education, Culture, Sports, Science and Technology-Japan, KAKENHI for Research on Priority Area Grant number 20025007 and for Scientific Research on Innovative Areas Grant number 23104002, the Slovenian Research Agency, the Spanish Ministry of Economy and Competitiveness through the Particle Physics National Program (ref. FPA2012-39055-C02-01 and FPA2012-39055-C02-02) and co-financed with FEDER funds, the financial support of the State Secretariat for Education, Research, and Innovation, the Swiss National Science Foundation and the Canton of Geneva, Switzerland, the UK Science and Technology Facilities Council (under Grant ST/M006409/1), and the United States Department of Energy, grant DE-FG02-13ER41983.

- [1] ATLAS Collaboration, JINST 3 (2008) S08003.
- [2] S. McMahon, 2015. Presented at this symposium.
- [3] M. Backhaus, 2015. Presented at this symposium.
- [4] I.-M. Gregor, 2015. Presented at this symposium.
- [5] K. Hara and Y. Ikegami, Nuclear Instruments and Method A731 (2013) 242.
- [6] ATLAS Collaboration, CERN-2012-022, LHCC-1-023 (2012).
- [7] I. Dawson and P. Miyagawa, ATL-GEN-2014-003 (2014).
- [8] A. Vasilescu (INPE Bucharest) and G. Lindstroem (University of Hamburg), Displacement damage in silicon, on-line compilation, 2000. <http://rd50.web.cern.ch/RD50/NIEL/default.html>.

- 423 [9] I. Dawson and P. Miyagawa (U. Sheffield), 2015 Aug. Private Communi-
424 cation.
- 425 [10] K. Hara, et al., Nuclear Instruments and Method A636 (2011) S83.
- 426 [11] Y. Unno, et al., Nuclear Instruments and Methods A636 (2011) S24.
- 427 [12] Y. Unno, et al., Nuclear Instruments and Method A765 (2014) 80.
- 428 [13] Alibava Systems, 2015. Homepage <http://www.alibavasystems.com/>.
- 429 [14] G. Kramberger, et al., IEEE TNS NS-57 (2010) 2294.
- 430 [15] L. Snoj, G. Žerovnik, and A. Trikov, Appl. Radiat. Isot. 70 (2012) 483.
- 431 [16] H. Bichsel, Review of Modern Physics 60-3 (1988) 663.
- 432 [17] G. Lindstroem, et al., Nuclear Instruments and Method A512 (2003) 30.
- 433 [18] I. Mandic, et al., Nuclear Instruments and Method A629 (2011) 101.
- 434 [19] M. Moll (ROSE Collaboration), Nuclear Instruments and Method A426
435 (1999) 87.
- 436 [20] RD50 Collaboration, CERN-LHCC-2010-012 and LHCC-SR-003
437 (2010).
- 438 [21] T. Affolder, Nuclear Instruments and Method A623 (2010) 177.
- 439 [22] G. Kramberger, et al., JINST 9 (2014) P10016.
- 440 [23] V. Eremin, et al., Nuclear Instruments and Methods A535 (2004) 622.
- 441 [24] Communication with ATLAS ITk Strip Module group (T. Affolder et. al.),
442 2015 Sept.