

## Epsilon-near-zero lens for beamshaping of sub-terahertz waves

Torres, V; Pacheco-Peña, V.; Orazbayev, B.; Teniente, J.; Beruete, M.; Navarro-Cia, Miguel; Sorolla, M.; Engheta, N.

DOI:

[10.1109/IRMMW-THz.2015.7327508](https://doi.org/10.1109/IRMMW-THz.2015.7327508)

License:

Other (please specify with Rights Statement)

*Document Version*

Peer reviewed version

*Citation for published version (Harvard):*

Torres, V, Pacheco-Peña, V, Orazbayev, B, Teniente, J, Beruete, M, Navarro-Cia, M, Sorolla, M & Engheta, N 2015, Epsilon-near-zero lens for beamshaping of sub-terahertz waves. in *2015 40th International Conference on Infrared, Millimeter, and Terahertz waves (IRMMW-THz)*. Institute of Electrical and Electronics Engineers (IEEE), pp. 1-2. <https://doi.org/10.1109/IRMMW-THz.2015.7327508>

[Link to publication on Research at Birmingham portal](#)

### **Publisher Rights Statement:**

(c) 2015 IEEE. Personal use of this material is permitted. Permission from IEEE must be obtained for all other users, including reprinting/republishing this material for advertising or promotional purposes, creating new collective works for resale or redistribution to servers or lists, or reuse of any copyrighted components of this work in other works

### **General rights**

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

### **Take down policy**

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact [UBIRA@lists.bham.ac.uk](mailto:UBIRA@lists.bham.ac.uk) providing details and we will remove access to the work immediately and investigate.

# Epsilon-near-zero lens for beamshaping of sub-terahertz waves

Víctor Torres<sup>1</sup>, Víctor Pacheco-Peña<sup>1</sup>, Bakhtiyar Orazbayev<sup>1</sup>, Jorge Teniente<sup>1</sup>, Miguel Beruete<sup>1</sup>, Miguel Navarro-Cía<sup>2,3</sup>, Mario Sorolla<sup>4</sup>, and Nader Engheta<sup>5</sup>

<sup>1</sup> Antennas Group-TERALAB, Universidad Pública de Navarra, Pamplona 31006, Spain

<sup>2</sup> Optical and Semiconductor Devices Group, Department of Electrical and Electronic Engineering, Imperial College London, London SW7 2BT, UK

<sup>3</sup> Ultrafast Laser Laboratory, Department of Electronic and Electrical Engineering, University College London, London WC1E 7JE, UK

<sup>4</sup> TERALAB (MmW - THz - IR & Plasmonics Laboratory), Universidad Pública de Navarra, Pamplona 31006, Spain

<sup>5</sup> Department of Electrical and Systems Engineering, University of Pennsylvania, Philadelphia, PA 19104, USA

**Abstract**—The focal properties and radiation characteristics of an epsilon-near-zero metamaterial lens are investigated numerically and experimentally in the D-band. The experimental focusing enhancement of the lens is  $\sim 16$  dB. The directivity of the lens antenna configuration at 144 GHz is  $\sim 18$  dBi and the corresponding gain scan loss below 3 dB is achieved for angles up to  $\pm 15$  deg.

## I. INTRODUCTION

STANDARD dielectric lenses operating at millimeter-waves suffer from significant Fresnel reflection loss [1]. At optics this can be easily reduced with anti-reflective coatings. However, at millimeter-waves the required anti-reflective coatings would be very thick, heavy and costly to implement for real applications.

With the advent of metamaterials [2], [3], scientists have been equipped with alternative disruptive approaches to address problems like the aforementioned. For instance, we tackle here the problem of impedance mismatch by implementing an epsilon-near-zero (ENZ) lens operating in the energy squeezing and tunneling realm where reflection is minimized [4]-[8]. Alternative solutions are based on gradient index lenses whose design and implementation is cumbersome [9]. The ENZ lens can be considered as an evolution of Kock's metallic lenses [10]. The focal properties of the lens as well as its radiation characteristics are studied analytically, numerically and experimentally in the D-band of the millimeter-wave regime.

## II. RESULTS

The ENZ lens is implemented via a two-dimensional arrangement of narrow rectangular aluminum waveguides operating near cut-off (for the fundamental  $TE_{10}$  mode), which is carved to produce a plano-concave profile. The hollow is  $1.1 \text{ mm} \times 0.05 \text{ mm}$  (along  $x$ - and  $y$ - axis, respectively), whereas the in-plane periodicities are  $d_x = 1.4 \text{ mm}$  and  $d_y = 0.5 \text{ mm}$ . The diameter of the spherical profile has a value of  $55.5 \text{ mm}$ . The fabricated prototype is shown in Fig. 1.

After a fast prototyping based on 2D Huygens-Fresnel principle, full-wave simulations of the 3D fabricated lens are carried out with CST Microwave Studio<sup>TM</sup> to assess the measurements. In the simulations, the lens model follows the fabrication dimensions (according to confocal microscope pictures) and aluminum is modelled with conductivity  $\sigma_{Al} = 3.56 \times 10^7 \text{ S/m}$ .

Initially, the focal properties of the lens are measured with two independent setups. The first setup uses as a feeder a corrugated horn antenna placed 1.3 m away from the flat face of the lens along with a flanged-ended WR-6.5 waveguide working as a detector. Both elements are connected to an ABmm vector network analyzer. The second setup uses the same corrugated horn antenna, but placed closer to the lens (160 mm away), together with a near-field probe with sharpened edges. Both elements are connected in this case to an Agilent Technologies N5242A PNA-X network analyzer.

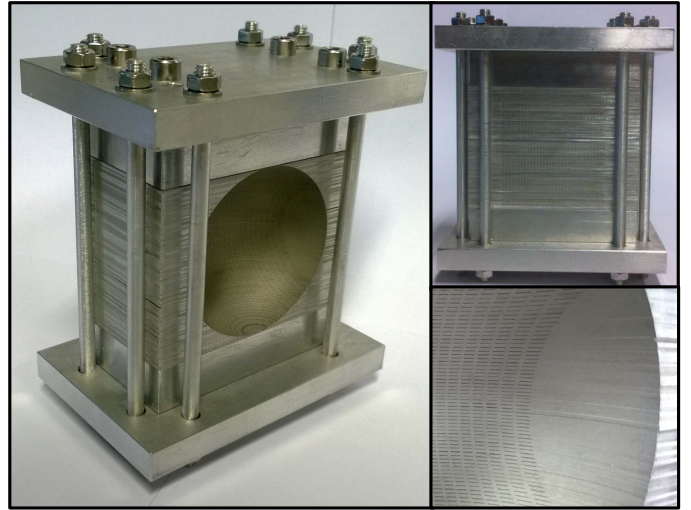


Fig. 1. Photographs of the plano-concave ENZ metallic lens: perspective view (left), back (top right) and detail of the front profiled profile (bottom right).

The experimental focal length estimated with both setups is  $\sim 40 \text{ mm}$ , which is in agreement with the simulation ( $\sim 39 \text{ mm}$ ). The full width at half-maximum (FWHM) along  $x$  is  $\sim 4.6 \text{ mm}$  and  $\sim 2.4 \text{ mm}$  for the ABmm and Agilent setup, respectively. The FWHM along  $y$  is  $\sim 3.5 \text{ mm}$  and  $3 \text{ mm}$ , respectively. Both results are shown in Fig. 2(a). The discrepancy between setups stems from the different invasiveness and collection of each detector.

In our next experiment, we characterize the radiation properties of the lens antenna configuration. A detailed description of the setup can be found in Ref. 8. The maximum directivity measured is  $17.6 \text{ dBi}$ , which is  $\sim 8 \text{ dB}$  below the simulations. The overall performance is worse than that predicted by the simulation and it could be arguably assigned

to experimental misalignments and degradation arisen from the waveguide roughness [11] (i.e., large propagation loss could forbid transmission through the longer lateral waveguides, reducing therefore the output radiating area) that was not been considered. The measured co-polar radiation patterns on the E- and H-plane are shown in Fig. 2(b). We also studied the steering of the beam by moving mechanically the feeder (a flange-ended WR-6.5 waveguide) [7]. The gain of 11 dB at 144 GHz drops more than 3 dB for angles larger than 15 deg. Experiments agree well with analytical and numerical calculations.

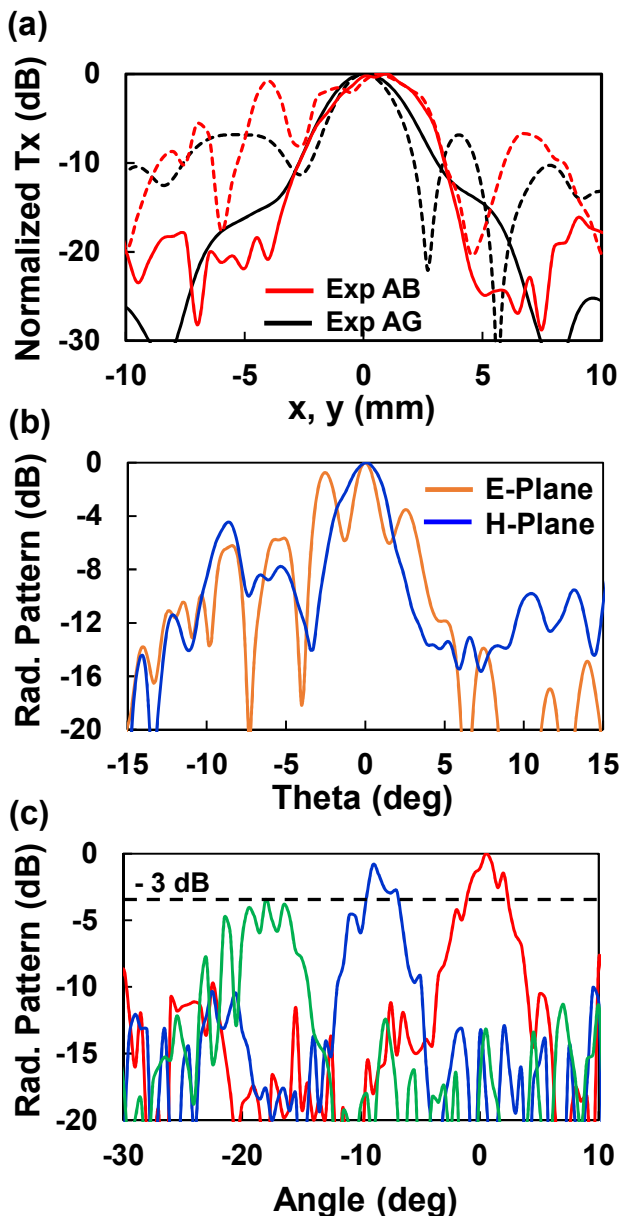


Fig. 2. (a) Normalized transmission along the x-axis (dashed lines) and along the y-axis (continuous lines) at the focal length. Exp AB and Exp AG represent experimental results obtained with the AB Millimetre and Agilent VNA setup, respectively. (b) Measured co-polar radiation pattern on the E-plane and H-plane. (c) Measured normalized radiation pattern for the output angles: 0 deg (red line), 9 deg (blue line) and 18 deg (green line).

### III. CONCLUSIONS

The performance of a metallic ENZ lens with a plano-concave profile working at 144 GHz has been demonstrated experimentally and compared with 3D full-wave numerical simulations. Experimental measurements with two different setups show a clear focus in both E- and H-planes with a minimum FWHM of  $1.46\lambda_0$  and  $1.13\lambda_0$ , respectively. Moreover, a directivity of 17.6 dBi is also measured with very low values of cross-polar components on the E- and H-plane. The mechanical beam steering performance has also been demonstrated with a gain scan loss below 3 dB for angles up to  $\pm 15$  deg. This work shows the possibilities of waveguide-based ENZ metamaterial lenses for applications in antenna systems that require steerable performance of the output beam with high gain and low losses.

### ACKNOWLEDGMENTS

This work was supported in part by the Spanish Government under contract Consolider Engineering Metamaterials CDS2008-00066 and contract TEC2011-28664-C02-01. V. T. is sponsored by the Universidad Pública de Navarra. V.P.-P. is sponsored by Spanish Ministerio de Educación, Cultura y Deporte under grant FPU AP-2012-3796. B. O. is sponsored by Spanish Ministerio de Economía y Competitividad under grant FPI BES-2012-054909. M. B. is sponsored by the Spanish Government via RYC-2011-08221. M. N.-C. is supported by the Imperial College Junior Research Fellowship.

### REFERENCES

- [1] B. Orazbayev, V. Pacheco-Peña, M. Beruete, M. Navarro-Cía, "Exploiting the dispersion of the double-negative index fishnet metamaterial to create a broadband low-profile metallic lens," *Opt. Express*, vol. 23, no. 7, pp. 8555-8564, 2015.
- [2] N. Engheta and Z. Ziolkowski, *Metamaterials: Physics and Engineering Exploration*. Hoboken, NJ, USA: Wiley, 2006.
- [3] R. Marqués, F. Martín, M. Sorolla, *Metamaterials with negative parameters: theory, design and microwave applications*. Hoboken, NJ, USA: Wiley, 2011.
- [4] M. Navarro-Cía, M. Beruete, M. Sorolla, and N. Engheta, "Lensing system and Fourier transformation using epsilon-near-zero metamaterials," *Phys. Rev. B*, vol. 86, no. 16, p. 165130, 2012.
- [5] V. Torres, V. Pacheco-Peña, P. Rodríguez-Ulibarri, M. Navarro-Cía, M. Beruete, M. Sorolla, and N. Engheta, "Terahertz epsilon-near-zero graded-index lens," *Opt. Express*, vol. 21, no. 7, pp. 9156-66, 2013.
- [6] V. Pacheco-Peña, V. Torres, M. Beruete, M. Navarro-Cía, and N. Engheta, "ε-near-zero (ENZ) graded index quasi-optical devices: steering and splitting millimeter waves," *J. Opt.*, vol. 16, no. 9, p. 094009, 2014.
- [7] V. Pacheco-Peña, V. Torres, B. Orazbayev, M. Beruete, M. Navarro-Cía, M. Sorolla, and N. Engheta, "Mechanical 144 GHz beam steering with all-metallic epsilon-near-zero lens antenna," *Appl. Phys. Lett.*, vol. 105, no. 24, pp. 243503-1-5, 2014.
- [8] V. Torres *et al.*, "Experimental demonstration of a millimetre-wave metallic lens based on the energy squeezing principle," *IEEE Trans. Antennas Propag.*, vol. 63, no. 1, pp. 231-239, 2015.
- [9] O. Quevedo-Teruel *et al.*, "Transformation optics for antennas: why limit the bandwidth with metamaterials?," *Sci. Rep.*, vol. 3, no. 1923, pp. 1-5, 2013.
- [10] W.E. Kock, "Metal-lens antenna," *Proc. IRE*, vol. 34, no. 11, pp. 828-836, 1946.
- [11] M. Navarro-Cía, M.S. Vitiello, C.M. Bledt, J.E. Melzer, J.A. Harrington, and O. Mitrofanov, "Terahertz wave transmission in flexible polystyrene-lined hollow metallic waveguides for the 2.5-5 THz band," *Opt. Express*, vol. 21, no. 20, pp. 23748-23755, 2013.