

Polyion complex (PIC) particles

Insua, Ignacio; Wilkinson, Andrew; Fernandez-Trillo, Francisco

DOI:

[10.1016/j.eurpolymj.2016.06.003](https://doi.org/10.1016/j.eurpolymj.2016.06.003)

License:

Creative Commons: Attribution (CC BY)

Document Version

Publisher's PDF, also known as Version of record

Citation for published version (Harvard):

Insua, I, Wilkinson, A & Fernandez-Trillo, F 2016, 'Polyion complex (PIC) particles: Preparation and biomedical applications', *European Polymer Journal*, vol. 81, pp. 198-215. <https://doi.org/10.1016/j.eurpolymj.2016.06.003>

[Link to publication on Research at Birmingham portal](#)

General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact UBIRA@lists.bham.ac.uk providing details and we will remove access to the work immediately and investigate.



Polyion complex (PIC) particles: Preparation and biomedical applications

Ignacio Insua, Andrew Wilkinson, Francisco Fernandez-Trillo*

School of Chemistry, University of Birmingham, B15 2TT, UK

ARTICLE INFO

Article history:

Received 1 April 2016
 Received in revised form 1 June 2016
 Accepted 3 June 2016
 Available online 6 June 2016

ABSTRACT

Oppositely charged polyions can self-assemble in solution to form colloidal polyion complex (PIC) particles. Such nanomaterials can be loaded with charged therapeutics such as DNA, drugs or probes for application as novel nanomedicines and chemical sensors to detect disease markers. A comprehensive discussion of the factors affecting PIC particle self-assembly and their response to physical and chemical stimuli in solution is described herein. Finally, a collection of key examples of polyionic nanoparticles for biomedical applications is discussed to illustrate their behaviour and demonstrate the potential of PIC nanoparticles in medicine.

© 2016 The Authors. Published by Elsevier Ltd. This is an open access article under the CC BY license (<http://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Macromolecules carrying multiple charges (*a.k.a.* polyelectrolytes) are ubiquitous in nature and include nucleic acids, proteins or polysaccharides. The presence of these charges often dictates the physical properties of these biopolymers, including their self-assembly or their solubility in physiological environments. More importantly, charge-charge interactions often mediate relevant biological processes, from the package of DNA around histones [1], to the initial adhesion of microbes to surfaces and hosts [2]. It is not surprising then that researchers have tried to imitate these important polyionic interactions to develop synthetic systems that can interact with biology. As such, polyionic complexes (PIC), *a.k.a.* polyelectrolyte complexes (PECs) [3] or interpolyelectrolyte complexes (IPECs) [4], have been investigated as novel platforms to stabilise and deliver drugs [5,6], proteins [7,8] or nucleic acids [9–11].

The morphology of the complexes formed depends on the topology of the polyelectrolytes employed and the way these are assembled. For instance, ionic-hydrophilic block copolymers have been used for the preparation of PIC micelles [12,13] and PIC vesicles (PICsomes) [14], while the sequential assembly of polyelectrolytes on surfaces and colloidal templates has been exploited for the preparation of layer-by-layer films [15] and capsules [16] respectively.

In this review we will focus on the preparation and biomedical applications of PIC particles, formed by the neutralisation of non-stoichiometric mixtures of polyelectrolytes. Other morphologies and their biomedical applications have been extensively reviewed elsewhere and interested readers are encouraged to read that literature [12–17].

2. Self-assembly of PIC nanoparticles

The preparation of PIC particles was first reported by Fuoss and Sadek in the late 1940's as a straightforward turbidimetric study of polyion condensation [18]. Over the last decades, more sophisticated instrumentation has allowed a deeper

* Corresponding author.

E-mail address: f.fernandez-trillo@bham.ac.uk (F. Fernandez-Trillo).

understanding of PIC particle assembly. It is now well established that non-stoichiometric mixtures of oppositely charged polyions lead to the formation of PIC particles, which consist of a neutral core entrapping 1:1 mixtures of oppositely charged polymers surrounded by a shell of excess polyion chains (Fig. 1) [19,20]. The charged corona stabilises the coacervate by repelling other PIC particles in solution. In contrast, stoichiometric mixtures of polyions lead to unstable shell-deficient PIC particles, which flocculate due to the hydrophobic attraction between neutral coacervates [21,22].

General models rationalise that PIC formation is primarily based on the electrostatic attraction between oppositely charged polyions [3,18,23,24]. However, it has been demonstrated that the increase in entropy upon counterion release from polyelectrolytes is the main driving force in PIC particle self-assembly [25,26].

PIC particles are often polydisperse systems with diameters comprised between 10 nm and 1 μm . Particle size is usually measured from indirect techniques, mainly static and dynamic light scattering, which maintain the integrity of the nanoparticles in solution. Imaging techniques are often used to support the results from light scattering, but it must be noted that in this case the size of PIC particles can be affected during sample preparation and analysis (especially in the case of drying and staining) [27].

The self-assembly of PIC particles is a reversible process where nanoparticles coexist in equilibrium with free polyions in solution (Fig. 1) [26,28]. This dynamic nature of PIC particles inherently compromises their integrity upon dilution and addition of other charged species, which can cause electrostatic shielding and polyion exchange from these nanomaterials [29]. As a result, the stability of PIC particles can be seriously compromised in biological settings, where high concentrations of small electrolytes and charged proteins can be found [30]. However, PIC particles can be easily stabilised by cross-linking of the polyelectrolyte components, minimising this way the exchange with free polymers in solution (see Section 2.7). On the other hand, the structural damage caused by physiological electrolytes to PIC particles can be beneficial, for example by increasing the permeability of these nanomaterials thus triggering the release of preloaded cargos [31,32].

Finally, it must be highlighted that only certain polyelectrolytes, mixed under suitable conditions, lead to disperse and stable PIC particles. Several factors need to be optimised during the formulation of these nanomaterials, in particular molecular weight, concentration and charge density of the polyelectrolytes, pH and ionic strength of the (aqueous) media, or relative ratio and mixing order of both polyelectrolytes. These parameters are normally interdependent, and have to be optimised in parallel. Often, stable colloidal PIC particles are therefore prepared at high dilution and low ionic strength, with an excess of one of the polyions, ideally with weak ionic groups in one of the polymers and a considerable mismatch in their molecular weights [28,33]. Under different conditions, coacervates separate from solution and coalesce into dense materials known as *compact polyelectrolyte complexes*, which have also shown great potential in some biomedical applications such as synthetic cartilage and enzymatically active biocomposites [34]. To give the reader a deeper understanding of the variables affecting the complexation of polyelectrolytes, we will now describe how these factors affect PIC particle formation, explaining their fundamentals and influence on the characteristics of PIC particles.

2.1. Charge density, molecular weight and topology

The binding properties of polyions to other charged species show a strong dependency on the density and number of charged groups in the polyelectrolyte's structure. As a result of the cooperative nature of polyelectrolyte binding, polymers with higher charge densities show stronger avidity for charged substrates.

The simplest way to increase charge density is to increase the polyelectrolyte's molecular weight. Given the partially entangled conformation of polymers in solution [35], higher molecular weight leads to larger polyelectrolyte cores. This molecular weight dependency was nicely demonstrated by Fischer et al. with a comparative study on the preparation of DNA polyplexes from poly(diallyldimethylammonium chloride) (PDADMA) of four different molecular weights (5–244 KDa) [36]. Higher charge densities, corresponding to higher PDADMA molecular weights, formed more stable polyplexes as indicated by the higher tolerance of complexed DNA to ultrasonication and enzymatic digestion. The authors explained these results from the possible rearrangement of polyions with low charge densities, weakly bound to the polyplex. It has been rationalised that the stability of PIC particles is influenced by the number of charged groups per

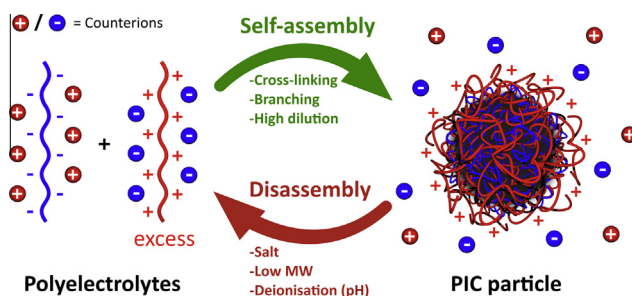


Fig. 1. Representation of polyion self-assembly into PIC nanoparticles and subsequent counterion release (charged spheres). In this example, the excess of polycation in the mixture leads to the formation of a neutral core surrounded by the excess of cationic material.

polymer chain (*i.e.* multivalency), and above an ‘upper critical length’ polyions can form stable complexes [37]. Nonetheless, a significant difference in the molecular weight of the polyions is often required for the colloidal stability of PIC particles [38].

Alternatively, charge density can be “diluted” by the addition of neutral monomers to the polyelectrolyte. Dautzenberg et al. evaluated the formation and stability of PIC particles from poly(styrene sulfonate) (PSS) and four PDADMA copolymers of comparable molecular weight, which contained increasing amounts (0, 25, 47 and 76%) of neutral *N*-methyl-*N*-vinylacetamide (p(DADMA)-co-(NMVA)) [21]. As the NMVA content in the copolymers increased (lower charge density), bigger particles formed with up to twice the size of those from 100% PDADMA. In addition, the destabilising effect of NaCl on PIC particles was significantly reduced with higher PDADMA contents. Nanoparticles prepared from pure PDADMA remained unaffected by concentrations of NaCl twice higher than those causing particles with weaker charge densities to swell. These results reinforce the direct correlation between charge density and the binding avidity of polyelectrolytes.

The topology of polyelectrolytes can also have a profound effect on their charge density. It is known that branched and dendritic polyelectrolytes show increased binding affinities to charged surfaces compared to their linear analogues [24]. This effect is due to the higher spatial density of monomers in branched structures and thus results in an increase in avidity. As such, branched polyelectrolytes can electrostatically cross-link multiple counter-polyion chains, creating tighter polymeric networks [39]. Dunlap et al. showed that, under the same conditions, whereas linear poly(ethylene imine) (PEI) formed polyplexes of 20–50 nm and left uncomplexed DNA fragments, branched PEI of similar molecular weight fully condensed DNA and formed significantly larger complexes (100–200 nm), probably due to interparticular condensation as a result of its higher binding capacity than linear PEI [40]. The high charge density of branched PEI is responsible for its remarkable capacity to tightly complex DNA, thus setting a benchmark for other transfection agents [41].

Although challenging due to their low charge density, PIC particles have been successfully prepared from small molecules bearing certain motifs that aid the nucleation process. For example, the Behr group studied the self-assembly of small cationic detergents with DNA into lipidic polyplexes or lipoplexes [42]. The authors prepared a dimerisable detergent ($C_{14}CO$) that could condense DNA despite its low charge density, aided by the hydrophobic interactions between aliphatic chains (Fig. 2). After the initial aggregation of $C_{14}CO$ with plasmid DNA, the oxidative dimerisation of this detergent into $(C_{14}CO)_2$ caused a drop in its critical micellar concentration, thus increasing the packing and stability of the complex.

2.2. Polyelectrolyte concentration

Recent work by Starchenco and co-workers rationalised the mechanism of PIC particle self-assembly as the sequential nucleation of polyions as primary molecular complexes, which then aggregate into colloidal complexes (Fig. 3A) [44]. The authors explained this behaviour by the increase in the Debye length of the nanoparticles as they become bigger, thus creating more intense repulsive electrostatics between the “secondary” complexes. In this article, the size of PIC particles from PSS/PDADMA was studied as a function of polyelectrolyte concentration. As shown in Fig. 3B, a linear correlation was found between polymer concentration and complex size, regardless of the molecular weight of PSS used (4.6–1132 KDa). It was observed that, at the lowest concentration of polyions tested (50 μ M), particles with a radius of 23 and 50 nm were found when using the lowest and highest PSS molecular weight, respectively. As observed here, the size of PIC particles can be finely tuned by a combination of polyion length and concentration.

Often during the assembly of PIC particles, high concentrations of the starting polyelectrolytes lead to the formation of micron-sized complexes with poor colloidal stability [28,33]. As a consequence, it can be generalised that dispersed PIC nanoparticles can only form in polyelectrolyte mixtures below a critical concentration, above which the system flocculates or precipitates (*ca.* <1 mg/mL) [3]. The concentration restraints during PIC particle preparation can be a limitation when it is required to prepare concentrated dispersions of these complexes. Nevertheless, Müller et al. showed that it was possible to

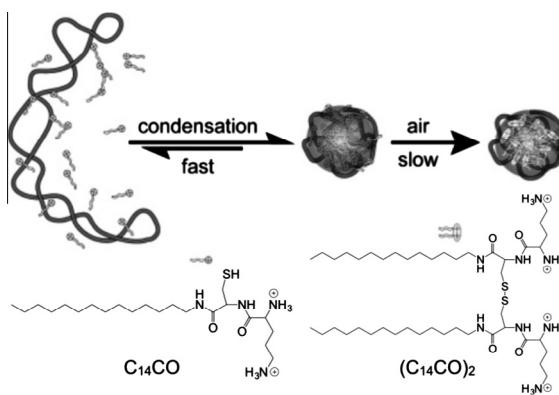


Fig. 2. Plasmid DNA is condensed into monomolecular particles with a thiol-containing cationic detergent. The particles are stabilised by spontaneous oxidation of the detergent. Adapted from Ref. [43].

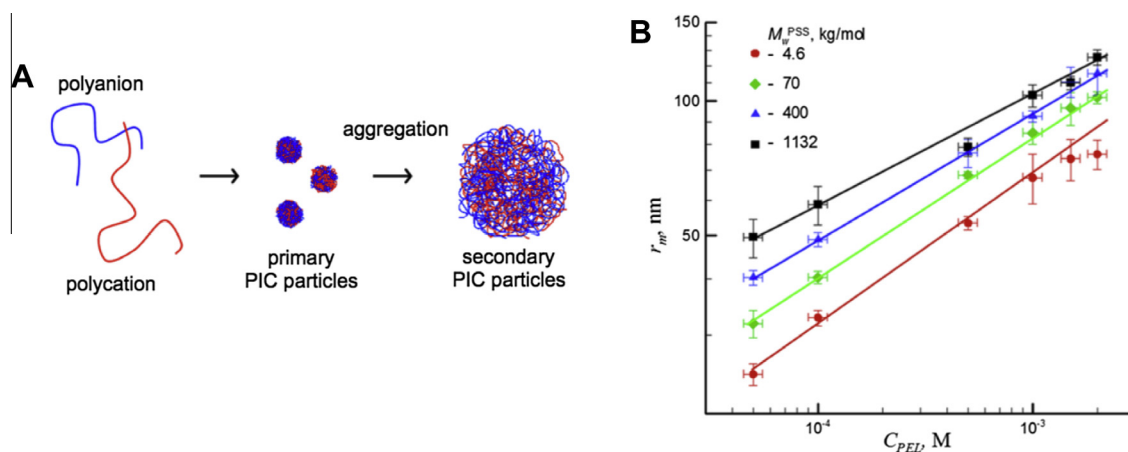


Fig. 3. (A) Schematic presentation of the processes occurring during mixing of polyelectrolytes and formation of PIC particles. (B) PIC particle size (r_m) dependence on polyelectrolyte concentration (C_{PEL}) using different PSS molecular weight with PDADMA. $n-/n+ = 1.5$. Adapted with permission from Ref. [44].

centrifuge and redisperse PIC particles from PDADMA and poly(maleic acid-*alt*- α -methylstyrene), and that consecutive centrifugation cycles allowed to refine the polydispersity of the complexes, ultimately achieving monomodal size distributions without affecting their initial size during the process [45]. Ouyang et al. found the same effect on PSS/PDADMA complexes of 318 nm in diameter and polydispersity index (PDI) = 0.38 [46]. After one centrifugation, the size of these complexes dropped to 250 nm, showing a much narrower size distribution (PDI = 0.06). After a second centrifugation, particle size was maintained (251 nm) and the PDI could be narrowed further down to 0.04. As such, it is possible to obtain concentrated PIC particles dispersions by centrifugation, although the final morphology of the complexes may be affected.

2.3. pH

From a biomedical perspective, polyelectrolytes can be classified as either weak or strong whether they undergo partial or full ionisation at physiological pH, respectively [35]. As a result, as opposed to strong polyelectrolytes, the charge density of weak polyions will strongly depend on the pH found in different tissues and organelles (4.5–7.4) [47]. Variations within this pH range can lead to significant changes in polyelectrolyte binding and PIC particle stability from the loss or gain of valency (*i.e.* charges per molecule). A good example of this pH-responsive behaviour of polyion complexes was reported by Han et al., where the authors studied a system comprised of a strong poly(allylamine) (PAH) and weak poly(acrylic acid) (PAA) polyelectrolytes at different pHs (Fig. 4) [48]. At low pH (2.0–2.5), PAA is only deprotonated to a small extent so that more swollen and loose complexes are formed as a consequence of its low charge density. However, at higher pH (3.5–5.5) the PAA chains are more ionised, and thus more packed complexes form with PAH from an increase in the number of electrostatic cross-links.

Weak polyions can therefore change their (de)protonation degree and charge density with changes in biological pH. In addition, the different chemical environments and sterics result in a range of different pK_a values for the same monomer in different positions of the polyelectrolyte. This is specially the case for branched polymers and translates into broad

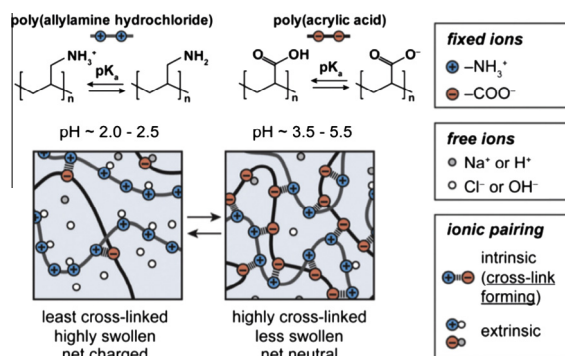


Fig. 4. Illustration of the pH-dependent binding between poly(allylamine hydrochloride) and poly(acrylic acid). Adapted from Ref. [48].

buffering capacity. As such, the changes in pH found in different physiological settings have been exploited to trigger the release of drugs and DNA from PIC particles by changes in the ionisation of the complexing polyions. A classic example of this behaviour is the so-called ‘proton sponge’ effect displayed by PEI, which allows polyplexes to escape the acidic endosome after cellular uptake (Section 3). For example, branched PEI (B-PEI) displays a wide buffering window from approximately pH 2–10 regardless of its molecular weight (Fig. 5) [49,50], and can therefore buffer the influx of protons into the endosome, ultimately causing an increase in osmotic pressure that causes the organelle to burst and release the polyplex into the cytosol.

Other relevant examples of pH-responsive PIC particles include enzyme [51] and antimicrobial [52] delivery, which are based on nanoparticle disassembly or swelling upon polyion (de)protonation, respectively. As shown by Sui et al., reversible pH-responsive PIC particles can be prepared by blending a weak polyacid (PAA) with a strong polybase (PDADMA) into PDADMA-co-PAA [53]. Mixing this copolymer with PSS at pH 4.1 led to the formation of PIC particles, which dissolved at pH > 5.7 due to the deprotonation of PAA in the copolymer and subsequent repulsion between PSS and this partially anionic copolymer. When the solution was acidified again, PIC particles reformed at pH 4.5–5.5, thus demonstrating the reversibility of the process.

Similarly, the pH chosen to self-assemble two polyions can affect their charge densities and therefore the final characteristics of the resulting nanoparticles. Feng et al. studied the effect of pH during PIC particle preparation from carboxymethyl cellulose (CMetC) and poly(vinylamine) (PVAm) in different proportions (*i.e.* mixing ratios) [22]. The authors observed a mixing ratio-dependent effect that originated more positive or negative PIC particles from more acidic or basic pH, respectively (Fig. 6A). This result is consistent with the higher (de)protonation of polyions at higher pH values. However, lower CMetC (weaker polyion) contents led to less pronounced changes in PIC particle charge, as expected from the higher pH-sensitivity of CMetC over PVAm. Size-wise, although an increase in one unit of pH led to a 4-fold increase in size at a 10/20 ratio (CMetC/PVAm), PIC particle size was not very sensitive to changes in pH above their isoelectric points (Fig. 6B).

2.4. Ionic strength

The addition of small electrolytes can aid the self-assembly of PIC particles by shielding the intramolecular charge repulsions of polyions, thus increasing the flexibility of the polymers and their ability to self-assemble [54]. On the other hand, high salt concentrations can lead to strong electrostatic screening between polyelectrolytes and quench the nucleation of PIC particles [3]. Therefore, the ionic strength of the medium must be carefully selected to successfully assemble PIC particles.

To this end, Dautzenberg et al. studied the effect of NaCl during the assembly of PIC particles from PSS and p(DADMA)-co-(NMVA) copolymers (Fig. 7A–C) [21]. In general, the sizes of PIC particles decreased when the polyions were mixed in the presence of higher concentrations of NaCl, probably due to a better packing of more flexible polyelectrolytes. The difference

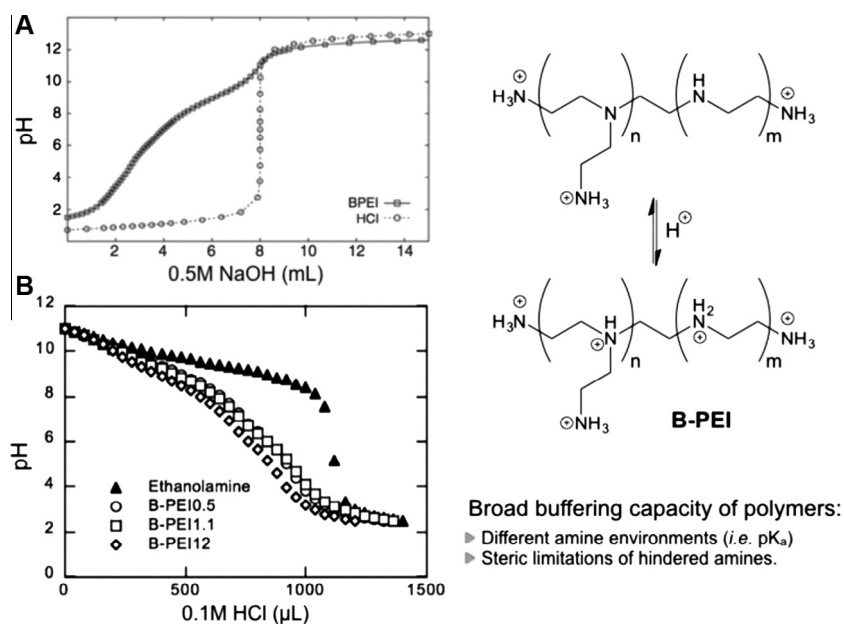


Fig. 5. Buffering capacity of branched poly(ethylene imine) (B-PEI). (A) Titration of 25 KDa B-PEI acidified with HCl (also titrated in the same concentration as control). (B) Potentiometric titration of 0.5, 1.1 and 12 KDa B-PEIs, compared to that of ethanolamine as control for a small monofunctional amine. Adapted from Refs. [49,50].

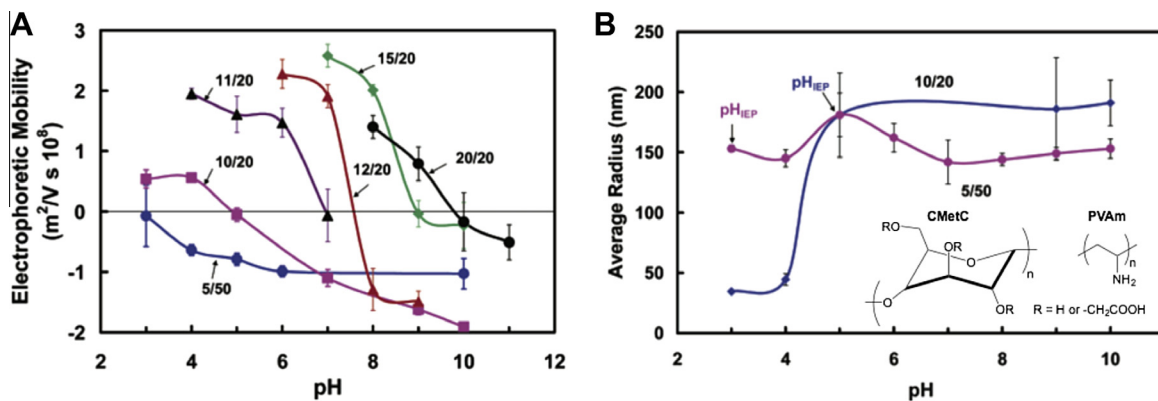


Fig. 6. Effect of pH during preparation of PIC particles from carboxymethyl cellulose (CMeTc) and poly(vinylamine) (PVAm) at different mixing ratios (labels: CMeTc/PVAm) on their charge (A) and size (B). Adapted from Ref. [22].

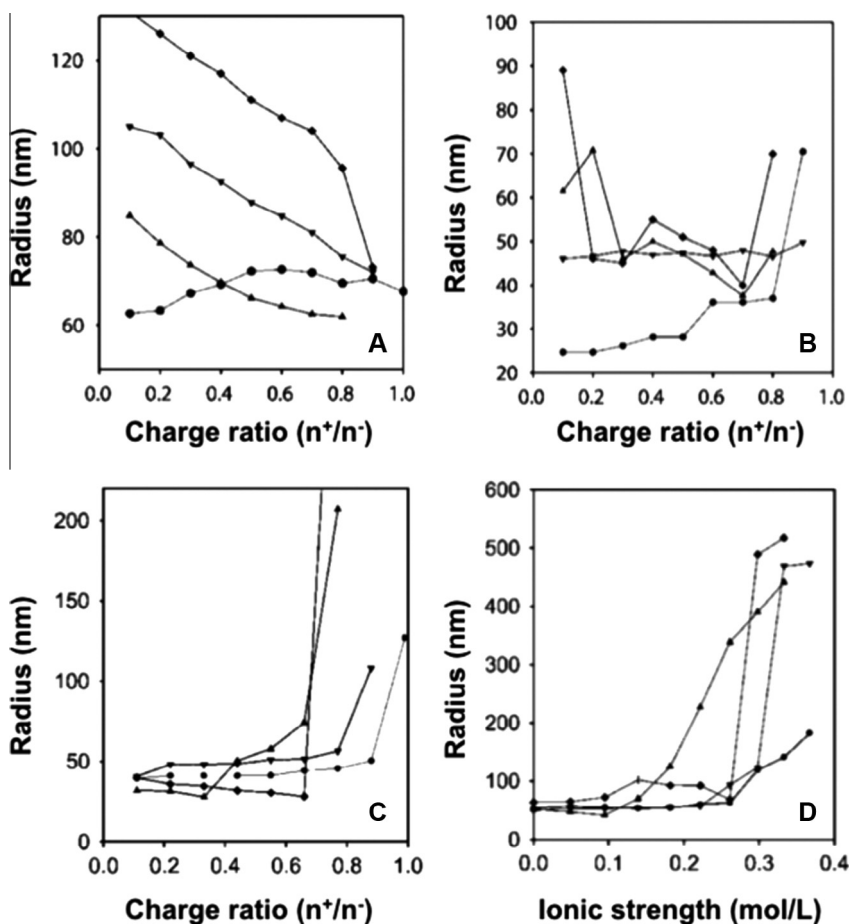


Fig. 7. Size of PIC particles prepared from PSS and p(DADMA)-co-(NMVA) with 100% (●), 75% (▼), 53% (▲) and 24% (◆) of PDADMA (*i.e.* cationic) content in pure water (A), 10 mM (B) and 100 mM (C) NaCl. (D) Swelling of PIC particles prepared in water at increasing NaCl concentrations. Adapted from Ref. [21].

in sizes found between copolymers in water decreased in 10 mM NaCl, ultimately forming particles of the same size at 100 mM NaCl. Overall, polyions with stronger charge densities (*i.e.* lower NMVA content) were more tolerant to NaCl during PIC particle preparation. The authors also observed that particles prepared in pure water swelled from 100 nm up to 1 μ m in diameter when exposed to NaCl once assembled (Fig. 7D) [21]. This post-assembly effect of NaCl is due to its infiltration within the core of the complexes, thus neutralising the electrostatic cross-links between polyelectrolytes and subsequently

causing pre-formed complexes to swell. In later work, the same group studied the kinetics and mechanism of salt-induced PIC particle swelling by static light scattering [19]. The authors observed that the increase in size occurs quickly after the addition of NaCl (ca. < 10 min) as a combination of swelling and subsequent aggregation of swollen complexes. Once again, copolymers with higher charge density (*i.e.* PDADMA content) showed improved tolerance to the swelling effect caused by NaCl due to their higher avidity, requiring in some cases twice the concentration of NaCl to swell compared to less charged copolymers (Fig. 7D).

Wang et al. studied the effect of increasing concentrations of KBr on complexes made from PDADMA and PSS [55]. The authors found dense PIC particles in the absence of KBr, which started swelling with increasing amounts of KBr (doping) due to electrostatic shielding. Higher KBr concentrations (ca. 1.5 M) led to disperse colloidal PIC particles, which dissolved above 1.8 M KBr. It is noteworthy that the dilution of concentrated KBr samples with water re-assembled PIC particles, evidencing the reversible nature of salt doping effects. Also the high molecular weights of the polymers used in this study (200 KDa PSS and 400 KDa PDADMA) required higher concentrations of KBr to shield such multivalent interactions and trigger these phase transitions. It is expected that PIC particles made from shorter polyelectrolytes with weaker avidities would require lower doping levels to undergo similar structural changes: *e.g.* particles in Fig. 7D from 66 KDa PSS and 100 KDa PDADMA required only about 0.35 M NaCl to swell twice in size.

Physiological electrolytes may also cause swelling and compromise the functionality and stability of PIC particles in biological settings. If salt-tolerant particles are required, the assembled chains of polyelectrolytes can be covalently cross-linked to maintain the complex together even after the weaker electrostatic forces have been screened with salt [56,57]. Nevertheless, the swelling of PIC particles with small electrolytes has been exploited to release entrapped drugs from within the complex as a result of its increased permeability [31,32].

2.5. Mixing ratio

This is the proportion of positive and negative charges in the polyelectrolytes that are mixed. Mixing ratio not only affects the final size and charge of PIC particles, but also their biological activity. It must be pointed out that, as seen in the previous section, the degree of ionisation of polyelectrolytes is pH-dependent, and therefore the 'effective' mixing ratio will vary for the same mixture of polyions at different pH values [6]. Mixing ratios are denoted regardless of the pH by the fraction or percentage of acidic and basic monomers in solution (*e.g.* 'N:P' ratios are normally used in polyplex formulations to indicate the 'N' number of amine monomers complexed with 'P' phosphate groups in the nucleic acid).

Non-stoichiometric mixing ratios are necessary to give colloidal PIC particles a stabilising shell of the polyion in excess (Fig. 1). On this basis, and as long as other variables such as pH, ionic strength and the polyions structure are kept constant, the absolute value and variations in ζ potential of PIC particles can be predicted from changes in their mixing ratio.

Given the strong dependency of numerous PIC particle systems on mixing ratio, it is always necessary to assess a range of ratios in order to draw consistent and representative conclusions of PIC particle behaviour. The range of mixing ratios usually evaluated varies from very positive-rich mixtures in polyplexes (up to 50 in N:P) [58] whereas other systems just explore values closer to equimolarity (*e.g.* 0.2–1.8 [59] or 0.5–2.0 [4] in n^-/n^+).

A thorough mixing ratio study was conducted by Drogoz et al., who studied the formation of PIC particles from mixtures of chitosan and dextran sulphate two orders magnitude above and below equimolarity [54]. Firstly, the authors observed that the absolute charge of the complex was that of the polyion in excess. Secondly, the size of the nanoparticles was distributed in three ranges of $[\text{NH}_3^+]/[\text{SO}_4^-]$ ratios: above 10 (420 nm), between 10 and 1 (250 nm) and below 1 (200 nm) (Fig. 8). The authors explained these three particle sizes from the different nucleation mechanisms taking place in excess of either polymer. At mixing ratios close to neutrality, unstable complexes formed and flocculated. The authors also found that at high excess of either polyion (5-fold and above), more than 70% of this polymer stays uncomplexed free in solution. Comparing this to other examples in the literature, whereas mixing ratio has the same effect on the ζ potential for other PIC

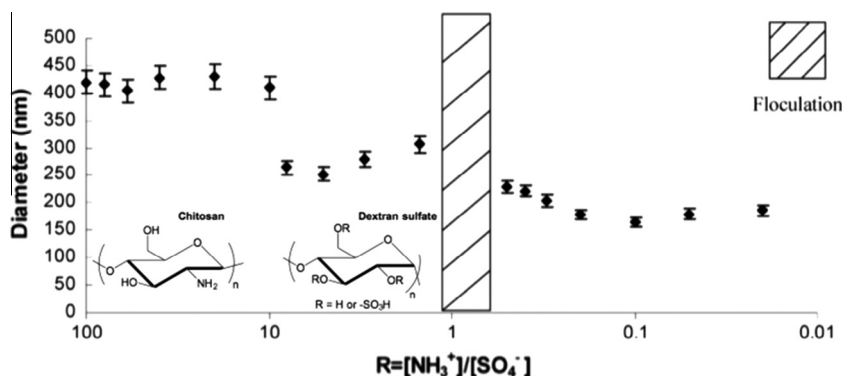


Fig. 8. Average hydrodynamic diameter of PIC particles from chitosan and dextran sulphate at different $[\text{NH}_3^+]/[\text{SO}_4^-]$ ratios. Adapted from Ref. [54].

particles, its influence in size is not consistent and seems to be influenced by other variables (e.g. molecular weight and strength of the polyions) [56,60,61].

2.6. Mixing order

The order in which polyelectrolytes are mixed together will dictate what polyion is in excess at the beginning of the assembling process. It is very important to notice that for the preparation of non-stoichiometric PIC particles, for example at $[n^+/n^-] = 2$, if the polyanion is added to the polycation there is always an excess of positive charge in the complexes, and repulsive forces between them help maintain colloidal stability. However, if the same polymer mixture is prepared by addition of polycation (in excess) to polyanion, the negative charge of the initial coacervates will reach a neutral value half way through the addition of polycation. As a result, neutral particles can flocculate if polyelectrolytes are mixed in the wrong order. Therefore, it is suggested that the polyion in deficit is added to the one in excess, which results in different nucleation dynamics depending on the nature of the polyelectrolytes [54].

The effects of the order of addition become evident when titrating mixing ratios of polyelectrolytes. For example, Dautzenberg et al. observed that the mixing order of polyelectrolytes not only affected the size of the resulting nanoparticles, causing up to a 2-fold change in size, but also the stability of these complexes to NaCl, probably due to a different packing of the polymers [21]. Other studies in the literature have shown rather dissimilar results, finding either a strong dependency or almost negligible effect on the final morphology of the complexes [3,62]. Discrepancies between studies should be attributed to the effects of other variables (e.g. molecular weight and polyion strength), and therefore each case should be evaluated individually.

2.7. PIC particle cross-linking

PIC nanoparticles, in particular those prepared from low molecular weight polymers, partially ionised polyions or when exposed to high salt concentrations, are in equilibrium with free polyions in solution [28]. This equilibrium can be displaced towards the release of polyions from the nanoparticles in circumstances that weaken their electrostatic binding (Fig. 1). As a result, PIC particles can disassemble when diluted or exposed to other charged species [29].

Alternatively, the stability of PIC particles can be greatly enhanced by covalently cross-linking the complexed polyions, thus preventing the detachment of polymer chains from the nanoparticle. In essence, cross-linking works by 'polymerising' polyelectrolyte chains, thus dramatically increasing the overall molecular weight of the polymer and consequently its binding affinity (see Section 2.1.). To this end, polyelectrolytes can be cross-linked during or after particle self-assembly, depending on whether the polyelectrolytes carry cross-linking groups in their structure or if a third component that cross-links pre-assembled complexes is added to the system, respectively.

An illustrative example of PIC particle post-cross-linking was reported by Hsieh et al., who prepared nanoparticles from poly(acrylic acid) (PAA) and poly(L-lysine) (PLL) cross-linked at their core and/or shell [56]. The amines or carboxylic acids found in the shell of these PIC particles were cross-linked using genipin or cystamine, respectively. PLL chains in the core were cross-linked by silica deposition using orthosilicic acid as precursor. These cross-linked particles tolerated up to a 150-fold dilution.

The post-assembly cross-linking of PIC particles has the advantage of not requiring the functionalisation of the polymers with cross-linking groups, thus being applicable to virtually any polyelectrolyte with the suitable functional group (e.g. amines or carboxylic acids in the case described). Given the wide application of polyamines in gene delivery, other amine cross-linkers have been applied to polyplex preparation, including glutaraldehyde [63], citric acid [64], carboximidates and *N*-hydroxysuccinimide esters [65].

Alternatively, functionalised polyelectrolytes allow to cross-link the PIC particles as they are formed. By far, the most used group to functionalise and cross-link the polyions in PIC particles are thiols, given their mild reaction conditions and reversible cross-link into disulphide bridges. For example, McKenzie et al. described the preparation of disulphide cross-linked polyplexes from plasmid DNA and PLL decorated with cysteine residues [66]. Polyplexes prepared from a difunctional Cys-PLL-Cys (Fig. 9A) did not show an increase in stability compared to a control PLL of the same molecular weight. However, when three cysteines were incorporated to PLL (Cys-PLL-Cys-PLL-Cys), the resulting nanoparticles tolerated 2.5 times the maximum concentration of salts Cys-PLL-Cys polyplexes could stand. The effect of this extra cysteine can be explained from the cross-linking of PLL into branched structures (Fig. 9B), leading to a higher charge density as discussed in Section 2.1. However, a dramatic increase in particle size was observed for Cys-PLL-Cys-PLL-Cys polyplexes (1.4 μm) compared to the analogous Cys-PLL-Cys (52 nm), an effect the authors attributed to inter-particle cross-linking by the former polyion. When exposed to reducing conditions, the disulphide cross-links in these polyplexes broke, leading to a sudden loss in the PLL's apparent molecular weight and thus triggering the disassembly of the nanoparticle and DNA release (Fig. 9A).

As described, cross-linking short polyions through labile cross-linkers allows the preparation of stimuli-responsive PIC particles, which can breakdown in the presence of agents that degrade such labile linkers, thus causing a sudden loss of charge density and binding affinity between polyions. As so, the reducing conditions found in the cytosol have been exploited to trigger intracellular drug and nucleic acid delivery through the reduction of disulphide cross-linked vehicles [67].

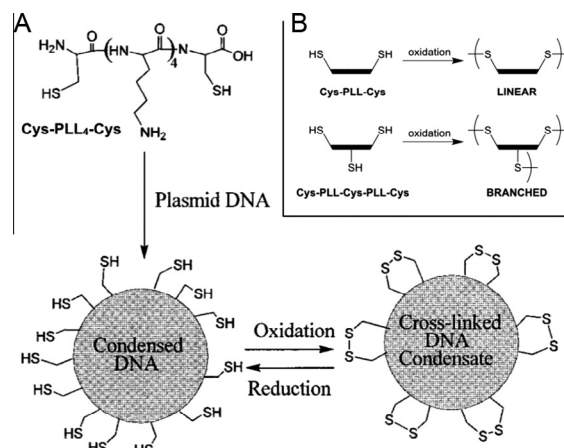


Fig. 9. (A) Formation of cysteine-containing PLL/plasmid DNA nanoparticles. The thiol groups in cysteine (Cys) residues can cross-link PLL molecules through oxidation into disulphide bridges. These cross-links will break under reducing conditions (e.g. human cytosol), destabilising the nanoparticles and thus allowing the release of DNA. (B) Schematic representation of the linear and branched cross-linking of these polyplexes that forms upon oxidation of PLL containing two and three Cys residues, respectively. Adapted from Ref. [66].

Our group combined two different labile linkers to develop dual-stimuli-responsive PIC particles, which disassembled in the presence of enzymes and reducing agents [68]. In this system, PEI was complexed with a short anionic peptide bearing two cysteine residues to allow their oxidative cross-linking (**P1_{SH}**, Fig. 10), endowing PIC particles with redox-responsive properties like those in the previous example. In addition, the amino acid sequence in those peptides could be specifically degraded by a bacterial elastase (LasB), thus providing another point to cleave the cross-linked peptide chains and ultimately the PIC particles themselves.

As just illustrated, the integrity of the cross-links in such particles is of paramount importance to ensure particle stability, but at the same time, labile cross-links can be designed as sacrificial groups that trigger particle disassembly and release of their cargo when cleaved.

3. Application of PIC particles in gene therapy

Possibly the widest application of PIC particles in biomedicine has been the non-viral delivery of nucleic acids [69–71]. Nucleic acids are strong polyelectrolytes that present one negative charge per nucleotide at neutral pH. This high negative charge density in nucleic acids poses a big challenge when trying to deliver them across negatively charged cellular and nuclear membranes to enable gene therapy (Fig. 11). Moreover, foreign nucleic acids will be readily degraded in biological environments, thus compromising their half-life *in vitro* and *in vivo*. In natural systems, this is often compensated by pro-

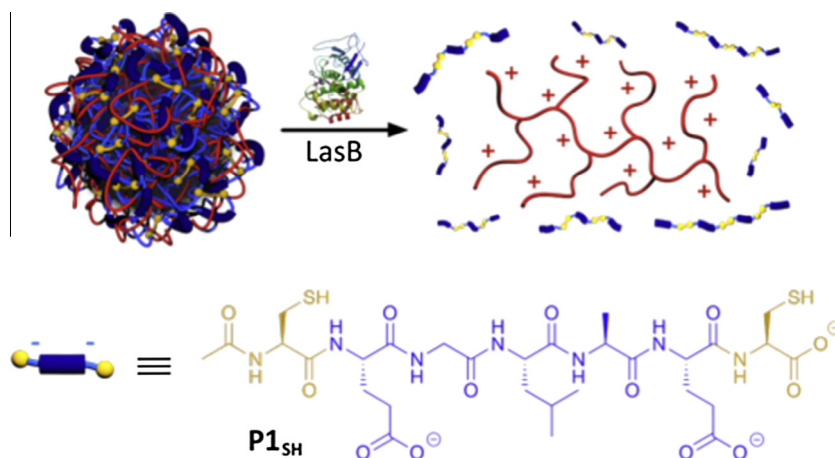


Fig. 10. LasB-triggered disassembly of responsive PIC particles prepared from branched PEI (red polycation) and anionic peptide **P1_{SH}**. The cysteine residues allowed peptide cross-link (in yellow) and the -GLA- amino acid sequence in the peptide (dark blue) hydrolysed by LasB. Adapted from Ref. [68]. (For interpretation of the references to colour in this figure legend, the reader is referred to the web version of this article.)

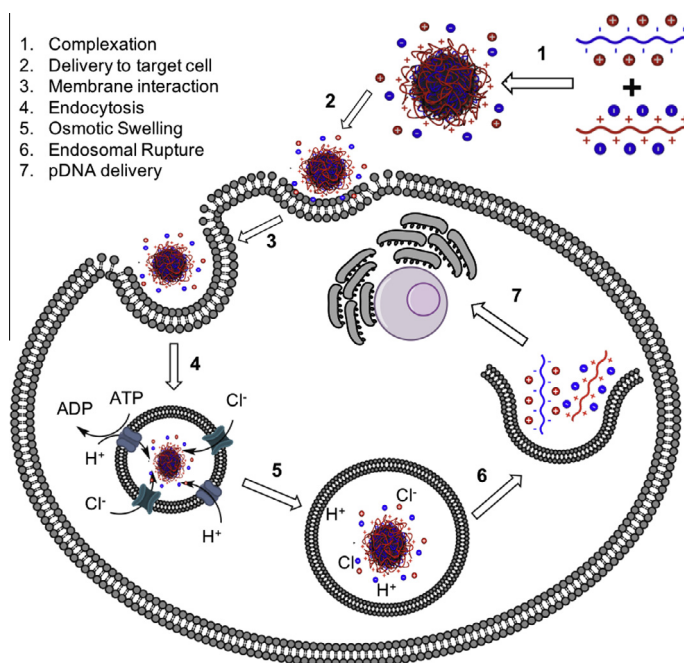


Fig. 11. Schematic representation of the uptake of polyplexes into cells, illustrating the different challenges faced in the development of PIC particles for gene delivery.

protecting the nucleic acids by complexation with positively charged proteins, such as histones [72], or within viral capsids [73]. Not surprisingly, the gene delivery community has placed its attention into mimicking nature's strategy using positively charged polyelectrolytes [69–71].

Often, it has been argued that PIC particles made with nucleic acids and cationic polyelectrolytes, *a.k.a.* polyplexes, can address some of the limitations observed in viral gene delivery (*i.e.* immunogenicity and scalability). However, as will be explained in the following sections, synthetic polyplexes developed so far for non-viral delivery have been found to have separate issues on their own that need to be overcome including stability, toxicity, cellular uptake, endosomal escape and for nucleic acids, delivery to the nuclei.

3.1. Toxicity

Most of the polymers employed in non-viral gene delivery are strong cationic polyelectrolytes, such as PEI, PLL or chitosan. However, it has been long established that most cationic polymers are cytotoxic and cause damage to cells [74,75]. The mechanism for this toxicity though is still widely debated. PEI and other polycations can cause disruption of lipidic bilayers. This is thought to be driven by electrostatic (and possibly hydrophobic) interactions between the negatively charged lipidic membrane and these polyelectrolytes, which often results in depolarisation of the membrane and the formation of pores [76]. This is further evidenced by the release of cytosolic contents such as lactate dehydrogenase [77].

Yet it is also postulated that cationic polyelectrolytes (*i.e.* PEI) can trigger cell apoptosis [78] by release of cytochrome *c* from mitochondria upon intracellular interaction of the polymer with organelles. A similar interaction may be expected here where interaction of PEI with the anionic organelle membrane leads to pore formation and release of the organelle contents [79]. Even if these two mechanisms are working in isolation or cooperatively towards cell death, this toxicity does need to be considered in the future development of PIC particles for gene delivery.

Several strategies have been reported to minimise the toxicity of these polyplexes. For instance, Zhao et al. found that inclusion of chitosan in a PEI/DNA complex significantly reduced the toxicity when compared to the PEI/DNA complex alone [58]. The authors argued that this decrease in cytotoxicity was related to the lower toxicity of chitosan, due to its increased steric hindrance and charge shielding ability.

The simplest way to reduce toxicity of cationic polymers though is reducing the molecular weight of the polyelectrolyte used [74,80]. In depth studies have demonstrated that both PEI and PLL have lower toxicity when the molecular weight is reduced [77,80]. However, as mentioned in the previous section, reducing the molecular weight of the polyelectrolytes has a dramatic effect on the stability of the PIC particles formed. With gene delivery, this is often translated into a lower transfection efficiency [81]. As such, much work has focused in the application of cross-linkers that can reversibly increase the polyelectrolyte molecular weight (Section 2.7) [82].

Disulphide formation has often been the preferred method of cross-linking. Of relevance to the delivery of nucleic acids is the ability of these cross-linkers to be cleaved in the presence of reducing media. This is what happens upon entry into the cell, where the concentration of glutathione is increased up to 100-fold when compared to the extracellular environment [83]. Using this strategy, transfection efficiencies with cross-linked 1.8 kDa PEI are equivalent to that of PIC particles made with 25 kDa PEI [84].

It was thought until recently that dendritic polymers could have reduced toxicity compared to linear analogues [85,86]. However a comprehensive study had not been completed on a comparison of the toxicities of linear vs. dendritic PLL. Klok et al. found that dendritic equivalents of PLL and hyper-branched versions have improved transfection efficiencies compared to their linear analogues (Fig. 12) [87]. However, when carrying out a toxicity study it was found that dendritic and hyper-branched PLL has greater cytotoxicity compared to an equivalently sized linear analogue [88]. The key factors that were highlighted for this increase in cytotoxicity were osmotic shock and cell membrane damage. Osmotic shock causes initial disruption to cells which leads to a marked decrease in EC_{50} values for dendritic and hyper-branched structures. Whilst the membrane disruption characteristics show that the dendritic and hyper-branched structures also cause cell apoptosis due to their interaction with mitochondria which leads to the release of cytochrome c as discussed previously [78]. What is interesting to note for the studies by Kadlecova is that although there is increased cytotoxicity seen for both the dendritic and hyper-branched forms of PLL, the hyper-branched structure is much simpler in its synthesis however, and has almost identical effects in terms of toxicity and transfection.

Finally, it is worth mentioning that conjugation of PEG to one of the polyelectrolytes is another strategy to minimise toxicity of the polyplexes. This strategy results in the formation of PIC micelles [12,13], which are stabilised by a PEGylated corona. It is thought that the reduction in toxicity is achieved thanks to the formation of a hydration shell around the polymer reducing interactions with the membrane during delivery [89,90]. This strategy has been used successfully, for example when coupled to PEI, to reduce the toxicity of the polyplexes used for *in vitro* delivery studies [91,92]. Further examples can be found in specialised reviews [12,13,93].

3.2. Transfection efficiency

The other key factor to consider when developing a non-viral gene delivery vehicle is transfection efficiency. How efficiently a gene is expressed (or knocked-down for small interfering RNA) is normally a consequence of several factors, including circulation half-life, uptake, endosomal escape and transfer to the nuclei in the case of plasmid DNA [94,95]. Representative examples of the effect of these factors over transfection efficiency will be described in the next sections.

3.2.1. Circulation half-life

As mentioned earlier, nucleic acids when introduced in biological environment (*i.e.* the body or serum) have a very poor circulation half-life. This is because nucleic acids are quickly degraded by extracellular nucleases, which are responsible for the elimination of any foreign genetic material [96]. Complexation of these nucleic acids in polyplexes is thus the first step to improve their circulation half-life. Normally, polycations are added in excess and nucleic acids are therefore contained within the neutral core, protected this way by the cationic corona from the action of these nucleases.

However, as described in the first section, the stability of the formed polyplexes would strongly depend on several factors. Assuming that parameters such as concentration, pH and ionic strength can be maintained constant when comparing different polyelectrolytes in the same application, factors such as polyelectrolyte molecular weight and topology dictate the stability of the formed polyplexes. This is often the case when comparing pDNA (normally over one thousand base pairs) to oligonucleotides such as siRNA, which have a significantly smaller size (20–25 base pairs). This was nicely illustrated by

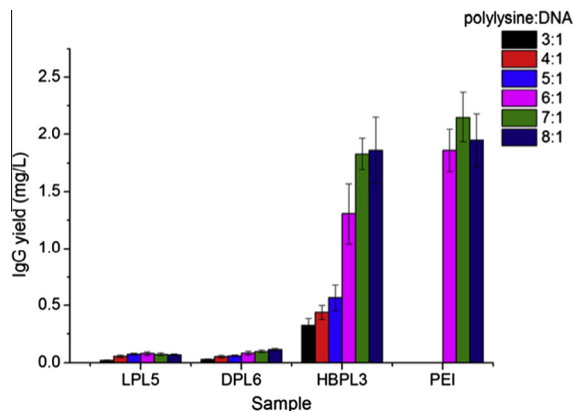


Fig. 12. Comparison of the percentage of eGFP positive cells obtained after 24 h transfection with polylysine analogues of comparable molecular weight. Reproduced from [87].

Seymour et al. with their reducible polycation-based system [97]. While a weight ratio of 5:1 (N:P 1.9:1) was enough to achieve complete retention of pDNA in an agarose gel, weight ratios of up to 20 (N:P 7.5:1) were insufficient to fully conjugate all of the siRNA employed. As expected, polyplex formation in the absence of other salts, resulted in full conjugation of the siRNA with the 20:1 weight ratios, highlighting once again the role of ionic strength in the formation and stability of PIC particles.

Another explanation for the reduced half-life of polyplexes is opsonisation, whereby soluble proteins (opsonins) bind to the surface of complexes leading to their targeted destruction through phagocytosis and subsequent removal from circulation [98]. This process is thought to occur due to the non-specific binding of serum proteins to the positively charged polymer [99].

It is commonly understood that circulation half-life of drugs in the body can be improved through the attachment of hydrophilic residues [100]. Again, in gene delivery this is often achieved through the introduction of PEG residues within the polymeric structure [12,13,89,93]. Kissel et al. evaluated the effect of PEGylation on the pharmacokinetic study carried *in vivo* of PEI polyplexes [101]. Less than 1%/mL of the injected dose (ID) was detected after 2 hours, following injection of polyplexes containing 1.5 μ g of pDNA. However, over 20% was still in blood when these polyplexes were PEGylated (Fig. 13).

3.2.2. Uptake

To be transfected, polyplexes have to be efficiently taken up by the cell. This is normally facilitated by the excess of positive charge in the corona of the polyplex. This has been demonstrated for instance using PEI [102], where transfection efficiency was increased with increasing amount of PEI (*i.e.* N/P ratios) (Fig. 14). However, increasing PEI content in the PIC particle also resulted in an increase in cytotoxicity, and thus transfection efficiency eventually was compromised.

Alternatively targeting ligands, that are recognised by the cell surface thus promoting binding and endocytosis of the polyplexes, can be employed to improve transfection efficiency. For instance, Behr and co-workers demonstrated that the use of glycosylated or RGD PEI derivatives, resulted in higher transfection efficiencies when compared to polyplexes prepared with “pristine” PEI [103]. Typically, transfection efficiencies increased by 1–2 orders of magnitude for the targeted PIC particles. Other targeting ligands such as antibodies, folic acid or prostaglandins have been [104] or could be employed [105] in the development of targeted polyplexes.

3.2.3. Endosomal escape

One of the key barriers that polyplexes need to overcome to mediate efficient transfection is the endosome. Uptake normally results in polyplexes trapped within the endosome, where the cell will try to either digest them or recycle the contents [106]. However, nucleic acids need to be transported into the cytosol, where they can carry out their function (*e.g.* siRNA) or be further trafficked into the nuclei (pDNA).

Part of the reason why PEI has garnered more interest than other polycations is because of its inherent ability to act as a buffer within the endosome (Fig. 5), causing osmotic swelling and potential leakage of the endosome contents (‘The proton sponge effect’) [107]. Behr et al. hypothesised that the reason for endosomal rupture is the protonation of the amine groups in PEI which subsequently leads to an influx of Cl^- counterions and water. It is known that protons can be pumped against the electrochemical gradient that is formed due to the presence of ATPase V type pumps, which helps support this hypothesis [108]. This influx then leads to osmotic swelling, eventually rupturing the endosome.

However, there is still debate as to whether this is the method for endosomal release. Benjaminsen et al. recently found that PEI complexes reach lysosomes to a high extent, but do not cause a change in lysosomal pH [49]. Instead Benjaminsen states that the failure of the ‘proton sponge model’ is that the swelling caused by this process would not cause rupture. This opinion directly contradicts computational calculations that have been made which support the proton sponge effect

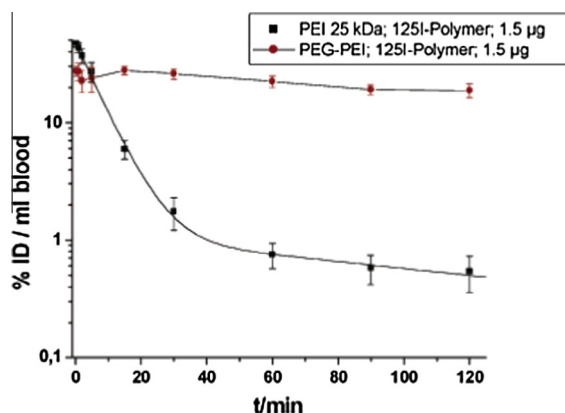


Fig. 13. Pharmacokinetic study showing the effect of PEGylation on circulation half-life as measured by radioactive isotopes ^{125}I . Reproduced from [101].

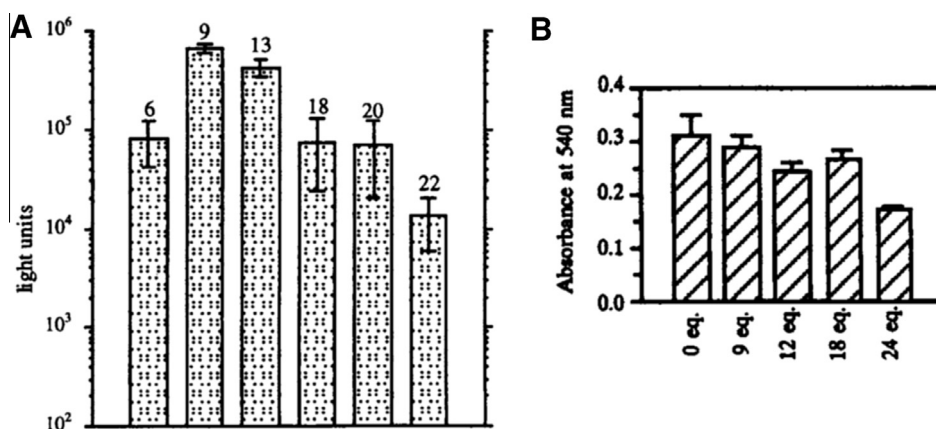


Fig. 14. Transfection efficiency (A) of PEI/pDNA increases with increasing equivalents of PEI, and has its maximum at 9–13.5 equivalents when toxicity towards 3T3 cells (B) starts to be apparent. Reproduced from [102].

[109,110]. Here it has been modelled that osmotic swelling is highly dependent on polymer pK_a as protonation needs to be caused by entry into the endosome.

In line with Benjaminsen's observations, some have argued that the sponge effect should result in an increase in pH [111]. However this doesn't have to be the case because if enough ATP is present in the cytosol, the lysosome could counteract PEI buffering with the influx of more protons. Even if the pH is not changed, osmotic swelling should occur upon the recruitment of protons to neutralise the endosomal pH. An alternative explanation to the proton sponge effect is that complexes are released from lysosomes through small membrane damage, and that the lysosome in fact stays intact [112]. Overall, whatever the actual mechanism of this 'sponge effect' polymers with high buffering capacity, such as PEI have a beneficial effect on endosomal escape.

Other common polycations such as PLL lack this ability to facilitate endosomal escape [113]. One way of addressing this issue is through the introduction of lysosomotropic reagents such as chloroquine to DNA polyplexes [114]. This method has successfully increased the transfection efficiency of PLL based delivery systems [115,116]. However, it has been found that these lysosomotropic reagents are also toxic [117], possibly due to the increased membrane permeabilisation that they cause [118]. As such, this method of delivery is limited in its application.

An alternative strategy to improve endosomal escape is through the introduction of histidine residues to the polymer [119]. It is thought that histidine can successfully increase transfection efficiency acting again as a proton sponge within the polyplex. This is due to the imidazole present in histidine that has a pK_a of ~ 6 meaning that in slightly acidic media of the endosome it will become protonated. Evidence for the success of this process can be seen through its escape from negatively charged liposomes in acidic media [120].

Niidome et al. employed this strategy to prepare novel PLL dendrimers. While no beneficial effect was observed for histidine capped-PLL polyplexes prepared at neutral pH, a significant increase in their transfection efficiency was observed when the histidine containing polyplexes were prepared at pH 5. The authors demonstrated that the latter polyplexes were more stable upon incubation in buffer, demonstrating the role of histidine protonation in polyplex formation.

4. Other biomedical applications of PIC particles

While gene delivery has been possibly the field where PIC particles have made the biggest impact, there are other areas where these particles have had a significant contribution [17]. In this section we will describe representative examples of the application of PIC particles for the encapsulation and delivery of proteins and small molecules. Interested readers are referred to specialised reviews [5–8].

Proteins and polysaccharides are other biomacromolecules that often present multiple charges in their backbone. Chitosan, alginate or hyaluronic acid are charged polysaccharides that have been commonly employed as biocompatible polyelectrolytes in the formulation of PIC particles [121]. They often play a passive/structural role, although their enzymatic degradation has been exploited to trigger the release of encapsulated materials [122]. Proteins however tend to have an active role and researchers have been interested in the application of PIC particles to protect and deliver 'functional' proteins such as enzymes [51]. When compared to polysaccharides and nucleic acids, proteins normally present a lower density of charges. Moreover, the presence of positively and negatively charged residues complicates things further and the overall charge of the protein will depend on their isoelectric point and the pH at which the formulation has to be prepared.

A good example of the challenges in the preparation of PIC particles from functional proteins has been described by Giannotti et al., who prepared PIC particles from *N*-trimethyl chitosan and the anionic lysosomal enzyme α -galactosidase A (α -GalA) [51]. These complexes only formed at pH values between 7.3 and 8.0, whereas no particles formed at pH

4.5–5.5, as expected from the neutralisation of α -GalA at pH values close to its isoelectric point ($pI \sim 5.7$). Similarly, these nanoparticles disassembled at acidic pH, which could be exploited to trigger enzyme release inside the lysosomes, where the authors found these complexes are accumulated *in vitro*. Although a fair 62% of the initial activity of α -GalA was retained after complexation into PIC particles, there is still room for improving this result and develop complexes that do not affect the complexed enzyme and maintain its full activity.

More challenging is the encapsulation of small peptides, which very often have few charge residues and thus weak charge densities, making their complexation into PIC particles particularly unfavourable (see Section 2.1). This is the case for insulin, whose molecular weight is almost 15 times smaller than that of the enzyme α -GalA discussed above. Despite this intrinsic limitation, Jintapattanakit et al. complexed acidic insulin with *N*-trimethyl chitosan into PIC particles, which they evaluated as potential vehicles for the oral delivery of insulin [123]. The oral administration of peptides is limited by their degradation by endogenous proteases. However, the authors found that the stability of free insulin to digestion by trypsin, used as a model gastric protease, was almost doubled when the peptide was complexed inside PIC particles. However, a recent report highlights how despite increasing the stability to proteases, it is the release and subsequent absorption of insulin in the gastrointestinal tract that currently limits the efficacy of PIC particles for this application [124]. Alternative ways of stabilising and administering such complexes must be explored to circumvent this limitation.

The complexation of short charged peptides with very few charges can be facilitated by the addition of cross-linkers, which allow peptide polymerisation and thus increase their binding affinity (Section 2.7). Our group has recently exploited this strategy for the targeted delivery of antimicrobial PEI (Fig. 10) [68]. Incorporation of cysteine residues into a short peptide sequence allowed self-assembly with as little as three negative charges per peptide, otherwise not possible. The peptides were designed to incorporate a short sequence that was cleavable by *Pseudomonas aeruginosa*'s elastase. When these nanoparticles were exposed to the bacterial elastase, the cross-linked peptides were hydrolysed, reducing this way charge density, thus causing particles to disassemble and release the PEI. PIC particles were stable in the absence of this bacterial elastase, and were not able to elicit an antimicrobial effect on a *P. aeruginosa* mutant that was unable to produce this enzyme.

More challenging is the complexation of singly charged molecules such as the chemotherapeutic doxorubicin (DOX) that presents a single amine group in its structure. Hsieh et al. prepared DOX-loaded PIC particle system from PAA/PLL blends, cross-linking the amines in PLL with genipin [56]. In this paper, the authors illustrate how the release kinetics of DOX (or virtually any loaded drug) could be tuned by changing the degree of cross-linking, thus changing the permeability of the nanoparticles. In addition, the weak polyelectrolyte PAA endowed PIC particles with pH-responsive behaviour, accelerating the release of DOX under acidic conditions.

Alternatively, PIC particles can have a “passive” role in the delivery of small molecules, where electrostatic interactions between the polyelectrolytes and the drug to be delivered do not play a role in the encapsulation. For example, non-ionic chemotherapeutic paclitaxel has been encapsulated into the hydrophobic core of PIC particles prepared in this case from hyaluronic acid and styrylpyridinium [125]. The UV cross-linking of styrylpyridinium in the core stabilised the assembled particle, which was then loaded with paclitaxel. High cellular uptake and sustained drug release were achieved from these nanoparticles, proving the utility of PIC particles as vehicles for non-charged drugs as well.

5. Conclusions and outlook

This review gives an overview of the preparation and biomedical applications of PIC particles. A comprehensive description of the factors affecting PIC particle self-assembly has been included: Here, we highlight the effect of polyelectrolyte molecular weight, concentration and charge density, pH and ionic strength of the (aqueous) media, or relative ratio and mixing order of both polyelectrolytes, in particle preparation and stability. Understanding how to optimise PIC particle preparation and stability is of key importance for the development of biomedical application of these nanomaterials. Representative examples of their application in gene, protein and small molecule delivery have been included to illustrate the particular challenges faced in these applications, in particular the issues surrounding toxicity and transfection efficiency in gene delivery. Selected examples of the use of targeted and responsive delivery systems have been included, which highlight how polymer synthesis and characterisation can allow the field of PIC particles, as well as other polyelectrolyte complex nanomaterials, to eventually develop truly mimics of natural delivery systems.

Acknowledgements

F. F-T. thanks the University of Birmingham for the John Evans Fellowship and the Wellcome Trust (177ISSFPP) for funding. II and AW thank the University of Birmingham for PhD studentships.

References

- [1] K. Luger, A.W. Mäder, R.K. Richmond, D.F. Sargent, T.J. Richmond, Crystal structure of the nucleosome core particle at 2.8 Å resolution, *Nature* 389 (1997) 251–260, <http://dx.doi.org/10.1038/38444>.
- [2] A.M. Krachler, K. Orth, Targeting the bacteria-host interface: strategies in anti-adhesion therapy, *Virulence* 4 (2013) 284–294, <http://dx.doi.org/10.4161/viru.24606>.
- [3] H. Dautzenberg, Polyelectrolyte complex formation in highly aggregating systems. 1. Effect of salt: polyelectrolyte complex formation in the presence of NaCl, *Macromolecules* 30 (1997) 7810–7815, <http://dx.doi.org/10.1021/ma970803f>.

- [4] E.S. Dragan, S. Schwarz, Polyelectrolyte complexes. VI. Polycation structure, polyanion molar mass, and polyion concentration effects on complex nanoparticles based on poly(sodium 2-acrylamido-2-methylpropanesulfonate), *J. Polym. Sci., Part A: Polym. Chem.* 42 (2004) 2495–2505, <http://dx.doi.org/10.1002/pola.20110>.
- [5] V. Vergaro, F. Scarlino, C. Bellomo, R. Rinaldi, D. Vergara, M. Maffia, et al, Drug-loaded polyelectrolyte microcapsules for sustained targeting of cancer cells, *Adv. Drug Delivery Rev.* 63 (2011) 847–864, <http://dx.doi.org/10.1016/j.addr.2011.05.007>.
- [6] M. Müller, Sizing, shaping and pharmaceutical applications of polyelectrolyte complex nanoparticles, in: *Polyelectrolyte Complexes in the Dispersed and Solid State II*, Springer Berlin Heidelberg, Berlin, Heidelberg, 2012, pp. 197–260 [10.1007/12_2012_170](http://dx.doi.org/10.1007/12_2012_170).
- [7] C.L. Cooper, P.L. Dubin, A.B. Kayitmazer, S. Turksen, Polyelectrolyte–protein complexes, *Curr. Opin. Colloid Interface Sci.* 10 (2005) 52–78, <http://dx.doi.org/10.1016/j.cocis.2005.05.007>.
- [8] A.B. Kayitmazer, D. Seeman, B.B. Minsky, P.L. Dubin, Y. Xu, Protein–polyelectrolyte interactions, *Soft Matter* 9 (2013) 2553–2583, <http://dx.doi.org/10.1039/C2SM27002A>.
- [9] C.M. Jewell, D.M. Lynn, Multilayered polyelectrolyte assemblies as platforms for the delivery of DNA and other nucleic acid-based therapeutics, *Adv. Drug Delivery Rev.* 60 (2008) 979–999, <http://dx.doi.org/10.1016/j.addr.2008.02.010>.
- [10] M. Soliman, S. Allen, M.C. Davies, C. Alexander, Responsive polyelectrolyte complexes for triggered release of nucleic acid therapeutics, *Chem. Commun.* 46 (2010) 5421–5433, <http://dx.doi.org/10.1039/c0cc00794c>.
- [11] H. Yin, R.L. Kanasty, A.A. Eltoukhy, A.J. Vegas, J.R. Dorkin, D.G. Anderson, Non-viral vectors for gene-based therapy, *Nat. Rev. Genet.* 15 (2014) 541–555, <http://dx.doi.org/10.1038/nrg3763>.
- [12] K. Miyata, R.J. Christie, K. Kataoka, Reactive & functional polymers, *React. Funct. Polym.* 71 (2011) 227–234, <http://dx.doi.org/10.1016/j.reactfunctpolym.2010.10.009>.
- [13] D.V. Pergushov, A.H.E. Müller, F.H. Schacher, Micellar interpolyelectrolyte complexes, *Chem. Soc. Rev.* 41 (2012) 6888–6901, <http://dx.doi.org/10.1039/C2CS35135H>.
- [14] A. Kishimura, Development of polyion complex vesicles (PICsomes) from block copolymers for biomedical applications, *Polym. J.* 45 (2013) 892–897, <http://dx.doi.org/10.1038/pj.2013.33>.
- [15] P.T. Hammond, Building biomedical materials layer-by-layer, *Mater Today* 15 (2012) 196–206, [http://dx.doi.org/10.1016/S1369-7021\(12\)70090-1](http://dx.doi.org/10.1016/S1369-7021(12)70090-1).
- [16] W. Tong, X. Song, C. Gao, Layer-by-layer assembly of microcapsules and their biomedical applications, *Chem. Soc. Rev.* 41 (2012) 6103, <http://dx.doi.org/10.1039/c2cs35088b>.
- [17] H. Yoon, E.J. Dell, J.L. Freyer, L.M. Campos, W.-D. Jang, Polymeric supramolecular assemblies based on multivalent ionic interactions for biomedical applications, *Polymer* 55 (2014) 453–464, <http://dx.doi.org/10.1016/j.polymer.2013.12.038>.
- [18] R.M. Fuoss, H. Sadek, Mutual interaction of polyelectrolytes, *Science* 110 (1949) 552–554, <http://dx.doi.org/10.1126/science.110.2865.552>.
- [19] H. Dautzenberg, G. Rother, Response of polyelectrolyte complexes to subsequent addition of sodium chloride: time-dependent static light scattering studies, *Macromol. Chem. Phys.* 205 (2004) 114–121, <http://dx.doi.org/10.1002/macp.200350083>.
- [20] H.-M. Buchhammer, M. Mende, M. Oelmann, Formation of mono-sized polyelectrolyte complex dispersions: effects of polymer structure, concentration and mixing conditions, *Colloids Surf. A: Physicochem. Eng. Aspects* 218 (2003) 151–159, [http://dx.doi.org/10.1016/S0927-7757\(02\)00582-4](http://dx.doi.org/10.1016/S0927-7757(02)00582-4).
- [21] H. Dautzenberg, W. Jaeger, Effect of charge density on the formation and salt stability of polyelectrolyte complexes, *Macromol. Chem. Phys.* 203 (2002) 2095–2102, [http://dx.doi.org/10.1002/1521-3935\(200210\)203:14<2095::AID-MACP2095>3.0.CO;2-9](http://dx.doi.org/10.1002/1521-3935(200210)203:14<2095::AID-MACP2095>3.0.CO;2-9).
- [22] X. Feng, R. Pelton, M. Leduc, S. Champ, Colloidal complexes from poly(vinyl amine) and carboxymethyl cellulose mixtures, *Langmuir* 23 (2007) 2970–2976, <http://dx.doi.org/10.1021/la0628064>.
- [23] K. Ueno, H. Ueno, T. Sato, Colloidal polyion complexation from sodium poly(acrylate) and poly(vinyl ammonium) chloride in aqueous solution, *Polym. J.* 44 (2011) 59–64, <http://dx.doi.org/10.1038/pj.2011.65>.
- [24] I. Szilagyai, G. Trefalt, A. Tiraferri, P. Maroni, M. Borkovec, Polyelectrolyte adsorption, interparticle forces, and colloidal aggregation, *Soft Matter* 10 (2014) 2479, <http://dx.doi.org/10.1039/c3sm52132j>.
- [25] C.B. Bucur, Z. Sui, J.B. Schlenoff, Ideal mixing in polyelectrolyte complexes and multilayers: entropy driven assembly, *J. Am. Chem. Soc.* 128 (2006) 13690–13691, <http://dx.doi.org/10.1021/ja064532c>.
- [26] J. Fu, J.B. Schlenoff, Driving forces for oppositely charged polyion association in aqueous solutions: enthalpic, entropic, but not electrostatic, *J. Am. Chem. Soc.* 138 (2016) 980–990, <http://dx.doi.org/10.1021/jacs.5b11878>.
- [27] J.P. Patterson, M.P. Robin, C. Chassenieux, O. Colombani, R.K. O'Reilly, The analysis of solution self-assembled polymeric nanomaterials, *Chem. Soc. Rev.* 43 (2014) 2412–2425, <http://dx.doi.org/10.1039/c3cs60454c>.
- [28] A. Zintchenko, G. Rother, H. Dautzenberg, Transition highly aggregated complexes soluble complexes via polyelectrolyte exchange reactions: kinetics, structural changes, and mechanism, *Langmuir* 19 (2003) 2507–2513, <http://dx.doi.org/10.1021/la0265427>.
- [29] Z. Sui, D. Salloum, J.B. Schlenoff, Effect of molecular weight on the construction of polyelectrolyte multilayers: stripping versus sticking, *Langmuir* 19 (2003) 2491–2495, <http://dx.doi.org/10.1021/la026531d>.
- [30] P.R. Dash, M.L. Read, L.B. Barrett, M.A. Wolfert, L.W. Seymour, Factors affecting blood clearance and in vivo distribution of polyelectrolyte complexes for gene delivery, *Gene Ther.* 6 (1999) 643–650, <http://dx.doi.org/10.1038/sj.gt.3300843>.
- [31] H. Cai, C. Ni, L. Zhang, Preparation of complex nano-particles based on alginate acid/poly[(2-dimethylamino) ethyl methacrylate] and a drug vehicle for doxorubicin release controlled by ionic strength, *Eur. J. Pharm. Sci.* 45 (2012) 43–49, <http://dx.doi.org/10.1016/j.ejps.2011.10.020>.
- [32] W.S. Cheow, K. Hadinoto, Self-assembled amorphous drug-polyelectrolyte nanoparticle complex with enhanced dissolution rate and saturation solubility, *J. Colloid Interface Sci.* 367 (2012) 518–526, <http://dx.doi.org/10.1016/j.jcis.2011.10.011>.
- [33] M. Mende, H.-M. Buchhammer, S. Schwarz, G. Petzold, W. Jaeger, The stability of polyelectrolyte complex systems of poly(diallyldimethyl-ammonium chloride) with different polyanions, *Macromol. Symp.* 211 (2004) 121–134, <http://dx.doi.org/10.1002/masy.200450709>.
- [34] P. Schaaf, J.B. Schlenoff, Saloplastics: processing compact polyelectrolyte complexes, *Adv. Mater.* 27 (2015) 2420–2432, <http://dx.doi.org/10.1002/adma.201500176>.
- [35] F. Oosawa, *Polyelectrolytes*, Marcel Dekker, New York, 1971.
- [36] D. Fischer, H. Dautzenberg, K. Kunath, T. Kissel, Poly(diallyldimethylammonium chlorides) and their N-methyl-N-vinylacetamide copolymer-based DNA-polyplexes: role of molecular weight and charge density in complex formation, stability, and in vitro activity, *Int. J. Pharm.* 280 (2004) 253–269, <http://dx.doi.org/10.1016/j.ijpharm.2004.05.018>.
- [37] N. Karibyants, H. Dautzenberg, Preferential binding with regard to chain length and chemical structure in the reactions of formation of quasi-soluble polyelectrolyte complexes, *Langmuir* 14 (1998) 4427–4434, <http://dx.doi.org/10.1021/la980301a>.
- [38] A. Shovskiy, I. Varga, R. Makuška, P.M. Claesson, Formation and stability of water-soluble, molecular polyelectrolyte complexes: effects of charge density, mixing ratio, and polyelectrolyte concentration, *Langmuir* 25 (2009) 6113–6121, <http://dx.doi.org/10.1021/la804189v>.
- [39] M. Xu, J.A. Lewis, Phase behavior and rheological properties of polyamine-rich complexes for direct-write assembly, *Langmuir* 23 (2007) 12752–12759, <http://dx.doi.org/10.1021/la702249u>.
- [40] D.D. Dunlap, A. Maggi, M.R. Soria, L. Monaco, Nanoscopic structure of DNA condensed for gene delivery, *Nucleic Acids Res.* 25 (1997) 3095–3101, <http://dx.doi.org/10.1093/nar/25.15.3095>.
- [41] K. Nam, S. Jung, J.-P. Nam, S.W. Kim, Poly(ethylenimine) conjugated bioreducible dendrimer for efficient gene delivery, *J. Controlled Release* 220 (2015) 447–455, <http://dx.doi.org/10.1016/j.jconrel.2015.11.005>.
- [42] E. Dauty, J.-S. Remy, T. Blessing, J.-P. Behr, Dimerizable cationic detergents with a low cmc condense plasmid DNA into nanometric particles and transfect cells in culture, *J. Am. Chem. Soc.* 123 (2001) 9227–9234, <http://dx.doi.org/10.1021/ja015867r>.


- [43] C. Chittimalla, L. Zammuto-Italiano, G. Zuber, J.-P. Behr, Monomolecular DNA nanoparticles for intravenous delivery of genes, *J. Am. Chem. Soc.* 127 (2005) 11436–11441, <http://dx.doi.org/10.1021/ja0522332>.
- [44] V. Starchenko, M. Müller, N. Lebovka, Sizing of PDADMAC/PSS complex aggregates by polyelectrolyte and salt concentration and PSS molecular weight, *J. Phys. Chem. B* 116 (2012) 14961–14967, <http://dx.doi.org/10.1021/jp3095243>.
- [45] M. Müller, B. Keßler, S. Richter, Preparation of monomodal polyelectrolyte complex nanoparticles of PDADMAC/poly(maleic acid-alt-alpha-methylstyrene) by consecutive centrifugation, *Langmuir* 21 (2005) 7044–7051, <http://dx.doi.org/10.1021/la050716d>.
- [46] W. Ouyang, M. Müller, Monomodal polyelectrolyte complex nanoparticles of PDADMAC/poly(styrenesulfonate): preparation and protein interaction, *Macromol. Biosci.* 6 (2006) 929–941, <http://dx.doi.org/10.1002/mabi.200600143>.
- [47] N.M. Moore, C.L. Sheppard, T.R. Barbour, S.E. Sakiyama-Elbert, The effect of endosomal escape peptides on in vitro gene delivery of polyethylene glycol-based vehicles, *J. Gene Med.* 10 (2008) 1134–1149, <http://dx.doi.org/10.1002/jgm.1234>.
- [48] B. Han, D.R. Chery, J. Yin, X.L. Lu, D. Lee, L. Han, Soft Matter, *Soft Matter* 12 (2016) 1158–1169, <http://dx.doi.org/10.1039/C5SM01430A>.
- [49] R.V. Benjaminsen, M.A. Matthebjerg, J.R. Henriksen, S.M. Moghimi, T.L. Andresen, The possible “proton sponge” effect of polyethylenimine (PEI) does not include change in lysosomal pH, *Mol. Ther.* 21 (2013) 149–157, <http://dx.doi.org/10.1038/mt.2012.185>.
- [50] K.A. Gibney, I. Sovadinova, A.I. Lopez, M. Urban, Z. Ridgway, G.A. Caputo, et al, Poly(ethylene imine)s as antimicrobial agents with selective activity, *Macromol. Biosci.* 12 (2012) 1279–1289, <http://dx.doi.org/10.1002/mabi.201200052>.
- [51] M.I. Giannotti, O. Esteban, M. Oliva, M.F. Garcia-Parajo, F. Sanz, PH-Responsive polysaccharide-based polyelectrolyte complexes as nanocarriers for lysosomal delivery of therapeutic proteins, *Biomacromolecules* 12 (2011) 2524–2533, <http://dx.doi.org/10.1021/bm2003384>.
- [52] F. Bigucci, B. Luppi, T. Cerchiara, M. Sorrenti, G. Bettinetti, L. Rodriguez, et al, Chitosan/pectin polyelectrolyte complexes: selection of suitable preparative conditions for colon-specific delivery of vancomycin, *Eur. J. Pharm. Sci.* 35 (2008) 435–441, <http://dx.doi.org/10.1016/j.ejps.2008.09.004>.
- [53] Z. Sui, J.A. Jaber, J.B. Schlenoff, Polyelectrolyte complexes with pH-tunable solubility, *Macromolecules* 39 (2006) 8145–8152, <http://dx.doi.org/10.1021/ma061098q>.
- [54] A. Drogoz, L. David, C. Rochas, A. Domard, T. Delair, Polyelectrolyte complexes from polysaccharides: formation and stoichiometry monitoring, *Langmuir* 23 (2007) 10950–10958, <http://dx.doi.org/10.1021/la7008545>.
- [55] Q. Wang, J.B. Schlenoff, The polyelectrolyte complex/coacervate continuum, *Macromolecules* 47 (2014) 3108–3116, <http://dx.doi.org/10.1021/ma500500q>.
- [56] Y.-H. Hsieh, Y.-T. Hsiao, J.-S. Jan, Shell and core cross-linked poly(L-lysine)/poly(acrylic acid) complex micelles, *Soft Matter* 10 (2014) 9568–9576, <http://dx.doi.org/10.1039/C4SM02033B>.
- [57] J.-G. Piao, J.-J. Yan, M.-Z. Wang, D.-C. Wu, Y.-Z. You, A new method to cross-link a polyplex for enhancing in vivo stability and transfection efficiency, *Biomater. Sci.* 2 (2014) 390–398, <http://dx.doi.org/10.1039/C3BM60204D>.
- [58] Y.H. Kim, J.H. Park, M. Lee, Y.-H. Kim, T.G. Park, S.W. Kim, Polyethylenimine with acid-labile linkages as a biodegradable gene carrier, *J. Controlled Release* 103 (2005) 209–219, <http://dx.doi.org/10.1016/j.jconrel.2004.11.008>.
- [59] S. Schwarz, W. Jaeger, S. Bratskaya, J. Bohrisch, T. Schimmel, M. Mende, et al, Formation of polyelectrolyte complexes in a polycarboxybetaine/weak polyanion system, *Colloids Surf. A: Physicochem. Eng. Aspects* 276 (2006) 65–71, <http://dx.doi.org/10.1016/j.colsurfa.2005.10.017>.
- [60] C. Schatz, J.-M. Lucas, C. Viton, A. Domard, C. Pichot, T. Delair, Formation and properties of positively charged colloids based on polyelectrolyte complexes of biopolymers, *Langmuir* 20 (2004) 7766–7778, <http://dx.doi.org/10.1021/la049460m>.
- [61] M.A. Hubbe, S.M. Moore, S.Y. Lee, Effects of charge ratios and cationic polymer nature on polyelectrolyte complex deposition onto cellulose, *Ind. Eng. Chem. Res.* 44 (2005) 3068–3074, <http://dx.doi.org/10.1021/ie048902m>.
- [62] M. Müller, B. Keßler, J. Fröhlich, S. Poeschla, B. Torger, Polyelectrolyte complex nanoparticles of poly(ethyleneimine) and poly(acrylic acid): preparation and applications, *Polymers* 3 (2011) 762–778, <http://dx.doi.org/10.3390/polym3020762>.
- [63] R.C. Adams, K.G. Rice, Metabolic stability of glutaraldehyde cross-linked peptide DNA condensates, *J. Pharm. Sci.* 88 (1999) 739–746, <http://dx.doi.org/10.1021/js990042p>.
- [64] M.D. Giron-Gonzalez, R. Salto-Gonzalez, F.J. Lopez-Jaramillo, A. Salinas-Castillo, A.B. Jodar-Reyes, M. Ortega-Muñoz, et al, Polyelectrolyte complexes of low molecular weight PEI and citric acid as efficient and nontoxic vectors for in vitro and in vivo gene delivery, *Bioconjugate Chem.* 27 (2016) 549–561, <http://dx.doi.org/10.1021/acs.bioconjchem.5b00576>.
- [65] M.A. Gosselin, W. Guo, R.J. Lee, Efficient gene transfer using reversibly cross-linked low molecular weight polyethylenimine, *Bioconjugate Chem.* 12 (2001) 989–994, <http://dx.doi.org/10.1021/bc0100455>.
- [66] D.L. McKenzie, E. Smiley, K.Y. Kwok, K.G. Rice, Low molecular weight disulfide cross-linking peptides as nonviral gene delivery carriers, *Bioconjugate Chem.* 11 (2000) 901–909, <http://dx.doi.org/10.1021/bc000056i>.
- [67] R. Cheng, F. Feng, F. Meng, C. Deng, J. Feijen, Z. Zhong, Glutathione-responsive nano-vehicles as a promising platform for targeted intracellular drug and gene delivery, *J. Controlled Release* 152 (2011) 2–12, <http://dx.doi.org/10.1016/j.jconrel.2011.01.030>.
- [68] I. Insua, E. Lamas, Z. Zhang, A.F.A. Peacock, A.M. Krachler, F. Fernandez-Trillo, Enzyme-responsive polyion complex (PIC) nanoparticles for the targeted delivery of antimicrobial polymers, *Polym. Chem.* 7 (2016) 2684–2690, <http://dx.doi.org/10.1039/C6PY00146G>.
- [69] T. Hashimoto, T. Yamaoka, Polymeric gene carriers, in: *Non-Viral Gene Therapy*, Springer-Verlag, Tokyo, 2005, pp. 35–50, http://dx.doi.org/10.1007/4-431-27879-6_4.
- [70] T. Wang, J.R. Upponi, V.P. Torchilin, Design of multifunctional non-viral gene vectors to overcome physiological barriers: dilemmas and strategies, *Int. J. Pharm.* 427 (2012) 3–20, <http://dx.doi.org/10.1016/j.ijpharm.2011.07.013>.
- [71] E. Wagner, Polymers for nucleic acid transfer—an overview, in: L. Huang, D. Liu, E. Wagner (Eds.), *Nonviral Vectors for Gene Therapy Lipid- and Polymer-Based Gene Transfer*, Academic Press, 2014, pp. 231–261, <http://dx.doi.org/10.1016/B978-0-12-800148-6.00008-0>.
- [72] W. Fischle, Y. Wang, C.D. Allis, Histone and chromatin cross-talk, *Curr. Opin. Cell Biol.* 15 (2003) 172–183.
- [73] J.A. Speir, J.E. Johnson, Nucleic acid packaging in viruses, *Curr. Opin. Struct. Biol.* 22 (2012) 65–71, <http://dx.doi.org/10.1016/j.sbi.2011.11.002>.
- [74] M.A. Wolfert, P.R. Dash, O. Nazarova, D. Oupický, L.W. Seymour, S. Smart, et al, Polyelectrolyte vectors for gene delivery: influence of cationic polymer on biophysical properties of complexes formed with DNA, *Bioconjugate Chem.* 10 (1999) 993–1004, <http://dx.doi.org/10.1021/bc990025r>.
- [75] S. Kawakami, Y. Ito, P. Charoensit, F. Yamashita, M. Hashida, Evaluation of proinflammatory cytokine production induced by linear and branched polyethylenimine/plasmid DNA complexes in mice, *J. Pharmacol. Exp. Ther.* 317 (2006) 1382–1390, <http://dx.doi.org/10.1124/jpet.105.100669>.
- [76] P.R. Leroueil, S.A. Berry, K. Duthie, G. Han, V.M. Rotello, D.Q. McNerny, et al, Wide varieties of cationic nanoparticles induce defects in supported lipid bilayers, *Nano Lett.* 8 (2008) 420–424, <http://dx.doi.org/10.1021/nl0722929>.
- [77] S. Choksalunimitr, S. Masuda, H. Tokuda, Y. Takakura, M. Hashida, In-vitro cytotoxicity of macromolecules in different cell-culture systems, *J. Controlled Release* 34 (1995) 233–241, [http://dx.doi.org/10.1016/0168-3659\(95\)00007-U](http://dx.doi.org/10.1016/0168-3659(95)00007-U).
- [78] B.I. Florea, C. Meaney, H.E. Junginger, G. Borchard, Transfection efficiency and toxicity of polyethylenimine in differentiated Calu-3 and nondifferentiated COS-1 cell cultures, *Aaps Pharmsci.* 4 (2002).
- [79] S.M. Moghimi, P. Symonds, J.C. Murray, A.C. Hunter, G. Debska, A. Szewczyk, A two-stage poly(ethyleneimine)-mediated cytotoxicity: implications for gene transfer/therapy, *Mol. Ther.* 11 (2005) 990–995, <http://dx.doi.org/10.1016/j.mthe.2005.02.010>.
- [80] D. Fischer, T. Bieber, Y. Li, H.P. Elsässer, T. Kissel, A novel non-viral vector for DNA delivery based on low molecular weight, branched polyethylenimine: effect of molecular weight on transfection efficiency and cytotoxicity, *Pharm. Res.* 16 (1999) 1273–1279, <http://dx.doi.org/10.1023/A:1014861900478>.
- [81] W.T. Godbey, K.K. Wu, A.G. Mikos, Poly(ethyleneimine) and its role in gene delivery, *J. Controlled Release* 60 (1999) 149–160, [http://dx.doi.org/10.1016/S0168-3659\(99\)00090-5](http://dx.doi.org/10.1016/S0168-3659(99)00090-5).
- [82] C. Alexander, F. Fernandez-Trillo, Bioresponsive polyplexes and micelleplexes, in: C. Alvarez-Lorenzo, A. Concheiro (Eds.), *Smart Materials for Drug Delivery*, first ed., Royal Society of Chemistry, 2013, pp. 256–282, <http://dx.doi.org/10.1039/9781849736800-00256>.

- [83] A. Meister, M.E. Anderson, Glutathione, *Annu. Rev. Biochem.* 52 (1983) 711–760, <http://dx.doi.org/10.1146/annurev.bi.52.070183.003431>.
- [84] S. Choi, K.-D. Lee, Enhanced gene delivery using disulfide-crosslinked low molecular weight polyethylenimine with listeriolysin o-polyethylenimine disulfide conjugate, *J. Controlled Release* 131 (2008) 70–76, <http://dx.doi.org/10.1016/j.jconrel.2008.07.007>.
- [85] M. Ohsaki, T. Okuda, A. Wada, T. Hirayama, T. Niidome, H. Aoyagi, In vitro gene transfection using dendritic poly(L-lysine), *Bioconjugate Chem.* 13 (2002) 510–517, <http://dx.doi.org/10.1021/bc015525a>.
- [86] T. Okuda, A. Sugiyama, T. Niidome, H. Aoyagi, Characters of dendritic poly((L)-lysine) analogues with the terminal lysines replaced with arginines and histidines as gene carriers in vitro, *Biomaterials* 25 (2004) 537–544, [http://dx.doi.org/10.1016/S0142-9612\(03\)00542-8](http://dx.doi.org/10.1016/S0142-9612(03)00542-8).
- [87] Z. Kadlecova, Y. Rajendra, M. Matasci, L. Baldi, D.L. Hacker, F.M. Wurm, et al, DNA delivery with hyperbranched polylysine: a comparative study with linear and dendritic polylysine, *J. Controlled Release* 169 (2013) 276–288, <http://dx.doi.org/10.1016/j.jconrel.2013.01.019>.
- [88] Z. Kadlecova, L. Baldi, D. Hacker, F.M. Wurm, H.-A. Klok, Comparative study on the in vitro cytotoxicity of linear, dendritic, and hyperbranched polylysine analogues, *Biomacromolecules* 13 (2012) 3127–3137, <http://dx.doi.org/10.1021/bm300930j>.
- [89] F.M. Veronese, G. Pasut, PEGylation, successful approach to drug delivery, *Drug Discovery Today* 10 (2005) 1451–1458, [http://dx.doi.org/10.1016/S1359-6446\(05\)03575-0](http://dx.doi.org/10.1016/S1359-6446(05)03575-0).
- [90] R.E.B. Fitzsimmons, H. Uludağ, Specific effects of PEGylation on gene delivery efficacy of polyethylenimine: interplay between PEG substitution and N/P ratio, *Acta Biomater* 8 (2012) 3941–3955, <http://dx.doi.org/10.1016/j.actbio.2012.07.015>.
- [91] S.-J. Sung, S.H. Min, K.Y. Cho, S. Lee, Y.-J. Min, Y.I. Yeom, et al, Effect of polyethylene glycol on gene delivery of polyethylenimine, *Biol. Pharm. Bull.* 26 (2003) 492–500.
- [92] Z. Zhong, J. Feijen, M.C. Lok, W.E. Hennink, L.V. Christensen, J.W. Yockman, et al, Low molecular weight linear polyethylenimine-b-poly(ethylene glycol)-b-polyethylenimine triblock copolymers: synthesis, characterization, and in vitro gene transfer properties, *Biomacromolecules* 6 (2005) 3440–3448, <http://dx.doi.org/10.1021/bm050505n>.
- [93] Y. Bae, H. Cabral, K. Kataoka, Block copolymer micelles for drug delivery in nanoscience, in: M. Lazzari, G. Liu, S. Lecommandoux (Eds.), *Block Copolymers in Nanoscience*, Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim, Germany, 2006, pp. 73–89, <http://dx.doi.org/10.1002/9783527610570.ch4>.
- [94] K. Miyata, N. Nishiyama, K. Kataoka, Rational design of smart supramolecular assemblies for gene delivery: chemical challenges in the creation of artificial viruses, *Chem. Soc. Rev.* 41 (2012) 2562–2574, <http://dx.doi.org/10.1039/c1cs15258k>.
- [95] C.H. Jones, C.-K. Chen, A. Ravikrishnan, S. Rane, B.A. Pfeifer, Overcoming nonviral gene delivery barriers: perspective and future, *Mol. Pharmaceutics* 10 (2013) 4082–4098, <http://dx.doi.org/10.1021/mp400467x>.
- [96] M.J. Roberts, M.D. Bentley, J.M. Harris, Chemistry for peptide and protein PEGylation, *Adv. Drug Delivery Rev.* 54 (2002) 459–476.
- [97] M. Stevenson, V. Ramos-Perez, S. Singh, M. Soliman, J.A. Preece, S.S. Briggs, et al, Delivery of siRNA mediated by histidine-containing reducible polyocations, *J. Controlled Release* 130 (2008) 46–56, <http://dx.doi.org/10.1016/j.jconrel.2008.05.014>.
- [98] C. Plank, K. Mechtler, F.C. Szoka, E. Wagner, Activation of the complement system by synthetic DNA complexes: a potential barrier for intravenous gene delivery, *Hum. Gene Ther.* 7 (1996) 1437–1446, <http://dx.doi.org/10.1089/hum.1996.7.12-1437>.
- [99] M. Ogris, S. Brunner, S. Schüller, R. Kircheis, E. Wagner, PEGylated DNA/transferrin-PEI complexes: reduced interaction with blood components, extended circulation in blood and potential for systemic gene delivery, *Gene Ther.* 6 (1999) 595–605, <http://dx.doi.org/10.1038/sj.gt.3300900>.
- [100] C. Monfardini, F.M. Veronese, Stabilization of substances in circulation, *Bioconjugate Chem.* 9 (1998) 418–450, <http://dx.doi.org/10.1021/bc970184f>.
- [101] T. Merdan, K. Kunath, H. Petersen, U. Bakowsky, K.H. Voigt, J. Kopeček, et al, PEGylation of poly(ethylene imine) affects stability of complexes with plasmid DNA under in vivo conditions in a dose-dependent manner after intravenous injection into mice, *Bioconjugate Chem.* 16 (2005) 785–792, <http://dx.doi.org/10.1021/bc049743q>.
- [102] O. Boussif, F. Lezoual'h, M.A. Zanta, M.D. Mergny, D. Scherman, B. Demeneix, et al, A versatile vector for gene and oligonucleotide transfer into cells in culture and in vivo: polyethylenimine, *Proc. Natl. Acad. Sci. U. S. A.* 92 (1995) 7297–7301, <http://www.pnas.org/content/92/16/7297.abstract>.
- [103] L. Poulain, C. Ziller, C.D. Muller, P. Erbacher, T. Bettinger, J.F. Rodier, et al, Ovarian carcinoma cells are effectively transfected by polyethylenimine (PEI) derivatives, *Cancer Gene Ther.* 7 (2000) 644–652, <http://dx.doi.org/10.1038/sj.cgt.7700170>.
- [104] E. Wagner, Polymers for siRNA delivery: inspired by viruses to be targeted, dynamic, and precise, *Acc. Chem. Res.* 45 (2012) 1005–1013, <http://dx.doi.org/10.1021/ar2002232>.
- [105] M. Somiya, S. Kuroda, Development of a virus-mimicking nanocarrier for drug delivery systems: the bio-nanocapsule, *Adv. Drug Delivery Rev.* 95 (2015) 77–89, <http://dx.doi.org/10.1016/j.addr.2015.10.003>.
- [106] T. Taguchi, Emerging roles of recycling endosomes, *J. Biochem.* 153 (2013) 505–510, <http://dx.doi.org/10.1093/jb/mvt034>.
- [107] J.-P. Behr, The proton sponge: a trick to enter cells the viruses did not exploit, *Chimia* 51 (1997) 34–36, <http://www.ingentaconnect.com/content/scs/chimia/1997/00000051/f0020001/art00026>.
- [108] A.R. Graves, P.K. Curran, C.L. Smith, J.A. Mindell, The Cl⁻/H⁺ antiporter ClC-7 is the primary chloride permeation pathway in lysosomes, *Nature* 453 (2008) 788–792, <http://dx.doi.org/10.1038/nature06907>.
- [109] E.C. Freeman, L.M. Weiland, W.S. Meng, Modeling the proton sponge hypothesis: examining proton sponge effectiveness for enhancing intracellular gene delivery through multiscale modeling, *J. Biomater. Sci. Polym. Ed.* 24 (2013) 398–416, <http://dx.doi.org/10.1080/09205063.2012.690282>.
- [110] S. Yang, S. May, Release of cationic polymer-DNA complexes from the endosome: a theoretical investigation of the proton sponge hypothesis, *J. Chem. Phys.* 129 (2008), <http://dx.doi.org/10.1063/1.3009263>.
- [111] W.T. Godbey, M.A. Barry, P. Saggau, K.K. Wu, A.G. Mikos, Poly(ethylenimine)-mediated transfection: a new paradigm for gene delivery, *J. Biomed. Mater. Res.* 51 (2000) 321–328, [http://dx.doi.org/10.1002/1097-4636\(20000905\)51:3<321::Aid-Jbm5>3.0.Co;2-R](http://dx.doi.org/10.1002/1097-4636(20000905)51:3<321::Aid-Jbm5>3.0.Co;2-R).
- [112] T. Bieber, W. Meissner, S. Kostin, A. Niemann, H.P. Elsasser, Intracellular route and transcriptional competence of polyethylenimine-DNA complexes, *J. Controlled Release* 82 (2002) 441–454, [http://dx.doi.org/10.1016/S0168-3659\(02\)00129-3](http://dx.doi.org/10.1016/S0168-3659(02)00129-3).
- [113] T. Merdan, K. Kunath, D. Fischer, J. Kopeček, T. Kissel, Intracellular processing of poly(ethylene imine)/ribozyme complexes can be observed in living cells by using confocal laser scanning microscopy and inhibitor experiments, *Pharm. Res.* 19 (2002) 140–146, <http://dx.doi.org/10.1023/A:1014212630566>.
- [114] C.W. Pouton, P. Lucas, B.J. Thomas, A.N. Uduehi, D.A. Milroy, S.H. Moss, Polycation-DNA complexes for gene delivery: a comparison of the biopharmaceutical properties of cationic polypeptides and cationic lipids, *J. Controlled Release* 53 (1998) 289–299.
- [115] K. Ciftci, R.J. Levy, Enhanced plasmid DNA transfection with lysosomotropic agents in cultured fibroblasts, *Int. J. Pharm.* 218 (2001) 81–92, [http://dx.doi.org/10.1016/S0378-5173\(01\)00623-8](http://dx.doi.org/10.1016/S0378-5173(01)00623-8).
- [116] C. Wong-Baeza, I. Bustos, M. Serna, A. Tescucano, V. Alcantara-Farfan, M. Ibanez, et al, Membrane fusion inducers, chloroquine and spermidine increase lipoplex-mediated gene transfection, *Biochem. Biophys. Res. Commun.* 396 (2010) 549–554, <http://dx.doi.org/10.1016/j.bbrc.2010.04.143>.
- [117] A.M. Funhoff, C.F. Van Nostrum, M.C. Lok, J.A.W. Kruijtzter, D.J.A. Crommelin, W.E. Hennink, Cationic polymethacrylates with covalently linked membrane destabilizing peptides as gene delivery vectors, *J. Controlled Release* 101 (2005) 233–246, <http://dx.doi.org/10.1016/j.jconrel.2004.06.023>.
- [118] A.M.V. Giraldo, H. Appelqvist, T. Ederth, K. Ollinger, Lysosomotropic agents: impact on lysosomal membrane permeabilization and cell death, *Biochem. Soc. Trans.* 42 (2014) 1460–1464, <http://dx.doi.org/10.1042/Bst20140145>.
- [119] C. Pichon, C. Gonçalves, P. Midoux, Histidine-rich peptides and polymers for nucleic acids delivery, *Adv. Drug Delivery Rev.* 53 (2001) 75–94, [http://dx.doi.org/10.1016/S0169-409X\(01\)00221-6](http://dx.doi.org/10.1016/S0169-409X(01)00221-6).
- [120] P.S. Uster, D.W. DEAMER, pH-dependent fusion of liposomes using titratable polycations, *Biochemistry* 24 (1985) 1–8.
- [121] Y. Luo, Q. Wang, Recent development of chitosan-based polyelectrolyte complexes with natural polysaccharides for drug delivery, *Int. J. Biol. Macromol.* 64 (2014) 353–367, <http://dx.doi.org/10.1016/j.ijbiomac.2013.12.017>.
- [122] Y. Wu, Y. Long, Q.-L. Li, S. Han, J. Ma, Y.-W. Yang, et al, Layer-by-layer (LBL) self-assembled biohybrid nanomaterials for efficient antibacterial applications, *ACS Appl. Mater. Interfaces* 7 (2015) 17255–17263, <http://dx.doi.org/10.1021/acsami.5b04216>.

- [123] A. Jintapattanakit, V.B. Junyaprasert, S. Mao, J. Sitterberg, U. Bakowsky, T. Kissel, Peroral delivery of insulin using chitosan derivatives: a comparative study of polyelectrolyte nanocomplexes and nanoparticles, *Int. J. Pharm.* 342 (2007) 240–249, <http://dx.doi.org/10.1016/j.ijpharm.2007.05.015>.
- [124] K. Al Rubeaan, M. Rafiullah, S. Jayavanth, Oral insulin delivery systems using chitosan-based formulation: a review, *Expert Opin. Drug Deliv.* 13 (2016) 223–237, <http://dx.doi.org/10.1517/17425247.2016.1107543>.
- [125] Y. Tao, J. Xu, M. Chen, H. Bai, X. Liu, Core cross-linked hyaluronan-styrylpyridinium micelles as a novel carrier for paclitaxel, *Carbohydr. Polym.* 88 (2012) 118–124, <http://dx.doi.org/10.1016/j.carbpol.2011.11.075>.



Ignacio Insua graduated from the University of Santiago de Compostela (Spain) in 2012 with a BSc in Pharmacy. He obtained his MSc degree in industry at InKemia-IUCT (Spain) in 2013. Later in 2013, he joined the laboratory of Dr. Francisco Fernandez-Trillo at the University of Birmingham (UK), where he is currently a PhD candidate studying bacteria-responsive nanomaterials and polyelectrolyte self-assembly.

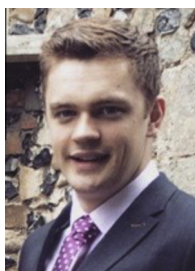

Andrew Wilkinson graduated from the University of Birmingham in 2015 with a MSci in Chemistry. He carried out his final year project in the synthesis and characterisation of polyacetylenes. Since 2015, he has been a PhD student working on the development of novel gene delivery techniques in the groups of Dr Robert Neely and Dr Francisco Fernandez-Trillo.



Francisco Fernandez-Trillo (Paco) is the John Evans Fellow of Nanotechnology at the University of Birmingham (UK) developing Biomedical Applications of Nanomaterials. Prior to this he received his PhD in Organic Chemistry in 2004 from the University of Santiago de Compostela (Spain). This was followed by post-doctoral positions, both in the UK (Durham and Nottingham) and Spain (Santiago de Compostela) working on polymeric nanomaterials for biocatalysis, cell recognition and synthetic biology. Paco now leads a diverse research group working at the interface between organic chemistry, polymer science and nanotechnology.