

Use of Desulfovibrio and Escherichia coli Pd-nanocatalysts in reduction of Cr(VI) and hydrogenolytic dehalogenation of polychlorinated biphenyls and used transformer oil

Macaskie, L.E.; Humphries, A.C.; Mikheenko, I.P.; Baxter-Plant, V.S.; Deplanche, K.; Redwood, M.D.; Wood, J.

DOI:
[10.1002/jctb.3763](https://doi.org/10.1002/jctb.3763)

Document Version
Peer reviewed version

Citation for published version (Harvard):
Macaskie, LE, Humphries, AC, Mikheenko, IP, Baxter-Plant, VS, Deplanche, K, Redwood, MD & Wood, J 2012, 'Use of Desulfovibrio and Escherichia coli Pd-nanocatalysts in reduction of Cr(VI) and hydrogenolytic dehalogenation of polychlorinated biphenyls and used transformer oil', *Journal of Chemical Technology and Biotechnology*, vol. 87, pp. 1430. <https://doi.org/10.1002/jctb.3763>

[Link to publication on Research at Birmingham portal](#)

Publisher Rights Statement:

The definitive version is available at www3.interscience.wiley.com. J Physiol (2003), 553.2, pp. 627–635 DOI: 10.1113/jphysiol.2003.049734
© The Physiological Society 2003 www.jphysiol.org

General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact UBIRA@lists.bham.ac.uk providing details and we will remove access to the work immediately and investigate.

Download date: 09. Apr. 2024

Use of *Desulfovibrio* and *Escherichia coli* Pd-nanocatalysts in reduction of Cr(VI) and hydrogenolytic dehalogenation of polychlorinated biphenyls and used transformer oil

Lynne E. Macaskie^{1*}, Andrea C. Humphries^{1#}, Iryna P. Mikheenko¹, Victoria S. Baxter-Plant^{1‡}, Kevin Deplanche¹, Mark D. Redwood¹, James A. Bennett², Joe Wood²

Schools of ¹Biosciences and ²Chemical Engineering, University of Birmingham, Edgbaston, Birmingham, B15 2TT, UK

*Correspondence to L.E. Macaskie
School of Biosciences, University of Birmingham. Edgbaston Birmingham,
B15 2TT, UK
Tel (44)-121-414-5889
Fax (44)-121-414-5925
e-mail L.E.Macaskie@bham.ac.uk

Current address:
Department of Crops, Harper Adams University College, Newport, Shropshire TF10 8NB, UK

‡Deceased

Abstract

BACKGROUND *Desulfovibrio* spp. biofabricate metallic nanoparticles (e.g. ‘Bio-Pd’) which catalyse the reduction of Cr(VI) to Cr(III) and dehalogenate polychlorinated biphenyls (PCBs). *Desulfovibrio* spp. are anaerobic and produce H₂S, a potent catalyst poison, whereas *Escherichia coli* can be pre-grown aerobically to high density, has well defined molecular tools, and also makes catalytically-active ‘Bio-Pd’. The first aim was to compare ‘Bio-Pd’ catalysts made by *Desulfovibrio* spp. and *E. coli* using suspended and immobilised catalysts. The second aim was to evaluate the potential for Bio-Pd-mediated dehalogenation of PCBs in used transformer oils, which preclude recovery and re-use.

RESULTS Catalysis via Bio-Pd_{*D. desulfuricans*} and Bio-Pd_{*E. coli*} was compared at a mass loading of Pd:biomass of 1:3 via reduction of Cr(VI) in aqueous solution (immobilised catalyst) and hydrogenolytic release of Cl from PCBs and used transformer oil (catalyst suspensions). In both cases Bio-Pd_{*D. desulfuricans*} outperformed Bio-Pd_{*E. coli*} by ~3.5-fold, attributable to a ~3.5-fold difference in their Pd-nanoparticle surface areas determined by magnetic measurements (Bio-Pd_{*D. desulfuricans*}) and by chemisorption analysis (Bio-Pd_{*E. coli*}). Small Pd particles were confirmed on *D. desulfuricans* and fewer, larger ones on *E. coli* via electron microscopy. Bio-Pd_{*D. desulfuricans*}-mediated chloride release from used transformer oil ($5.6 \pm 0.8 \mu\text{g mL}^{-1}$) was comparable to that observed using several PCB reference materials.

CONCLUSIONS At a loading of 1:3 Pd: biomass Bio-Pd_{*D. desulfuricans*} is 3.5-fold more active than Bio-Pd_{*E. coli*}, attributable to the relative catalyst surface areas reflected in the smaller nanoparticle sizes of the former. This study also shows the potential of Bio-Pd_{*D. desulfuricans*} to remediate used transformer oil.

Keywords: chromium (VI), polychlorinated biphenyl, sulphate-reducing bacteria, *Desulfovibrio* *Escherichia coli*, palladium catalyst

INTRODUCTION

Problematic environmental industrial contaminants, e.g. heavy metals and chlorinated organic compounds, can occur in the same ecosystem.^{1,2} Conventional methods for removing Cr(VI) from water (e.g.³) are relatively expensive and/or require addition of chemicals. Cr(VI)-waters could be treated by bioreduction to Cr(III);⁴ various microorganisms are capable of this reduction e.g.⁵⁻¹⁰ including sulphate-reducing bacteria (SRB).^{11,12} The latter can also reduce various other metals¹³ including precious metals (see^{14,15}) at the expense of formate or H₂.

Chlorinated aromatic molecules are environmentally-important contaminants, e.g. pentachlorophenol is found in wood preservatives (often with Cr), while polychlorinated biphenyls (PCBs) have historical uses, e.g. as insulators and plasticisers.¹⁶ PCBs also occur in used transformer oils, complicating oil disposal or recovery. Environmental biodegradation of PCBs is slow¹⁷ and their long-term persistence is problematic.¹⁸ The recent use of polybrominated diphenyl ethers (PBDEs) as flame retardants is causing their environmental accumulation and these may be similarly persistent.¹⁹ A tenfold accumulation of a more recent alternative, tris(chloroisopropyl) phosphate (TCPP), was found in groundwater over a 10 year period.²⁰ The ability of zero-valent iron to promote reductive dehalogenation of PCBs was potentiated by incorporation of Pd(0),^{21,22} which prompted this investigation.

Some SRB can reductively dehalogenate chlorinated aromatic compounds by ill-defined metabolic mechanisms.^{17,23} Microbial approaches to the co-treatment of chlorophenols and Cr(VI) have been described⁸ but biological systems require physiologically compatible conditions. A robust alternative, SRB cells coated with Pd particles (Bio-Pd), reduced Cr(VI)^{24,25} and also reductively dehalogenated chlorinated aromatic compounds,²⁶ PBDEs¹⁹ and TCPP.²⁰ The latter (hydrogenolysis reactions) accords with the known activity of Pd(0) as a hydrogenolytic catalyst.²⁷

Previous studies on the use of Bio-Pd for catalysis utilised SRB but other bacteria able to couple hydrogen or formate oxidation to Pd(II) reduction can make catalytically active Bio-Pd and, indeed, other precious metal bionanocatalysts (for review see¹⁵), a new area of biotechnology which is burgeoning since the initial reports.^{24,26}

E. coli provides a potentially useful alternative to SRB since this organism provides ready molecular

tools for strain improvement,²⁸ it does not produce H₂S (a powerful catalyst poison) and cells can be grown aerobically to high cell density and then placed anoxically for upregulation of hydrogenase activity for metal reduction.

The aim of this study was to compare the catalytic efficacy of Bio-Pd_{*D. desulfuricans*} and Bio-Pd_{*D. vulgaris*} with the corresponding Bio-Pd made on *E. coli* using two environmentally-relevant, independent criteria: reduction of Cr(VI) to Cr(III) in a flow-through system using gel-immobilised palladised cells and liberation of chloride ion from polychlorinated biphenyls in a batch system. With respect to potential applications in resource efficiency in a climate of increasing oil prices and dwindling supplies, used transformer oils could be reprocessed but the presence of high levels of PCBs currently limits their re-use. The second aim of the study was to show the potential for Bio-Pd-mediated decontamination of waste transformer oil.

MATERIALS AND METHODS

Organisms and growth conditions

Desulfovibrio vulgaris NCIMB 8303 and *D. desulfuricans* NCIMB 8307 were grown anaerobically as described previously.^{12,26} Cultures were harvested after 24 h (OD₆₀₀ 0.7 ± 0.2). *E. coli* MC4100 was grown as described previously (24 h; 30 °C;²⁹) in 1 L closed anoxic bottles (OD₆₀₀ at harvest = 0.8). Cells were washed in isotonic saline (8.5 g L⁻¹ of NaCl) and stored under oxygen-free nitrogen (OFN; 4 °C) as concentrates in 20 mM MOPS/ NaOH buffer, pH 7, until use (within 24 h). The biomass concentration was estimated by converting the OD₆₀₀ to dry cell weight using a previously determined calibration.

Preparation of Bio-Pd on bacteria

The required volume of 2 mM Na₂PdCl₄ (98 %, Aldrich Chemicals, UK) solution (to pH 2 with HNO₃), was placed in a 200 mL serum bottle sealed with a butyl-rubber stopper. Cells were added (final mass ratio of dry cells: Pd was 3:1), left at 30 °C for 1 h for Pd(II) biosorption and then sparged with H₂ (15 min) to deposit Pd(0) on the cell surface (25% Pd by mass). Removal of Pd(II) from solution was monitored by loss of the yellow colour spectrophotometrically, cross-validated using the SnCl₂ method, and polarographically.³⁰ Pd-coated cells (Bio-Pd) were recovered by centrifugation (3800 g, 10 min); no residual Pd(II) remained in the supernatant by assay. The pellet was washed once with distilled H₂O and three times with acetone,

dried (60 °C) to constant weight and ground to a fine powder to make the final Bio-Pd catalyst.

Transmission electron microscopy

Pd-loaded bacteria were rinsed twice with distilled water, fixed in 2.5 % (w/v) aqueous glutaraldehyde, washed once in distilled water then in 1 % osmium tetroxide in 0.1 M phosphate buffer (pH 7, 60 min). Cells were dehydrated using an ethanol series (70, 90, 100, 100, 100 % dried ethanol; 15 min each step) washed twice in propylene oxide (15 min), embedded in epoxy resin (degassed under vacuum for 30 min) and left to polymerize (24 h; 60 °C). Sections (~100 nm) were cut, placed onto a copper grid and viewed with a JEOL 120CX2 transmission electron microscope (TEM); accelerating voltage 80 kV.

Determination of catalyst surface area

mg mL⁻¹ agar (mass of Pd was 25% by weight)

Catalytic testing of the Bio-Pd

For testing suspensions of Bio-Pd against Cr(VI) reaction mixtures were set up in 12 mL serum bottles. Bio-Pd (5 mg) or Bio-Pd beads (2 mL, 2.5 mg Bio-Pd⁰ mL agar gel⁻¹) were suspended in 5 mL solution comprising 20 mM MOPS/NaOH buffer and 25 mM each of sodium formate (electron donor), sodium acetate, and sodium citrate (to chelate the Cr(III) product), with 500 µM sodium chromate, pH 7. For anaerobic tests, reaction mixtures were degassed with oxygen free nitrogen (OFN) for 10 min before addition of chromate. Samples were withdrawn periodically (under OFN for anaerobic tests) via a syringe, and supernatants were analysed for residual Cr(VI) using diphenylcarbazide.^{12,19,31}

For continuous Cr(VI) reduction tests, Bio-Pd agar beads (4 mL) were placed in a glass column (i.d. 12 mm, length 10 cm). Solution (500 µM sodium chromate and 25 mM each of sodium formate, citrate and acetate in 20 mM MOPS/NaOH buffer, pH 7) was passed upwards (flow rate: 13.2 mL h⁻¹). The outflow was analysed for residual Cr(VI) using diphenylcarbazide as above. Controls

Release of chloride from PCBs in waste transformer oil

Waste transformer oil was provided by C-Tech Innovation, Capenhurst, UK. It contained ~ 2.5 mg mL⁻¹ of PCBs, (mixture of arochlors 60, 42 and 54: analysis by H₂b Ltd., Capenhurst, UK). The oil was

CO chemisorption was used to estimate the active particle size of Bio-Pd_{E.coli} using a Micromeritics Autochem II Chemisorption Analyser equipped with a thermal conductivity detector (TCD). Samples (0.5 g) were slowly heated (10 °C min⁻¹) to 100 °C under an H₂ atmosphere (50 mL min⁻¹) and allowed to cool and stabilise at 40 °C. Pulses of CO (loop volume = 0.5389 mL) were applied to the sample until consistent TCD peak sizes were obtained, indicating that metallic particles had reached CO saturation. The determined active Pd(0) surface area (m² g⁻¹ Pd metal) was used to calculate the average nanoparticle size using 'Autochem II 2920V2.00' software supplied with the Chemisorption Analyser.

Immobilisation of Bio-Pd preparations

Immobilisation of Bio-Pd in agar beads was as described previously.³¹ The catalyst loading was 7.5 mg Bio-Pd(0) cm⁻³ agar; Pd content was 1.87 contained agar beads only. Previous studies had shown that live or killed cells removed negligible Cr(VI) in the absence of Pd(0) under these conditions.²⁴

For testing reductive dehalogenation Bio-Pd (2 mg) or Pd prepared by chemical reduction under H₂ (2 mg) was placed in 12 mL serum bottles in 20 mM MOPS-NaOH buffer pH 7.0 and chlorinated aromatic compound (Table 1) was added in 1 ml of hexane carrier and shaken well (the nominal concentration was as shown in Table 1; the actual concentration chlorinated aromatic compound in the aqueous phase was not determined). Bottles were outgassed with OFN (15 min) and tests were initiated via the addition of sodium formate (aq.) (to 10 mM, pH 7.3; final volume was 10 mL) and re-shaken. Chloride release was estimated in withdrawn samples by spectrophotometric assay of Cl⁻ ion in the aqueous supernatant fraction using the colorimetric mercury (II) thiocyanate method³² with NaCl as the standard. The range of sensitivity was 0.5-100 µg mL⁻¹ Cl⁻. For these tests the washing procedures in the preparation of the Bio-Pd used high purity distilled water to ensure a low background level of Cl⁻, and Analar grade reagents.

extracted into tetrahydrofuran at C-Tech Innovation to give a solution comprising 978 ppm PCBs (analysis H₂b, Capenhurst, UK). The final PCB concentration in the test (set up as for pentachlorobiphenyl) was 9.78 ppm; the arochlor extraction efficiency (not tested) was assumed to be the same for all arochlors.

Table 1 Chlorinated aromatic compounds used in this study

Short title	Systematic title	Nominal concentration
2-chlorophenol		5 mM
pentachlorophenol		5 mM
PCB# 28	2,4,4'- trichlorobiphenyl	0.31 mM
PCB# 52	2,2',5,5'-tetrachlorobiphenyl	0.27 mM
PCB# 101	2,2',4,5,5'-pentachlorobiphenyl	0.12 mM
PCB# 118	2,3',4,4',5'-pentachlorobiphenyl	0.12 mM
PCB# 138	2,2',3,4,4',5'-hexachlorobiphenyl	0.11 mM
PCB# 153	2,2',4,4',5,5'-hexachlorobiphenyl	0.11 mM
PCB# 180	2,2',3,4,4',5,5'- heptachlorobiphenyl	0.05 mM

RESULTS AND DISCUSSION

Deposition of Pd by *Desulfovibrio* spp. and *E. coli*

Examples of Pd-loaded cells of the *Desulfovibrio* and *E. coli* are shown in Fig. 1 a-c. Following nucleation of Pd(0) in the biosorption step the growing Pd clusters erupt through the outer membrane where they form outgrowing nanoparticles. Fig. 1 shows the locations of nano-Pd(0) deposits; their identity as Pd was confirmed using energy dispersive X-ray microanalysis and X-ray powder diffraction analyses as described by Deplanche et al.³³ with identical results for all preparations (not shown). The total loading of Pd(0) onto the cells was the same throughout, hence the pattern and size of Pd particles would reflect the distribution and cellular content of the hydrogenases. Given that *Desulfovibrio* has significantly more levels of hydrogenase than *E. coli*³⁴ and, hence more potential Pd-deposition sites, the same amount of Pd distributed around many sites should result in a greater number of smaller deposits, given that Pd removal proceeds to completion. Fig. 1 a,b confirms that Pd(0) deposition is widespread in *D. desulfuricans* and *D. vulgaris*, with small crystals deposited uniformly and no difference between the two *Desulfovibrio* strains but it is less widespread on *E. coli* cells (Fig. 1c), which show fewer, larger crystals at the same loading (Pd:biomass 1:3 by mass). Fig. 1 shows that (apart from the different hydrogenase activities of the two genera: above) the preparations also differed in that nearly all cells of *Desulfovibrio* participated in Pd(0) deposition (Fig. 1a,b) but only some *E. coli* cells did so (Fig 1c). The reason for this was not examined (e.g. this was possibly attributable to metal toxicity to the cells and/or hydrogenases) but for a given Pd(0) loading fewer participating cells would also result in fewer, larger crystals as seen in Fig 1c.

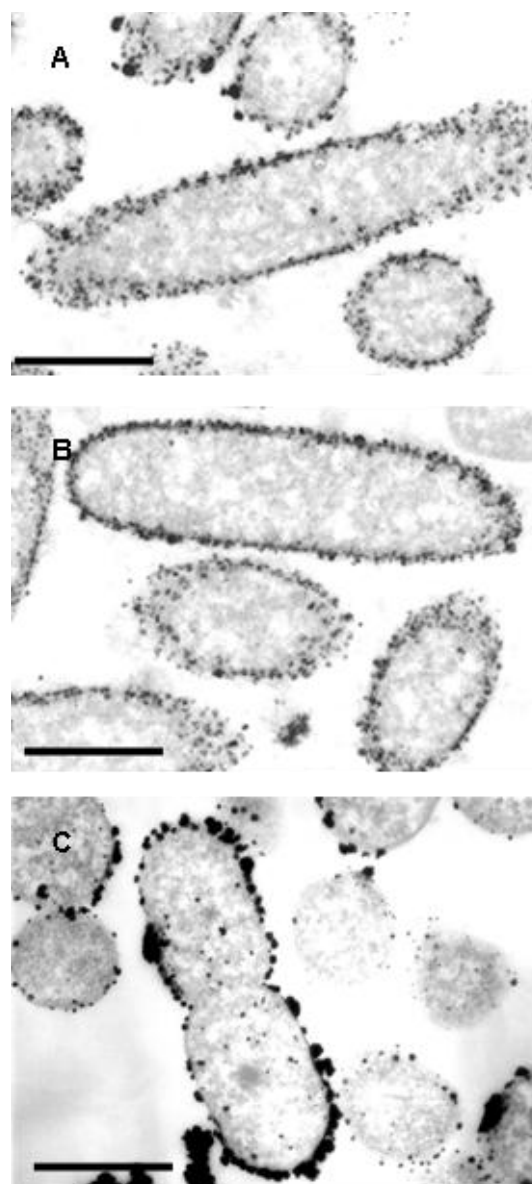


Fig. 1. Deposits of Pd(0) on the surface of *D. desulfuricans* (a), *D. vulgaris* (b) *E. coli* strain MC4100 (c). Cells were exposed to Pd(II) as described in Materials and Methods. The biomass: Pd ratio was 3:1 (see text). Bars are 1 μ m.

Table 2. Effect of Bio-Pd bacterial source on Cr(VI) reduction by Bio-Pd in batch suspensions of Bio-Pd.

Bacterial strain	Initial rate ^a of Cr(VI) reduction (nmol Cr(VI) reduced h ⁻¹ mg Bio-Pd ⁻¹)	
	Reduction in air	Reduction under OFN ^b
Bio-Pd(0) (<i>D. vulgaris</i>)	152 ± 7	175 ± 32
Bio-Pd(0) (<i>D. desulfuricans</i>)	166 ± 22	168 ± 15
Bio-Pd(0) (<i>E. coli</i> MC4100)	91 ± 15	115 ± 16

Bio-Pd samples (prepared as described in Materials and Methods and shown in Fig. 1) were challenged with 500 µM Cr(VI), 25 mM each of formate, acetate, and citrate, 20 mM MOPS/ NaOH, pH 7. Data are means ± SEM from 3 experiments.

^aInitial rates were taken over the first 1.5 h as gradients from linear regions of the appropriate graphs.

^bOFN = Oxygen Free Nitrogen

Catalytic activity of Bio-Pd made on surfaces of *Desulfovibrio* spp. and *E. coli*

To establish whether anaerobic conditions were required for catalytic activity of Bio-Pd once formed under H₂, preliminary Cr(VI) reduction tests were carried out in air with batch suspensions of Bio-Pd. This established that exposure to O₂ did not affect the catalytic activity (at P = 0.95; Table 2).

When Bio-Pd was immobilised in agar ~ 20% of the Cr(VI) was removed onto the Bio-Pd in suspensions using gel beads, attributable to absorption by the immobilisation matrix (no biological activity was present since the catalyst was dried and ground); little Cr(VI) was removed by Bio-Pd alone.

Further tests used flow-through reactors fixed at the flow rate giving 50% reduction of Cr(VI) by the best strain (Bio-Pd_{*D. desulfuricans*}), with the activities of the other Bio-Pds expressed relative to this (Fig. 2). Columns containing Bio-Pd_{*D. desulfuricans*} and Bio-Pd_{*D. vulgaris*} reduced Cr(VI) comparably (~50 % Cr(VI) reduction at 24 h, declining to 20% after 96h). Columns containing Bio-Pd_{*E. coli*} MC4100 reduced Cr(VI) poorly (10-15 % removal of Cr(VI) after 24 h). At 24 h (Fig. 2) the difference between Cr(VI) reduction by Bio-Pd_{*Desulfovibrio*} spp. and Bio-Pd_{*E. coli*} was ~3.5-fold.

Reductive dehalogenation tests against pentachlorobiphenyl, PCBs and transformer oil extract used Bio-Pd_{*D. desulfuricans*} since it was shown previously that this was more effective in reductive dehalogenation of PCBs than Bio-Pd_{*D. vulgaris*}.²⁶ The control was Pd(0) reduced chemically from solution under H₂ (Chem-Pd) which gave negligible chloride release from all compounds except 2-chlorophenol and 2,4,4' trichlorobiphenyl (Table 3). Pd-free bacteria gave no Cl⁻ release, confirming the stability of the dried cells with respect to chloride release in the hexane suspension. Table 3 shows that the

relative catalytic efficacy of the two Bio-Pds was dependent on the substrate used, e.g. for pentachlorophenol they gave a similar activity, whereas Bio-Pd_{*E. coli*} was ineffective against PCB# 52, PCB# 118, PCB# 138, PCB# 153 and PCB#180, with low activity seen against PCB# 28 and with no apparent relation to the degree or positioning of the chloride substituents (c.f. Table 1). For the compounds supporting Cl⁻ release by Bio-Pd_{*E. coli*} the median value for superiority of the Bio-Pd_{*D. desulfuricans*} was 3.5-fold (Table 3). The median takes into account the large range of comparative values. The transformer oil, being an average of several arochlors, is more representative of real samples and, similarly, Bio-Pd_{*D. desulfuricans*} was 3.5-fold higher than Bio-Pd_{*E. coli*} against the PCB mixture present in the used oil (Table 3).

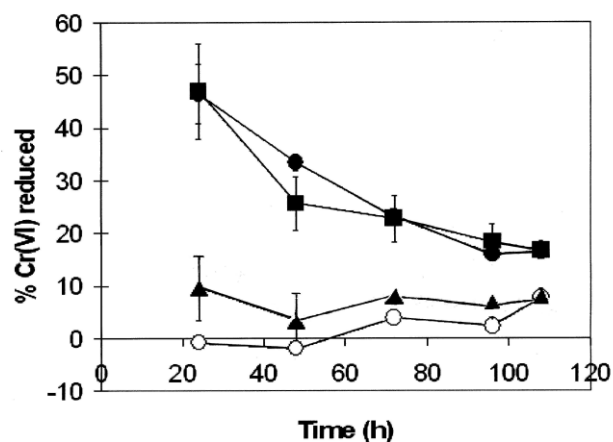


Fig. 2. Continuous Cr(VI) reduction by Bio-Pd immobilized in agar (loading 7.5 mg cm⁻³). Columns were challenged at a flow rate of 13.2 mL h⁻¹ with 500 µmol dm⁻³ sodium chromate in the presence of electron donor (see Materials and Methods). Bio-Pds were: ●, *D. vulgaris*; ■, *D. desulfuricans*; ▲, *E. coli* MC4100; ○ agar beads (no Bio-Pd). Error is ± SEM from 3 experiments. Where no errors are shown these were within the dimensions of the symbols.

Table 3 Release of chloride from chlorinated aromatic compounds by Bio-Pd_{D. desulfuricans} and Bio-Pd_{E. coli}

Compound	Chloride released ($\mu\text{g mL}^{-1}$)*			
	Chem-Pd(0)	Bio-Pd _{D. desulfuricans}	Bio-Pd _{E. coli}	
2-chlorophenol	5.9 ± 2.4 .	144.4 ± 11.2	47.2 ± 6.4	3.05
pentachlorophenol	0.2 ± 1.5	18.8 ± 6.4	13.6 ± 6.4	1.38
PCB# 28	2.8 ± 0.5	52.8 ± 10.8	2.8 ± 0.4	18.8
PCB# 52	0.2 ± 0.0	4.0 ± 0.4	NS	
PCB#101	0.02 ± 0	15.6 ± 4.0	4.4 ± 0.4	3.54
PCB#118	NS	17.2 ± 5.2	NS	
PCB# 138	NS	4.8 ± 0.4	NS	
PCB# 153	0.3 ± 0	10.4 ± 2.4	NS	
PCB# 180	0.2 ± 0	9.6 ± 3.2	NS	
Transformer oil extract	0.01 ± 0	5.6 ± 0.8	1.6 ± 0	3.5

Palladised cells were challenged with chlorinated aromatic compounds in hexane-in-water suspensions, with palladium loaded at 1:3 ratio to biomass. Data are means \pm SEM from 3 experiments using different Bio-Pd preparations. * Released chloride was determined after 1 h for 2-chlorophenol and pentachlorophenol and 24 h for the PCBs. NS: No significant chloride detected. Note that for the 2-chlorophenol, 2,2',4,5,5' pentachlorobiphenyl and the transformer oil extract the Bio-Pd_{D. desulfuricans} was 3-3.5 fold more effective than the Bio-Pd_{E. coli}

It is shown that Bio-Pd_{D. desulfuricans} promoted a 3-3.5-fold increase of Cl^- released as compared to Bio-Pd_{E. coli} for 2-chlorophenol, pentachlorobiphenyl and transformer oil extract (Table 3), i.e. the difference between them was similar to that seen in the Cr(VI) reduction test using immobilised cells (above). Taking the immobilised cell Cr(VI) tests and the PCB Cl^- release tests together, it is clear that Bio-Pd (at 1:3 ratio of Pd:biomass; 25% loading) made on *Desulfovibrio* gives a ~3.5-fold better Pd-catalyst than that made on *E. coli*. The electron microscopy data (Fig 1) suggested that, due to the smaller particle sizes, the surface area of the Bio-Pd_{D. desulfuricans} would be greater than that of Bio-Pd_{E. coli}.

Comparison of catalytic nanoparticles

The nanoparticle size of Bio-Pd_{D. desulfuricans} was calculated previously from magnetic measurements as 17.6 nm and 14.7 nm for two preparations.³⁵ A mean value of 16.15 nm was assumed. The Bio-Pd_{E. coli} was not sufficiently active magnetically to facilitate a similar analysis. Instead the chemisorption method was used, which gave an active particle diameter calculated for Bio-Pd_{E. coli} as 30.04 nm (metallic surface area was $4.15 \text{ m}^2/\text{g Pd}$). Assuming that the surface area of a sphere is $4\pi r^2$ the corresponding particle surface areas were calculated as 2835.3 and 819.5 nm^2 respectively, i.e.

the estimated surface area was 3.5-fold greater for the Bio-Pd(0)_{D. desulfuricans} which is in agreement with the difference in catalytic activities (above). It can therefore be deduced that the catalytic activity is related to the surface area but this is not the only factor involved; other studies have shown that by removal of specific hydrogenases the catalytic activity of Bio-Pd can be manipulated in both *E. coli*³³ and *Desulfovibrio fructosovorans*,³⁶ in the latter case the most highly active Bio-Pd catalyst was located on the inner membrane with few if any discrete nanoparticles visible.³⁷

Future prospects: potential applications of Bio-Pd(0) to industrial wastes and decontamination

The use of a Pd-based catalyst for treatment of environmental contaminants (e.g. by doping of Fe-catalyst as suggested by Korte et al.^{21,22} would appear economically unattractive. However, a 'dirty' catalyst can be used, bypassing the costs of precious metal refining and using biorecycled scrap for this purpose. Bacteria biorecovered precious metals from processing wastes,³⁸ spent automotive catalyst leachates^{20,39} and electronic scrap⁴⁰ and biorecovered material was catalytically active.^{15,41} Taking into account the costs of landfilling wastes and the high costs associated with hazardous waste disposal, the economic feasibility of this approach becomes apparent. The use of spent biomass from

other processes as nanocatalyst support (e.g. ^{28,42}) would also mitigate against the costs of biomass waste disposal and hence the overall cost. Although the release of chloride from used transformer oil was limited in this study further investigations would be justified as a potential clean route to oil recovery for re-use, given the rapidly rising price of crude oil.

Acknowledgements

We acknowledge the support of the EPSRC and BBSRC (grants GR/NO8445/01, GR/S4262/01, EPD05768X/1, BB/C516128/1, BB/E003788/1 and E19998) and the Royal Society (Industrial Fellowship to LEM). ACH and MDR were supported by studentships from EPSRC and BBSRC respectively.

References

- 1 Lyytikäinen M, Sormunen A, Peraniemi S and Kukkonen JVK, Environmental fate and bioavailability of wood preservatives in freshwater sediments near an old sawmill site. *Chemosphere* **44**:341-350 (2001).
- 2 Anon. NPL Site narrative for St.Regis Paper Co. U.S.Environmental Protection Agency National Priorities List. <http://www.epa.gov.superfund/sites/npl/nar650.htm> (2006).
- 3 Korngold E, Belayev N and Aronov L, Removal of chromates from drinking water by anion exchangers. *Sep Purif Technol* **33**:179-187 (2003).
- 4 Wang YT, Microbial reduction of chromate. In: Lovley D (ed) *Environmental Microbe-metal Interactions* ASM Press Washington DC, pp 225-235 (2000)
- 5 Wang PC, Mori T, Komori K, Sasatsu M, Toda K and Ohtake H, Isolation and characterization of an *Enterobacter cloacae* strain that reduces hexavalent chromium under anaerobic conditions. *Appl Environ Microbiol* **55**:1665-1669 (1989).
- 6 Ishibashi Y, Cervantes C and Silver S, Chromium reduction in *Pseudomonas putida*. *Appl Environ Microbiol* **56**:2268-2270 (1990).
- 7 Llovera S, Bonet R, Simonpujol MD and Congregado F, Chromate reduction by resting cells of *Agrobacterium radiobacter* EPS 916. *Appl Environ Microbiol* **59**:3516-3518 (1993).
- 8 Shen H and Wang YT, Simultaneous chromium reduction and phenol degradation in a coculture of *Escherichia coli* ATCC 33456 and *Pseudomonas putida* DMP-1. *Appl Environ Microbiol* **61**:2754-2758 (1995).
- 9 Bae W, Kang T, Jung J, Park C, Choi S and Jeong BC, Purification and characterization of NADH-dependent Cr(VI) reductase from *Escherichia coli* ATCC 33456. *J Microbiol Biotechnol* **10**:580-586 (2000).
- 10 Guha H, Jayachandran K and Maurrasse F, Kinetics of chromium (VI) reduction by a type strain *Shewanella alga* under different growth conditions. *Environ Pollut* **115**:209-218 (2001).
- 11 Lovley DR and Phillips EJP, Reduction of chromate by *Desulfovibrio vulgaris* and its c₃ cytochrome. *Appl Environ Microbiol* **60**:726-728 (1994).
- 12 Mabbett AN, Loyd JR and Macaskie LE, Effect of complexing agents on reduction of Cr(VI) by *Desulfovibrio vulgaris* ATCC 29579. *Biotechnol Bioeng* **79**:389-397 (2002).
- 13 Lloyd JR, Mabbett AN, Williams DR and Macaskie LE, Metal reduction by sulphate-reducing bacteria: physiological diversity and metal specificity. *Hydrometallurgy* **59**:327-337. (2001).
- 14 Macaskie LE, Mikheenko IP, Deplanche K, Murray AJ, Paterson-Beedle M, Coker VS, Pearce CI, Patrick RAD, Vaughan D, Van der Laan G and Lloyd JR Today's wastes tomorrow's materials for environmental protection in *Comprehensive Biotechnology* Eds M. Moo-Young, M. Butler, C. Webb, A. Moreira, B. Grodzinski, Z.F. Cui, S. Agathos 2nd Edition Vol 6 pp 719-725; Elsevier Amsterdam ISBN 978-0-444-53353-4. (2011).
- 15 Deplanche K, Murray AJ, Mennan C, Taylor S and Macaskie LE, Biorecycling of precious metals and rare earth elements In *Nanomaterials* Ed M.M. Rahman pp 279-314 InTech Publications ISBN 978-953-307-913-4, (2011).
- 16 Philp JC, Bamforth SM, Singleton I and Atlas RM, Environmental Pollution and Restoration: a role for bioremediation. In: Atlas RM, Philp JC (eds) *Bioremediation: Applied Microbial Solutions for Real World Environmental Cleanup*. ASM Press, Washington DC, pp 1-48 (2005).
- 17 Bedard DL, Polychlorinated biphenyls in aquatic sediments: environmental fate and outlook for biological treatment. In: Haggblom MM, Bossert I (eds) *Dehalogenation: Microbial Processes and Environmental Applications*, Kluwer Press, pp 443-465 (2003).

- 18 Wiegel J and Wu Q, Microbial reductive dehalogenation of polychlorinated biphenyls. *FEMS Microbial Ecology* **32**:1-15 (2000).
- 19 Harrad S, Robson M, Hazrati S, Baxter-Plant VS, Deplanche K, Redwood MD and Macaskie LE, Dehalogenation of polychlorinated biphenyls and polybrominated diphenyl ethers using a hybrid bioinorganic catalyst. *J Environ Monit* **9**:314-318 (2007).
- 20 Deplanche K, Snape TJ, Hazrati S, Harrad S and Macaskie LE, Versatility of a new bioinorganic catalyst: palladized cells of *Desulfovibrio desulfuricans* and application to dehalogenation of flame retardant materials. *Environ Technol* **30**:681-692 (2009).
- 21 Korte N, Lang L, Muftikan R, Grittini C and Fernando Q, Palladised iron utilised for ground water purification. *Platinum Metals Review* **41**:2-7 (1997).
- 22 Korte NE, West OR, Lian L, Gu B, Zutman JL and Fernand Q, The Effect of solvent concentration on the use of palladized-iron for the step-wise dechlorination of polychlorinated biphenyls in soil extracts. *Waste Management* **22**:343-349 (2002).
- 23 Smidt H and de Vos WM, Anaerobic microbial dehalogenation. *Ann Rev Microbiol* **58**:43-73 (2005).
- 24 Mabbett AN, Yong P, Farr JPG and Macaskie LE, Reduction of Cr(VI) by palladized biomass of *Desulfovibrio desulfuricans* ATCC 29577. *Biotechnol Bioeng* **87**:104-109 (2004).
- 25 Mabbett AN, Sanyahumbi D, Yong P and Macaskie LE, Biorecovered precious metals from industrial wastes: single step conversion of mixed metal liquid waste to bioinorganic catalyst ("MMBio-Pd(0)") with Environmental Application. *Environ Sci Technol* **40**:1015-1021 (2006).
- 26 Baxter-Plant VS, Mikheenko IP and Macaskie LE Sulphate-reducing bacteria, palladium and the reductive dehalogenation of chlorinated aromatic compounds. *Biodegradation* **14**:83-90 (2003).
- 27 Nishimura S, *Handbook of Heterogeneous Catalytic Hydrogenation for Organic Synthesis*. John Wiley & Sons, New York, (2001)
- 28 Orozco R, Redwood MD, Yong P, Caldelari I, Sargent F and Macaskie LE, Towards an integrated system for bio-energy: Hydrogen production by *Escherichia coli* and use of palladium-coated waste cells for electricity generation in a fuel cell. *Biotechnol Lett* **32**: 1837-1845 (2010).
- 29 Lloyd JR, Thomas GH, Finlay JA, Cole JA and Macaskie LE Microbial reduction of technetium by *Escherichia coli* and *Desulfovibrio desulfuricans*: Enhancement via the use of high-activity strains and effect of process parameters. *Biotechnol Bioeng* **66**:122-130 (1999).
- 30 Mikheenko IP Nanoscale palladium recovery. *Ph.D Thesis*. The University of Birmingham, UK (2004).
- 31 Humphries AC, Mikheenko IP and Macaskie LE, Chromate reduction by immobilized palladized sulfate-reducing bacteria. *Biotechnol Bioeng* **94**:81-90 (2006).
- 32 Jeffrey GH, Bassett J, Mendham J and Denny RC, *Vogels Textbook of Quantitative chemical analysis, 5th edn*. Bath Press, Avon, UK (1989)
- 33 Deplanche K, Caldelari I, Sargent F and Macaskie LE, Involvement of hydrogenases in the formation of highly catalytic Pd(0) nanoparticles by bioreduction of Pd(II) using *Escherichia coli* strains. *Microbiology* **156**: 2630-2640 (2010).
- 34 Lloyd JR, Thomas GH, Finlay JA, Cole JA and Macaskie LE, Microbial reduction of technetium by *Escherichia coli* and *Desulfovibrio desulfuricans*: Enhancement via the use of high-activity strains and effect of process parameters. *Biotechnol Bioeng* **66**:122-130 (1999).
- 35 Mikheenko IP, Mikheenko PM, Darlington CNW, Muirhead CM and Macaskie LE, Magnetic testing of Pd-loaded bacteria. In *Biohydrometallurgy: Fundamentals, Technology and Sustainable Development* V.S.T. Ciminelli and O. Garcia Jr. (eds) Elsevier, Amsterdam, ISBN 0444 50623 3 pp 525-532 (2001).
- 36 Rousset ML, Casalot P, de Philip A, Bélaich I, Mikheenko I and Macaskie LE, Use of bacterium strains for the preparation of metallic biocatalysts, in particular for the preparation of palladium biocatalysts. European Patent Application Number: WO/2006/087334. International Application No.: PCT/EP2006/05094 (2006).
- 37 Mikheenko IP, Rousset M, Dementin S and Macaskie LE, Bioaccumulation of palladium by *Desulfovibrio fructosovorans* and hydrogenase deficient mutants *Appl Environ Microbiol* **19**: 6144-6146 (2008).

- 38 Yong P, Rowson NA, Farr JPG, Harris IR and Macaskie LE, Bioreduction and biocrystallization of palladium by *Desulfovibrio desulfuricans* NCIMB 8307. *Biotechnol Bioeng* **80**:369-379 (2002).
- 39 Yong P, Rowson NA, Farr JPG, Harris IR and Macaskie LE, A novel electrobiotechnology for the recovery of precious metals from spent automotive catalysts. *Environ Technol* **24**:289-297 (2003).
- 40 Creamer NJ, Baxter-Plant VS, Henderson J, Potter M and Macaskie LE, Palladium and gold removal and recovery from precious metal solutions and electronic scrap leachates by *Desulfovibrio desulfuricans*. *Biotechnol Lett* **28**: 1475-1484 (2006).
- 41 Murray AJ, Mikheenko IP, Goralska E, Rowson NA and Macaskie LE (2007) Biorecovery of platinum group metals from secondary sources *Adv Mats Res* **20-21**:651-654.
- 42 Dimitriadis S, Nomikou N and McHale AP, Pt-based electrocatalytic materials derived from biosorption processes and their exploitation in fuel cell technology. *Biotechnol Lett* **29**:545-551 (2007).