

Cement-Bentonite in comparison with other Cemented Materials

Alzayani, Nuha Jamal; Royal, Alexander; Ghataora, Gurmel; Jefferson, Ian

DOI:

[10.1680/jenge.14.00050](https://doi.org/10.1680/jenge.14.00050)

License:

None: All rights reserved

Document Version

Peer reviewed version

Citation for published version (Harvard):

Alzayani, NJ, Royal, A, Ghataora, G & Jefferson, I 2016, 'Cement-Bentonite in comparison with other Cemented Materials', *Environmental Geotechnics*. <https://doi.org/10.1680/jenge.14.00050>

[Link to publication on Research at Birmingham portal](#)

Publisher Rights Statement:

Eligibility for repository: Checked on 9/3/2016

General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact UBIRA@lists.bham.ac.uk providing details and we will remove access to the work immediately and investigate.

Cement-Bentonite in Comparison with other Cemented MaterialsAlzayani NJ¹, Royal ACD², Ghataora GS³, Jefferson I⁴

¹ MSc, DIC, BSc. Doctoral Research student, School of Civil Engineering, University of Birmingham, UK., Email: AXN325@student.bham.ac.uk

² MEng, PhD. Lecturer in Geotechnical Engineering, School of Civil Engineering, University of Birmingham, UK, Email: a.c.royal@bham.ac.uk

³ BEng, PhD, MIMM, MILT. Senior lecturer in Geotechnical Engineering, School of Civil Engineering, University of Birmingham, UK, Email: ghataogs@bham.ac.uk

⁴ BEng, DIS, PhD, FGS. Professor of Geotechnical Engineering, School of Civil Engineering, University of Birmingham, UK, Email: i.jefferson@bham.ac.uk

Abstract

The deformation behaviour of cement-bentonite (CB) materials used in low permeability cut-off walls is critical to the performance of these barriers *in situ*. Whilst a number of investigations have focused on the deformation behaviour of CB materials, it is suggested that insufficient knowledge has been generated to allow for the determination of the behaviour of a CB wall *in situ* with confidence. This paper reviews the deformation behaviour of other cemented particulate systems commonly encountered in civil engineering: concrete, rock, clays and cemented soils, and compares them with CB response to determine if the greater research effort associated with these materials could be used to improve understanding of CB. It is concluded a direct comparison of physical behaviour between these materials is problematic due to the differences observed. Furthermore, the formation of microcracks prior to reaching the peak strength in cemented materials (rocks, etc.) is

an area that does not appear to have been studied previously with CB materials; yet microcrack formation could have a significant detrimental impact on the ability of a CB barrier to retard groundwater migration. Therefore, additional research is required into CB behaviour, prior to achievement of the peak strength, to determine if microcracking in CB is a significant hazard.

Keywords: Geoenvironment; Geomaterial Characterization; Waste Containment and Disposal System

1 Introduction

Cement-Bentonite (CB) cut-off walls are low permeability barriers that are used in geotechnical engineering to contain contamination plumes and control groundwater flow in engineering structures (such as dams and levees). Cement-bentonite (CB) slurry cut-off walls were initially developed in the 1970s, arising from the slurry trench cut-off walls (soil-bentonite) used in construction projects since the 1940s (Jefferis, 1997) (with soil-bentonite barriers being installed in earth dams from the mid-1960s, US EPA, 1984). The major perceived advantages of CB are (when compared with most other remedial cut-off walls used in environmental projects; Manassero et al., 1995): the self-supporting nature of the barrier; the relative uniformity of the mixture; the cost effectiveness of the technique; and the low hydraulic conductivity. The thixotropic nature of the dispersed bentonite provides the newly installed slurry wall with the ability to resist ground movements and prevent segregation of the constitutive materials as the initial stages of curing take place; over time the cementitious materials cure to form the hardened barrier.

Garvin and Hayles (1999) state that a typical CB mixture would comprise water, bentonite (30 g to 60 g per litre of water), cement (100 g to 350 g per litre of water), and cement replacement

materials (Pulverised Fuel Ash, PFA, or Ground Granulated Blast furnace Slag, GGBS, at 52
replacement levels up to 30 % and 80 % respectively) in order to achieve the low hydraulic 53
conductivities required (ICE, 1999, specifies hydraulic conductivity of 1×10^{-9} m/s or lower); 54
although mixtures outside these stated proportions can still result in the desired physical properties. 55

56
It could be argued that as the primary function of these barriers is to retard the movement of 57
groundwater, and not to transmit load, then the deformation response of these barriers is not of 58
paramount importance. Whilst the authors accept that these barriers must achieve the hydraulic 59
conductivity performance criteria in order to meet the engineering need, it is difficult to justify that 60
these barriers will not experience changes in loading conditions throughout their engineering lives; 61
such changes could have a detrimental effect upon the performance of the barrier. For example, if a 62
CB barrier is installed on a site that is being remediated and redeveloped then changes in loading 63
conditions acting on the barrier could conceivably take place relatively quickly after installation due 64
to subsequent construction activities associated with redevelopment. Therefore, it is suggested that 65
the deformation response of these barriers must be well understood, and consideration of potential 66
changes in loading on a barrier should be undertaken during the design stages, to ensure that these 67
CB barriers are a sustainable engineering solution. 68

69
Whilst there has been a significant research effort into the behaviour of cements and clays, there 70
appears to have been comparatively little research undertaken on combined cement-clay behaviour 71
(Jefferis, 2012), resulting in a comparative lack of understanding of the behaviour of these systems. 72
However, as considerable research has been undertaken in investigating other cemented materials, 73
perhaps knowledge arising from this research could be applied directly to the behaviour of CB. 74
Therefore, this paper reviews and highlights similarities and differences in stress-strain behaviour of 75

CB materials (particularly pre-peak to peak response to deformation) with various examples of the following materials: concrete, sedimentary rocks, clay soils and cemented soils.

2 Need for Improved Understanding of CB Deformation Behaviour

Previous research illustrates that CB slurry walls have variable physico-chemical and mechanical properties (Deschênes et al., 1995; Manassero et al., 1995; Philip, 2001; Opdyke and Evans, 2005; Joshi, 2009; Williams and Ghataora, 2011; Jefferis, 2012; Royal et al., 2013; and Soga et al., 2013). Furthermore, the combination of small proportions of high-swelling bentonite with cementitious materials results in some 'unusual' behaviour. CBs exhibit various types of failure when deformed: brittle, ductile and strain-hardening deformation response, resulting in failure via shear or tension (Manassero et al., 1995; Joshi, 2009; Jefferis, 2012; Royal et al., 2013; and Soga et al., 2013). Models have been proposed (Manassero et al., 1995; and Joshi, 2009) to describe deformational behaviour of CB (based on observed behaviour for specific CB mixtures investigated by the researchers). However, there would appear to be variations in the behaviour predicted by these models and it is suggested that deformation behaviour of other CB mixtures should be considered to improve understanding and refine the models.

2.1 Uncertainty Regarding the Required Testing Methodologies to Determine Representative Deformation Response

Manassero et al. (1995) state that specifications of mechanical properties of CB material do not often provide detailed introduction about the required tests to be conducted to check whether the requirements of minimum shear strength and maximum allowable strain without cracking are achieved: i.e. drained/undrained loading conditions, magnitude of confining stresses for triaxial tests, and rate of strain for unconfined compression strength (UCS) tests, etc. These parameters

fundamentally affect the observed failure mechanisms exhibited by the CB (Section 3) and thus 100
must be chosen carefully to reflect the loading environment that cured barrier is likely to experience 101
in-situ if the suitability of the CB mixture is to be validated. Jefferis (2012) states that UCS is 102
typically used as quality control check for CB material, while occasionally confined drained triaxial 103
tests are specified to help in identifying the *in-situ* behaviour of the material. However, UCS is, at 104
best, an indicative test rather than an authoritative means of determining shear strength. 105
Furthermore, as CBs have very low hydraulic conductivities, it is uncertain under what conditions 106
drained deformation behaviour should be considered to be applicable when CBs appear to be 107
weaker in undrained conditions (and therefore more likely to fail before drained conditions are 108
established). 109

3 Variations in CB Stress-Strain Behaviour 111

The deformation characteristics of CB are a function of: the constitutive materials and their 112
respective quantities (Jefferis, 1981; and Fratolocchi and Pasqualini, 2007); the curing age (Plee et 113
al., 1990; Deschênes et al., 1995; and Soga et al., 2013); and the environmental conditions, i.e. the 114
nature of surrounding soil and groundwater (Joshi et al., 2010; and Soga et al., 2013), which 115
influence the volume changes of slurry prior to hardening (due to filtration, bleed, and syneresis) 116
(Jefferis, 2012). In addition, the deformation characteristics of CB barriers also depend on: the 117
confining stress acting upon the newly installed and cured barrier (Manassero et al., 1995; Joshi, 118
2009; and Soga et al., 2013); chemical interactions between barrier and contamination (Garvin and 119
Hayles, 1999; Philip, 2001; Jefferis, 2012; Fratolocchi et al., 2013; and Soga et al., 2013); and 120
loading drainage conditions (Manassero et al., 1995; Joshi, 2009; and Soga et al., 2013). 121

Stress-strain and shear strength behaviour of CB materials have been investigated in a number of 123
laboratory based studies, including: Deschênes et al. (1995), Manassero et al.(1995), Philip (2001), 124

Opdyke and Evans (2005), Fratolocchi and Pasqualini (2007), Joshi (2009), Williams and Ghataora (2011), Royal et al. (2013), Soga et al.(2013) and Royal et al. (under review). The results, summarised in Figures 1 to 5, revealed broad variation in the stress-strain behaviour and shear strength with constitutive components within the CB mixtures, duration of curing, confinement and loading conditions, although these results appear to broadly support the fundamental aspects of the available models.

3.1 Constitutive Materials and Duration of Curing on the Deformation Response of the CB

The range in physical properties exhibited by the different CB mixtures described within the introduction is considerable. The type and quantities of bentonite, cement or cement-replacement materials used within the CB mixture have a significant impact upon its deformation response. In addition the duration of curing also has a significant impact upon the strength of the CB (over the first 90 days of curing, after this point the rate of change in strength with time diminishes considerably).

Royal et al. (2013) observed stress-strain behaviour for three CB mixtures containing PFA (minimum of 28 % PFA as cement replacement) in UCS and unconsolidated, undrained triaxial (TXUU) tests, and found that the mean UCS were generally lower than the ICE (1999) specification's recommendations for minimum strength (100 kPa), Figure 1 (which presents results for the strongest of the three mixtures investigated). The results in Figure 1 also show unexpected decrease in strength from 60 days to 90 days of curing, which is not considered to be indicative of the material deformation response with curing but more likely due to the natural variation of material batched from slurry. Royal et al. (2013) noted that samples containing PFA at 14 days of curing or less generally failed through development of an inclined shear plane, and rarely through propagation of vertical tension cracks, whereas those cured for 28 days or more failed through

shearing of a 'cone' or 'wedge' that developed at the base of the loading cap with associated development of longitudinal tension cracks.

In contrast, CB containing GGBS were far stronger than those containing PFA. Soga et al. (2013) conducted UCS testing (unconfined compression strength tests give the ultimate strength at failure under compressive loading) with CB, containing GGBS (80.1% cement replacement) and obtained mean UCS as of approximately 360 kPa and 890 kPa at 28 days and 90 days respectively. Williams and Ghataora (2011) encountered similar findings (CB samples containing 80% GGBS as cement replacement investigated using TXUU, at confining pressure of 60 kPa (Figure 2) and 120 kPa, and UCS) to Soga et al., (2013). Fratolocchi and Pasqualini (2007) investigated a CB material (using a blended cement containing between 66 % to 80 % GGBS) using TXUU and TXCU (consolidated, undrained triaxial) and observed that the mixture exhibited significant increase in shear strength with curing on both types of test and the material was sensitive to the magnitude of the confining pressure in TXCU tests (more so within the first month of curing).

Royal et al. (under review) tested samples containing GGBS (80 % cement replacement, although the amount of bentonite and total cementitious material was the same as those with PFA) and found mean UCS values of approximately 260 kPa and 405 kPa for 28 days and 90 days respectively. The samples tested on UCS predominantly failed via cone and tensile cracking, with shear failure observed in samples cured for seven days (and a minority of samples at 14 days). Beads of water were observed to form on the surface of samples cured for 14 days or less, during deformation of the samples, these would flow down and pool at the base; this was not observed in samples cured for 28 days or longer.

The outcomes of these studies illustrate the differences in CB behaviour in UCS/triaxial tests with respect to variation of mixture design and particularly cement replacement materials; PFA appears to result in low compressive strengths and this supports the statement, by Jefferis (2012), that PFA should be included in addition to the cement (to improve resistance to chemical degradation) rather than act as a replacement material. The effect of mix design variation can be seen through the difference in UCS between mix design adopted by Royal et al (2013) (Figure 1) and Deschênes et al. (1995) (Figure 3). Deschênes et al. (1995) mixture did not contain any cement replacement material, and this has dramatically increased the UCS achieved in 7 days comparative to mixes which contains PFA as a cement replacement. Conversely, CB containing GGBS would appear to result in more rapid strength gain and stronger materials with curing than for mixtures containing a similar proportion of cement or cement-PFA.

3.2 Impact of Confining Pressure on Deformation Behaviour

Manassero et al. (1995) undertook triaxial testing (UU, CU, and Consolidated Drained, CD) on CB samples containing 60% GGBS as cement replacement at curing ages of 5 to 7 months, and observed that the failure mechanism varied with confinement and drainage conditions (Figure 4). Manassero et al. (1995) observed that under CU conditions the samples were brittle and developed tension cracks at low confining pressures (lower than 100 kPa effective confinement) and were brittle but developed shear planes at higher confining pressures (greater than 400 kPa effective confinement). Under CD conditions the samples failed via brittle-hardening (shear failure) at low confining pressures (less than or equal 100 kPa effective confinement) and ductile-hardening (uniform contractive failure) at higher confining pressures (greater than or equal 400 kPa effective confinement).

Deschênes et al. (1995) and Soga et al. (2013) encountered similar behaviour. Deschênes et al. (1995) observed that strain at failure in TXCD tests could exceed 8%, whereas a range of strains, 0.8 % to 1.3 % (depending on duration of curing), was encountered on the UCS (Figure 3 and Figure 4). Soga et al. (2013) noted that samples consolidated at 100 kPa (effective confinement); which was below compression yield stress of the mixture (300 kPa to 320 kPa; Joshi, 2009), exhibited ductile behaviour in drained conditions (drained strength at 660 kPa to 850 kPa, and peak axial strain at 5 % to 10 %); while samples consolidated above the compression yield stress (at 500 kPa effective confinement) exhibited strain-hardening and did not fail. This is shown in stress-strain behaviour of 'mixer cast' samples (containing 80.1% GGBS as cement replacement) in drained triaxial tests at 35 days and 90 days in Figure 5.

Soga et al. (2013) also observed that the failure pattern (UCS) for many samples was via tension cracking and were brittle (occasionally samples had inclined cracks); this is similar to failure patterns observed by Royal et al. (2013). Therefore, as confining pressures approaches zero, the triaxial conditions will be similar to UCS conditions. The undrained strength determined by Soga et al. (2013) varies from 535 kPa to 745 kPa at axial strain ranging from between 0.5 % and 2 %. Opdyke and Evans (2005) investigated a CB containing 15 % cementitious materials (air entraining cement with 75 % GGBS replacement) and noted that the majority of samples tested on the UCS failed by an inclined shear plane. The samples investigated were stronger than those investigated by Royal et al. (under review) but had a significantly lower preconsolidation pressure (100 kPa to 200 kPa as opposed to approximately 800 kPa at 90 days, respectively).

Both Manassero et al. (1995) and Soga et al. (2013) suggest that transformation in failure mechanisms observed in TXUU, TXCU and TXCD tests are a result of restructuring (collapse) of the fabric of CB samples when the compression yield stress (preconsolidation pressure) is exceeded

by the effective confining pressure (it is presumed that this explains the early strength behaviour 223
under the greater confining pressures for TXCU testing by Fratolocchi and Pasqualini, 2007). This 224
restructuring is dependent on the effective confining pressure, the preconsolidation pressure (which 225
will increase during the early stages of curing), and type of admixture/cement replacement material 226
used. 227

Manassero et al., (1995) developed a ‘tentative’ conceptual elasto-plastic-work hardening model 229
(based on the outcome of experimental study) which categorised the stress-strain behaviour of a 230
specific mix CB into four zones: brittle-softening, brittle-hardening, ductile-softening, and ductile- 231
hardening. Subsequent experimental investigations undertaken by additional researchers appear to 232
support this model. However, the model compares deviatoric stress and void ratio with isotropic 233
effective stress and the range of void ratios considered does not appear to represent the materials 234
encountered by Opdyke and Evans (2005) or Royal et al., (under review), suggesting additional 235
research is require to determine if the model is valid for additional other CB mixtures. 236

3.3 Impact of Undrained and Drained Conditions under Low Effective Confining Pressures (200 238 kPa or less) on Deformation Behaviour of CB 239

Results of triaxial testing undertaken by Philip (2001) imply that the stress-strain behaviour for 240
drained (effective stress) triaxial loading is more sensitive to confining stress variation than for 241
undrained (total stress) triaxial loading; due to the eliminated pore water pressure in drained triaxial 242
tests. This is confirmed by Fratolocchi and Pasqualini (2007), Royal et al. (2013), and Soga et al. 243
(2013) who also observed that undrained strength does not vary (generally) with variation of 244
confining pressure for CB material cured for 90 days or more. 245

246

Comparison of the range of peak strengths and corresponding strains at failure for drained and undrained conditions indicates that under drained conditions the material is stronger. The practical implication being that short term response to ‘rapid’ loading, i.e. in undrained conditions, may result in brittle failure with inducement of cracking within the barrier, hence risking the main function of CB slurry wall: a low permeability structure. Philip (2001) states the maximum effective confining pressure is expected in field to be around 200 kPa (for shallow barriers), and from the trends illustrated in Figures 2 to 5, the low confining pressure is likely to be a dominant factor in material response to deformation. Hence, even if drained conditions were to prevail, strain-hardening may not occur. This is supported by Manassero et al.’s (1995) model which suggests at low confining pressures (up to 200 kPa), brittle-softening is the likely deformation response.

The brittle deformation response under low confinement, is likely to be accompanied with the development of cracking in the material. Royal et al. (2013) observed tension cracks develop and widen well before the peak stresses were achieved on the UCS. If cracks develop within the CB fabric before the cemented products shear, then the implications this has on the hydraulic conductivity of the barrier are not clear. It is possible that these barriers could achieve the stated strength parameter (implemented to ensure the barrier is both self-supporting and able to resist ground deformations) yet be compromised due to an increase in hydraulic conductivity with response to loading post hardening. Such an occurrence clearly is to be avoided if the barrier is to be a resilient design solution. Microcracking in other cemented structures has been studied previously and observed to happen in rocks (as discussed in section 5).

4 Comparison of CB with Concrete Deformation Behaviour

Concrete might not be an obvious material to directly compare to CB, due to differences in water-cement ratios, inclusion of well graded aggregates, etc., although there is (albeit) limited

commonality in overall stress-strain response and failure mechanisms between the two materials. 272
The general behaviour of concrete depends mainly on the mix design and water/cement ratio, which 273
results in a variation of strength. The mechanical properties of concrete are influenced by: the 274
water-cement ratio, the degree of compaction, properties of cement paste, and the type and grading 275
of the aggregates (Neville, 1995; Khandelwal and Ranjith, 2013). 276

277

4.1 Brittle and Ductile Behaviour of Concrete 278

Concrete is commonly assumed to be brittle and this behaviour has been observed using both UCS 279
and triaxial tests. Neville (1995) proposed that the greater the compressive strength, the lower the 280
strain at failure (Table 1). Concrete can exhibit plastic behaviour through fracturing at relatively 281
low strains (0.1 % to 0.5 %, Neville, 1995), thus the strain at failure of CB is approximately one 282
order of magnitude higher than strain of failure of concrete. In addition, the higher the rate of 283
deformation applied, the higher compressive strength achieved (Figure 6). At zero, or low confining 284
pressures, concrete shows typical brittle failure mode followed by strain-softening behaviour 285
(Dragon and Mróz, 1976; Neville, 1995; Kang et al., 2000; Jafarzadeh and Mousavi, 2012; and 286
Khandelwal and Ranjith, 2013). 287

288

The application of increasing confining pressures can result in transformation of the stress-strain 289
behaviour from brittle to ductile. Neville (1995) states that, concrete exhibits two failure 290
mechanisms in unconfined compression: firstly, concretes tend to exhibit tensile failure 291
perpendicular to the direction of acting load, secondly, concretes exhibits shear failure through 292
propagation of inclined shear planes. This is in keeping with observed behaviour to CB, although 293
the concrete's peak strength tends to be significantly greater and strain at failure smaller than CB. 294
Conversely, Neville (1995) observes that concrete tends to fail by crushing in triaxial compression; 295
the authors are not aware of this failure mechanisms being observed with CB. Compression 296

crushing is exhibited by extremely stiff cemented materials such as rocks and concrete. The reported outcomes of research into CB deformation behaviour have not mentioned such a mechanism being observed in UCS or triaxial tests (Manassero et al., 1995; Joshi, 2009; Jefferis, 2012; Royal et al., 2013; and Soga et al., 2013).

4.2 Plastic Concrete

Inclusion of bentonite slurry within concrete mixes creates ‘plastic concrete’, an alternative low permeability cut-off wall material to CB. The addition of the bentonite results in a comparative increase in ductility; peak strength mobilization at strains from 0.4 % to 0.9 % was reported by: Mahboubi and Ajorloo (2005), Hinchberger et al. (2010), and Jafarzadeh and Mousavi (2012), which is considered to be slightly greater than for normal concretes, and the material achieves the low hydraulic conductivities required for cut-off walls.

Mahboubi and Ajorloo (2005), Hinchberger et al. (2010), and Jafarzadeh and Mousavi (2012) conducted UCS and consolidated drained triaxial tests (TXCD) on plastic concrete mixtures (at varying ages, water-cement ratios, and bentonite contents), Figure 7. The stress-strain relationships of plastic concrete show that increasing the age and the effective confining pressure from zero, in unconfined testing, to 800 kPa in drained triaxial testing resulted in increasing compressive strength and corresponding strain at failure. Furthermore, the behaviour changed from brittle strain-softening to become ductile, and the failure modes of plastic concrete change from tensile to shear as confining pressure is increased (Figure 8). This is similar to the pre-peak behaviour of CB materials with GGBS in certain circumstances (i.e. under effective confining pressures less than 500 kPa), but is not an ideal comparison as CB experiences strain-hardening in drained conditions and also appears to experience greater strains at failure (for lower peak strengths).

5 Comparison of CB with Sedimentary Rock Deformation Behaviour 322

Certain types of sedimentary rocks could be considered analogous to both concrete and CB, for 323
example sedimentary rocks can experience changing deformation characteristics with confinement 324
similar to CB. Jones et al. (1984), and Clayton and Mathews (1987) investigated various chalks, 325
Nygard et al. (2006) investigated different shales and mudrocks, and variable deformation 326
behaviour from brittle to ductile response with loading conditions were observed. Similar responses 327
have been observed with sandstones, etc.: Yang et al., 2011; Yang and Jing, 2011; Wang and Xu, 328
2013; and Alam et al., 2014. However, the compressive strength of these relatively ‘weak’ rocks 329
are often significantly greater than those encountered with CB, and it is clear that direct comparison 330
between the strength of rock and hardened CB slurry is unsatisfactory. 331

332
Despite this, sedimentary rocks can experience tension and combination (tension-shear) modes of 333
failure at zero or low confining pressures (Figure 9), which is similar to CB (Figure 4) and plastic 334
concrete (Figure 8). Research reveals the development of microcracking within sedimentary rock's 335
fabric prior to achievement of the peak strength (Farmer, 1983; Yang et al., 2011; Yang and Jing, 336
2011; Wang and Xu, 2013; Jia et al., 2013; and Alam et al., 2014), and this behaviour could also 337
occur in CB materials when deformed. 338

5.1 Microcracking 340

A generalised curve of stress-strain behaviour of brittle rock is presented in Figure 10: the model 341
suggests that rock deformation process in UCS test can be divided into six stages which are 342
indicated by letters A-F. Stages B, C, and D are the main three stages at which microcracking 343
events are concentrated. Stage (B) denotes deformation that is largely recoverable but microcrack 344
propagation is argued to onset within this stage at about 35 % to 40 % of the peak stress (Farmer, 345
1983). Stage (C) still represents recoverable deformation but microcracks exhibit an increase in 346

growth; this stage ends at approximately 80% of the peak strength at which non-recoverable deformation begins (stage D). Stage (D) results in rapid acceleration of microcracking events: clusters of cracks in the zones of highest stress tend to coalesce and start to form tensile fractures or shear planes (this is a function of rock strength and degree of confinement) (Farmer, 1983). Therefore, during stage (D) the rock is suspected to experience changes in hydraulic conductivity due to initiation and propagation of microcracks, yet the rock has not reached its peak strength.

Subsequent research into the brittle behaviour of sedimentary rocks have furthered understanding of microcrack development (Yang et al., 2011; Yang and Jing, 2011; Nicksiar and Martin, 2012; and Jia et al., 2013) and validated the basic principle of the model presented in Figure 10. Whilst rocks are likely to be much stronger than CB, this model (Figure 10) is worthy of note as it depicts the development of microcracking at stresses significantly less than the peak strength. If the primary role CB barriers are to control groundwater flow, then the development of microcracks prior to peak strength may result in significant loss of performance. It is unclear if this model is valid with respect to CB material behaviour, and further research is clearly required to understand the relationship between: loading environment, development of cracking, and hydraulic conductivity of the CB barrier material.

6 Comparison of CB with Clay Deformation Behaviour

6.1 Stiff Clay Deformation Response

CB behaviour has previously been compared to that of clays (Evans, 1993; and Garvin and Hayles, 1999). Evans (1993) refers to the strength of CB being akin to stiff clay soils. Whilst the behaviour in certain instances appears similar, it is not clear if the mechanisms controlling stabilised colloidal suspensions (CB) (Jefferis, 2012) are the same as those for clays. Clay soils experience phenomena such as electrostatic, physio-chemical, or other forces that act to connect the particles (Cotecchia

and Chandler, 1997), often labelled as cohesion; these attractive interparticle forces are essentially a function of the clay minerals present, and control the flocculation-deflocculation behaviour in suspension (Mitchell and Soga 2005; Atkinson, 2007). These forces are also important in denser soils as they may influence the intergranular stresses and control the strength at interparticle contacts, which in turn controls resistance to compression and strength (Mitchell and Soga, 2005). Therefore, the mechanical response of clays depends on: their consolidation state, their structure (the combination of fabric and bonding), their loading history (Cotecchina et al., 2007) as well as the loading conditions (undrained/drained). Whilst these conditions may be quantified, or justifiably estimated, this is not the case of CB slurry barriers where the loading history does not exist, and consolidation conditions are not confidently known.

6.2 Overconsolidated Clay Deformation Response

CB has previously been likened to overconsolidated clay as the undrained response of overconsolidated clays would appear to be similar to that of CB (containing GGBS, those with PFA illustrate significant softening post-peak). However, this analogy appears to be less than ideal as the consolidated drained response for overconsolidated clays do not appear to replicate those encountered for CB. Burland (1990) investigated London Clay (Figure 11) and a clay from Todi, Italy (overconsolidated intensely fissured), and found the behaviour of the two clays to be similar. The response of overconsolidated soils to deformation reported by Burland (1990) has also been encountered by others (e.g. Roscoe et al., 1958; Georgiannou and Burland, 2001; and Atkinson, 2007).

Whilst there may be similarities between undrained stress-strain response and consolidation behaviour of CB (Figure 12) with overconsolidated clays (with respect to the presence of preconsolidation pressures in overconsolidated soils and apparent ‘preconsolidation pressures’, or

critical stresses, in the case of CBs), the similarities between volumetric responses of these materials seems less clear. Overconsolidated clays are expected to dilate upon shearing, in contrast, Soga et al. (2013) illustrated that CB compresses upon loading (with large amount of volume change in drained triaxial tests, regardless of the magnitude of confining pressure). It is these differences that make comparisons between deformation behaviour of CB and overconsolidated/stiff clays unsatisfactory.

7 Comparison of CB with Cemented Soil Deformation Behaviour

CB deformation behaviour bears, albeit it limited, similarities to concretes and clays, and may experience microcracking with deformation (as identified with deformation of brittle sedimentary rocks), although attempting to make such comparisons between these materials is an effort to better understand CB response appears inadequate. Clearly the behaviour of cemented soils should also be compared to the behaviour of CB mixtures, although many soils stabilised with cement differ from CB as the latter has cemented colloidal structure.

Soils may be naturally cemented due to geological processes (i.e. precipitation of minerals such as calcite, silica, and/or other inorganic or organic components), or 'man-made' with the inclusion of cementitious materials, or stabilisers, such cement, PFA, GGBS, rice husk ash (RHA), lime, gypsum, etc. (Indraratna et al., 1995; Cokca, 2000; Lee and Lee, 2002; Chew et al., 2004; Rao and Shivananda, 2005; and Consoli et al., 2007). Introducing stabilising materials into a soil is undertaken for a number of reasons including the creation of bonds to enhance the mechanical properties of weak soils and reduce compressibility.

7.1 Deformation Behaviour of Cemented Soils

422

Mitchell and Soga (2005) state that behaviour of cemented soils is a function of the time at which cementation bonds developed. Overburden loading might be applied after cementation in artificially cemented soils, whereas it might be applied during, or shortly after, the development of cementation in natural soils. If a particle contact is cemented, it is possible for some interparticle forces to become negative due to the tensile resistance (or strength) of bonds; thus stiffness and strength properties of a soil are likely to differ according to when, and how, cementation was developed (Mitchell and Soga, 2005). Schnaid et al. (2001) observed that cemented soils exhibit very stiff behaviour prior to a well-defined yield point that is extensively controlled by cementation bonds, followed by plastic deformation upon reaching failure. Furthermore, cemented soils have been observed to dilate upon shearing, much like overconsolidated clays, (e.g. Lade and Overton, 1989; Indraratna et al., 1995; Lee and Lee, 2002; Moses et al., 2003; Horpibulsuk et al., 2004; Chew et al., 2004; Chiu et al., 2008; and Kamruzzman et al., 2009) (Figures 13 to 17).

435

Cementation increases peak strength, initial stiffness and brittleness, and generates tensile strength (Leroueil and Vaughan, 1990). In artificially cemented soils, for a given water content, an increase in cement content (over the range of proportions investigated) results in an increase in peak strength and stiffness, thereby reducing the strain at which failure occurs (Lade and Overton, 1989; Moses et al., 2003; Horpibulsuk et al., 2004; Chew et al., 2004; Consoli et al., 2007; and Kamruzzaman et al., 2009) (Figure 13). Cementation also results in change in behaviour from plastic to brittle under drained conditions (Lee and Lee, 2002). However, the brittle behaviour (for a given cement content) has also been observed to transform to a ductile response, resulting in higher peak strengths, with increasing effective stress levels; although the confining stresses required for this transformation in behaviour are significant (i.e. 10 MPa) (Schnaid et al., 2001; Horpibulsuk et al., 2004; and Kamruzzaman et al., 2009) (Figure 15). These descriptions also demonstrably apply, to

446

varying degrees, to: concrete, sedimentary rocks and CB. Manassero et al. (1995) and Soga et al. (2013) illustrated that if confining pressure is sufficient, and drained conditions prevail, then the material transforms from ductile response to strain-hardening from very low strains, and at this point, CB appears to deviate from the trends of other cemented soils.

7.2 Limitations When Comparing Behaviour of Cemented Soils with CB

Seeking to further understanding of CB behaviour with comparison to published behaviour of cemented soils appears unadvisable due to the considerable range of deformation responses encountered with cemented soils (Lade and Overton, 1989; Indraratna et al., 1995; Cokca, 2001; Lee and Lee, 2002; Moses et al., 2003; Rao and Shivanda, 2003; Chew et al., 2004; Horpibulsuk et al., 2004; Lee et al., 2005; Consoli et al., 2007; Tang et al., 2007; Chiu et al., 2008; Kamruzzman et al., 2009; and Horpibulsuk et al., 2012).

For example, Lee and Lee (2002) investigated cement-stabilised kaolin, and Kamruzzaman et al. (2009) studied cement-stabilised soft clay both in UCS (Figure 15) and triaxial tests. Strength increased with duration of curing for all mixes investigated, and the material increased in brittleness with age and increasing cement content. Strain-softening occurred post peak strength under both UCS and triaxial loading, even under high effective confining pressures. In undrained testing of cement-stabilised kaolin within the triaxial, failure was not brittle, instead strain-softening behaviour was encountered; samples were mostly failing through developing shear planes, and occasionally by crushing through growth of nearly vertical cracks at the bottom or the top of the sample. The failure behaviour observed in drained conditions within the triaxial once again was brittle, (especially pronounced at high cement contents and duration of curing with low confining pressures); plastic shearing in all drained triaxial tests and samples failed through development shear failure planes with associated sample barrelling. Lee and Lee (2002) concluded that the

material was stiffer under undrained condition than under drained conditions, and the stiffness of 472
cement-stabilised kaolin is greatly influenced by confining pressure. This behaviour bears 473
similarities with the other cemented materials considered herein (i.e. drainage conditions and 474
stiffness on CBs, Figure 4, and stiff clays, Figure 11; influence of confining pressure on CBs, 475
concretes, and rocks). Fedá and Herle (1995) observed the behaviour of undisturbed saturated 476
samples of clay (naturally cemented clay) from western Bohemia (Figure 16) in TXCU (effective 477
confining pressure range of 400 kPa to 1200 kPa), and suggested that the post-peak behaviour is a 478
result of progressive debonding of such soils culminating in the total collapse of the cemented 479
structure. Increasing the confining pressure resulted in increased peak deviator stresses, whereas no 480
significant change in strain at failure was observed. Conversely, Moses et al. (2003) investigated 481
undisturbed soft clays (Indian costal marine, naturally cemented clay) under TXUU (Figure 17) and 482
did not observe a noticeable peak strength, instead strain-hardening was exhibited when applying 483
confining pressures higher than preconsolidation pressure (75 kPa). CB material does not exhibit 484
post-peak strain-hardening under TXUU conditions; and does not always undergo significant strain- 485
softening behaviour under undrained triaxial loading, this appears to be a function of the cement- 486
replacement material used within the mixture. 487

488

8 Conclusions 489

Stress-strain behaviour, shear strength, and failure modes of CB mixtures, for low permeability cut- 490
off barriers, show significant variation in behaviour that depends on: duration of curing, type and 491
proportion of cementitious material within the mixture, drainage conditions, as well as magnitude of 492
confining pressure in drained conditions. CB would appear to be stiffer, yet weaker, in undrained 493
conditions when compared to drained. In drained conditions the deformation response changes with 494
confinement: from brittle to ductile, then to strain-hardening (apparent from low strains) the 495
transformation from ductile to strain-hardening requires significant confining pressures, and it has 496

been questioned if such confining pressures are likely to be encountered in shallow barrier installations. 497
498

499
Understanding of CB behaviour is limited, leaving many questions regarding barrier performance 500
unanswered. In an effort to broaden understanding of CB behaviour, this paper has considered the 501
deformation behaviour of other cemented particulate systems used in civil engineering to determine 502
if the deformation response for these materials are comparable to CB; and thus if understanding 503
developed from the significantly greater research effort into these materials could be applied to CB. 504

505
Concrete does not appear to be a particularly suitable material to compare to CB as the strength and 506
brittleness of concrete are significantly greater than CB. Concrete does not suffer from the extreme 507
variability of post-peak behaviour (in UCS and triaxial tests) encountered with CB. Plastic concrete 508
is used in the same applications as CB, and has two common ingredients: cement and bentonite, yet 509
plastic concrete does not appear to illustrate the transformation in deformation behaviour with 510
magnitude of confining pressure. The comparison of plastic concrete with CB is less than ideal as 511
CB can exhibit strain-hardening behaviour under drained loading as well as greater strains at failure 512
(for lower peak strengths than plastic concrete). 513

514
The behaviour of rocks would appear a poor comparison to CB, even ‘weak’ sedimentary rocks are 515
likely to be significantly stronger than the majority of CB used for low permeability cut-off wall 516
applications. However, deformation behaviour of rocks has been widely studied, and it has been 517
identified that microcracks will form (within brittle materials) and congregate well before the peak 518
strength is achieved, and this could also occur within CB barriers. Microcracking prior to peak 519
strength in undrained conditions could result in an increase in the hydraulic conductivity of the CB 520

barrier, therefore potentially compromising its ability to achieve its primary role, and thus this merits investigation.

CB material has much lower strength than concrete, and hence it was argued that perhaps CB has more in common with clays. This suggestion does not seem wholly applicable; behaviour of ‘clay’ soils are subjected to extensive variability due to the significant spectrum of properties and composition of soils that can be classified as clay, and such variation makes direct comparison of behaviour between CB and published findings of clay deformation difficult.

Cemented soils would appear to be an obvious comparator with CB as, in general cemented soils exhibit brittle behaviour similar to CB materials. In addition, cemented soils are sensitive to: confining pressure, drainage condition, and age (in case of cement-stabilised clays). However, it is difficult to use published information on cemented soils when attempting to further understanding of CB behaviour due to the wide range of behaviours associated with these materials. This would also appear to be the case with clay soil deformation response.

Having considered, concrete, plastic concrete, sedimentary rocks, clay soils and cemented soils in an effort to further understanding of CB behaviour it is concluded that these comparisons are unsatisfactory. There is either too great a range of differences between the materials when compared to CB or, where there does appear to be comparability (for example cemented clays), there is such a range of behaviours exhibited by these types of materials that making such comparison could be either misleading or fundamentally flawed. Jefferis (2012) states that there is insufficient research undertaken on cemented clay systems and the authors fundamental echo these sentiments; increased understanding of CB is required if these materials are to be used efficiently.

References

- Alam MS, Chakraborty T, Matsagar V, Rao KS, Sharma P, Singh M (2014) Characterization of Kota Sandstone under different strain rates in uniaxial loading. *Geotech Geol Eng.* DOI 10.1007/s10706-014-9810-3.
- Atkinson J (2007) Peak strength of overconsolidated clays. *Géotechnique* 57(2): 127–135.
- Burland JB (1990) Rankine lecture: On compressibility and shear strength of natural clays. *Geotèchnique* 40(3): 329-378.
- Chew SH, Kamruzzaman AHM, Lee FH (2004) Physicochemical and engineering behavior of cement treated clays. *J. Geotech. Geoenviron. Eng.* 130: 696-706.
- Chiu CF, Zhub W, Zhang CL (2008) Yielding and shear behaviour of cement-treated dredged materials. *Eng. Geo.* 103: 1–12.
- Clayton CRI, Matthews MC (1987) Deformation, diagenesis and the mechanical behaviour of chalk. Jones ME, Preston RMF (eds), *Deformation of sediments and sedimentary rocks*. 1st edn. *Geol. Soc. Spec. Publ.*, London. ISBN: 0-632-01733-3.
- Cokca E (2001) Use of class C fly ashes for the stabilization of an expansive soil. *J. Geotech. Geoenviron. Eng.* 127: 568-573.

Consoli NC, Foppa D, Festugato L, Heineck KS (2007) Key parameters for strength control of artificially cemented soils. <i>J. Geotech. Geoenviron. Eng.</i> 133: 197-205.	569 570 571
Cotecchia F, Carfaro F, Aresta B (2007) Structure and mechanical response of sub-Apennine Blue clays in relation to their geological and recent loading history. <i>Geotèchnique</i> 57(2): 167-180.	572 573 574
Cotecchia F, Chandler RJ (1997) The influence of structure on the pre-failure behaviour of a natural clay. <i>Geotèchnique</i> 47(3): 523-544.	575 576 577
Deschênes J-H, Massiéra M, Tournier J-P (1995) Testing of a cement-bentonite mix for a low-permeability plastic barrier. Dredging, remediation, and contaminated sediments. Demars KR, Richardson GN, Yong RN, Chaney RC (eds). <i>ASTM STP 1293</i> , Philadelphia, pp. 252-270.	578 579 580 581
Dragon A, Mróz Z (1976) On plastic-brittle behaviour of rock and concrete. <i>Mech. Res. Comm.</i> 3: 429-434	582 583 584
Evans JC (1993) Vertical cutoff walls. Daniel DE (eds) <i>Geotechnical practice for waste disposal</i> . 1 st edn. Chapman & Hall, London. ISBN 0 412 35170 6.	585 586 587
Farmer I (1983) <i>Engineering behaviour of rocks</i> , 2 nd edn. Chapman and Hall, London. ISBN 0 412 25280 5.	588 589 590
Feda J (1995) Mechanisms of collapse of soil structure. Derbyshire E, Dijkstra T, Smalley IJ (eds) <i>Genesis and properties of collapsible soils</i> . 1 st edn. Kluwer Academic Publishers, Netherlands. ISBN: 0-7923-3587-2.	591 592 593

Fratolocchi E, Pasqualini E, Balboni P (2006) Performance of a cement-bentonite cut-off wall in an acidic sulphate environment. <i>Proc. 5 ICEG, International Congress on Environmental Geotechnics</i> , Cardiff (UK), pp.133-139 .	594 595 596
Fratolocchi E, Pasqualini E (2007) Vertical barriers for side containment. Proc. XXI Geotechnical Conference , Geosynthetics and Environment, Torino, Italy.	597 598 599 600
Fratolocchi E, Brianzoni V, Di Sante M, Mazzieri F, Pasqualini E (2013) Migration of aggressive solutions through cement-bentonite slurry walls. Manassero et al. (eds) <i>Coupled Phenomena in Environmental Geotechnics</i> , pp. 243-252.	601 602 603 604
Garvin SL, Hayles CS (1999) Chemical compatibility of cement–bentonite cut-off wall material. <i>Constr. Build. Mater.</i> 13:329–341.	605 606 607
Georgiannou VN, Burland JB (2006) A laboratory study of slip surface formation in an intact natural stiff clay. <i>Geotèchnique</i> 56(8): 551-559.	608 609 610
Hinchberger S, Wech J, Newson T (2010) Mechanical and hydraulic characterization of plastic concrete for seepage cut-off walls. <i>Can. Geotech. J.</i> 47:461-471.	611 612 613
Horpibulsuk S, Miura N, Bergado DT (2004) undrained shear behavior of cement admixed clay at high water content. <i>J. Geotech. Geoenviron. Eng.</i> 130: 1096-1105.	614 615 616
ICE (1999) <i>Specification for the construction of slurry trench cut-off walls as barriers to pollution migration</i> , Thomas Telford Publishing, London, ISBN: 0 7277 2625 0.	617 618


Indraratna B, Balasubramaniam AS, Khan MJ (1995) Effect of fly ash with lime and cement on the behaviour of a soft clay. <i>Quarterly J. Eng. Geo.</i> 28: 131-142.	619 620 621
Jafarzadeh F, Mousavi SH (2012) Effect of specimen' s age on mechanical properties of plastic concrete walls in dam foundations. <i>EJGE</i> 17: 473-482.	622 623 624
Jefferis SA (1981) Bentonite-cement slurries for hydraulic cut-offs. <i>Proc. 10thICSMFE, A.A. Balkema, Rotterdam</i> , pp. 435–440.	625 626 627
Jefferis, S. A. (1997) The origins of the slurry trench cut-off and a review of cement-bentonite cut-off walls in the UK. <i>Land Contamination and Reclamation</i> . Vol. 5, n3, p239-245	628 629 630
Jefferis SA (2012) Cement-bentonite slurry systems. <i>ASCE Proceedings of the 4th International Conference on Grouting and Deep Mixing GSP</i> 228:1–24.	631 632 633
Jia L, Chen M, Zhang W, Xu T, Zhou Y, Hou B, Jin Y (2013) Experimental study and numerical modeling of brittle fracture of carbonate rock under uniaxial compression. <i>Mechanics Research Communications</i> 50: 58-62.	634 635 636 637
Jones ME, Bedford J, Clayton C (2013) On natural deformation mechanisms in the chalk. <i>J. Geo. Soc.</i> 141:675-683.	638 639 640
Joshi K (2009) <i>Long-term engineering performance and in-situ Assessment of cement-bentonite cut-off walls</i> . Dissertation submitted for the degree of Doctor of Philosophy, University of Cambridge.	641 642 643

Joshi K, Kechavarzi C, Sutherland K, Ng MYA, Soga K, Tedd P (2010) Laboratory and in situ tests for long-term hydraulic conductivity of a cement-bentonite cut-off wall. <i>J. Geotech. Geoenviron. Eng.</i> 136:562-572.	644 645 646 647
Kamruzzaman AHM, S. H. Chew SH, Lee FH (2009) structuration and destructuration behavior of cement-treated Singapore Marine Clay. <i>J. Geotech. Geoenviron. Eng.</i> 135: 573-589.	648 649 650
Kang HD, Willam K, Shing B, Spacone E (2000) Failure analysis of R/C columns using a triaxial concrete model. <i>Computers and Structures</i> 77:423-440.	651 652 653
Khandelwal M, Ranjith PG (2013) Behaviour of brittle material in multiple loading rates under uniaxial compression. <i>Geotech. Geol. Eng.</i> 31:1305-1315.	654 655 656
Lade PV, Overton DD (1989) Cementation effects in frictional materials. <i>J. Geotech. Eng.</i> 115:1373-1387.	657 658 659
Lee KH, Lee S (2002) Mechanical properties of weakly bonded cement stabilized kaolin. <i>KSCE J. of Civil Eng.</i> 6(4): 389-398.	660 661 662
Leroueil S, Vaughan PR (1990) The general and congruent effects of structure in natural soils and weak rocks. <i>Geotèchnique</i> 40(3): 467-488.	663 664 665
Mahboubi A, Ajorloo A (2005) Experimental Study of the mechanical behaviour of plastic concrete in triaxial compression. <i>Cement and Concrete Research</i> 35:412-419.	666 667 668

- Manassero M, Fratalocchi E, Pasqualini E, Claudia S, and Verga F (1995) Containment with vertical cutoff walls. *Proc. Geoenviron. – 2000*, Geotechnical special publication 46, ASCE, New Orleans, pp. 1142–1172.
- Mitchell J K, Soga K (2005) *Fundamentals of soil behaviour*. 3rd edn. Wiley, USA. ISBN-10: 0-471-46302-7.
- Moses GG, Rao SN, Rao PN (2003) Undrained strength behaviour of a cemented marine clay under monotonic and cyclic loading. *Ocean Eng.* 30: 1765–1789.
- Neville AM (1995) *Properties of concrete*, 4th edn. Longman, England. ISBN: 0-582-23070-5.
- Nicksiar M, Martin CD (2012) Evaluation of methods for determining crack initiation in compression tests on low-porosity rocks. *Rock Mech. Rock Eng.* 45:607-617.
- Nygaard R, Gutierrez M, Bratli RK, Hoeg K (2006) Brittle–ductile transition, shear failure and leakage in shales and mudrocks. *Marine and Petroleum Geo.* 23: 201–212.
- Opdyke SM, Evans JC (2005) Slag-cement–bentonite slurry walls. *J. Geotech Geoenviron. Eng.* 131:673–681.
- Philip LK (2001) An investigation into contaminant transport processes through single-phase cement-bentonite slurry walls. *Eng. Geol.* 60:209-221.

Plee D, Lebedenko F, Obrecht F, Letellier M, Van Damme H (1990) Microstructure, permeability and rheology of bentonite-cement slurries. <i>Cement and Concrete Research</i> 20:45-61.	693 694 695
Rao SM, Shivanda P (2005) Compressibility behaviour of lime-stabilized clay. <i>Geotech. Geol. Eng.</i> 23: 309–319.	696 697 698
Roscoe KH, Schofield AN, Wroth CP (1958) On The Yielding of Soils. <i>Géotechnique</i> 8(1): 22 –53.	699 700
Royal ACD, Makhover Y, Moshirian S, Hesami D (2013) Investigation of Cement–Bentonite Slurry Samples Containing PFA in the UCS and Triaxial Apparatus. <i>Geotech. Geol. Eng.</i> 31(1): 767-781.	701 702 703 704
Royal ACD, Opukumo, AW, Qadr, CS, Perkins LM and Walenna MA (Under review) Deformation and compression behaviour of a cement-bentonite slurry for groundwater control applications. <i>Paper submitted to Geotechnical and Geological Engineering</i>	705 706 707 708
Schnaid F, Prietto PDM, Consoli NC (2001) Characterization of cemented sand in triaxial compression. <i>J. Geotech. Geoenviron. Eng.</i> 127:857-868.	709 710
Smith PR, Jardine RJ, Hight DW (1992) On yielding of Bothkenner clay. <i>Geotèchnique</i> 42(2): 257-274.	711 712 713
Soga K, Joshi K, Evans JC (2013) Cement bentonite cutoff walls for polluted sites, Manassero et al (eds), <i>Coupled phenomena in environmental geotechnics</i> . 1 st edn. Taylor & Francis, London, ISBN 978 1 138 00060 5.	714 715 716 717

US EPA (1984) Slurry trench construction for pollution migration control. <i>US Environmental</i>	718
<i>Protection Agency</i> , Cincinnati, Ohio, EPA-540/2-84-001.	719
	720
Tang C, Shi B, Gao W, Chen F, Cai Y (2007) Strength and mechanical behaviour of short	721
polypropylene fiber reinforced and cement stabilized clayey soil. <i>Geotextiles and Geomembranes</i>	722
25: 194–202.	723
	724
Wang H, Xu W (2013) Relationship between permeability and strain of sandstone during the	725
process of deformation and failure. <i>Geotech. Geol. Eng.</i> 31:347-353.	726
	727
Williams M, Ghataora GS (2011) Effect of fibre reinforcement on the properties of ground	728
granulated blast furnace slag-cement–bentonite slurry. <i>Stud. Geotech. Mech.</i> 33:63–83.	729
	730
Yang SQ, Jing HW (2011) Strength failure and crack coalescence behaviour of brittle sandstone	731
samples containing a single fissure under uniaxial compression. <i>Int. J. Fract.</i> 168:227-250.	732
	733
Yang SQ, Jing HW, Wang SY (2011) Experimental investigation on the strength, deformability,	734
failure behaviour and acoustic emission locations of red sandstone under triaxial compression. <i>Rock</i>	735
<i>Mech. Rock Eng.</i> 168:227–250.	736
	737
	738

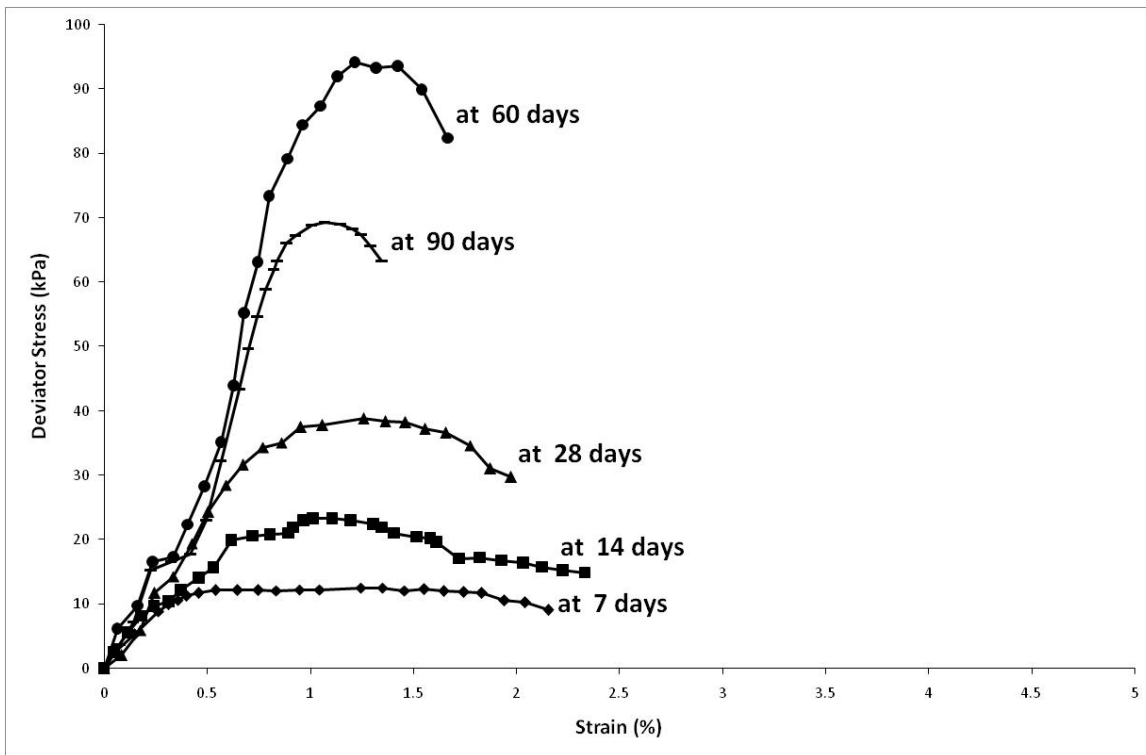

740

Figure 1: Mean stress-strain behaviour of CB samples in unconfined compressive strength (UCS) test at 1.0 mm/min rate of deformation. Mix design used: 40 g of bentonite per litre of water, and 200g of cementitious material per litre of water (with 28% PFA as cement replacement). Reproduced from Royal et al. (2013) with kind permission of Springer Science+Business Media.


741

742

743

744

745

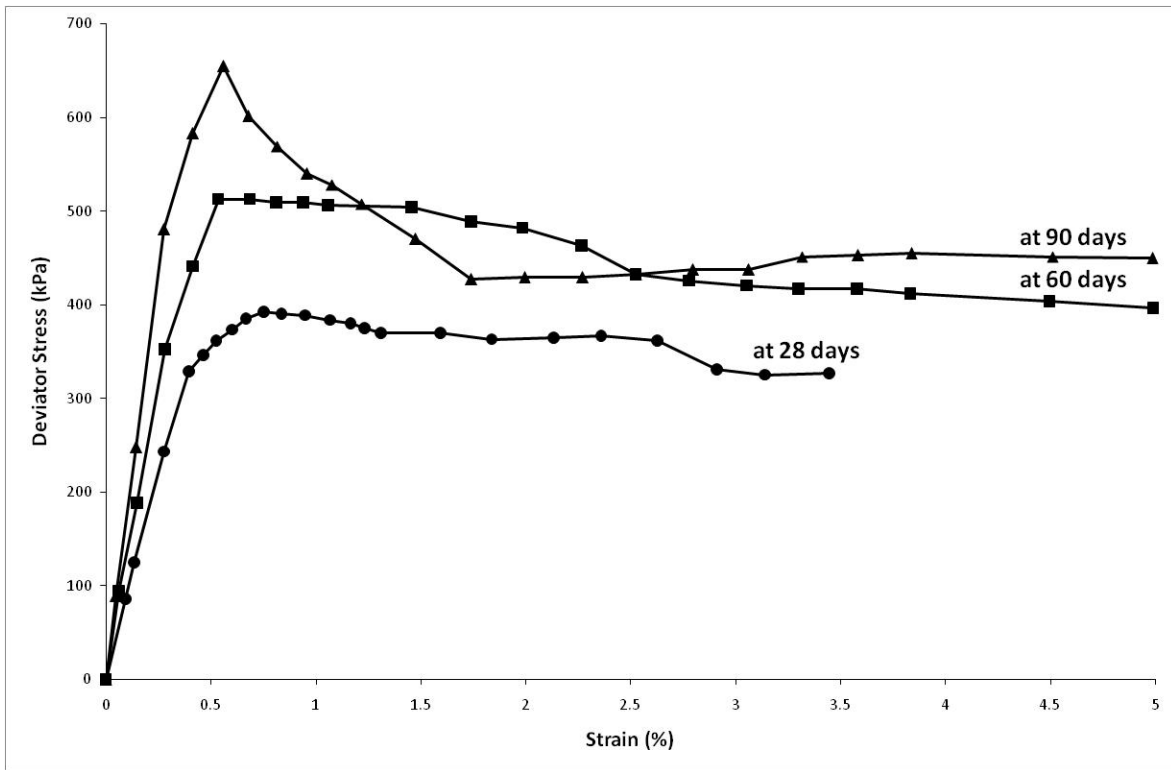

746

Figure 2: Stress-strain behaviour of CB samples containing 80% GGBS (proportion of cementitious material) in undrained triaxial tests at 0.4 mm/min at 60 kPa confining pressure, after Williams and Ghataora (2011). Mix design used: 37g bentonite per litre of water, and 160g of cementitious material (with 80% GGBS as cement replacement).


747

748

749

750

751

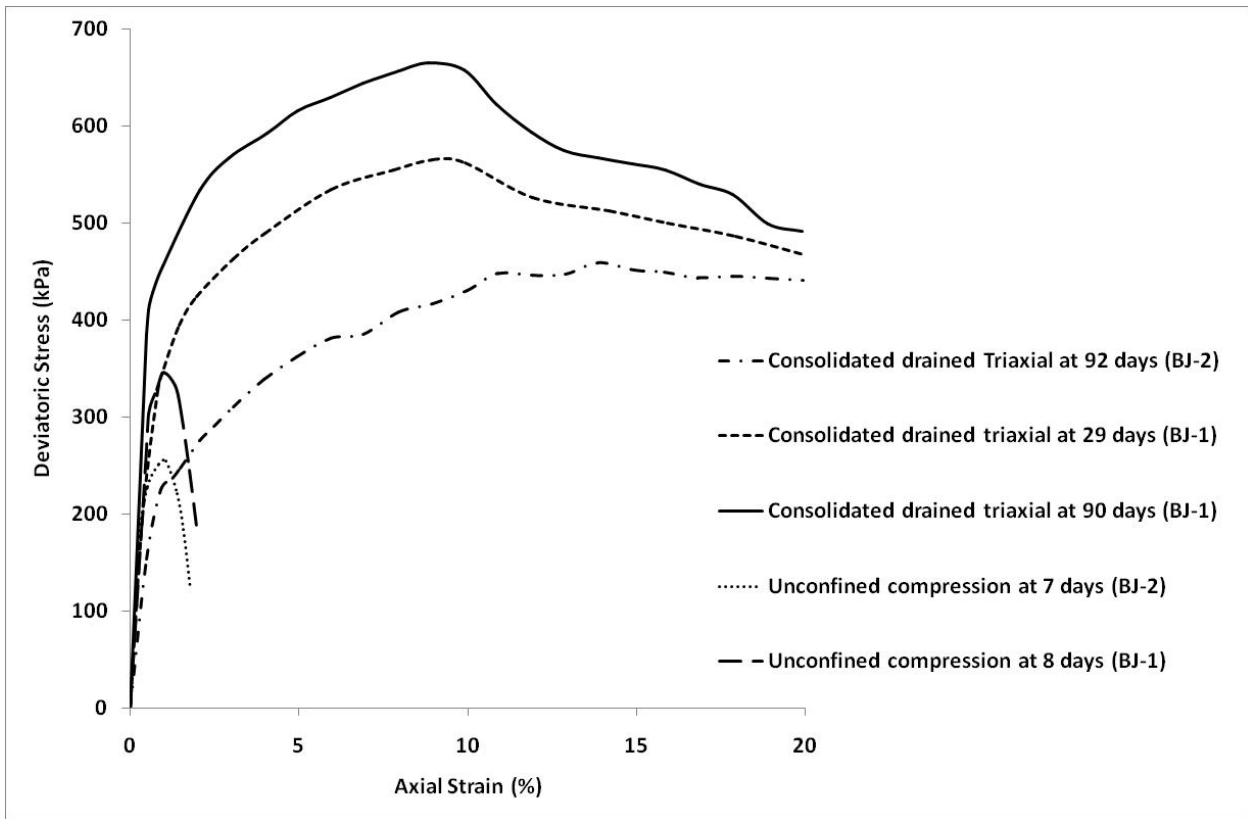

752

Figure 3: Typical CB stress-strain relationships in UCS tests and consolidated drained triaxial tests after Deschênes et al. (1995). The effective confining pressure was 100 kPa, and the back pressure was 690 kPa. Mix designs used:

753

754

755

* BJ-1(% by weight): bentonite/water= 3.72%; cement/water=35%; retarding agent/water= 0.17

756

* BJ-2(% by weight): bentonite/water= 3.68%; cement/water=30%; retarding agent/water= 0.11

757


Reprinted, with permission, from "STP 1293 Dredging, Remediation, and Containment of Contaminated Sediments," copyright ASTM International, 100 Barr Harbor Drive, West Conshohocken, PA 19428.

758

759

760

761

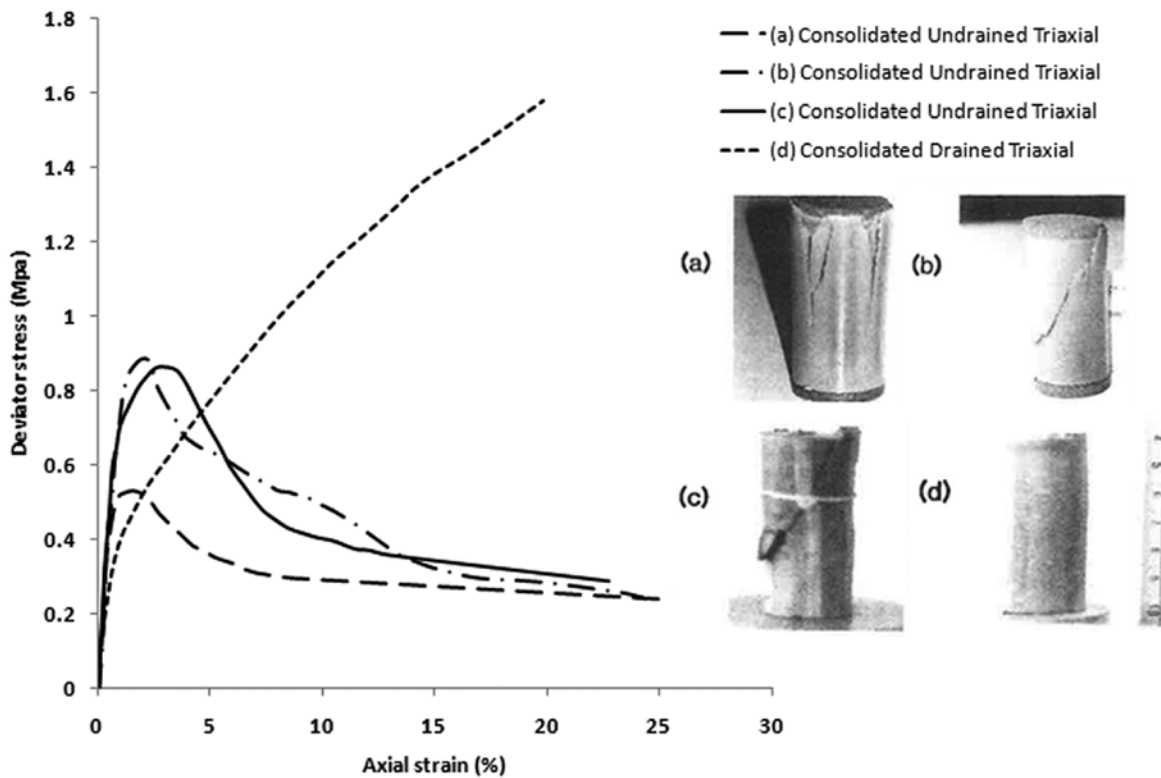

762

Figure 4: Stress-Strain relationships and modes of failure in different triaxial tests: (a) consolidated undrained triaxial (brittle-softening, tension failure); (b) consolidated undrained triaxial (brittle-hardening, shear failure); (c) consolidated drained triaxial (brittle-hardening, shear failure); (d) consolidated drained triaxial (ductile-hardening, uniform contractive failure). Curing age of samples tested vary from 5 to 7 months. Mix design (by weight): 76.8% water, 4% bentonite, and 19.2% blast furnace cement (containing 60% GGBS). Reproduced from Manassero et al. (1995) with kind permission from ASCE.

763

764

765


766

767

768

769

770

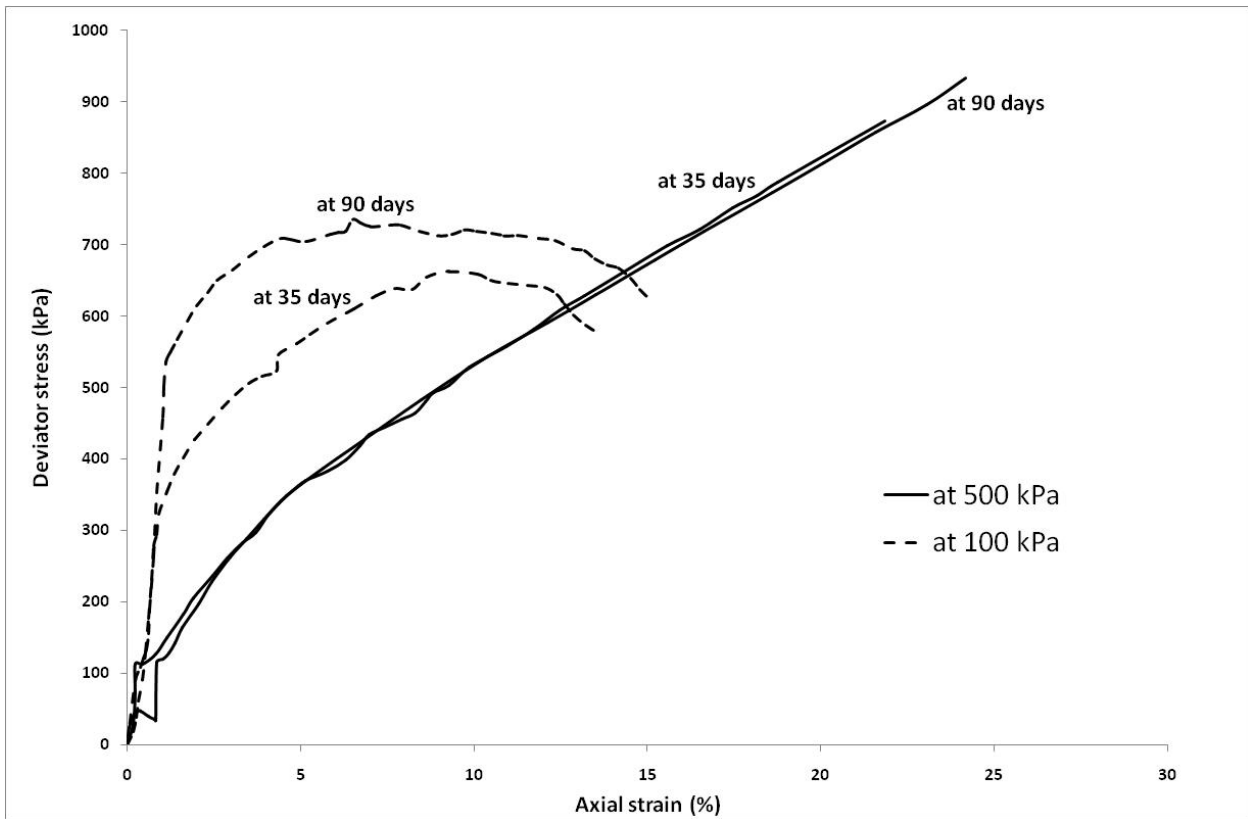

771

Figure 5: Stress-Strain behaviour in drained triaxial test at varying confining stresses (100 kPa and

772

500 kPa) on 'mixer-cast' samples at 35 days and 90 days. Mix design (by weight): 3.4% bentonite,

773

2.5% ordinary Portland cement, 10.1% GGBS (i.e. 80.1% cement replacement), and 84.0% water.

774


Reproduced from Soga et al. (2013) (figure 23, page 159) with kind permission from Taylor and

775

Francis Group.

776

777

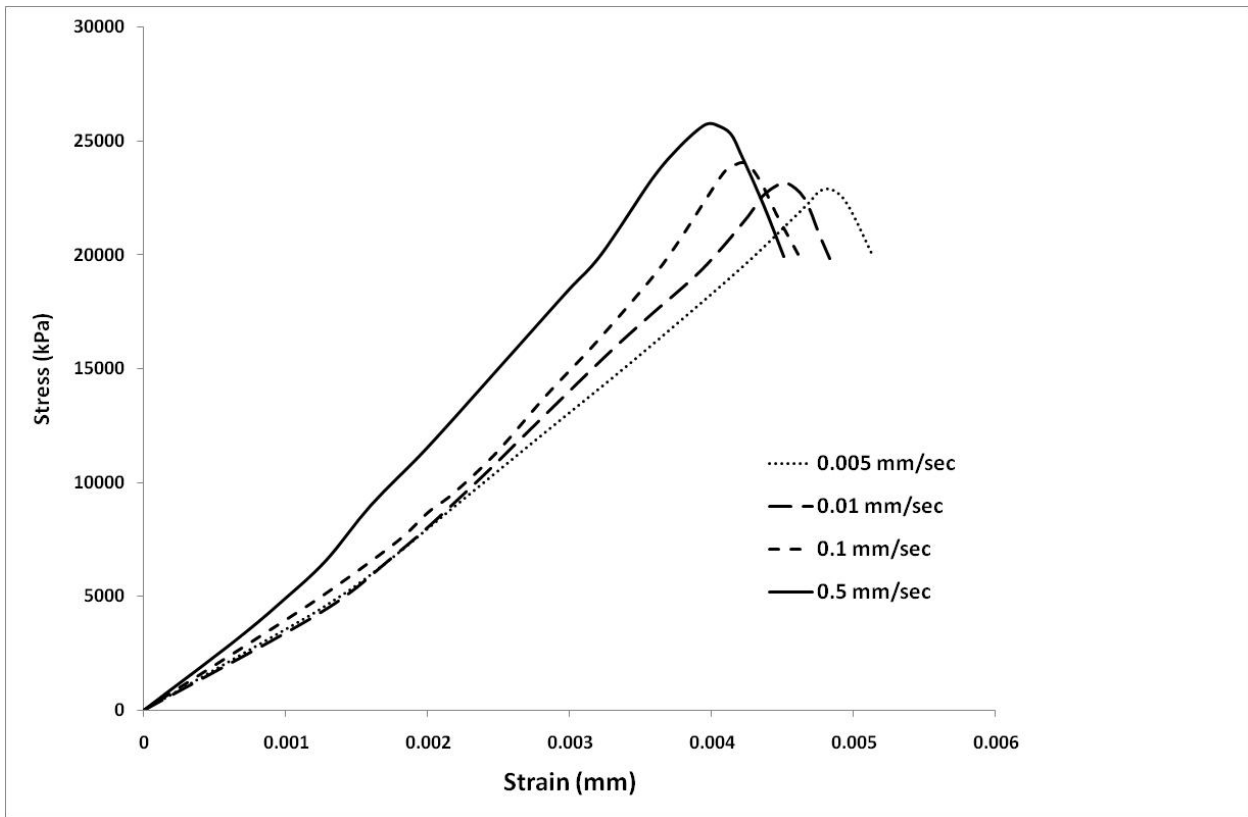


778

Figure 6: Typical stress-strain relationships for cement mortar mix at varying strain rates. 779

Reproduced from Khandelwal and Ranjith (2013) with kind permission of Springer 780

Science+Business Media. 781

782

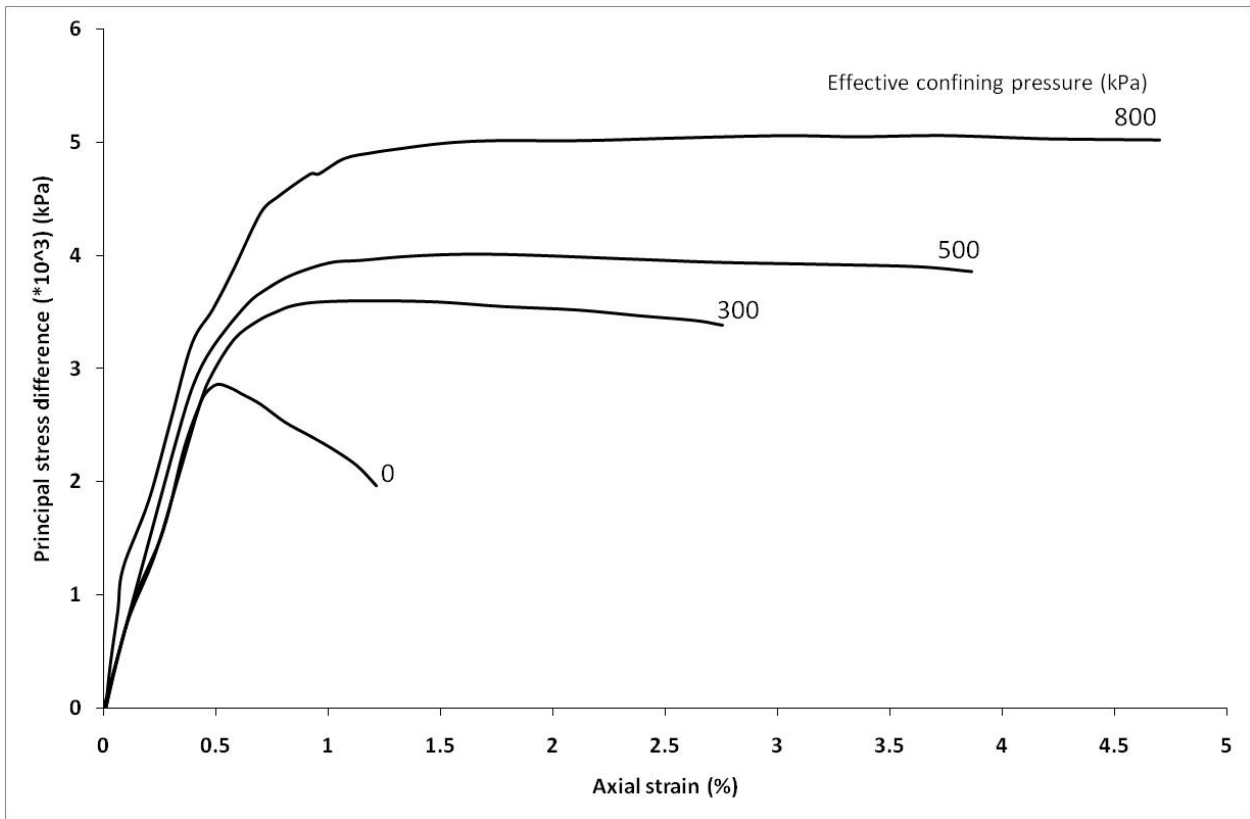

783


Figure 7: Effect of confining pressure on stress-strain behaviour of plastic concrete specimens (water-cement ratio= 1.59, and bentonite-cement ratio= 0.14) at 28 days. Reproduced from Mahboubi and Ajourloo (2005) with kind permission from Elsevier.

784

785

786

787

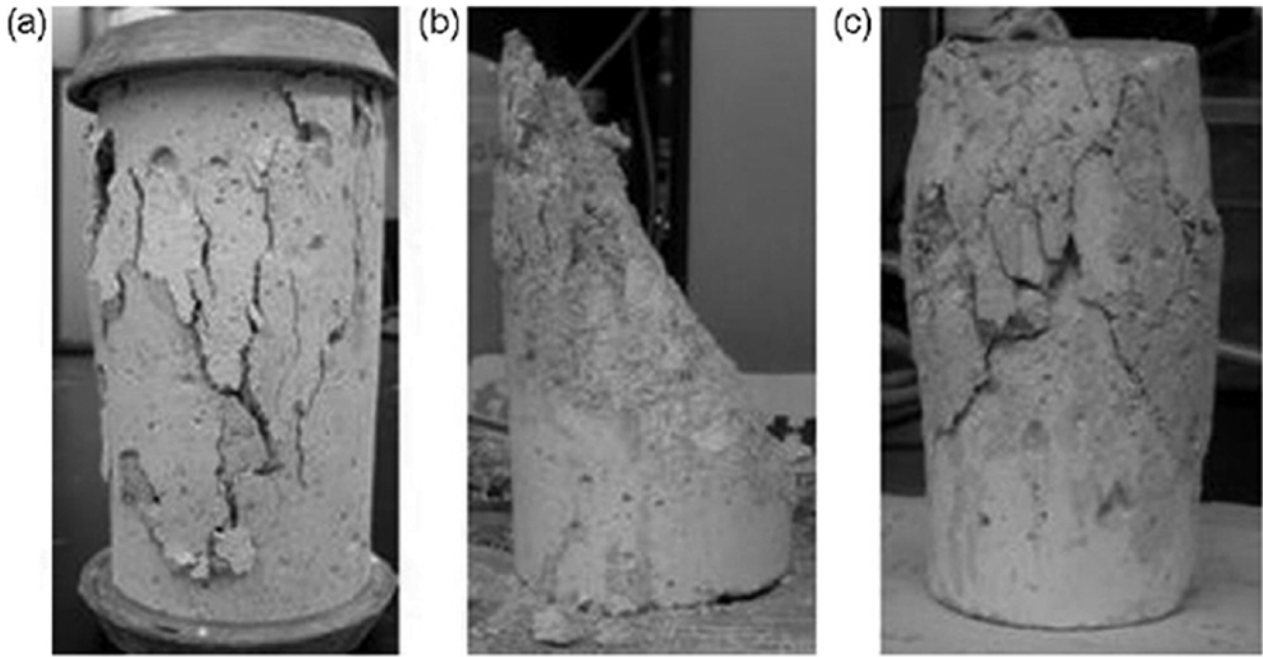

788

789

790


791

792

793

794

Figure 8: Crack patterns in plastic concrete for (a) low confinement (100 kPa), (b) intermediate confinement (400 kPa), (c) high confinement (900 kPa). Reproduced from Hinchberger et al. (2010) with kind permission of NRC Research Press, National Research Council of Canada in format Republish in a journal/magazine via Copyright Clearance Center.

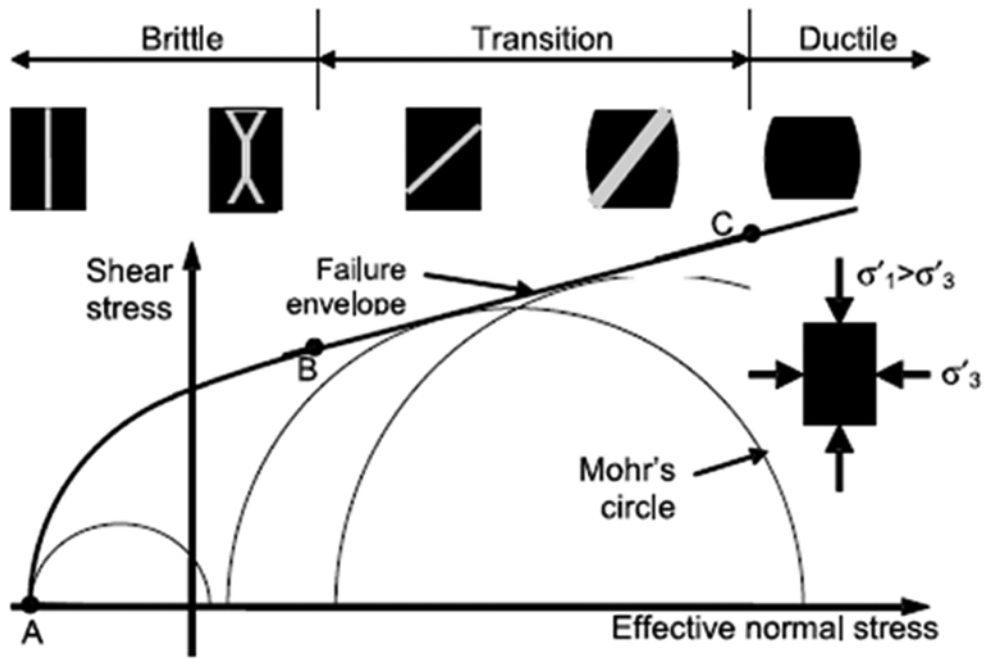

795

796

797

798

Figure 9: Effect of increasing effective confining pressures on the failure modes and fracturing of sedimentary rocks. Reproduced from Nygard et al. (2006) with kind permission from Elsevier.

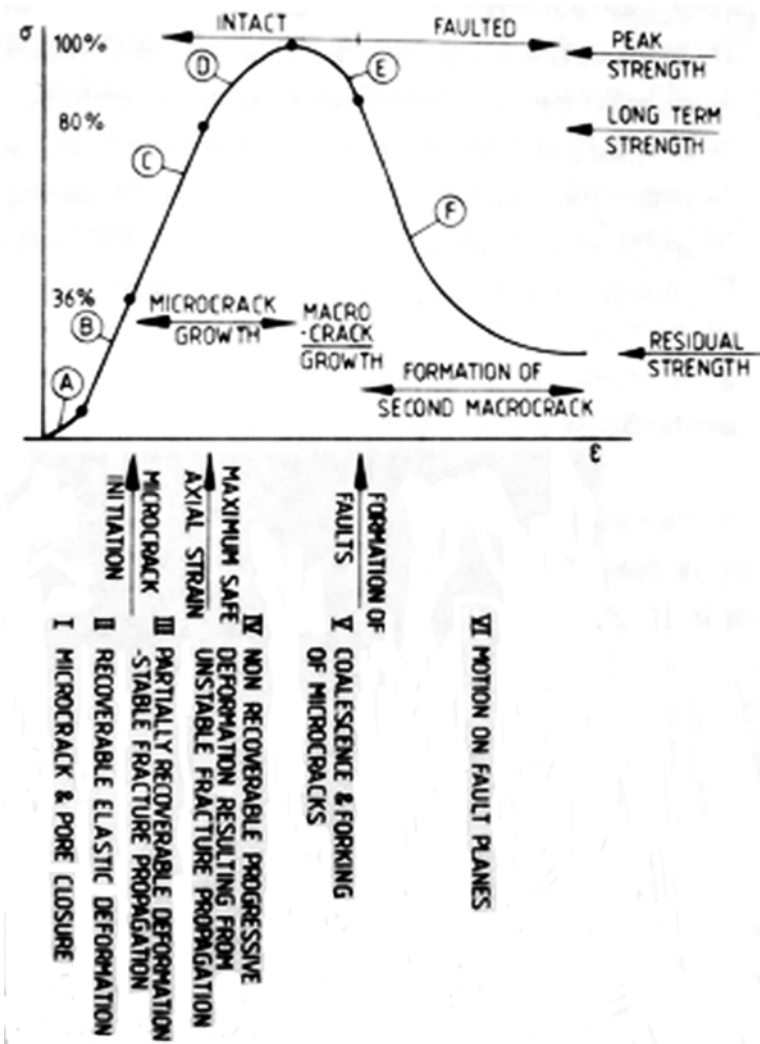



Figure 10: A description of rock deformation in UCS test (after Price 1979), taken from (Farmer, 1983)

799

800

801

802

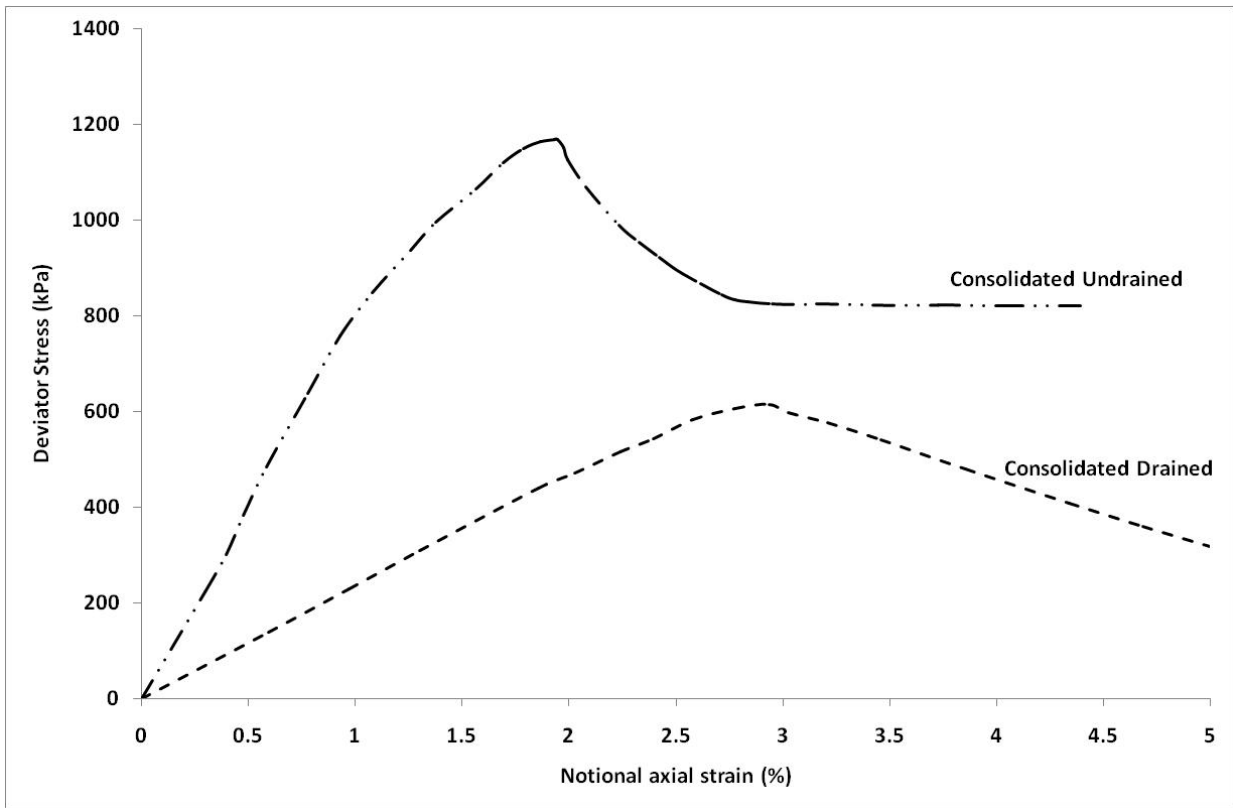

803


Figure 11: Typical consolidated undrained and consolidated drained tests on intact London Clay from Ashford Common (Level E (at 34.8 m depth): plastic index= 27%, liquid index= 70%, natural water content= 23.89%, effective overburden pressure= 386 kPa, $K_0= 2.1$) after Burland (1990)

804

805

806

807

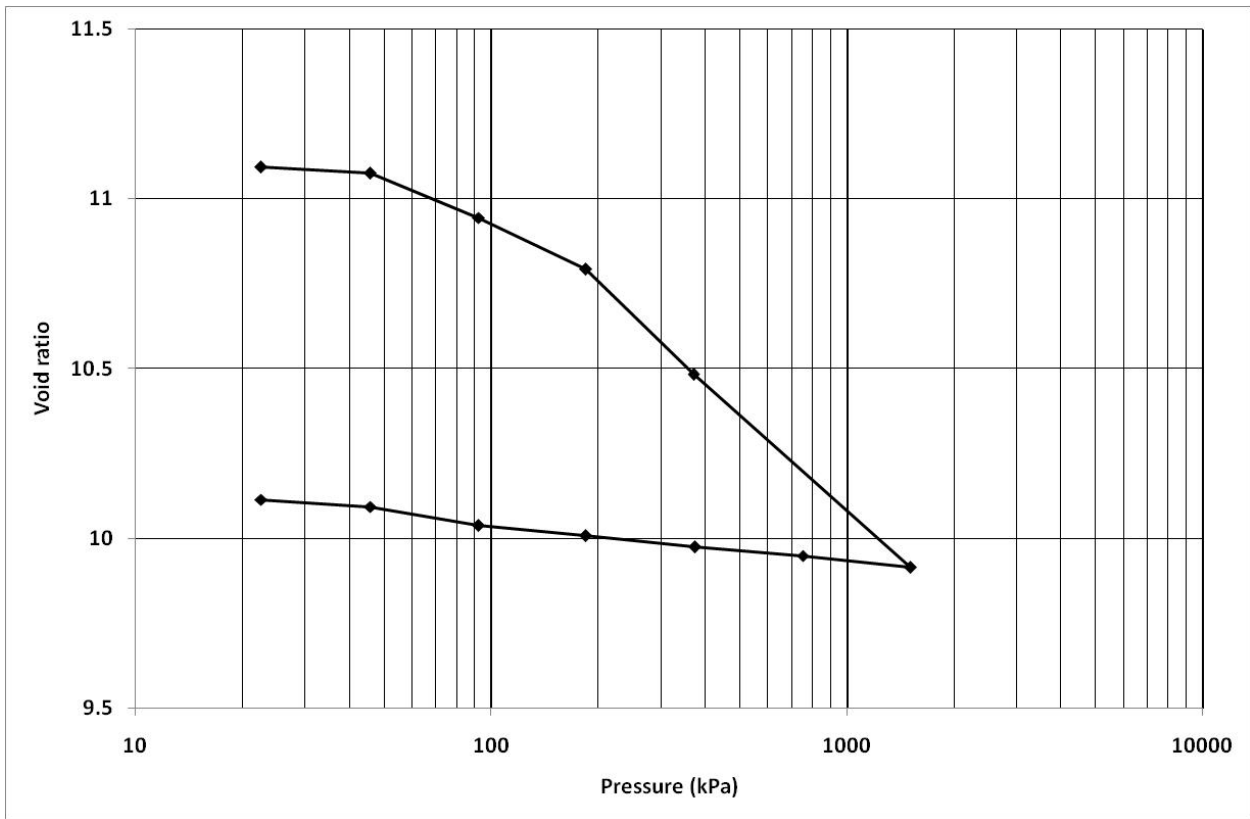

808


Figure 12: Consolidation behaviour of a CB mixture at 15 months age of curing (contains 15% cementitious material with 75% slag replacement). Reproduced from Opdyke and Evans (2005) with kind permission from ASCE.

809

810

811

812

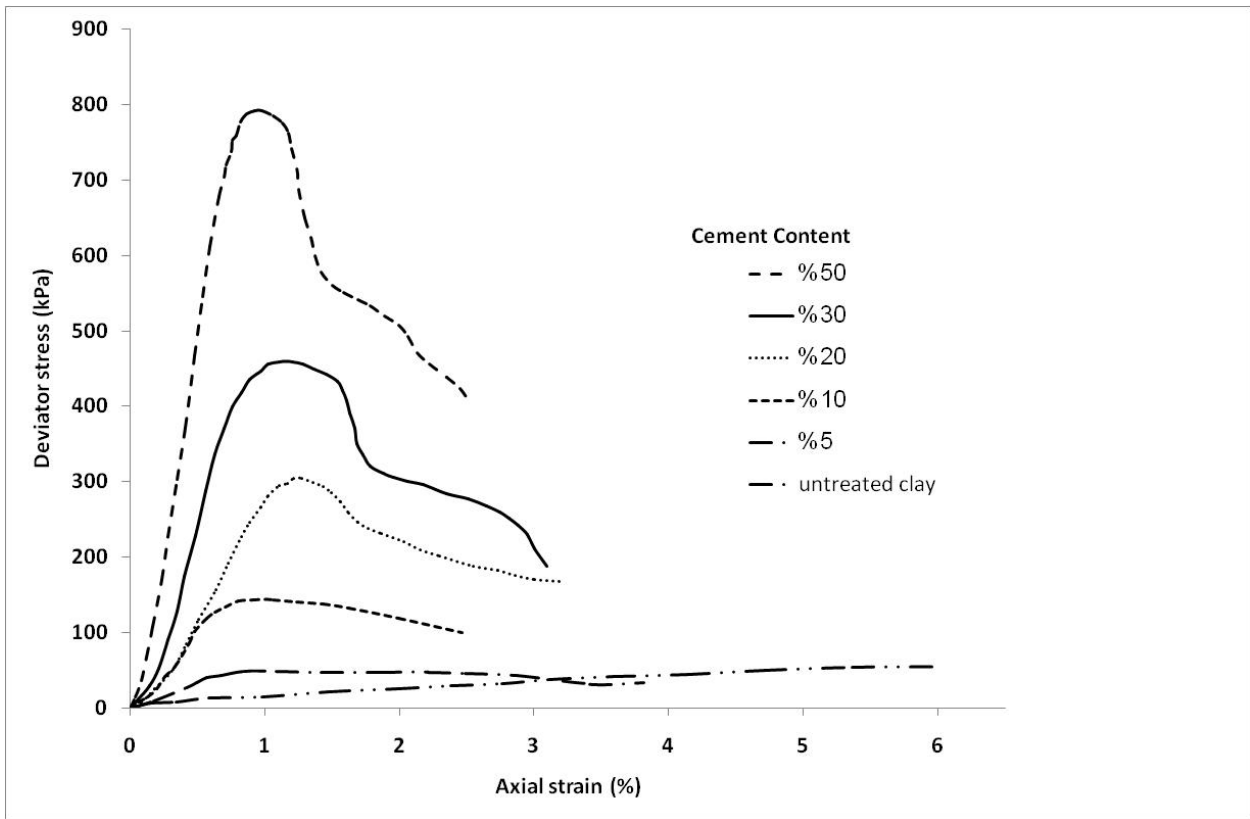


813

Figure 13: Stress-strain relationships of cement treated soft clays at varying cement content at 28 curing days. Reproduced from Chew et al. (2004) with kind permission from ASCE.

814

815

816

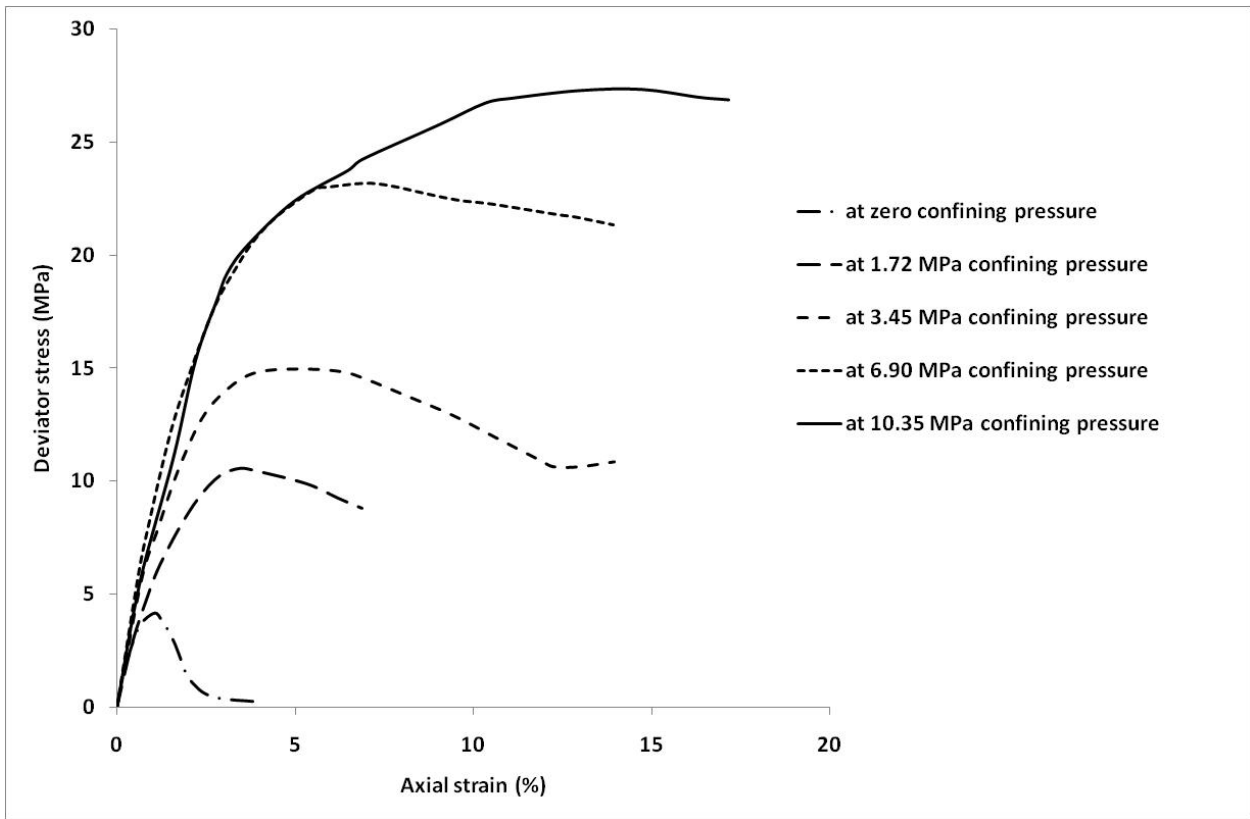

817


Figure 14: stress-strain relationship for cemented soil in consolidated drained triaxial testing (cement content = 6% by weight). Reproduced from Lade and Overton (1989) with kind permission from ASCE.

818

819

820

821

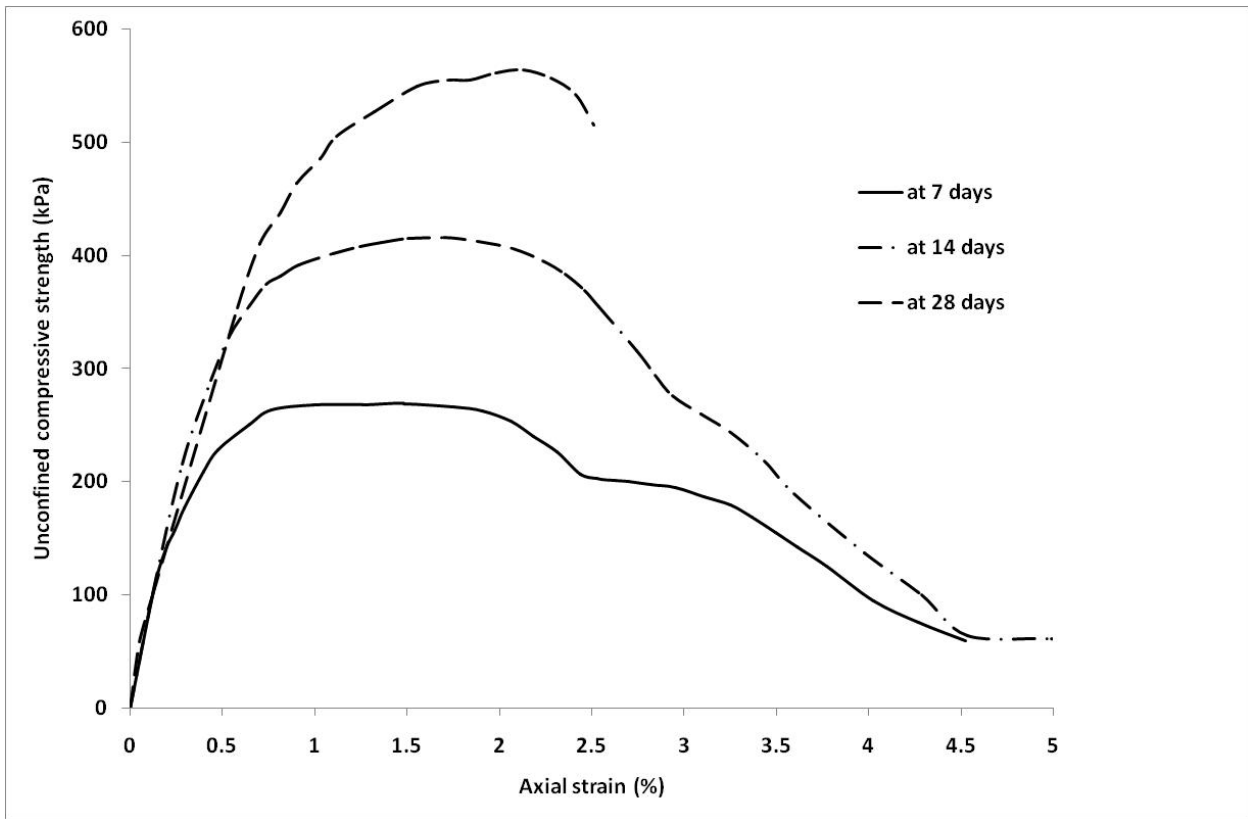

822


823

824

825

826

Figure 15: Stress-Strain behaviour in UCS tests for cement-stabilised kaolin at 5% cement ratio, humid cured for 7, 14, and 28 days. Reproduced from Lee and Lee (2002) with kind permission of Springer Science+Business Media.

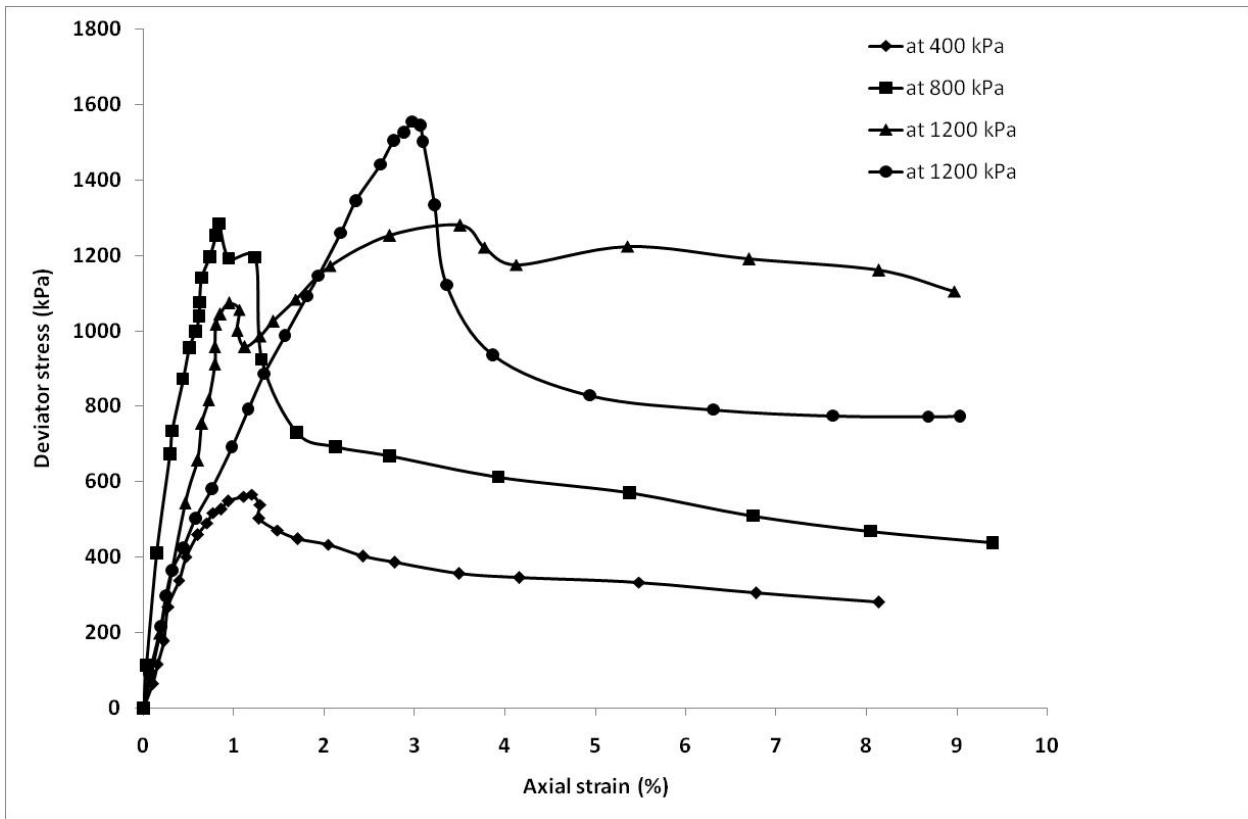

827

Figure 16: Stress-strain relationships of undisturbed saturated specimens of Miocene clay of Western Bohemia in consolidated undrained triaxial tests (plasticity index of about 38%, index of colloid activity of 0.6 to 0.8, consolidation cell pressure 400 to 1200 kPa) after Feda and Herle, (1993)


828

829

830

831

832

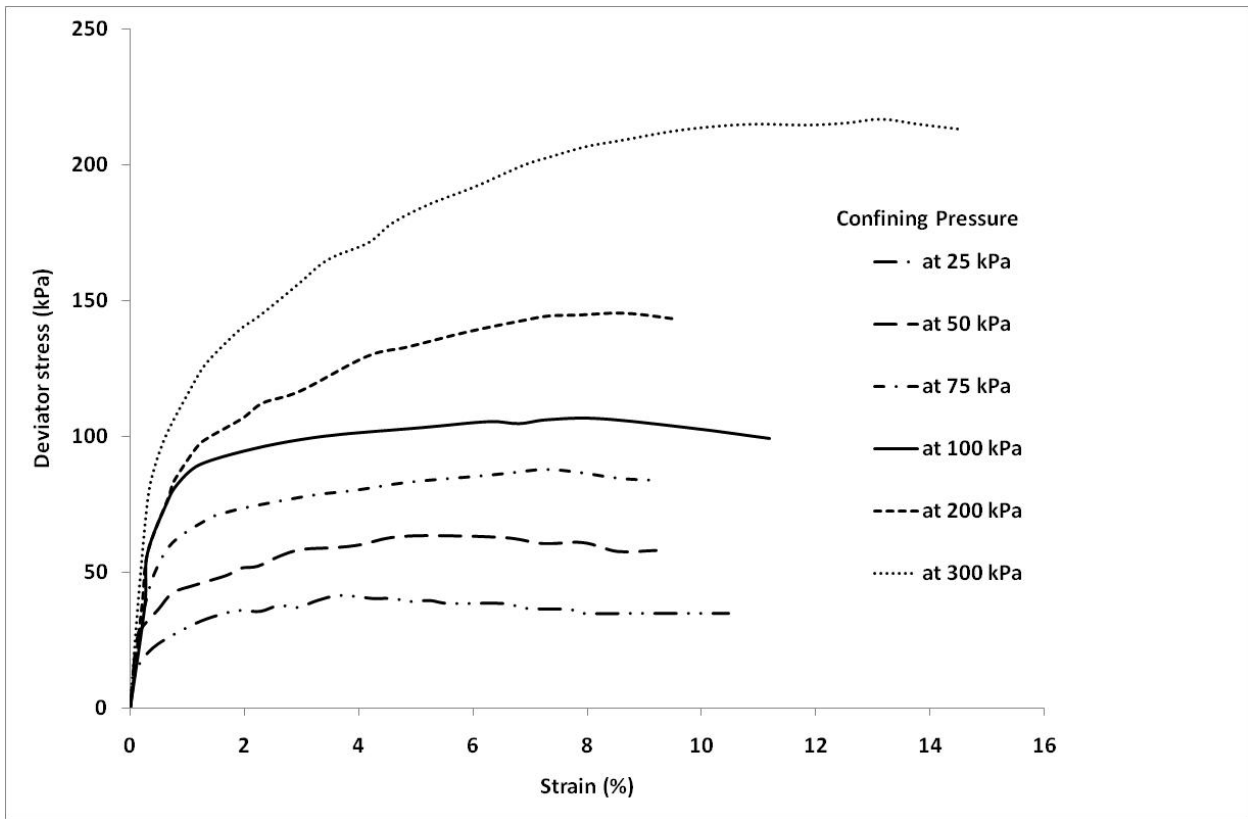

833

Figure 17: stress-strain relationship for undisturbed soft clay in undrained triaxial testing (natural moisture content= 80%-85%, plastic limit= 28%, liquid limit= 88%, clay= 54%, silt= 46%, preconsolidation pressure=75 kPa). Reproduced from Moses et al. (2003) with kind permission from Elsevier.

834

835

836

837

838

List of Tables

839

Table 1: Nominal compressive strength of concrete and maximum strain at failure. Reproduced from Neville (1995) with kind permission from Pearson Education Limited.

840

841

Maximum Strain at Failure (10^{-3})	Nominal Compressive strength($*10^3$) (KN/m ²)
4.5	7
4	14
3	35
2	70

842