

# Tissue Response and Immunoexpression of Interleukin 6 Promoted by Tricalcium Silicate-based Repair Materials after Subcutaneous Implantation in Rats

Andrade, Aline S.; Silva, Guilherme F.; Camilleri, Josette; Cerri, Estela S.; Guerreiro-Tanomaru, Juliane M.; Cerri, Paulo S.; Tanomaru-Filho, Mário

DOI:

[10.1016/j.joen.2017.12.006](https://doi.org/10.1016/j.joen.2017.12.006)

License:

Creative Commons: Attribution-NonCommercial-NoDerivs (CC BY-NC-ND)

*Document Version*

Peer reviewed version

*Citation for published version (Harvard):*

Andrade, AS, Silva, GF, Camilleri, J, Cerri, ES, Guerreiro-Tanomaru, JM, Cerri, PS & Tanomaru-Filho, M 2018, 'Tissue Response and Immunoexpression of Interleukin 6 Promoted by Tricalcium Silicate-based Repair Materials after Subcutaneous Implantation in Rats', *Journal of Endodontics*, vol. 44, no. 3, pp. 458-463. <https://doi.org/10.1016/j.joen.2017.12.006>

[Link to publication on Research at Birmingham portal](#)

## **Publisher Rights Statement:**

Checked for eligibility: 11/04/2018

<https://www.sciencedirect.com/science/article/pii/S0099239917312797>

<https://doi.org/10.1016/j.joen.2017.12.006>

## **General rights**

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

## **Take down policy**

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact [UBIRA@lists.bham.ac.uk](mailto:UBIRA@lists.bham.ac.uk) providing details and we will remove access to the work immediately and investigate.

Manuscript Number: JOE 17-441R1

Title: Tissue response and immunoexpression of IL-6 promoted by tricalcium silicate-based repair materials after subcutaneous implantation in rats

Article Type: Basic Research - Biology

Keywords: Tricalcium Silicate; Zirconium Oxide; Biocompatibility; Immunohistochemistry; Interleukin-6.

Corresponding Author: Dr. Mário Tanomaru-Filho, PhD

Corresponding Author's Institution: Araraquara School of Dentistry

First Author: Aline S Andrade, MSc

Order of Authors: Aline S Andrade, MSc; Guilherme F Silva, PhD; Josette Camilleri, PhD; Estela S Cerri, PhD; Juliane M Guerreiro-Tanomaru, PhD; Paulo S Cerri, PhD; Mário Tanomaru-Filho, PhD

Manuscript Region of Origin: Latin & South America

Abstract: The aim of the present study was to evaluate the inflammatory response induced by experimental tricalcium silicate cement with 20% zirconium oxide (TSC) and MTA Plus (MTAP) in rat subcutaneous tissues. Polyethylene tubes were filled with TSC (n = 20) and MTAP (n = 20), and implanted in the dorsal subcutaneous tissues of thirty two rats. Empty tubes were used as control (CG; n = 20). After 7, 15, 30 and 60 days, the tubes with connective tissue were removed and the inflammatory cells (IC) and immunolabelled cells for interleukin-6 (IL-6) were counted. Data were statistically analyzed by ANOVA and the Tukey tests ( $p \leq 0.05$ ). An increased number of inflammatory and immunolabelled cells for IL-6 were observed at 7 days. The number of inflammatory cells was higher for TSC and MTAP than the GC ( $p < 0.001$ ) at 7 days; after 30 and 60 days, no significant differences were observed among TSC, MTAP and CG ( $p = 0.955$ ). The number of immunolabelled cells for IL-6 was similar for TSC, MTAP and CG at all evaluated periods. A gradual and significant decrease was observed in the number of IC and IL-6-immunopositive cells. At 60 days, the capsules adjacent to TSC and MTAP exhibited fibroblasts and bundles of collagen fibers. The TSC and MTAP caused similar subcutaneous reaction in rats, suggesting that they are biocompatible and present similar immune responses.

**Tissue response and immunoexpression of IL-6 promoted by tricalcium silicate-based repair materials after subcutaneous implantation in rats**

*Aline Silva Andrade<sup>1</sup> DDS, MS, Guilherme Ferreira da Silva<sup>1</sup> DDS, MS, PhD, Josette Camilleri<sup>2</sup> DDS, MS, PhD, Estela Sasso Cerri<sup>3</sup> MS, PhD, Juliane Maria Guerreiro-Tanomaru<sup>1</sup> DDS, MS, PhD, Paulo Sergio Cerri<sup>3</sup> DDS, MS, PhD, and Mario Tanomaru-Filho<sup>1</sup> DDS, MS, PhD*

<sup>1</sup> Department of Restorative Dentistry, Araraquara Dental School, UNESP – São Paulo State University, Araraquara, SP, Brazil;

<sup>2</sup> Department of Restorative Dentistry, Faculty of Dental Surgery, University of Malta, Malta;

<sup>3</sup> Department of Morphology, Araraquara Dental School, UNESP – São Paulo State University, Araraquara, SP, Brazil

The authors deny any conflicts of interest related to this study.

Address requests for reprints to Dr Mario Tanomaru-Filho  
Araraquara Dental School, UNESP – Univ Estadual Paulista, Rua Humaitá 1680, CEP  
14801-903 Araraquara, SP, Brazil  
E-mail address: [tanomaru@uol.com.br](mailto:tanomaru@uol.com.br)  
Phone: +55 16 3301-6390

### **Statement of Clinical Relevance**

- The evaluation of inflammatory response induced by experimental tricalcium silicate cement with 20% zirconium oxide and MTA Plus showed similar subcutaneous reaction in rats, suggesting that they are biocompatible to be used as reparative materials.

## HIGHLIGHTS

- Inflammatory response induced by experimental tricalcium silicate cement with 20% zirconium oxide and MTA Plus was evaluated.
- A gradual decrease was observed in the number of the inflammatory and IL-6-immunopositive cells.
- Tricalcium silicate repair materials caused similar subcutaneous and immune responses in rats, suggesting that they are biocompatible.
- The tricalcium silicate cements may be use as reparative materials.

**Tissue response and immunoexpression of IL-6 promoted by tricalcium silicate-based repair materials after subcutaneous implantation in rats**

**Abstract**

The aim of the present study was to evaluate the inflammatory response induced by experimental tricalcium silicate cement with 20% zirconium oxide (TSC) and MTA Plus (MTAP) in rat subcutaneous tissues. Polyethylene tubes were filled with TSC (n = 20) and MTAP (n = 20), and implanted in the dorsal subcutaneous tissues of thirty two rats. Empty tubes were used as control (CG; n = 20). After 7, 15, 30 and 60 days, the tubes with connective tissue were removed and the inflammatory cells (IC) and immunolabelled cells for interleukin-6 (IL-6) were counted. Data were statistically analyzed by ANOVA and the Tukey tests ( $p \leq 0.05$ ). An increased number of inflammatory and immunolabelled cells for IL-6 were observed at 7 days. The number of inflammatory cells was higher for TSC and MTAP than the GC ( $p < 0.001$ ) at 7 days; after 30 and 60 days, no significant differences were observed among TSC, MTAP and CG ( $p = 0.955$ ). The number of immunolabelled cells for IL-6 was similar for TSC, MTAP and CG at all evaluated periods. A gradual and significant decrease was observed in the number of IC and IL-6-immunopositive cells. At 60 days, the capsules adjacent to TSC and MTAP exhibited fibroblasts and bundles of collagen fibers. The TSC and MTAP caused similar subcutaneous reaction in rats, suggesting that they are biocompatible and present similar immune responses.

**Key Words:** Tricalcium Silicate, Zirconium Oxide, Biocompatibility, Immunohistochemistry, Interleukin-6.

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17

## Introduction

Mineral Trioxide Aggregate (MTA) is a tricalcium silicate-based cement, with bismuth oxide ( $\text{Bi}_2\text{O}_3$ ) as radiopacifier (1). Tricalcium silicate-based biomaterials have demonstrated proper biological and physicochemical properties (2-5). The replacement of  $\text{Bi}_2\text{O}_3$  by other radiopacifiers has been proposed (6-8), since  $\text{Bi}_2\text{O}_3$  interferes in the hydration of MTA (9), resulting in an increase in porosity and reduction of material strength (10). Furthermore, bismuth oxide interferes in cellular proliferation (11) and calcium silicate-based materials containing  $\text{Bi}_2\text{O}_3$  induce inflammatory response in rat subcutaneous tissue (12).

Another disadvantage of some MTA materials is the presence of Portland cement as major component, which may contain heavy metal contamination (13). MTA Plus (MTAP) (Avalon Biomed Inc., Bradenton, FL, USA) is composed of tricalcium silicate and dicalcium silicate added to  $\text{Bi}_2\text{O}_3$  (14). As a material used in the pulpotomies, MTAP produced calcium hydroxide and did not exhibit dental discoloration (15). Moreover, MTAP promoted low immunoeexpression of interleukin- $1\beta$  and  $-1\alpha$ , inflammatory cytokines, and allowed mineralized tissue formation over the pulp tissue of rats (16). Gomes-Cornélio *et al.* demonstrated that MTAP presents biocompatibility and bioactivity in human osteoblast-like cells (17).

A manufactured tricalcium silicate cement [ $(\text{CaO})_3\text{SiO}_2$ , Mineral Research Processing, Meyzieu, France], associated with zirconium oxide ( $\text{ZrO}_2$ ) as a radiopacifier is used as reparative material (18). The association of 80% pure tricalcium silicate (TSC) and 20%  $\text{ZrO}_2$  presents proper properties, such as, solubility, radiopacity, compressive strength, setting time and microhardness (3). Furthermore, this cement in contact with simulated tissue fluid demonstrated bioactivity (3,19). Despite these, until now, there is no other evidence of the biological *in vivo* response of this material reported in the literature.

The aim of the present study was to evaluate the tissue response promoted by TSC and MTAP in rat subcutaneous tissues. Morphological and morphometric analyses and the immunohistochemical reaction for detection of interleukin-6, a pro-inflammatory cytokine, were performed. The null hypothesis was that there would be no difference in tissue reactions caused by TSC and MTAP.

58  
59  
60  
61  
62  
63  
64  
65

## Material and methods

The present research protocol was analyzed and approved by the Ethical Committee for Animal Research of Araraquara Dental School, UNESP, Brazil (Process CEUA No. 33/2014).

In this study thirty two rats were used, distributed into three groups: TSC (Tricalcium silicate, Mineral Research Processing, Meyzieu, France, and 20% ZrO<sub>2</sub>, Sigma Chemicals, St Louis, Missouri, USA), MTAP (MTA Plus<sup>TM</sup> Avalon Biomed Inc., Bradenton, Florida, USA) and CG (Control Group; empty polyethylene tubes). The composition and proportion of the materials evaluated are described in Table 1.

After anesthesia with 80 mg/kg ketamine chloride 10% (Virbac do Brasil Indústria e Comércio Ltda, São Paulo, São Paulo, Brazil) and 8 mg/kg xylazine chloride 2% (União Química Farmacêutica Nacional S/A, São Paulo, São Paulo, Brazil), administered by intraperitoneal route, dorsal skin was shaved and disinfected with 5% iodine solution. A 2 cm incision was made with a n°15 scalpel blade (Fibra Cirúrgica, Joinville, Santa Catarina, Brazil). Afterwards, polyethylene tubes (Embramed Indústria e Comércio Ltda., São Paulo, São Paulo, Brasil), measuring 10 mm long x 1.5 mm in diameter, were filled with TSC or MTAP and immediately implanted into the subcutaneous tissue. The site of the incised skin was sutured with simple stitches using 4-0 silk thread (Ethicon Inc., São José dos Campos, São Paulo, Brazil). Two polythene tubes was used in each animal; 5 animals per group were used in each time point.

After 7, 15, 30 and 60 days of implantation, the animals were euthanized with anesthetic overdose, and the implants with the surrounding tissues were removed. The specimens were immediately immersed in a formaldehyde 4% solution (prepared from paraformaldehyde) buffered with sodium phosphate 0.1 M with pH 7.2, for 48 hours. After fixation, the specimens were dehydrated, treated with the xylene and embedded in paraffin. Longitudinal sections (6 µm thick) were obtained and were stained with hematoxylin and eosin (HE) for morphological analysis and quantification of inflammatory cells in the capsules. Other sections were adhered to slides previously treated with silane 4% (Sigma-Aldrich Co., Saint Louis, Missouri, USA), to perform the immunohistochemical reaction for interleukin-6 (IL-6) detection.



### *Numerical density of inflammatory cells*

The images were obtained with a digital camera (DP-71, Olympus, Tokyo, Japan) attached to a light microscope (BX-51, Olympus, Tokyo, Japan).

The number of inflammatory cells (IC) was quantified using an image analysis system (Image Pro-Express 6.0, Olympus), as previously described (12). The quantitative analysis was performed in all samples or implants; in each implant, three HE-stained sections of the capsule were used at intervals of at least 100  $\mu\text{m}$ . In each section, a standardized field of 0.09  $\text{mm}^2$  of the capsule in close juxtaposition to the opening of implanted tube was captured totalling 0.27  $\text{mm}^2$  per implant. In each field, the number of IC (neutrophils, lymphocytes, plasma cells and macrophages) was computed. In this way, in each implant, the number of IC/ $\text{mm}^2$  was obtained. The numerical density of inflammatory cells was measured by two calibrated and blinded examiners.

### *Immunohistochemical reaction for detection of IL-6*

For IL-6 detection, the primary goat antibody anti-IL-6 (Santa Cruz Biotechnology Inc., Santa Cruz, California, USA) was used. Deparaffinized sections were immersed in 0.001 M sodium citrate buffer with pH 6.0, and submitted to microwave oven cycles for 20 minutes at 90-94°C for antigen retrieval. After cooling, the slides were washed in 0.05 M Tris-HCl buffer with pH 7.4, and subsequently immersed in 5% hydrogen peroxide for 20 minutes, for blocking endogenous peroxidase. After washing, the sections were incubated with 2% bovine serum albumin (Sigma-Aldrich Co., Saint Louis, Missouri, USA), for 20 minutes. Sections were incubated overnight in a humid chamber at 4°C with anti-IL-6 antibody, diluted 1:100.

Subsequent to washing in Tris-HCl buffer, the sections were incubated for 40 minutes at room temperature with a multi-link solution containing biotinylated rabbit/mouse/goat antibodies (LSAB, Dako Inc., Carpinteria, California, USA). After washing in Tris-HCl buffer, the sections were incubated with HRP complex (System-HRP, Dako Inc., Carpinteria, California, USA), for 40 minutes at room temperature. Subsequent to washing in buffer, peroxidase activity was revealed by the chromogen 3,3-diaminobenzidine-HCl (DAB, Dako Inc., Carpinteria, California, USA) for 3 minutes. The sections were counterstained with Carazzi's hematoxylin. As negative control, some sections were submitted to all the stages, except incubation with primary antibody; in this step the sections were incubated in non-immune serum.

1  
2 *Numerical Density of cells positive for IL-6*

3  
4 With the purpose of verifying whether there were differences among the groups,  
5 the number of IL-6-immunolabeled cells was estimated in the capsules of the 5 implants  
6 of each group/time point. As previously described, the Image Pro-Express 6.0 Olympus  
7 software was used. The numerical density of IL-6-immunolabeled cells was obtained by  
8 two calibrated and blinded examiners. For each animal, the number of immunolabeled  
9 cells was quantified at x695, in a standardized field (0.09 mm<sup>2</sup>) of the capsule in close  
10 juxtaposition to the opening of the implanted tube. Thus, the number of IL-6  
11 immunolabeled/mm<sup>2</sup> per animal was obtained (8,12).  
12  
13  
14  
15  
16  
17  
18  
19

20 *Statistical Analysis*

21  
22 The quantitative data were submitted to statistical analysis by using the Sigma  
23 Stat 2.0 program (Jandel Scientific, Sausalito, California, USA). After normality was  
24 confirmed, the two-way ANOVA and Tukey tests were used, at a level of significance  
25 of 5%.  
26  
27  
28  
29  
30

31 **Results**

32 *Morphological and numerical density analysis of inflammatory cells*

33  
34 At 7 days, the capsules in all the groups exhibited several inflammatory cells,  
35 mainly lymphocytes and macrophages among the blood vessels (Figs. 1A-1C). At 15  
36 days, the capsules contained fibroblasts and collagen fibers, particularly in TSC and  
37 CG. However, inflammatory cells and blood vessels were still clearly observed in the  
38 capsules (Figs. 1D and 1F). Occasionally, some multinucleated giant cells were also  
39 observed, mainly in the internal portion of the capsules, adjacent to the materials (Fig.  
40 1D). After 30 and 60 days, the connective tissue of the capsules contained several  
41 fibroblasts between the collagen fiber bundles; the scarce inflammatory cells were  
42 represented by plasma cells, macrophages and mast cells (Figs. 2A-2F).  
43  
44  
45  
46  
47  
48  
49  
50

51 Quantitative analysis revealed that in all the groups, the number of inflammatory  
52 cells was significantly higher at 7 days. After this period, the statistical analysis of each  
53 group revealed a gradual and significant reduction in the number of inflammatory cells  
54 in the capsules of all groups (p<0.001) over time. At 7 days, no significant differences  
55 were verified between TSC and MTAP (p=0.592), however, these values were  
56 statistically higher in comparison with those of the control group (p<0.001). In turn, in  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

the periods of 30 and 60 days, no significant differences were observed among TSC, MTAP and control group (p=0.955) (Table 2).

#### *Immunohistochemical detection of IL-6 and numerical density of immunopositive cells*

The sections of capsules submitted to the immunohistochemical reaction for IL-6 showed inflammatory cells (lymphocytes, plasma cells, macrophages and mast cells) and some fibroblasts exhibiting positivity to immunoreaction. Morphological analysis revealed immunolabeled cells in the capsules of all the groups; however, an accentuated immunopositivity was observed in the capsules at 7 days in comparison with the other periods (Figure 3). On the other hand, sections of capsules incubated without the primary antibody (negative control) exhibited no immunopositive cells (data not illustrated).

According to Table 2, the number of IL-6-immunolabeled cells was significantly higher at 7 days than at 15, 30 and 60 days. In all the groups, the number of immunolabeled cells was significantly reduced from 7 to 60 days. However, no statistically significant differences were detected among TSC, MTAP and CG, in any of the periods.

#### **Discussion**

Histopathological analysis of the subcutaneous response after different experimental periods evaluate not only the tissue characteristics to irritant potential but also the duration of this effect on tissues (5,20,21).

The present study showed that the TSC and MTAP induced an inflammatory reaction in the subcutaneous tissues. However, this reaction was gradually reduced, leading to the formation of dense connective tissue in the capsules. The reduction in the inflammatory reaction occurred concomitantly with the reduction in the immunoexpression of IL-6 in the capsules adjacent to the materials, indicating that the experimental TSC cement and MTAP are biocompatible materials. The inflammatory reaction initially caused by TSC and MTAP may be related to the hydroxyls (OH<sup>-</sup>) released after hydration of the materials, providing an environment with an alkaline pH (3,14,18). The alkaline pH stimulates recruitment of the leukocytes of the blood vessels (8,12,22,23) and therefore, may explain the higher values of inflammatory cells verified in the initial time point.

1 The tissue reaction observed is a consequence of the host response to substances  
2 released by the materials. Therefore, the host cells (inflammatory and resident) produce  
3 and release several cytokines and growth factors that play a specific role in the complex  
4 cascade of cellular events involved in the tissue response. Among the different  
5 cytokines, IL-6 is considered a powerful mediator of the inflammatory process (24).  
6  
7

8  
9 An association has been observed between the reduction in immunoexpression  
10 of IL-6 and a reduction in the inflammatory process in the capsules adjacent to the  
11 calcium silicate-based cements implanted in the rat subcutaneous tissues (8,12),  
12 indicating that these materials do not have an irritating effect on connective tissue  
13 during a prolonged period.  
14  
15  
16  
17

18 The gradual and significant reduction in the number of immunolabeled cells for  
19 IL-6 suggests that the capsules adjacent to the materials implanted undergo an intense  
20 remodeling process from 7 to 60 days. Moreover, our results point out that this cytokine  
21 may be involved in the response promoted by tricalcium silicate-based materials,  
22 because a reduction in both immunolabeled cells for IL-6 and in the number of  
23 inflammatory cells was observed. Considering that no significant differences in the IL-6  
24 immunoexpression was observed for TSC and MTAP compared with the control group,  
25 it is possible to suggest low irritant potential of the materials to the tissues. In spite of  
26 this, materials promoted a greater recruitment of inflammatory cells than the empty  
27 tube. Therefore, these materials may release some substances that stimulate the  
28 migration and differentiation of cells, such as macrophages and plasma cells, frequently  
29 observed in the capsules at 7 days. However, the inflammatory process was replaced by  
30 a capsule containing well-developed bundles of collagen fibers between fibroblasts at  
31 30 and 60 days after implantation. This tissue response indicates that the materials are  
32 biocompatible.  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44

45 It has been demonstrated that  $ZrO_2$  added to calcium silicate cement promotes  
46 adequate physicochemical properties and a better biologic response than  $Bi_2O_3$  (12).  
47 Nevertheless, in the present study, MTAP which presents  $Bi_2O_3$  promoted a  
48 subcutaneous tissue response similar to that of TSC. The hypothesis for this finding  
49 may be related to the fact that MTAP does not have Portland cement in its composition  
50 but instead it has tricalcium silicate (approximately 50%), dicalcium silicate, calcium  
51 sulphate and silicon dioxide in addition to  $Bi_2O_3$  (approximately 30%). The substitution  
52 of Portland cement by tricalcium silicate and dicalcium silicate allows better control of  
53 heavy metals that are found in the MTA (18), favoring the hydration reaction (3).  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

1  
2 **Conclusion**

3  
4 The TSC and MTAP caused similar subcutaneous implantation reaction in rats,  
5 indicating that both present similar immune response. The significant reduction in the  
6 inflammatory reaction accompanied by decrease in the IL-6 immunoexpression in the  
7 capsules over time indicates that these tricalcium silicate-based materials may have  
8 potential as root repair material.  
9  
10  
11  
12  
13  
14

15 **Acknowledgements**

16  
17  
18 The authors thank to Mr. Pedro Sérgio Simões and Mr. Luis Antonio Potenza for  
19 kind help and technical assistance.  
20

21  
22 This study was supported by São Paulo Research Foundation (FAPESP – n°  
23 2015/03437-6 and 2014/13353-1).  
24  
25  
26

27 **The authors deny any conflicts of interest related to this study.**  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

## References

1. Camilleri J, Montesin FE, Brady K, Sweeney R, Curtis RV, Pitt Ford TR. The constitution of mineral trioxide aggregate. *Dent Mater* 2005;21:297–303.
2. Camilleri J, Sorrentino F, Damidot D. Investigation of the hydration and bioactivity of radiopacified tricalcium silicate cement, Biodentine and MTA Angelus. *Dent Mater* 2013;29:580-93.
3. Grech L, Mallia B, Camilleri J. Investigation of the physical properties of tricalcium silicate cement-based root-end filling materials. *Dent Mater* 2013;29:20-8.
4. Camilleri J, Laurent P, About I. Hydration of Biodentine, Theracal LC, and a prototype tricalcium silicate-based dentin replacement material after pulp capping in entire tooth cultures. *J Endod* 2014;40:1846-54.
5. Taha NA, Safadi RA, Alwedaie MS. Biocompatibility evaluation of EndoSequence root repair paste in the connective tissue of rats. *J Endod* 2016;42:1523-27.
6. Bortoluzzi EA, Guerreiro-Tanomaru JM, Tanomaru-Filho M, Duarte MA. Radiographic effect of different radiopacifiers on a potential retrograde filling material. *Oral Surg Oral Med Oral Pathol Oral Radiol Endod* 2009;108:628-32.
7. Camilleri J, Cuttajar A, Mallia B. Hydration characteristics of zirconium oxide replaced Portland cement for use as a root-end filling material. *Dent Mater* 2011;27:845-54.
8. Silva GF, Tanomaru-Filho M, Bernardi MIB, Guerreiro-Tanomaru JM, Cerri PS. Niobium pentoxide as radiopacifying agent calcium silicate-based material: evaluation of physicochemical and biological properties. *Clin Oral Invest* 2015;19:2012-25.
9. Camilleri J. Hydration mechanisms of mineral trioxide aggregate. *Int Endod J* 2007;40:462-70.
10. Coomaraswamy KS, Lumley PJ, Hofmann MP. Effect of bismuth oxide radioopacifier content on the material properties of an endodontic Portland cement based (MTA-like) system. *J Endod* 2007;33:295–8.
11. Camilleri J, Montesin FE, Papaioannou S, McDonald F, Pitt Ford TR. Biocompatibility of two commercial forms of mineral trioxide aggregate. *Int Endod J* 2004;37:699-704.
12. Silva GF, Bosso R, Ferino RV et al. Microparticulated and nanoparticulated zirconium oxide added to calcium silicate cement: evaluation of physicochemical and biological properties. *J Biomed Mater Res A* 2014;102:4336-45.

- 1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65
13. Chang SW, Shon WJ, Lee W, Kum KY, Baek SH, Bae KS. Analysis of heavy metal contents in gray and white MTA and 2 kinds of Portland cement: a preliminary study. *Oral Surg Oral Med Oral Pathol Oral Radiol Endod* 2010;109:642-6.
14. Formosa LM, Mallia B, Camilleri J. Mineral trioxide aggregate with anti-washout gel - properties and microstructure. *Dent Mater* 2013;29:294-306.
15. Camilleri, J. Staining Potential of Neo MTA Plus, MTA Plus, and Biodentine Used for Pulpotomy Procedures. *J Endod* 2015;41:1139-45.
16. Kramer PR, Woodmansey KF, White R, Primus CM, Opperman LA. Capping a pulpotomy with calcium aluminosilicate cement: comparison to mineral trioxide aggregates. *J Endod* 2014;40:1429-34.
17. Gomes-Cornélio AL, Rodrigues EM, Salles LP et al. Bioactivity of MTA Plus, Biodentine and an experimental calcium silicate-based cement on human osteoblast-like cells. *Int Endod J* 2017;50:39-47.
18. Formosa LM, Mallia B, Camilleri J. The effect of curing conditions on the physical properties of tricalcium silicate cement for use as a dental biomaterial. *Int Endod J* 2012;45:326-36.
19. Camilleri J, Formosa L, Damidot. The setting characteristics of MTA Plus in different environmental conditions. *Int Endod J* 2013;46: 831-40.
20. Zmener O. Tissue response to a new methacrylate-based root canal sealer: preliminar observations in the subcutaneous connective tissue of rats. *J Endod* 2004;30:348-51.
21. Shahi S, Rahimi S, Lotfi M, et al. A comparative study of the biocompatibility of three root-end filling materials in rat connective tissue. *J Endod* 2006;32:776-80.
22. Vosoughhosseini S, Lotfi M, Shahi S et al. Influence of white versus gray mineral trioxide aggregate on inflammatory cells. *J Endod* 2008;34:715-7.
23. Shahi S, Rahimi S, Yavari HR et al. Effect of mineral trioxide aggregates and Portland cements on inflammatory cells. *J Endod* 2010;36:899-903.
24. Azuma MM, Samuel RO, Gomes-Filho JE, Dezan-Junior E, Cintra LT. The role of IL-6 on apical periodontitis: a systematic review. *Int Endod J* 2014;47:615-21.

**Figure legends:**

**Figure 1** – Light micrographs of sections showing portions of capsules adjacent to the opening of the tubes implanted (T) in the subcutaneous tissue after 7 (**Figs. 1A-1C**) and 15 (**Figs. 1D-1F**) days. In **Figs. 1A, 1B** and **1C**, several inflammatory cells (arrows) are observed, mainly, in the portion of the capsule adjacent to the opening of the tubes (T). N, neutrophil; Bv, blood vessels. **Figs. 1D, 1E** and **1F**, exhibit inflammatory cells (arrows) among blood vessels (Bv) and fibroblasts (Fb). Gc, giant cells. HE. 695x.

**Figure 2** – Light micrographs of sections showing portions of capsules adjacent to the opening of the tubes implanted (T) in the subcutaneous tissue after 30 (**Figs. 2A-2C**) and 60 (**Figs. 2D-2F**) days. Typical fibroblasts (Fb) are observed among bundles of collagen fibers (Cf) in the capsules. Few inflammatory cells (arrows) are present, mainly in the capsules of MTAP and control group. Mp, macrophages; P, plasma cells; M, mast cells; Bv, blood vessels. HE. 695x.

**Figure 3** – Light micrographs of sections showing portions of capsules adjacent to the opening of the tubes (T) implanted in the subcutaneous tissue after 7 (**Figs. 3A-3C**), 15 (**Figs. 3D-3F**), 30 (**Figs. 3G-3I**) and 60 (**Figs. 3J-3L**) days of implantation. Sections were submitted to immunohistochemistry reaction for IL-6 detection and counterstained with haematoxylin. Several immunolabeled cells (arrows; brown/yellow colour), especially, plasma cells, mast cells and some fibroblasts (Fb) are observed in the capsules at 7 and 15 days. At 60 days, scarce cells exhibit immunolabelling for IL-6. Bv, blood vessels. 500x.



1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22

**Tables:**

**Table 1** – Materials evaluated and used proportions.

Group	Material	Composition	Proportion (powder/distilled water)
TSC	Cement tricalcium silicate* with 20% ZrO <sub>2</sub> **	Tricalcium Zirconium oxide silicate,	1g/ 340 µL
MTAP	White Mineral Trioxide Aggregate***	Tricalcium Dicalcium Sulphate, Oxide Silicate, Calcium Silica, Bismuth Oxide	1g/ 340 µL

23  
24  
25  
26  
27  
28  
29  
30  
31

\* Mineral Research Processing, Meyzieu, France

\*\* Sigma Chemicals, St Louis, Missouri, USA

\*\*\* MTA Plus<sup>TM</sup> Avalon Biomed Inc., Bradenton, Florida, USA

32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52

**Table 2** – Numerical density of inflammatory cells (IC) and IL-6 immunolabeled cells in the capsules of TSC, MTAP e control groups at 7, 15, 30 and 60 days.

	TSC	MTAP	control
<b>7 days</b>			
IC	482.5 (45.9) <sup>b,1</sup>	448.8 (34.8) <sup>b,1</sup>	324.0 (29.9) <sup>a,1</sup>
IL-6	475.5 (16.4) <sup>a,1</sup>	480.0 (14.4) <sup>a,1</sup>	464.4 (19.8) <sup>a,1</sup>
<b>15 days</b>			
IC	185.1 (28.2) <sup>ab,2</sup>	214.8 (43.6) <sup>b,2</sup>	154.0 (8.1) <sup>a,2</sup>
IL-6	186.6 (18.2) <sup>a,2</sup>	195.5 (12.6) <sup>a,2</sup>	182.2 (12.6) <sup>a,2</sup>
<b>30 days</b>			
IC	160.0 (30.3) <sup>a,2</sup>	135.5 (29.0) <sup>a,3</sup>	148.8 (8.0) <sup>a,2</sup>
IL-6	148.8 (18.5) <sup>a,3</sup>	151.1 (14.9) <sup>a,3</sup>	144.4 (17.5) <sup>a,3</sup>
<b>60 days</b>			
IC	71.1 (9.5) <sup>a,3</sup>	70.3 (16.1) <sup>a,4</sup>	69.0 (6.5) <sup>a,3</sup>
IL-6	75.9 (8.9) <sup>a,4</sup>	75.5 (9.3) <sup>a,4</sup>	71.1 (9.9) <sup>a,4</sup>


53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

\*mean (standard deviation) The comparison amongst groups (p<0.05) is indicated by different superscript (a, b, c and d) in the various lines.

The comparison amongst periods (p<0.05) is indicated by number superscripts in the various columns.

**Figure 1**  
[Click here to download high resolution image](#)



1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

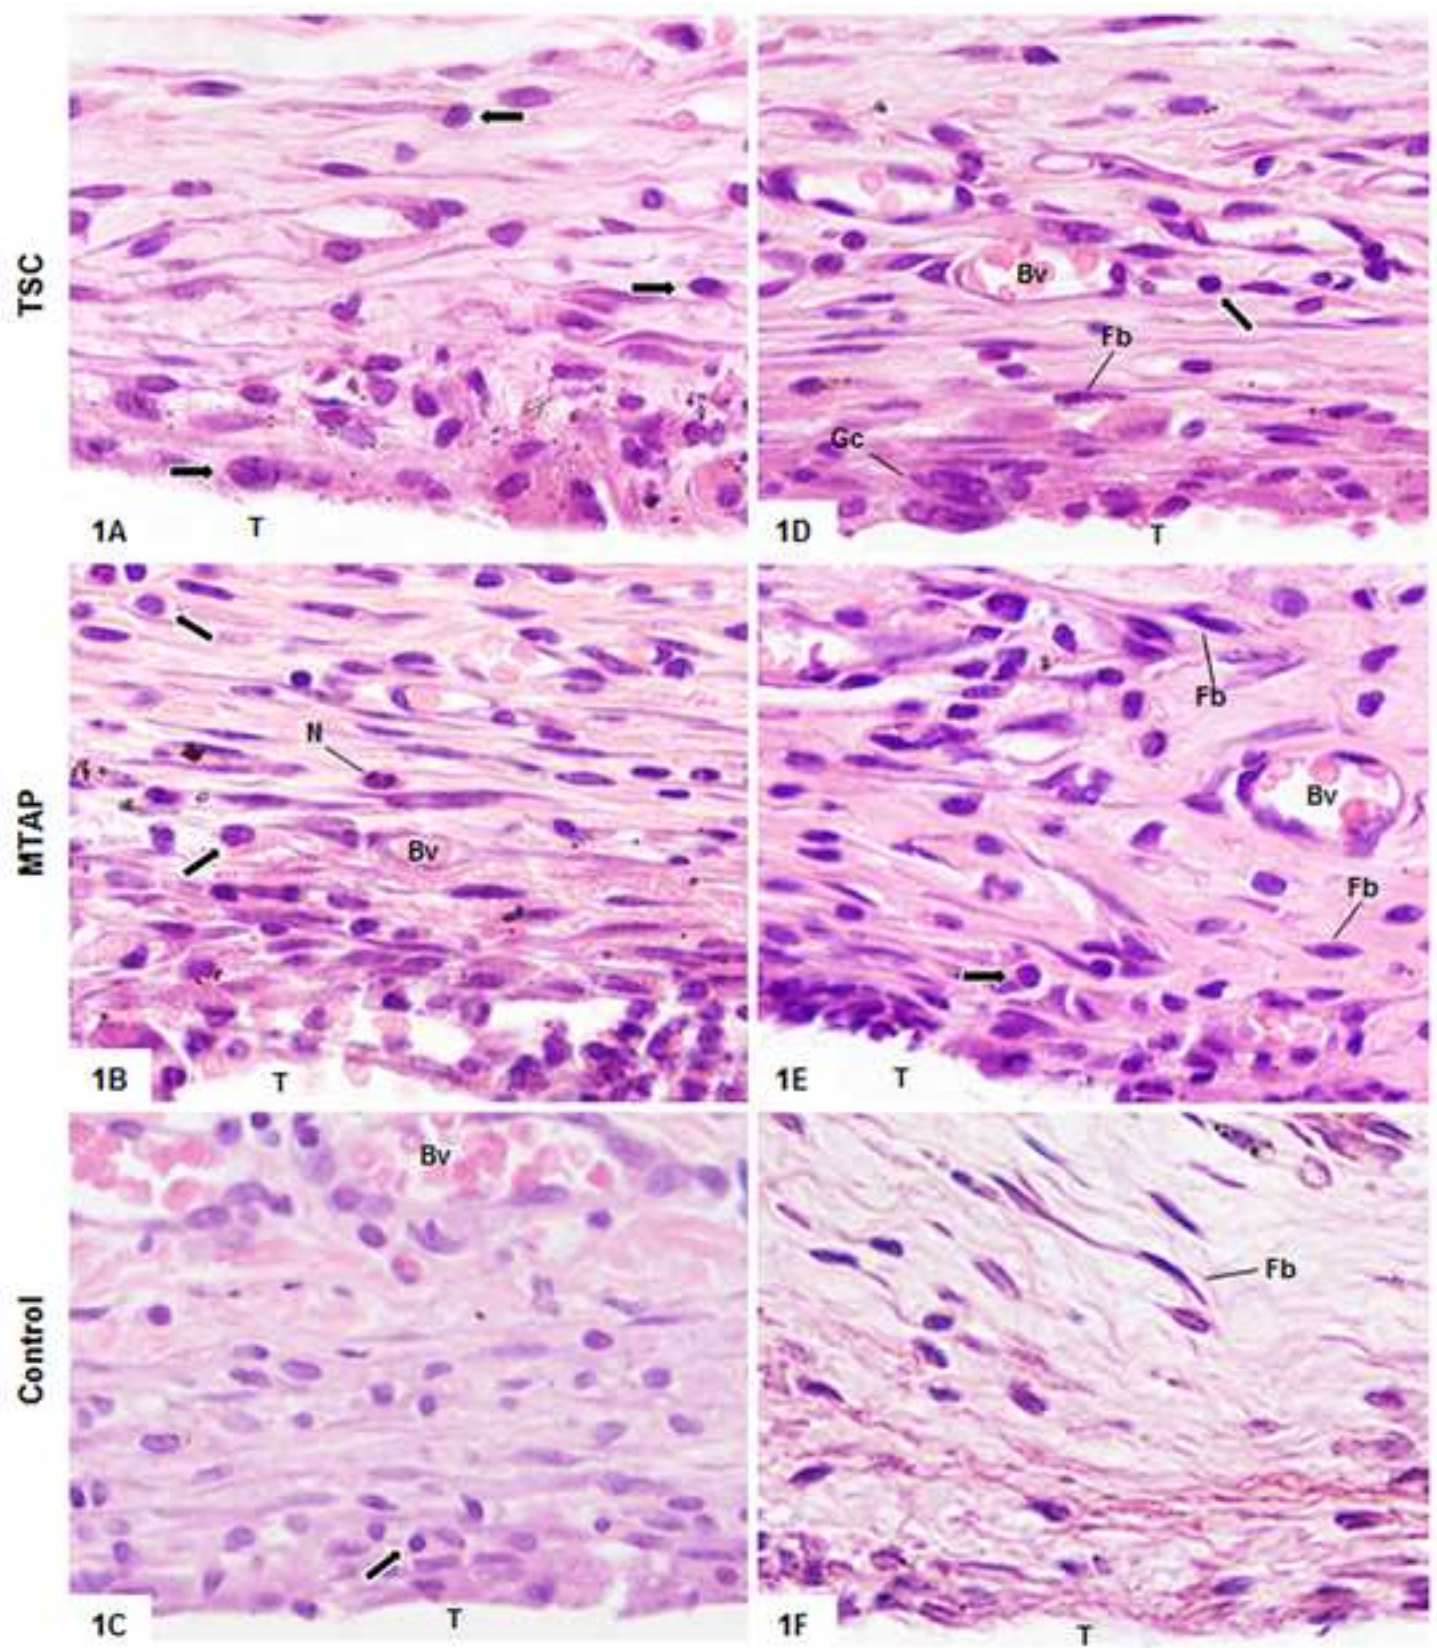



**Figure 2**  
[Click here to download high resolution image](#)

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65



**TSC**

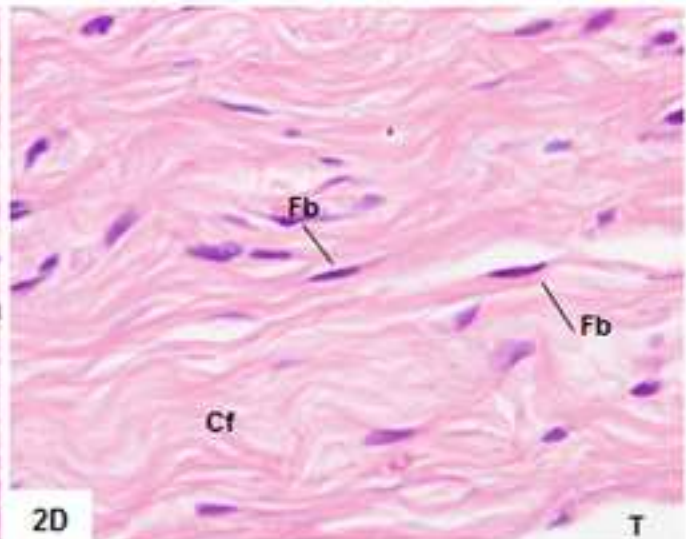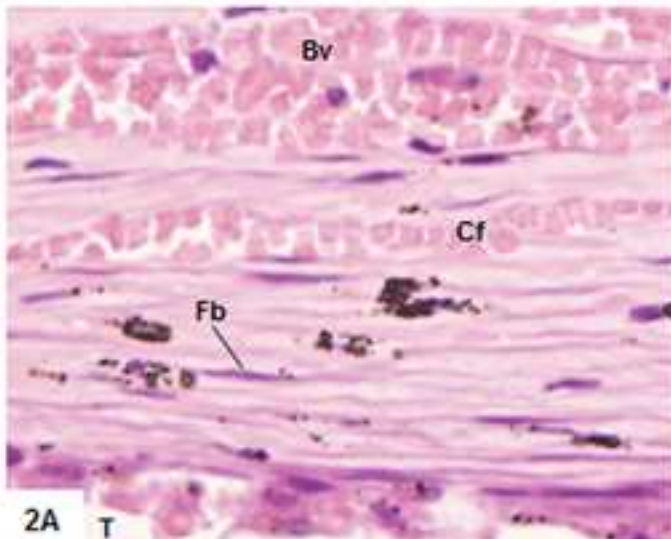

**MTAP**

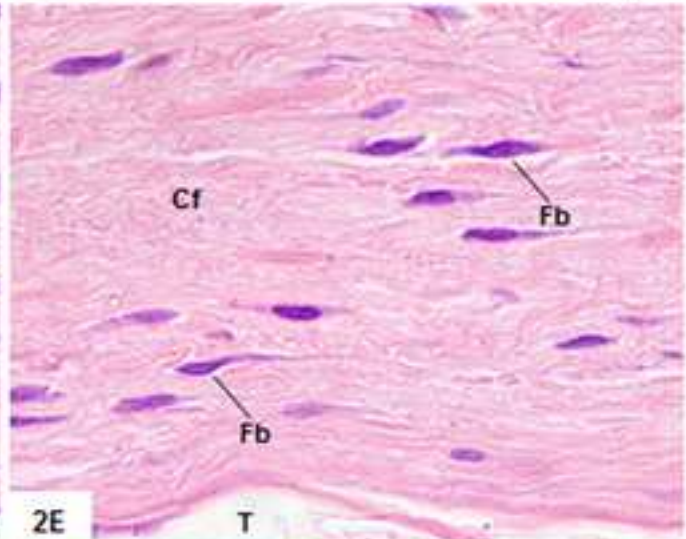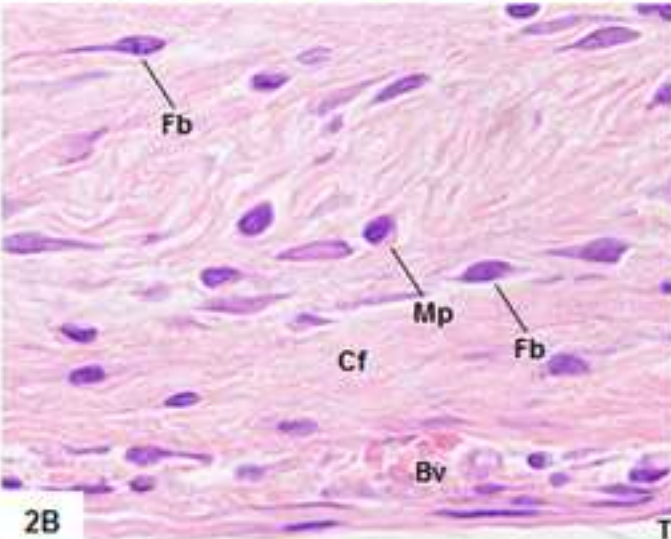


**Control**

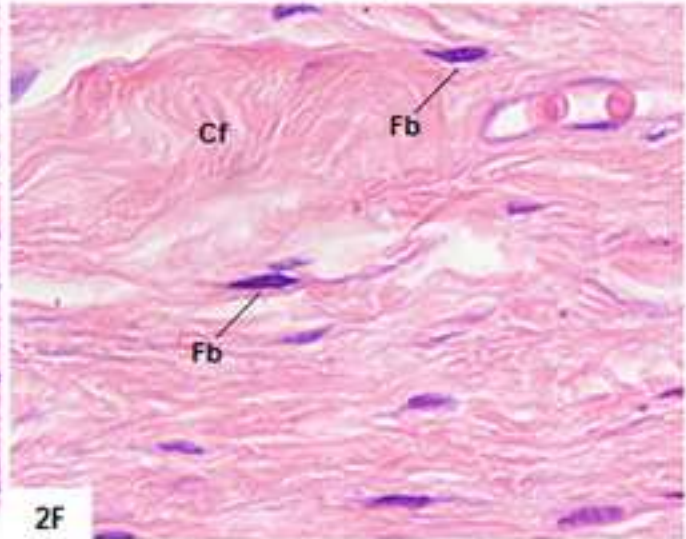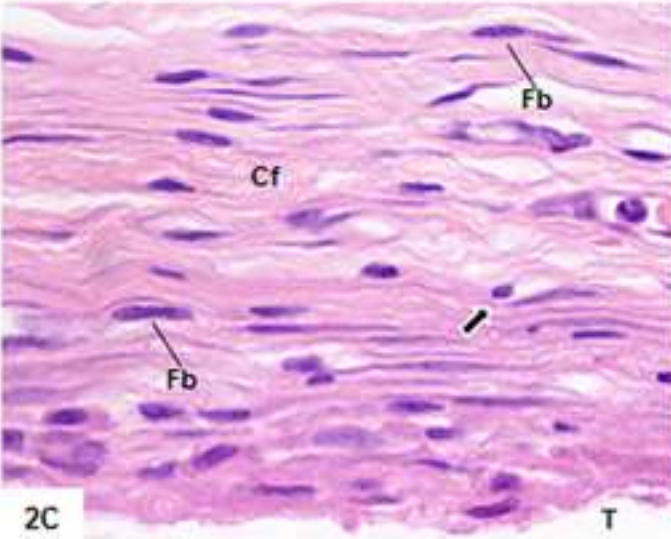

**Figure 3**  
[Click here to download high resolution image](#)

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

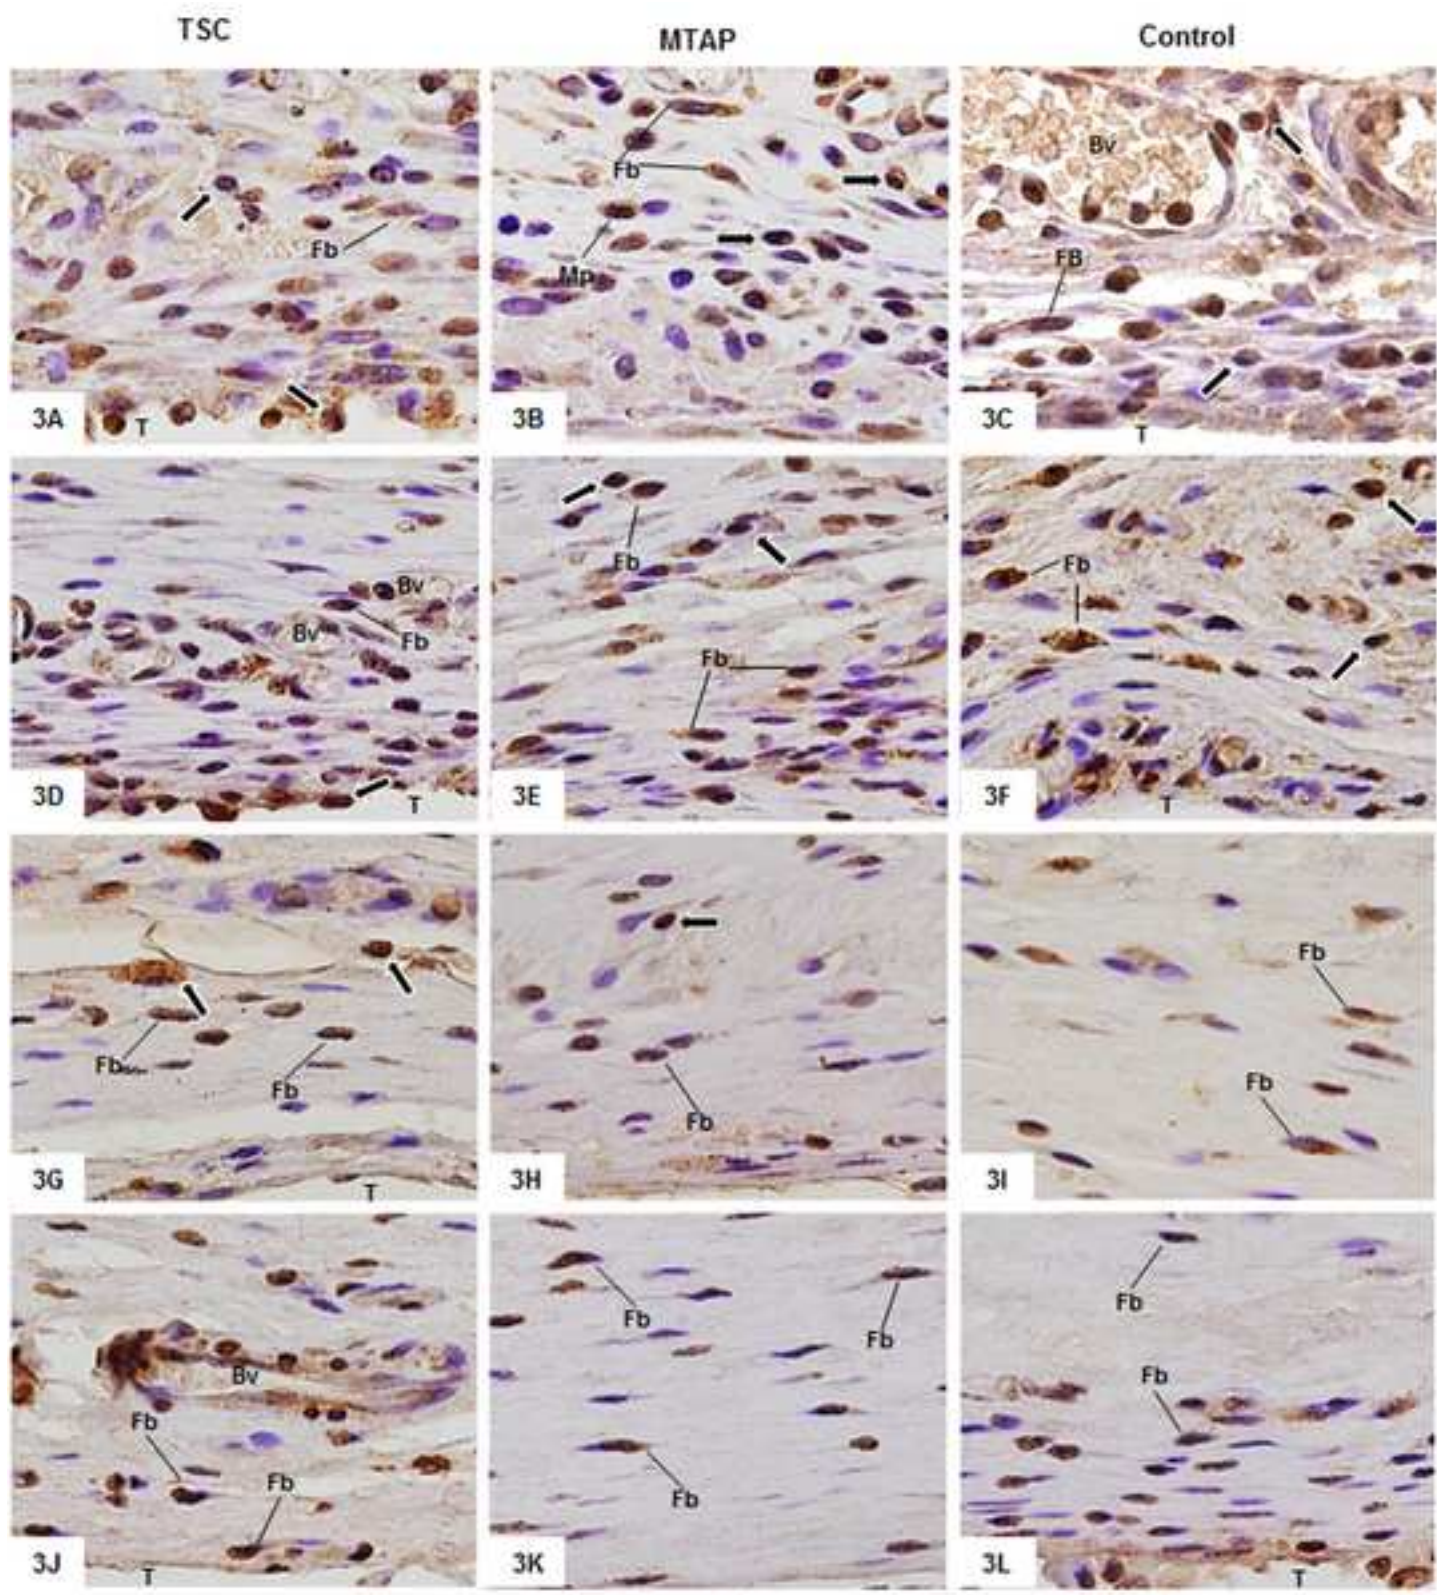

## Author's Point-by-Point Response to Reviewers

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

*Reviewers' comments:*

*Reviewer #1:*

Introduction

*1. Paragraph 1. Reference 7 not applicable here; join with reference 9 instead?*

A: Reference 7 (Camilleri et al., 2011) is related to a study of some characteristics, such as, microstructure and pH, of Portland cement with zirconium oxide. The authors stated that zirconium oxide is inert and can be used as a substitute of bismuth oxide. On the other hand, reference 9 (Camilleri 2007) evaluate the hydration mechanisms of calcium silicate materials with bismuth oxide. That is why we used the reference in the text.

*2. Paragraph 2. Line 24. Change to, "as a material used in pulpotomies...". Line 31: move the reference (17) to the end of the sentence.*

A: The corrections were performed in the text.

*3. Paragraph 3. Line 36. Change to, "as a radiopacifier...". Line 45: change to, "There is no other evidence of the biological in vivo response of this material reported in the literature."*

A: The corrections were performed in the text.

*4. Paragraph 4. Line 48. Remove "thus"; remove since this method determined...". Line 55 change to " ...there would be no difference..."*

A: The corrections were performed in the text.

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65

## Material and Methods

*1. Paragraph 3. Why not use an unbranded, monofilament suture to decrease inflammatory response.*

A: We really appreciate the suggestion and it will be considered for future studies. However, incision was performed in the centre of dorsal subcutaneous and the pockets, where tubes were implanted, were performed at a distance of 10 mm. Based on the histological images, we believe that the inflammatory response caused by the incision and its healing process does not interfere with the tissue reaction of the materials.

*2. Immunohistochemical reaction for detection of IL-6: Paragraph 2. Line 60. "In this step the sections were incubated in non-immune...?"*

A: We have made the correction.

## Discussion.

*1. Paragraph 5. Lines 35-42. Consider shortening this into 2-3 sentences instead of one. General rule is that shorter sentences allow for better reading comprehension.*

A: We have made the corrections

## References.

*1. Recommendations as stated above.*

A: We have made the corrections.

## Legends.

*1. Add "tissue" after "subcutaneous".*

A: We have made the corrections.


December 05, 2017.

The manuscript title

**Tissue response and immunoexpression of IL-6 promoted by tricalcium silicate-based repair materials after subcutaneous implantation in rats**

In consideration of the Editors of the Journal of Endodontics taking action in reviewing and editing this submission, the author(s) undersigned hereby transfer, assign, or otherwise convey all copyright ownership to the AAE in the event that such work is published in that Journal."

I affirm that I have no financial affiliation (e.g., employment, direct payment, stock holdings, retainers, consultantships, patent licensing arrangements, or honoraria) or involvement with any commercial organization with direct financial interest in the subject or materials discussed in this manuscript, nor have any such arrangements existed in the past three years. Any other potential conflict of interest is disclosed.



Aline Silva Andrade




Guilherme Ferreira da Silva



Josette Camilleri



Estela Sasso Cerri



Juliane Maria Guerreiro-Tanomaru



Paulo Sergio Cerri



Mário Tanomaru-Filho

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60  
61  
62  
63  
64  
65