

# Electrocatalytic regeneration of atmospherically aged MoS<sub>2</sub> nanostructures via solution-phase sulfidation

Burch, H. A.; Isaacs, M.; Wilson, K.; Palmer, Richard; Rees, N. V.

DOI:  
[10.1039/C6RA03326A](https://doi.org/10.1039/C6RA03326A)

License:  
Creative Commons: Attribution (CC BY)

*Document Version*  
Publisher's PDF, also known as Version of record

*Citation for published version (Harvard):*  
Burch, HA, Isaacs, M, Wilson, K, Palmer, R & Rees, NV 2016, 'Electrocatalytic regeneration of atmospherically aged MoS<sub>2</sub> nanostructures via solution-phase sulfidation', *RSC Advances*, vol. 6, no. 32, pp. 26689-26695.  
<https://doi.org/10.1039/C6RA03326A>

[Link to publication on Research at Birmingham portal](#)

## General rights

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

## Take down policy

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact [UBIRA@lists.bham.ac.uk](mailto:UBIRA@lists.bham.ac.uk) providing details and we will remove access to the work immediately and investigate.



CrossMark  
click for updates

Cite this: *RSC Adv.*, 2016, 6, 26689

# Electrocatalytic regeneration of atmospherically aged MoS<sub>2</sub> nanostructures *via* solution-phase sulfidation†

H. A. Burch,<sup>ab</sup> M. Isaacs,<sup>c</sup> K. Wilson,<sup>c</sup> R. E. Palmer<sup>b</sup> and N. V. Rees<sup>\*a</sup>

The performance of MoS<sub>2</sub> as a hydrogen evolution catalyst is diminished by exposure to air. We demonstrate a solution phase technique to resulfidate MoS<sub>x</sub>O<sub>2-x</sub> using Na<sub>2</sub>S<sub>2</sub>O<sub>3</sub>. The success of the method was judged by performance as a H<sup>+</sup> reduction catalyst. Following sulfidation samples displayed a favourable decrease in both onset potential and Tafel slope, with the best decreasing from -0.23 V to -0.18 V (vs. SHE), and 282 mV dec<sup>-1</sup> to 87 mV dec<sup>-1</sup> respectively. Ageing studies indicate that this method may be used to recycle the MoS<sub>2</sub> repeatedly without losing catalytic performance, although repeated sulfidation did result in homogenisation of the nanostructure.

Received 4th February 2016


Accepted 4th March 2016

DOI: 10.1039/c6ra03326a


[www.rsc.org/advances](http://www.rsc.org/advances)

## Introduction

MoS<sub>2</sub> is an earth abundant, 2D-layered transition metal dichalcogenide (TMD) which is already deployed in hydrodesulfurisation catalysis,<sup>1,2</sup> electrocatalysis,<sup>3,4</sup> and shows potential for photoelectrocatalysis (PEC).<sup>5,6</sup> One application is the photoelectrocatalytic hydrogen evolution reaction (HER).



This in conjunction with the oxygen evolution reaction (OER) (eqn (2)) comprises photoelectrocatalytic water splitting.<sup>7</sup>



In order for spontaneous light driven water splitting to proceed the free-energy stored in the photogenerated electron–holes pairs must exceed the energy separation between the H<sup>+</sup>/H<sub>2</sub> and O<sub>2</sub>/H<sub>2</sub>O redox energy levels (1.23 V at 298 K).<sup>8</sup> In practice an overpotential is also required to drive the separation of charge carriers.<sup>8</sup> This can be achieved either by one material which straddles the water splitting redox energy levels, or two or more materials with overlapping bandgaps connected in tandem.<sup>9</sup> MoS<sub>2</sub> meets the requirements for PEC HER as it is catalytically active for HER, and absorbs sufficient light to generate an electron–hole pair with enough potential to drive the HER.<sup>10</sup> The free energy level of the conduction band is also negative of the reduction potential of H<sup>+</sup>/H<sub>2</sub>.<sup>8,11</sup>

Nanopatterning is common technique used to adapt the band gap, as well as increasing the number of active edge sites.<sup>10</sup> Various nanostructuring techniques have been applied to attempt to improve the catalytic properties of MoS<sub>2</sub> including: electrodeposition,<sup>3</sup> cluster deposition,<sup>12</sup> sonochemical synthesis,<sup>13</sup> chemical vapour deposition,<sup>14</sup> and chemical exfoliation.<sup>15</sup>

The basal plane of MoS<sub>2</sub> is inert for the HER, while the (10 $\bar{1}$ 0) edge sites are catalytically active.<sup>5,16</sup> The initial step of the HER is the binding of hydrogen to sulfur atoms on the Mo-edge (10 $\bar{1}$ 0),<sup>5</sup> however these edge sites adsorb oxygen at room temperature.<sup>17</sup> Due to this poor stability is an issue with MoS<sub>2</sub> electrocatalysis, although long term performance has not been studied in depth.<sup>18</sup>

Little attention has been paid to restoring the functionality of MoS<sub>2</sub> partially oxidised to MoS<sub>x</sub>O<sub>(2-x)</sub> in air. To address this issue nanopatterned MoS<sub>2</sub> was prepared using nanosphere lithography and plasma etching<sup>19,20</sup> in order to produce a larger number of catalytically active edge sites, these sites were then allowed to oxidise in air before regeneration. In this paper we present a rapid, room temperature, solution-phase method to sulfidise air-exposed MoS<sub>2</sub> through electrochemical deposition of sulfur from a sodium thiosulfate solution. Although MoS<sub>2</sub> has been synthesised in the solution phase using Na<sub>2</sub>S<sub>2</sub>O<sub>3</sub> and a Mo ion source,<sup>21</sup> this technique has not been applied to restoring the functionality of air-exposed MoS<sub>2</sub>, nor has MoS<sub>2</sub> synthesised *via* this method been investigated for HER.<sup>22</sup> This method avoids the use of toxic chemicals such as H<sub>2</sub>S, Na<sub>2</sub>S, or vapourised sulfur at high temperature employed in many current methods to synthesise MoS<sub>2</sub> from MoO<sub>x</sub>.<sup>23–26</sup> The sulfidation process was analysed physically through SEM and XPS, and electrochemically *via* the electrochemical reduction of protons on the air-exposed MoS<sub>2</sub> before and after sulfidation. The electrode surfaces before and after sulfur deposition have been imaged by SEM, and the chemical composition confirmed by XPS.

<sup>a</sup>School of Chemical Engineering, University of Birmingham, UK. E-mail: N.Rees@Bham.ac.uk

<sup>b</sup>Nanoscale Physics Research Laboratory (NPRL), University of Birmingham, UK

<sup>c</sup>European Bioenergy Research Institute (EBRI), Aston University, UK

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c6ra03326a




It was found that the sulfidation results in an increase in MoS<sub>2</sub> composition from 49.5% to 58%. This increase in MoS<sub>2</sub> composition had a beneficial effect on the cyclic voltammetry of the sample, resulting in a lower overpotential for the HER as evidenced by the decrease in onset potential from  $-0.23$  V SHE to  $-0.18$  V, plus a decrease in the Tafel slope from  $282$  mV dec<sup>-1</sup> to  $87$  mV dec<sup>-1</sup>. For comparison a freshly nanopatterned MoS<sub>2</sub> was found to have an onset potential of  $-0.2$  V SHE, and a Tafel slope of  $120$  mV dec<sup>-1</sup>. Ageing studies found that when left exposed to air for 21 days following sulfidation HER performance steadily decreases, but can be reinstated by further sulfidation.

## Results and discussion


### Nanostructuring and sulfidation

The structuring by nanosphere lithography and plasma etching is covered briefly here.<sup>19,20</sup> First, naturally occurring MoS<sub>2</sub> crystals were mounted onto a GC substrate, cleaved between basal planes, then placed at the bottom of a beaker of water. Polystyrene nanospheres were deposited from a suspension in ethanol onto the surface of the water, forming a self-assembled monolayer. The water level was lowered using a syringe until the nanospheres deposited onto the MoS<sub>2</sub>. The nanospheres were then exposed to oxygen plasma at 100 SCCM (standard cubic centimetres per minute) for 30 to 50 seconds in order to reduce their size before the MoS<sub>2</sub> was etched with SF<sub>6</sub> plasma at 25 SCCM for 25 to 40 seconds. After both etches the nanospheres were washed off the MoS<sub>2</sub> with acetone, leaving a nanopatterned crystal, which was imaged by SEM. Following the nanopatterning the MoS<sub>2</sub> samples were stored for a period of 5 to 28 days, it was found however, that the samples stored for longer than 23 days had already fully aged (Fig. S1†). For this reason the bulk and freshly fabricated samples (Fig. 2) were electrochemically tested immediately following manufacture. Following exposure to air the crystals were sulfidated electrochemically and subsequently re-tested. The methodology was inspired by strategies to synthesise MoS<sub>2</sub> and other metal sulphides from metal ions and sodium thiosulfate.<sup>21,22,27–29</sup>

The air-exposed MoS<sub>2</sub> modified GC working electrode was placed in a solution containing 10 mM Na<sub>2</sub>S<sub>2</sub>O<sub>3</sub>, and 0.1 M Na<sub>2</sub>SO<sub>4</sub> which has been acidified to pH 3 in order to reduce the S<sub>2</sub>O<sub>3</sub><sup>2-</sup> *via*<sup>28,30</sup>



An oxidative voltage scan was then used to fully oxidise the Mo as this has previously been found to yield MoS<sub>2</sub> on exposure to sulfur.<sup>22,26</sup> A reductive voltage scan was then applied (at a scan rate of  $25$  mV s<sup>-1</sup>) to electroreduce the colloidal sulfur onto the electrode (eqn (3)).<sup>28</sup>



Experimental results confirmed that the sulfidation gave improved voltammetric results if the electrode was swept anodically prior to the reductive deposition (Fig. S2†). The sulfidated MoS<sub>2</sub> samples were then characterised by SEM and XPS,

and the electrochemical performance as HER catalysts recorded and compared to the pre-sulfidated results.

### Physical characterisation

The SEM images (Fig. 1) reveal that repeated deposition results in the filling of gaps between the pillars, which builds up over repeated sulfidations, and could explain the lowering of current as fewer catalytically active edge sites are available, provided that sufficient active sites are lost over a diffusionally-relevant area to effect a change in diffusional character of the nanoarray from case IV.<sup>31</sup> The H<sup>+</sup> reduction measurements corresponding to each of these sulfidations are provided in Fig. S7.† However the remaining edge sites appear to have improved catalytic properties, indicating this method would be well suited to robust morphologies, or electrodes that do not require multiple re-use.

Surface XPS data identified a decrease in the MoS<sub>2</sub> content of the Mo 3d region and concurrent increase in MoO<sub>2</sub> when the sample degraded in air, and that the sulfidation reverses this process (Table 1, Fig. S5†). MoO<sub>3</sub>, readily identified by a significant Mo 3d<sub>3/2</sub> peaks at 235.6 eV, appears to decrease largely to the Mo(IV) species, of which sulfidation is unable to reoxidise. MoS<sub>2</sub> is identified at a binding energy of 229 eV for the 5/2 peak, with MoO<sub>2</sub> existing at a slightly higher binding energy of 229.7 eV. The broadening and shift to a higher energy of the major Mo 3d<sub>5/2</sub> species could therefore be deconvoluted to probe the chemical composition. The MoS<sub>2</sub> composition of the freshly fabricated sample was very similar to that of the sulfidated sample indicating that sulfidation did indeed regenerate the samples surface. This conclusion is corroborated by the electrochemical measurements in Fig. 3(a).

### Electrochemical characterisation

The performance of the MoS<sub>2</sub> as a H<sup>+</sup> reduction catalyst was tested as a means of comparison (see Experimental). The electrode was immersed into a thoroughly degassed solution of 2 mM HClO<sub>4</sub> and 0.1 M NaClO<sub>4</sub> in ultrapure water along with a saturated Ag/AgCl reference electrode and Pt mesh counter electrode. Cyclic voltammograms were recorded from 0 V Ag/AgCl to  $-1.6$  V at a scan rate of  $25$  mV s<sup>-1</sup> (Fig. 2(a)).

It can be seen that following sulfidation the MoS<sub>2</sub> displays improved catalysis for H<sup>+</sup> reduction (Fig. 2(a) sulfidated) with the onset potentials, identified by where the trace departs from the baseline, changed from  $-0.23$  V SHE in the air-exposed state to  $-0.18$  V SHE. These values are favourable compared with bulk MoS<sub>2</sub> ( $-0.65$  V SHE), and the sulfidated onset is comparable to the freshly prepared sample ( $-0.20$  V SHE). These results are in good agreement with other studies on nanostructured MoS<sub>2</sub> HER, with an onset of  $\approx -0.20$  V SHE commonly reported.<sup>4,32–35</sup>

The magnitude of the post-sulfidation current is intermediate to the crystals' aged state and freshly prepared state.

Tafel plots were constructed from the voltammetric results in order to measure the effect of the sulfidation on the HER kinetics. The HER in acidic media is well known to proceed *via* two pathways, each composed of two reaction steps.






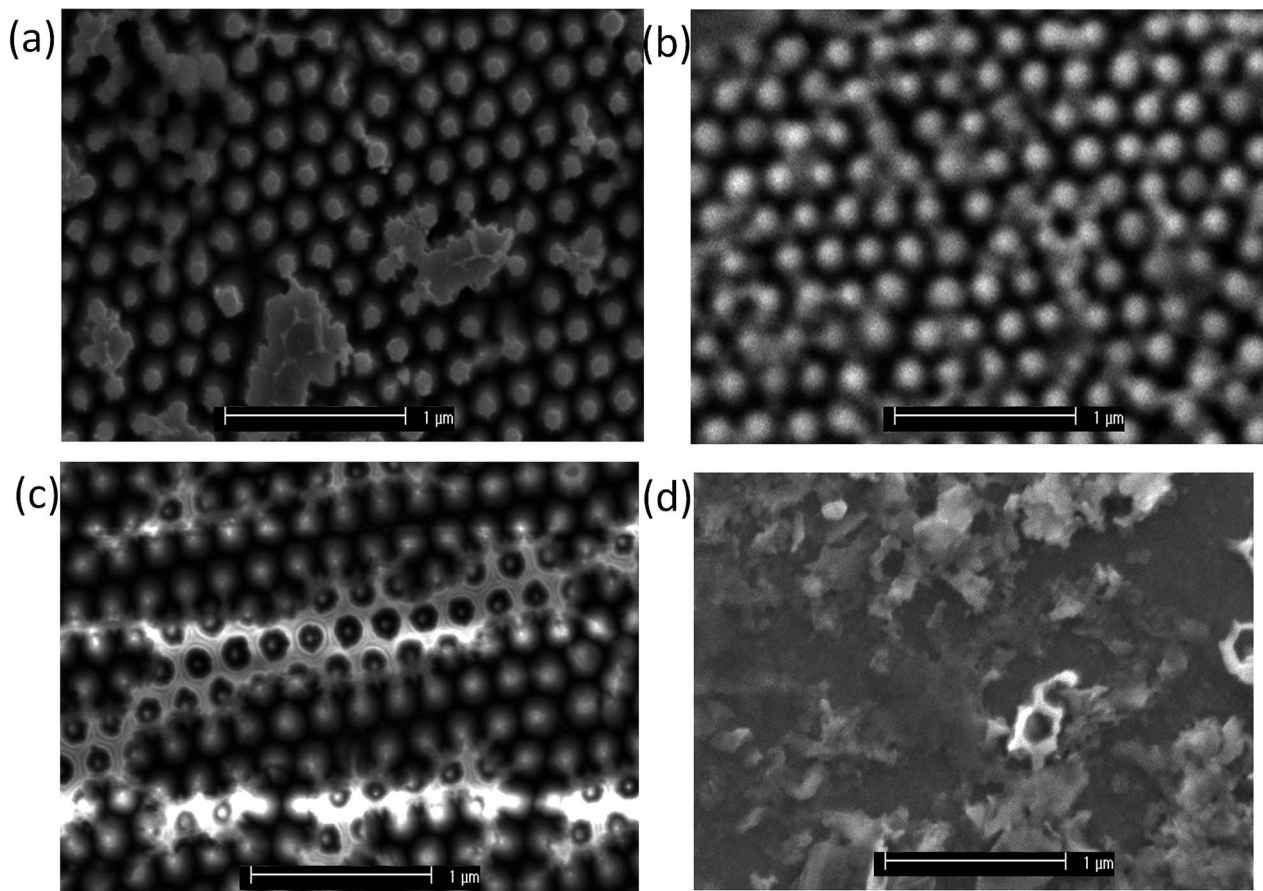


Fig. 1 SEM images showing the effect of sulfidation on the surface of nanopatterned MoS<sub>2</sub>. (a) Sample 1 before sulfidation: the features are individual and distinct, and (b) after 2 sulfidations: the features remain distinct. (c) Sample 2 before sulfidation: the features are individual and distinct, and (d) after 8 sulfidations: the surface has homogenised though some features remain visible.

Table 1 Molar percentage of molybdenum species in fresh, air-exposed, and sulfidated films obtained from XPS spectra (Fig. S5)

Sample	% MoS <sub>2</sub>	% MoO <sub>3</sub>	% MoO <sub>2</sub>
Freshly fabricated	56.07	35.83	8.10
Air-exposed	45.52	2.51	51.97
Sulfidated	57.99	5.03	36.98



where  $R$  is the gas constant,  $T$  is the absolute temperature,  $\alpha$  is the transfer coefficient, and  $F$  is the Faraday constant.<sup>10,36,37</sup>

The first step common to both pathways is the primary discharge step (Volmer reaction, eqn (5)). What follows this is either an electrochemical desorption step (Heyrovský reaction, eqn (6)) or a recombination/desorption step (Tafel reaction, eqn (7)).

Due to the fast kinetics of the HER on Pt, it is widely considered a benchmark catalyst, and is known to proceed through the Volmer–Tafel reaction (eqn (5) and (7)).<sup>36–38</sup>

The precise pathway of hydrogen evolution on MoS<sub>2</sub> is still unknown.<sup>37</sup> However, MoS<sub>2</sub> has been combined with reduced-graphene oxide (RGO), as well as single-walled carbon nanotubes to achieve Tafel slopes of  $\approx 41 \text{ mV dec}^{-1}$  (ref. 32 and 37) indicating a Volmer–Heyrovský reaction.

Various structuring techniques have been applied to optimise the performance of MoS<sub>2</sub> in the HER. The lowest measured Tafel slope for pure MoS<sub>2</sub> is  $49 \text{ mV dec}^{-1}$  and was achieved through edge termination and layer expansion.<sup>39</sup> Other structures include nanoparticulate MoS<sub>2</sub>, 2D MoS<sub>2</sub>, and vertically aligned layers; achieving  $55 \text{ mV dec}^{-1}$ ,<sup>33</sup>  $67 \text{ mV dec}^{-1}$ ,<sup>32</sup> and  $86 \text{ mV dec}^{-1}$ ,<sup>4</sup> respectively. Bulk MoS<sub>2</sub> has a slope of  $\approx 120 \text{ mV dec}^{-1}$  which suggests the primary discharge step is rate limiting.<sup>34,35,40</sup>

The Tafel responses obtained from the above samples showed some variation, but all displayed a decrease in Tafel slope following sulfidation. The freshly nanopatterned MoS<sub>2</sub> from this work had a slope of  $120 \text{ mV dec}^{-1}$  indicating the primary discharge step (eqn (4)) was rate limiting (Fig. 2(b)) as in the case of bulk MoS<sub>2</sub>.<sup>34,35,40</sup> When the samples were exposed





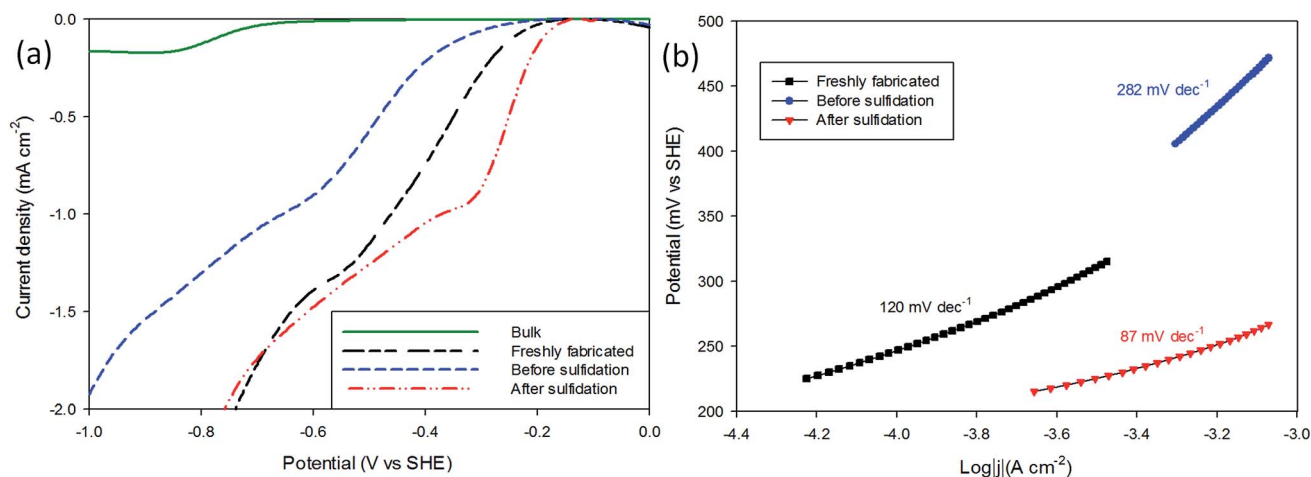


Fig. 2 Comparison of electrocatalytic performance of freshly nanopatterned, and before and after sulfidation nanopatterned MoS<sub>2</sub> as well as bulk MoS<sub>2</sub> for proton reduction. The data presented here is baseline corrected, and numbers quoted in the text are adjusted to SHE and corrected for Nernstian shift. (a) *i*-*V* curves of before and after sulfidation, compared to freshly nanopatterned and bulk MoS<sub>2</sub>. (b) Tafel slopes derived from (a).

to air for over 23 days the HER kinetics slowed considerably, evidenced by the increase in the Tafel slope to 282 mV dec<sup>-1</sup>. Sulfidation of the surface improved catalysis to a Tafel slope of 87 mV dec<sup>-1</sup>, comparable with other structured MoS<sub>2</sub> reports.<sup>4,32,33</sup> This is consistent with the restoration of catalytically active sulfur atoms on the MoS<sub>2</sub> (1010) edge enabling faster primary discharge kinetics as compared with the air-exposed state.<sup>10</sup> Proton reduction measurements were used to record how the HER performance of the sulfidated crystals changed (Fig. 3). A sulfidated sample was left exposed to air for 2 months and voltammetrically cycled from 0 V Ag/AgCl to -1.6 V in 2 mM HClO<sub>4</sub> solution three times over a three week period. After the three weeks the H<sup>+</sup> reduction kinetics were still faster than in

the crystals' (pre-sulfidated) air-exposed state, however both the onset potential and current were inferior to the first H<sup>+</sup> reduction test. The Tafel slope before sulfidation was 204 mV dec<sup>-1</sup>, and decreased to 128 mV dec<sup>-1</sup> after the deposition (Fig. S6†).

The slope steadily increased with each subsequent measurement to 188 mV dec<sup>-1</sup> after the three week period. After the final air-exposed measurement the sulfidation process was repeated and the catalytic ability remeasured. It was found that the performance was in very close agreement with the day one sulfidation, with a Tafel slope of 119 mV dec<sup>-1</sup>. This result indicates the sulfidation process can be used to repeatedly cycle air-exposed MoS<sub>2</sub> without a permanent decrease in HER catalytic performance.

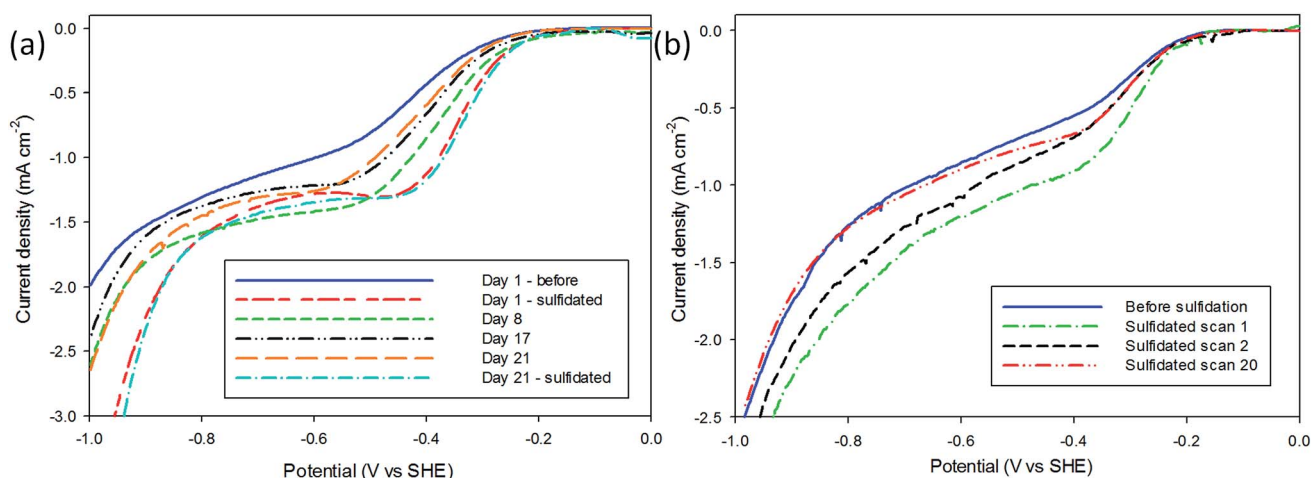


Fig. 3 H<sup>+</sup> reduction tests before and after sulfidation to investigate the rate of ageing. (a) *i*-*V* curves showing the effect of sulfidation followed by gradual air-exposure and resulfidation. The sample had previously been exposed to air for two months before being H<sup>+</sup> reduction tested and sulfidated. Following this H<sup>+</sup> reduction test was performed at regular intervals over a three week period, before re-sulfidation. The performance improved after the first sulfidation, and steadily decreased, the second sulfidation restored H<sup>+</sup> reduction performance to roughly the same. (b) *i*-*V* curves of the ageing caused by cycling of the electrode in dilute acid. Sulfidation improved performance, but there was significant degradation between cycle 1 and 2. The sample was stable between cycle 2 and 20.



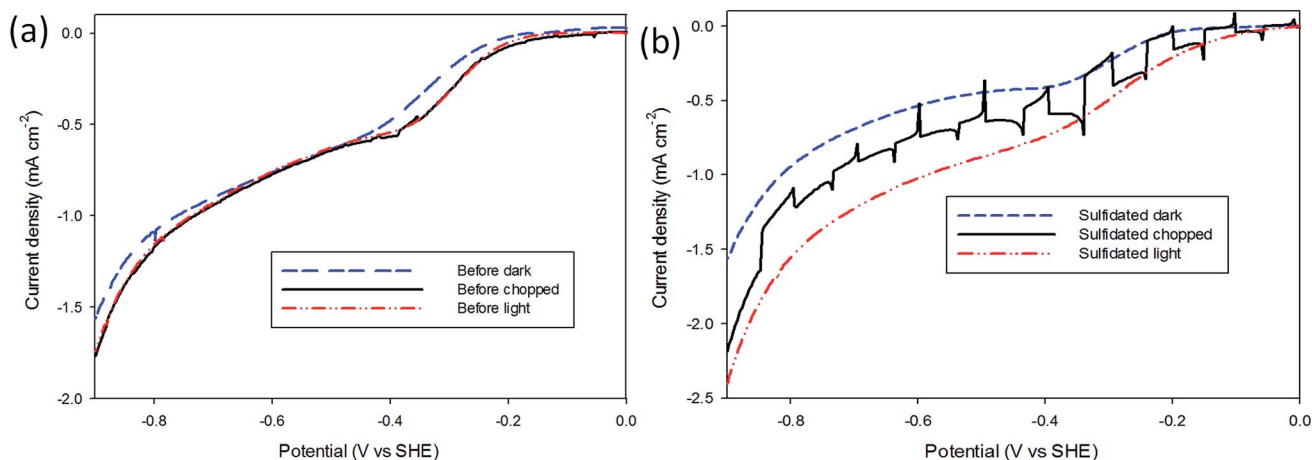


Fig. 4 H<sup>+</sup> reduction on air-exposed and sulfidated MoS<sub>2</sub> under dark and light conditions. (a) *i*-*V* curves of air-exposed MoS<sub>2</sub> under light, dark and interrupted light conditions. The light had a slight increase in current, however the interrupted showed peaks and troughs of only  $\approx 0.3 \mu\text{A}$ . (b) *i*-*V* curves of sulfidated MoS<sub>2</sub> under light, dark and interrupted conditions. Exposure to light led to an increase in current, and the difference between the peaks and troughs during the interrupted condition were  $\approx 10$  times that of the air-exposed state.

### Photoelectrochemistry

A brief investigation into the photoelectrochemical H<sup>+</sup> reduction of both air-exposed and sulfidated MoS<sub>2</sub> was performed under AM 1.5 (1 kW m<sup>-2</sup>) intensity from a Hg-Xe discharge lamp. The PEC measurements (Fig. 4) were performed in the same 2 mM HClO<sub>4</sub> electrolyte, and using the same experimental procedure as above, except the electrochemical cell was fitted with a quartz window. The H<sup>+</sup> reduction performance of three samples that had been air-exposed for longer than one month was first tested under dark, light, and interrupted conditions, before undergoing sulfidation. The same sample was then retested in dark, light and interrupted conditions, and the results shown in Fig. 4. It can be seen that the pre-sulfidation measurements showed little activity as a photocatalyst. The sulfidated sample displays a significant increase in light current as compared with dark current, the current increased tenfold compared to the pre-sulfidated sample, indicating that the sulfidation restores the photoelectrocatalytic activity of air-exposed MoS<sub>2</sub>. The onset potential moves to lower overpotentials due to illumination providing additional applied potential as a result of separating charge carriers in the sulfidated MoS<sub>2</sub>. This was not observed in the pre-sulfidated state implying that the sulfidation process has altered the material bandgap to a value more applicable for PEC HER.<sup>41,42</sup>

### Conclusion

The ageing of nanopatterned MoS<sub>2</sub> in air is detrimental to its use as a photocatalyst for the HER. We have demonstrated a simple room temperature technique by which oxygen aged MoS<sub>2</sub> can be restored to functionality. XPS data was used to verify the change in composition when MoS<sub>2</sub> is left exposed to air, and that the sulfidation technique proposed here causes a reversal. H<sup>+</sup> reduction was used to measure the success of the method, it was found that both onset potential and current were improved post-sulfidation as compared with an air-exposed sample.

Tafel slopes varied from sample to sample, but sulfidation always resulted in a decrease. The lowest Tafel slope for sulfidated MoS<sub>2</sub> was 87 mV dec<sup>-1</sup>, indicating a substantially faster HER kinetics than the oxygen-aged state (282 mV dec<sup>-1</sup>). Once sulfidated the MoS<sub>2</sub> was found to age in air once more, however by repeating the sulfidation process catalytic performance was restored without loss in performance, enabling the same electrode to be recycled. The sulfidated electrodes also aged between the first and second H<sup>+</sup> reduction *i*-*V* scans, but were then stable for at least 20 scans. Photoelectrochemical H<sup>+</sup> reduction under AM 1.5 (1 kW m<sup>-2</sup>) demonstrated that the air-exposed electrodes have very little photocatalytic performance, while once sulfidated there is a significant increase in both current and onset potential in light over dark conditions.

### Experimental

Naturally occurring MoS<sub>2</sub> (99% purity, SPI Supplies Ltd) was adhered to a glassy carbon (GC) substrate (Alfa Aesar Ltd, 5 mm dia., type 2) using conductive double sided carbon adhesive tape (SPI Supplies Ltd) and cleaved between basal planes to present a flat surface (Fig. S8<sup>†</sup>). The GC was then coated with epoxy resin (Permatex quick set epoxy glue) leaving only the MoS<sub>2</sub> exposed for use as the working electrode. Nanosphere solution (0.22  $\mu\text{m}$ , Thermo Scientific Microparticle Technology) was deposited on the surface, and the nanospheres shrunk and MoS<sub>2</sub> etched with an Oxford Instruments PlasmaPro NGP80 etcher. The geometric area of the MoS<sub>2</sub> was measured using a Zeiss Lab A1 optical microscope. Images were recorded using a MicroPublisher 3.3 RTV camera. The geometric area of the MoS<sub>2</sub> was calculated by Klonk image measurement software.

All electrochemical measurements were performed in a three-electrode electrochemical cell using a PGSTAT128N potentiostat (Metrohm Autolab BV, Utrecht, NL) under a nitrogen atmosphere. The proton reduction experiments were performed in 2 mM perchloric acid (70%, Sigma-Aldrich)



electrolyte with 0.1 M sodium perchlorate (98%, Sigma-Aldrich) supporting electrolyte prepared in ultra pure water (MilliQ by Millipore, with resistivity  $\geq 18$  M $\Omega$  cm) and thoroughly purged with N<sub>2</sub> gas to remove dissolved oxygen. A silver–silver-chloride electrode (saturated KCl) (Sigma-Aldrich) and a bright Pt mesh were used as reference and counter electrodes, respectively. The potential *vs.* SHE was calculated using the following equation:<sup>26</sup>

$$E_{\text{SHE}} = E_{\text{measured}} + E_{\text{Ag/AgCl}}^0 + (0.059 \times \text{pH})$$

where  $E_{\text{SHE}}$  is the converted potential value *versus* SHE,  $E_{\text{measured}}$  is the voltage reading from the potentiostat, and  $E_{\text{Ag/AgCl}}^0$  is the experimentally determined electrode potential of an Ag/AgCl (sat. KCl) electrode (0.197 V *vs.* SHE). The pH was 2.7. For ease of comparison all graphs and quoted potentials are given *vs.* SHE.

The sulfidation of MoS<sub>2</sub> crystals was carried out in a solution of 10 mM sodium thiosulfate (99%, Sigma-Aldrich), 1 mM sulfuric acid (98%, Sigma-Aldrich), with 0.1 M sodium sulfate (99% Sigma-Aldrich) supporting electrolyte prepared in ultra pure water purged with N<sub>2</sub> gas. A double-junction Ag/AgCl (3 M KCl) electrode (Sigma-Aldrich) was used as a reference electrode to prevent interference from sulphide ions.<sup>43</sup> The counter electrode was a bright Pt mesh.

PEC measurements were made using an electrochemical cell equipped with a quartz window, and a Lot-Oriel Hg–Xe lamp calibrated to 1000 W m<sup>-2</sup> (AM 1.5) light source. The graphs for EC and PEC measurements are presented as recorded baseline correction, whereas the values in the text have been adjusted against SHE and corrected for Nernstian shift in order to aid comparison with other published values, and to account for the low concentration of electrolyte used in this study for the purpose of removing the effects of migration from the electrochemical results.

An XL 20 SFEG Scanning Electron Microscope (FEI) was used to image the surfaces.

XPS spectra were acquired using a Kratos Axis HSi XP spectrophotometer equipped with a charge neutraliser and a magnesium K<sub>α</sub> source (1253.7 eV). Spectra were recorded at normal emission using a pass energy of 160 for survey scans and 20 for high resolution scans under a vacuum of 10<sup>-10</sup> Torr. Curve fitting was performed using CasaXPS software version 2.3.16 and energy calibrated to the adventitious carbon 1s peak at 284.6 eV, employing Gaussian–Lorentz peak shapes and a Shirley background.

## Acknowledgements

This work was funded by the Engineering and Physical Sciences Research Council (EPSRC).

## References

- 1 R. Chianelli, *J. Catal.*, 1984, **86**, 226–230.
- 2 N. Liu, X. Wang, W. Xu, H. Hu, J. Liang and J. Qiu, *Fuel*, 2014, **119**, 163–169.
- 3 J. Kibsgaard, Z. Chen, B. N. Reinecke and T. F. Jaramillo, *Nat. Mater.*, 2012, **11**, 963–969.
- 4 D. Kong, H. Wang, J. J. Cha, M. Pasta, K. J. Koski, J. Yao and Y. Cui, *Nano Lett.*, 2013, **13**, 1341–1347.
- 5 Y. Huang, R. J. Nielsen, W. A. Goddard and M. P. Soriaga, *J. Am. Chem. Soc.*, 2015, **137**, 6692–6698.
- 6 S. Shin, Z. Jin, D. H. Kwon, R. Bose and Y. S. Min, *Langmuir*, 2015, **31**, 1196–1202.
- 7 M. G. Walter, E. L. Warren, J. R. McKone, S. W. Boettcher, Q. Mi, E. A. Santori and N. S. Lewis, *Chem. Rev.*, 2010, **110**, 6446–6473.
- 8 L. M. Peter and K. G. Upul Wijayantha, *ChemPhysChem*, 2014, **15**, 1983–1995.
- 9 S. J. A. Moniz, S. A. Shevlin, D. J. Martin, Z. X. Guo and J. Tang, *Energy Environ. Sci.*, 2015, **8**, 731–739.
- 10 A. B. Laursen, S. Kegnaes, S. Dahl and I. Chorkendorff, *Energy Environ. Sci.*, 2012, **5**, 5577–5591.
- 11 Y. Zhao, Y. Zhang, Z. Yang, Y. Yan and K. Sun, *Sci. Technol. Adv. Mater.*, 2013, **14**, 043501.
- 12 M. J. Cuddy, K. P. Arkill, Z. W. Wang, H. P. Komsa, A. V. Krashennikov and R. E. Palmer, *Nanoscale*, 2014, **6**, 12463–12469.
- 13 M. M. Mdeleni, T. Hyeon and K. S. Suslick, *J. Am. Chem. Soc.*, 1998, **120**, 6189–6190.
- 14 L. Zhang, K. Liu, A. B. Wong, J. Kim, X. Hong, C. Liu, T. Cao, S. G. Louie, F. Wang and P. Yang, *Nano Lett.*, 2014, **14**, 6418–6423.
- 15 D. Voiry, M. Salehi, R. Silva, T. Fujita, M. Chen, T. Asefa, V. B. Shenoy, G. Eda and M. Chhowalla, *Nano Lett.*, 2013, **13**, 6222–6227.
- 16 C. Tsai, F. Abild-Pedersen and J. K. Nørskov, *Nano Lett.*, 2014, **14**, 1381–1387.
- 17 S. M. Davis and J. C. Carver, *Appl. Surf. Sci.*, 1984, **20**, 193–198.
- 18 Y. Yan, B. Xia, Z. Xu and X. Wang, *ACS Catal.*, 2014, **4**, 1693–1705.
- 19 K. Seeger and R. E. Palmer, *Appl. Phys. Lett.*, 1999, **74**, 1627–1629.
- 20 K. Seeger and R. E. Palmer, *J. Phys. D: Appl. Phys.*, 1999, **32**, L129–L132.
- 21 R. S. Patil, *Thin Solid Films*, 1999, **340**, 11–12.
- 22 E. Shembel, R. Apostolova, I. Kirsanova and V. Tsyachny, *J. Solid State Electrochem.*, 2008, **12**, 1151–1157.
- 23 T. Weber, J. C. Muijsers, J. H. M. C. van Wolput, C. P. J. Verhagen and J. W. Niemantsverdriet, *J. Phys. Chem.*, 1996, **100**, 14144–14150.
- 24 Z. Zhang, J. Zhang and Q. Xue, *J. Phys. Chem.*, 1994, 12973–12977.
- 25 H. Nolan, N. McEvoy, M. O'Brien, N. C. Berner, C. Yim, T. Hallam, A. R. McDonald and G. S. Duesberg, *Nanoscale*, 2014, **6**, 8185–8191.
- 26 J. Miao, F. X. Xiao, H. B. Yang, S. Y. Khoo, J. Chen, Z. Fan, Y. Y. Hsu, H. M. Chen, H. Zhang and B. Liu, *Sci. Adv.*, 2015, **1**, e1500259.
- 27 S. Nakamura and A. Yamamoto, *Sol. Energy Mater. Sol. Cells*, 2001, **65**, 79–85.



- 28 T. Yukawa, K. Kuwabara and K. Koumoto, *Thin Solid Films*, 1996, **286**, 151–153.
- 29 M. Pac, X. Han and M. Tao, *ECS Trans.*, 2011, **41**, 157–166.
- 30 K. LaMer and A. Kenyon, *J. Colloid Sci.*, 1947, **2**, 257–264.
- 31 T. J. Davies and R. G. Compton, *J. Electroanal. Chem.*, 2005, **585**, 63–82.
- 32 Y. Cai, X. Yang, T. Liang, L. Dai, L. Ma, G. Huang, W. Chen, H. Chen, H. Su and M. Xu, *Nanotechnology*, 2014, **25**, 465401.
- 33 T. F. Jaramillo, K. P. Jørgensen, J. Bonde, J. H. Nielsen, S. Horch and I. Chorkendorff, *Science*, 2007, **317**, 100–102.
- 34 H. Wang, C. Tsai, D. Kong, K. Chan, F. Abild-Pedersen, J. K. Nørskov and Y. Cui, *Nano Res.*, 2015, **8**, 566–575.
- 35 M. A. Lukowski, A. S. Daniel, F. Meng, A. Forticaux, L. Li and S. Jin, *J. Am. Chem. Soc.*, 2013, **135**, 10274–10277.
- 36 B. E. Conway and B. V. Tilak, *Electrochim. Acta*, 2002, **47**, 3571–3594.
- 37 Y. Li, H. Wang, L. Xie, Y. Liang, G. Hong and H. Dai, *J. Am. Chem. Soc.*, 2011, **133**, 7296–7299.
- 38 S. J. Rowley-Neale, D. A. C. Brownson, G. C. Smith, D. A. G. Sawtell, P. J. Kelly and C. E. Banks, *Nanoscale*, 2015, **7**, 18152–18168.
- 39 M. R. Gao, M. K. Y. Chan and Y. Sun, *Nat. Commun.*, 2015, **6**, 7493.
- 40 Y. Shi, J. Wang, C. Wang, T.-T. Zhai, W.-J. Bao, J. J. Xu, X. Xia and H. Y. Chen, *J. Am. Chem. Soc.*, 2015, **137**, 7365–7370.
- 41 D. E. Scaife, *Sol. Energy*, 1980, **25**, 41–54.
- 42 Z. Chen, T. F. Jaramillo, T. G. Deutsch, A. Kleiman-Shwarsstein, A. J. Forman, N. Gaillard, R. Garland, K. Takanabe, C. Heske, M. Sunkara, E. W. McFarland, K. Domen, E. L. Miller, J. A. Turner and H. N. Dinh, *J. Mater. Res.*, 2010, **25**, 3–16.
- 43 F. J. Millero, T. Plese and M. Fernandez, *Limnol. Oceanogr.*, 1988, **33**, 269–274.

