

# A feasibility study on wire electrical discharge machining of carbon fibre reinforced plastic composites

Abdallah, Ramy; Soo, Sein Leung; Hood, Richard

DOI:

[10.1016/j.procir.2018.08.284](https://doi.org/10.1016/j.procir.2018.08.284)

License:

Creative Commons: Attribution-NonCommercial-NoDerivs (CC BY-NC-ND)

*Document Version*

Publisher's PDF, also known as Version of record

*Citation for published version (Harvard):*

Abdallah, R, Soo, SL & Hood, R 2018, 'A feasibility study on wire electrical discharge machining of carbon fibre reinforced plastic composites', *Procedia CIRP*, vol. 77, pp. 195-198. <https://doi.org/10.1016/j.procir.2018.08.284>

[Link to publication on Research at Birmingham portal](#)

**Publisher Rights Statement:**

Checked for eligibility: 28/09/2018

First published in *Procedia CIRP*

<https://doi.org/10.1016/j.procir.2018.08.284>

**General rights**

Unless a licence is specified above, all rights (including copyright and moral rights) in this document are retained by the authors and/or the copyright holders. The express permission of the copyright holder must be obtained for any use of this material other than for purposes permitted by law.

- Users may freely distribute the URL that is used to identify this publication.
- Users may download and/or print one copy of the publication from the University of Birmingham research portal for the purpose of private study or non-commercial research.
- User may use extracts from the document in line with the concept of 'fair dealing' under the Copyright, Designs and Patents Act 1988 (?)
- Users may not further distribute the material nor use it for the purposes of commercial gain.

Where a licence is displayed above, please note the terms and conditions of the licence govern your use of this document.

When citing, please reference the published version.

**Take down policy**

While the University of Birmingham exercises care and attention in making items available there are rare occasions when an item has been uploaded in error or has been deemed to be commercially or otherwise sensitive.

If you believe that this is the case for this document, please contact [UBIRA@lists.bham.ac.uk](mailto:UBIRA@lists.bham.ac.uk) providing details and we will remove access to the work immediately and investigate.

8th CIRP Conference on High Performance Cutting (HPC 2018)

# A feasibility study on wire electrical discharge machining of carbon fibre reinforced plastic composites

Ramy Abdallah<sup>a, b</sup>, Sein Leung Soo<sup>a, \*</sup>, Richard Hood<sup>a</sup>

<sup>a</sup> Machining Research Group, Department of Mechanical Engineering, School of Engineering, University of Birmingham, Edgbaston, Birmingham B15 2TT, UK

<sup>b</sup> Production Engineering Department, Faculty of Engineering, Helwan University, Helwan, Cairo, Egypt

\* Corresponding author. Tel.: +44 121 414 4196; fax: +44 121 414 4201. E-mail address: [s.l.soo@bham.ac.uk](mailto:s.l.soo@bham.ac.uk)

## Abstract

This paper details preliminary experimental work to investigate the wire electrical discharge machining (WEDM) of unidirectional carbon fibre reinforced plastic (CFRP) composites using a high tensile strength zinc rich coated brass wire (0.25 mm diameter). A fractional factorial L18 Taguchi experimental design was employed to evaluate the influence of varying open gap voltage (120 and 140 V), ignition current (3 – 5 A) as well as pulse on-time (0.8 – 1  $\mu$ s) and off-time (4 – 8  $\mu$ s) on material removal rate (MRR), top ( $W_t$ ) and bottom ( $W_b$ ) kerf widths as well as workpiece edge damage. The ignition current and pulse off-time were found to be statistically significant factors affecting MRR based on an analysis of variance, with percentage contribution ratios (PCR) of 48.5% and 24.3% respectively. It was observed that MRR, which ranged between 0.43 and 2.41 mm<sup>3</sup>/min, increased with both ignition current and pulse on-time due to the higher discharge energy generated in the machining gap. No signs of workpiece damage in terms of delamination or surface burning was apparent, despite the higher MRR. Conversely, the larger open gap voltage surprisingly led to reductions in MRR, which was likely due to unstable gap conditions caused by greater levels of residual melted resin within the gap or re-deposition on the workpiece surface. In terms of kerf width, ignition current was revealed as the sole significant factor with respect to the top surface (up to ~ 0.28 mm) having a PCR of 56.6%, while none of the variable parameters had a major effect on the bottom kerf width.

© 2018 The Authors. Published by Elsevier Ltd.

This is an open access article under the CC BY-NC-ND license (<https://creativecommons.org/licenses/by-nc-nd/4.0/>)

Selection and peer-review under responsibility of the International Scientific Committee of the 8th CIRP Conference on High Performance Cutting (HPC 2018).

*Keywords:* Composite; Electrical discharge machining (EDM); Material removal; Kerf

## 1. Introduction

Carbon fibre reinforced plastic (CFRP) composites are used extensively in various industrial sectors such as aerospace, automotive, textile and sporting equipment due to its outstanding attributes including high strength to weight ratio (~785 kN.m/kg), high modulus of elasticity (75-105% of steel), low thermal expansion/shrinkage and good resistance to wear, corrosion and fatigue [1-4]. Currently, CFRP constitutes up to ~50% of weight in modern civil aircraft such as the Airbus A350XWB and Boeing 787, which has a marked influence in reducing their operational fuel consumption [5]. The machinability of CFRP however is generally considered to be

poor, particularly when employing conventional processes such as drilling and milling, as they are prone to low tool life and adverse workpiece surface integrity with defects such as delamination, fibre pullout, matrix melting/burn and cracking being commonly prevalent [6-8]. This is largely due to the highly abrasive nature of the carbon fibres as well as the anisotropy/heterogeneity of the material. Various non-conventional cutting processes including laser beam, abrasive waterjet and vibration assisted machining have been evaluated as potential alternatives [9], with each showing benefits as well as limitations in terms of productivity, process complexity and workpiece damage. Another non-traditional machining process that has been investigated is electrical discharge machining

(EDM), where material removal is not hindered by workpiece mechanical properties such as hardness and strength. However, the relatively low bulk electrical conductivity of CFRP is currently a major barrier to EDM being an effective option.

The majority of published literature regarding the EDM of CFRP has focused on die-sink based operations with scant information involving the wire EDM (WEDM) configuration. Ichii et al. [10] investigated the effect of duty cycle, pulse width, electrode material (copper/graphite) and cut direction (parallel/perpendicular to fibre orientation) during EDM of unidirectional CFRP and SKD11 tool steel. When machining perpendicular to the fibre direction, material removal rate (MRR) was significantly higher for CFRP (up to  $\sim 5 \text{ mm}^3/\text{min}$  using graphite electrode) compared to SKD11 ( $\sim 0.1 \text{ mm}^3/\text{min}$ ) due to the rapid melting of the epoxy matrix. However, substantially rougher surfaces were evident on the CFRP workpieces ( $\sim 50 \mu\text{m Rz}$  as opposed to  $\sim 9 \mu\text{m Rz}$  for SKD11). A similar study conducted on unidirectional and bidirectional/woven CFRP lay-ups showed that MRR was up to  $\sim 25\%$  higher in the latter, as increased levels of the polymer matrix phase were present in the bidirectional CFRP composites [11]. In an investigation concerning EDM die-sinking of CFRP laminates, Hayakawa et al. [12] reported that the local material removal rate was greater in plies with fibres parallel to the electrode surface. This was attributed to the increased frequency of short-circuiting between the electrode and frayed/exposed fibres, which led to Joule heating of the resin matrix. By employing a thermal camera, Akematsu et al. [13] showed that the discharge energy during the EDM of CFRP was typically confined to flow along the longitudinal direction of fibres. Islam et al. [2] studied the use of EDM to deburr conventionally drilled holes in CFRP involving 4 different electrode materials. Productivity was highest when utilising copper electrodes ( $\sim 6.3 \text{ mm}^2/\text{min}$ ) while no evidence of delamination or hole deformation was detected following EDM deburring. A comparative assessment between WEDM and laser machining of 2.5 mm thick CFRP workpieces showed that while considerably higher MRR was achieved in the latter ( $\sim 95 \text{ mm}^2/\text{min}$  as opposed to  $12 \text{ mm}^2/\text{min}$ ); the former produced superior edge quality and lower workpiece damage [14].

The current paper details initial research aimed at assessing the influence of key process parameters on workpiece MRR, kerf width and surface damage when WEDM of CFRP composites.

## 2. Experimental work

### 2.1. Workpiece material and equipment

The workpiece material employed was unidirectional CFRP composite plates measuring  $100 \times 100 \times 8.4 \text{ mm}$ . Each of the plates comprised 32 prepreg layers laid up in a single direction ( $0^\circ$ ), which contained intermediate modulus carbon fibres impregnated within an epoxy resin (34% of weight). The key mechanical/physical properties of the carbon fibres are detailed in Table 1. All machining trials were conducted on a wire electrical discharge machine (AgieCharmilles Robofil FI 240 CC) equipped with a minimum damage generator. The

diameter of the wire electrode utilised was 0.25 mm, which consisted of a brass core (80%Cu20%Zn) with a dual layer coating containing  $\beta$  (50%Cu50%Zn) and  $\gamma$  (35%Cu+65%Zn) phases. The wire composition provided high tensile strength (800 MPa) and electrical conductivity appropriate for machining high resistivity materials such as CFRP. The conductivity of the deionised water dielectric was maintained at  $\sim 5 \mu\text{S}/\text{cm}$ , with the corresponding experimental setup shown in Fig. 1.

Table 1. Properties of the carbon fibre.

Parameter	Value
Fibre diameter	5 $\mu\text{m}$
Tensile modulus	294 GPa
Tensile strength	5880 MPa
Fibre areal weight	268 $\text{g}/\text{m}^2$
Density	1.8 $\text{g}/\text{cm}^3$
Thermal conductivity	70 $\text{W}/\text{m}\cdot\text{K}$
Strain	2%

Machined kerf width was measured using an Alicona G5 InfiniteFocus microscope while the CFRP workpieces were weighed before and after each test using a digital precision scale (measurement range of 0.5 to 3500 g) to record the mass of material removed. Optical micrographs of workpiece surface damage were captured using a toolmakers microscope connected to a digital camera.

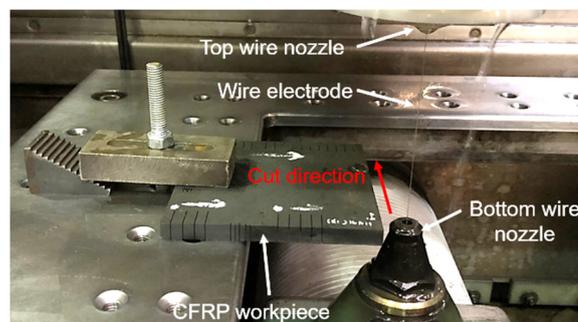


Fig. 1. Experimental setup

### 2.2. Design of experiment and test procedures

Experiments were undertaken according to a Taguchi fractional factorial L18 orthogonal array involving variation in open gap voltage at 2 levels together with ignition/peak current, pulse on-time and off-time, each at 3 levels as detailed in Table 2. Fixed parameters included wire tension (13 N), wire speed (10 m/min), flushing pressure (16 bar) and servo voltage (15 V). The operating parameter values were selected following preliminary scoping trials to ascertain workable process windows. All tests involved straight cuts with machining performed parallel to the carbon fibre direction. The end of test criterion was a cut length of 12 mm with the associated machining time recorded using a stopwatch. The MRR was calculated based on the relationship in Eq. 1:

$$MRR = \frac{m_b - m_a}{\rho * t_m} \quad (1)$$

where  $m_b$  and  $m_a$ : mass of the workpiece before and after machining respectively (g),  $\rho$ : workpiece density ( $\text{g}/\text{mm}^3$ ) and  $t_m$ : machining time (min).

Kerf widths for both the top ( $W_t$ ) and bottom ( $W_b$ ) surfaces of the workpiece were determined based on the mean of measurements at 9 positions (approximately equidistant) along the cut length.

Table 2. Variable machining parameter levels.

Machining parameter	Level 1	Level 2	Level 3
Open gap voltage, $V_0$ (V)	120	140	-
Ignition current, IAL (A)	3	4	5
On-time, A ( $\mu\text{s}$ )	0.8	0.9	1.0
Off-time, B ( $\mu\text{s}$ )	4	6	8

### 3. Results and discussion

#### 3.1. Material removal rate and workpiece damage

All of the tests achieved the 12 mm cut distance with machining times varying from 13.3 to 49.1 minutes. This resulted in MRR's of between 0.43 and 2.41  $\text{mm}^3/\text{min}$  for the range of tests performed. Corresponding analysis of variance (ANOVA) revealed that ignition current and pulse off-time were both statistically significant factors at the 5% level, with percentage contribution ratios (PCR) of 48.5% and 24.3% respectively. The main effects plot in Fig. 2 showed that MRR increased with ignition current and pulse on-time due to the greater discharge energy, whereas higher pulse off-times reduced MRR due to the lower spark efficiency/frequency. Surprisingly, operating at the larger open gap voltage level (140 V) generally led to a reduction in mean MRR. A possible reason for this was the rise in molten resin material in the gap caused by the elevated discharge energy leading to unstable machining.

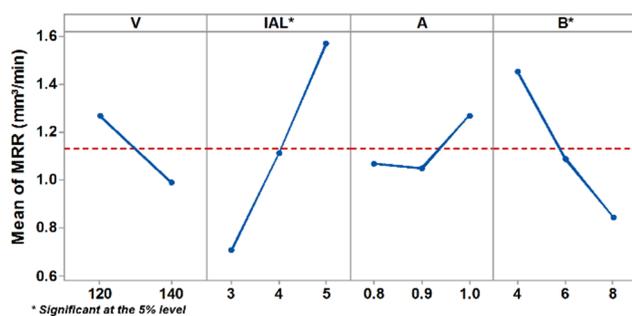


Fig. 2. Main effects plot for MRR.

Fig. 3 details optical micrographs of the machined kerf on the top and bottom of the workpiece from the test achieving the highest MRR. Aside from a relatively uneven edge profile, there was no evidence of major damage such as delamination, matrix burning or uncut fibres on the kerf periphery in any of the workpieces examined. There was however bronze coloured patches of suspected adhered debris/contamination visible around the bottom surface of the workpiece, see Fig. 3b, which may be deposits of re-solidified wire electrode material. This was possibly due to the differences in flushing

efficiency/conditions between the top and bottom sides of the workpiece.

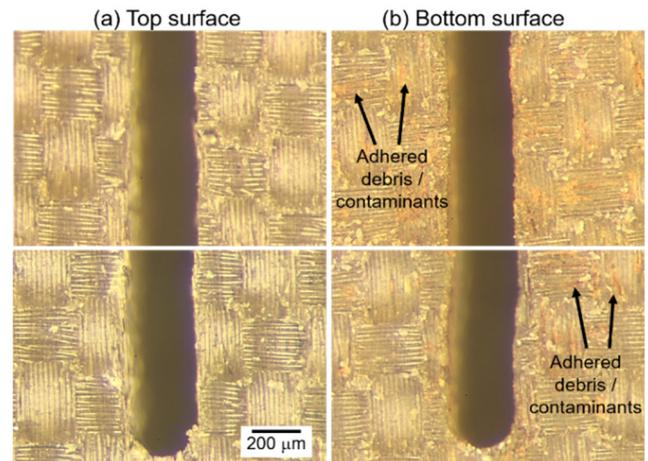


Fig. 3. Sample micrographs of machined kerf on the (a) top and (b) bottom surfaces from the test achieving the highest MRR.

#### 3.2. Kerf width

The kerf width results highlighted discrepancies between measurements at the top and bottom surfaces of the CFRP workpiece. Average  $W_t$  was found to vary between  $\sim 256$  and  $289 \mu\text{m}$  while  $W_b$  was generally smaller, ranging from  $\sim 243$  to  $277 \mu\text{m}$ . The ANOVA shown in Table 3 for  $W_t$  demonstrated that the ignition current was the only significant factor with a corresponding PCR of 56.6%, while none of the variable parameters were found to be statistically significant with respect to the bottom kerf width. The main effects plot in Fig. 4 revealed that mean  $W_t$  decreased with increasing current and pulse off-time whilst increasing voltage enlarged the kerf width as expected due to the larger spark gap generated. In terms of  $W_b$ , both open gap voltage and pulse off-time exhibited similar effects compared to the top kerf, however the trends for ignition current and pulse on-time were reversed as shown in Fig. 5.

Table 3. ANOVA table for top kerf width.

Source	DF	Seq. SS	Adj. MS	F	P	PCR%
Voltage, $V_0$	1	40.18	40.18	1.91	0.197	4.1%
Current, IAL	2	559.73	279.78	13.31	0.002*	56.6%
On-time, A	2	32.19	16.10	0.77	0.490	3.3%
Off-time, B	2	146.65	73.33	3.49	0.071	14.8%
Residual error	10	210.21	21.02			21.3%
Total	17	988.97				100%

\*Significant at the 5% level

The relatively smaller mean  $W_b$  ( $\sim 261 \mu\text{m}$ ) compared to  $W_t$  ( $\sim 282 \mu\text{m}$ ) when operating at the lowest current level of 3 A was possibly due to greater machining instability at the bottom side of the workpiece. However, the disparity between the top and bottom kerf width was found to reduce significantly as ignition current increased to 5 A, which suggests that the wire advanced more uniformly through the workpiece, most likely as a result of the higher discharge energy.

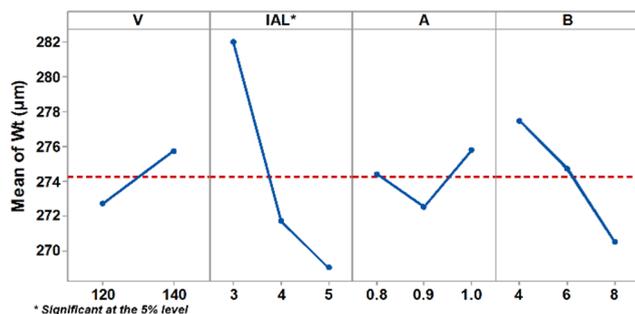


Fig. 4. Main effects plot for top kerf width.

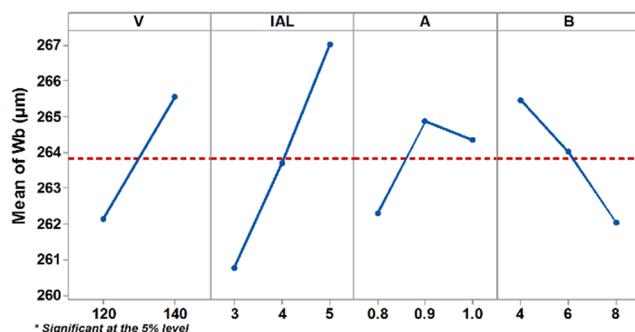


Fig. 5. Main effects plot for bottom kerf width.

### 3.3. Confirmation tests

Confirmation trials were carried out to validate the preferred combination of operating parameter levels to achieve maximum MRR and minimum top/bottom kerf widths. Although the recommended parameter combinations for MRR and  $W_t$  were undertaken as part of the orthogonal array, confirmation trials for all 3 responses were carried out to verify the results. Table 4 details the predicted and experimental values of the mean and signal to noise (S/N) ratio for the respective confirmation trials. The percentage error between the experimental and predicted data did not exceed 5% for all of the responses evaluated, which indicates that the accuracy of the Taguchi experiment was acceptable.

Table 4. Predicted and experimental values of mean and S/N ratio.

Response	Mean		S/N ratio (dB)		Error %
	Pred.	Exp.	Pred.	Exp.	
MRR	2.17	2.28	7.79	7.16	4.95
$W_t$	262.14	263.67	-48.37	-48.42	0.58
$W_b$	255.72	262.97	-48.15	-48.43	2.75

## 4. Conclusions

- All of the trials were successfully completed to a cut length of 12 mm. This suggests that the process parameters and electrode material selected were suitable for enabling the wire electrical discharge machining of unidirectional CFRP composites.
- The highest MRR of 2.41 mm<sup>3</sup>/min was achieved when utilising an ignition current of 5 A, pulse on-time of 1 µs, open gap voltage of 120 V and pulse off-time of 4 µs.

- Ignition current and pulse off-time were statistically significant factors with regard to MRR while current was the sole parameter influencing the kerf width on the top surface. The difference in measured kerf width between the top and bottom surfaces of the workpiece was possibly due to the variation in flushing conditions/efficiency at the respective locations.
- None of the machined workpieces showed any indications of thermal damage or serious defects around the vicinity of the kerf, apart from rough edges and some minor adhered debris on the bottom surface of the workpiece.

## Acknowledgements

The authors wish to thank the Egyptian Cultural Bureau for funding a research studentship and GF Machining Solutions for providing the WEDM machine for the tests.

## References

- [1] Mohee FM, Al-Mayah A, Plumtree A. Anchors for CFRP plates: State-of-the-art review and future potential. *Composites Part B* 2016;90:432-442.
- [2] Islam MM, Li CP, Won SJ, Ko TJ. A deburring strategy in drilled hole of CFRP composites using EDM process. *J Alloys Compd* 2017;703:477-485.
- [3] Zhang Y., Liu Y, Ji R, Cai B, Wang F, Tian X. Carbon fiber in micro-electric discharge machining. *Mater Manuf Processes* 2013;28:1133-6.
- [4] McGraw-Hill Encyclopedia of Science & Technology Vol. 1, 8th ed, 1997, p. 375.
- [5] El-Hofy MH, Soo SL, Aspinwall DK, Sim WM, Pearson D, M'Saoubi R, Harden P. Tool temperature in slotting of CFRP composites. *Procedia Manuf* 2017;10:371-381.
- [6] Pecat O, Rentsch R, Brinksmeier E. Influence of milling process parameters on the surface integrity of CFRP. *Procedia CIRP* 2012;1:466-470.
- [7] Jia Z, Fu R, Niu B, Qian B, Bai Y, Wang F. Novel drill structure for damage reduction in drilling CFRP composites. *Int J Mach Tools Manuf* 2016;110:55-65.
- [8] El-Hofy MH, Soo SL, Aspinwall DK, Sim WM, Pearson D, Harden P. Factors affecting workpiece surface integrity in slotting of CFRP. *Procedia Eng* 2011;19:94-9.
- [9] Che D, Saxena I, Han P, Guo P, Ehmann KF. Machining of carbon fiber reinforced plastics/polymers: A literature review. *J Manuf Sci Eng* 2014;136:034001-1-22.
- [10] Ichii S, Okada A, Okamoto Y, Uno Y. Influence of carbon fiber direction on EDM characteristics of CFRP. In: *Proceedings of the 6<sup>th</sup> Int Conference on Leading Edge Manufacturing in 21<sup>st</sup> Century (LEM 2011)*, Saitama, Japan 2011.
- [11] Habib S, Okada A, Ichii S. 2013. Effect of cutting direction on machining of carbon fibre reinforced plastic by electrical discharge machining process. *Int J Mach Mach Mater* 2013;13:414-427.
- [12] Hayakawa S, Tominaga K, Ito A, Itoigawa F, Nakamura T. Effect of carbon fiber orientation on machining phenomena in electrical discharge machining of carbon fiber reinforced plastics. *Int J Electr Mach* 2012;17:29-34
- [13] Akematsu Y, Kageyama K, Murayama H. 2016. Basic characteristics of electrical discharge on CFRP by using thermal camera. *Procedia CIRP* 2016;42:197-200.
- [14] Lau WS, Lee WB. 1991. A comparison between EDM wire-cut and laser cutting of carbon fibre composite materials. *Mater Manuf Processes* 1991;6:331-342.